



**SLOVENSKI STANDARD**  
**SIST EN ISO 14632:2000**

**01-maj-2000**

---

9\_glf i Xj fUbY d`cý Y`jn`dc`jYh`YbUfd9!<8Ł!`NU hYj Y`jb`dfYg\_i gbY`a YfcXY fIGC  
%`\*' &% - , Ł

Extruded sheets of polyethylene (PE-HD) - Requirements and test methods (ISO 14632:1998)

Extrudierte Tafeln aus Polyethylen (PE-HD) - Anforderungen und Prüfverfahren (ISO 14632:1998)

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

Plaques extrudées en polyéthylène (PE-HD) - Prescriptions et méthodes d'essai (ISO 14632:1998)

[SIST EN ISO 14632:2000](https://standards.iteh.ai/catalog/standards/sist/4b8dc7b7-298a-4eb7-a946-35f7b96a1fd/sist-en-iso-14632-2000)

[https://standards.iteh.ai/catalog/standards/sist/4b8dc7b7-298a-4eb7-a946-](https://standards.iteh.ai/catalog/standards/sist/4b8dc7b7-298a-4eb7-a946-35f7b96a1fd/sist-en-iso-14632-2000)

[35f7b96a1fd/sist-en-iso-14632-2000](https://standards.iteh.ai/catalog/standards/sist/4b8dc7b7-298a-4eb7-a946-35f7b96a1fd/sist-en-iso-14632-2000)

**Ta slovenski standard je istoveten z: EN ISO 14632:1998**

---

**ICS:**

83.140.10      Filmi in folije

Films and sheets

**SIST EN ISO 14632:2000**

**en**

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST EN ISO 14632:2000

<https://standards.iteh.ai/catalog/standards/sist/4b8dc7b7-298a-4eb7-a946-35f7b96a1fld/sist-en-iso-14632-2000>

EUROPEAN STANDARD

EN ISO 14632

NORME EUROPÉENNE

EUROPÄISCHE NORM

December 1998

ICS 83.140

Descriptors: plastics, polyethylene, extruded products, plates, designation, delivery condition, dimensions, dimensional tolerances, mechanical properties, thermal properties, tests, marking

English version

## Extruded sheets of polyethylene (PE-HD) - Requirements and test methods (ISO 14632:1998)

Plaques extrudées en polyéthylène (PE-HD) - Prescriptions et méthodes d'essai (ISO 14632:1998)

Extrudierte Tafeln aus Polyethylen (PE-HD) - Anforderungen und Prüfverfahren (ISO 14632:1998)

This European Standard was approved by CEN on 2 October 1998.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

<https://standards.iteh.ai/catalog/standards/sist/4b8dc7b7-298a-4eb7-a946-35f7b96a1fd/sist-en-iso-14632-2000>



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

## Foreword

The text of EN ISO 14632:1998 has been prepared by Technical Committee CEN/TC 249 "Plastics", the secretariat of which is held by IBN, in collaboration with Technical Committee ISO/TC 61 "Plastics".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 1999, and conflicting national standards shall be withdrawn at the latest by June 1999.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Annex A is normative.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN ISO 14632:2000

<https://standards.iteh.ai/catalog/standards/sist/4b8dc7b7-298a-4eb7-a946-35f7b96a1f1d/sist-en-iso-14632-2000>



## 1 Scope

This standard specifies the requirements and test methods for solid flat extruded sheets of polyethylene homopolymers (PE - HD) without fillers or reinforcing materials. This standard applies only to thicknesses of 0,5 mm to 40 mm. This standard also applies to PE - HD sheet in rolled form.

## 2 Normative references

This European standard incorporates, by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

EN ISO 179	Plastics - Determination of Charpy impact strength (ISO 179:1993)
EN ISO 291	Plastics - Standard atmospheres for conditioning and testing (ISO 291:1997)
EN ISO 527- 1	Plastics - Determination of tensile properties Part 1: General principles (ISO 527-1:1993 including Corr 1:1994)
EN ISO 527-2	Plastics - Determination of tensile properties Part 2: Test conditions for moulding and extrusion plastics (ISO 527-2:1993 including Corr 1:1994)
ISO 1 133	Plastics - Determination of the melt mass - flow rate (MFR) and the melt volume - flow rate (MVR) of thermoplastics
ISO 1 183	Plastics - Methods for determining the density and relative density of non - cellular plastics
ISO 1 872-1	Plastics - Polyethylene (PE) moulding and extrusion materials Part 1: Designation system and basis for specifications
EN ISO 2 818	Plastics - Preparation of test specimens by machining (ISO 2818:1994)
ISO/ TR 9 080	Thermoplastics pipes for the transport of fluids - Methods of extrapolation of hydrostatic stress rupture data to determine the long-term hydrostatic strength of thermoplastics pipe materials

## 3 Material

Sheets consist of PE extrusion compounds designated by ISO 1 872-1 without fillers or reinforcing materials. Extrusion compounds can contain additives such as processing aids, stabilisers, flame protective agents and colorants.

Compounds and additives of unknown identity shall not be used.

NOTE: Legal requirements can cause a specific choice of extrusion compounds (see 4.3.3).

## 4 Requirements

### 4.1 Appearance

Sheets shall be substantially free from bubbles, voids, cracks, visible impurities and other defects which would make them unfit for the intended use. Surfaces shall be substantially smooth and free from sharp grooves, sink marks or damage.

Colorants shall be homogeneously distributed throughout the material. Slight colour differences due to the particular extrusion compound or processing procedure used are admissible. Admissible variations in any of the above shall be agreed between the interested parties.

Sheets shall be examined in accordance with 5.3.

### 4.2 Dimensional tolerances

#### 4.2.1 Thickness

Within any individual sheet, referring to the nominal thickness, the tolerance on thickness shall be:

$$|\Delta h| \leq \pm 10,08 \text{ mm} + 0,03 \times h_n \quad (1)$$

Where:

$\Delta h$  is the tolerance on thickness, in millimetres  
 $h_n$  is the nominal thickness, in millimetres

Testing shall be in accordance with 5.4.1.

#### 4.2.2 Length and width

Nominal length,  $l_n$ , and nominal width,  $b_n$ , of sheets shall be agreed between the interested parties. Unless agreed differently, the length shall be in the direction of extrusion.

For any individual sheet selected at random from any delivery, the tolerances on length and width shall be in accordance with table 1. Testing shall be in accordance with 5.4.2.

**Table 1: Tolerances for length and width of sheet**

Nominal value of dimension, $D_n$	Tolerances	
	Length	Width
$D_n \leq 500$	+ 2	+ 2
	- 1	- 1
$500 < D_n \leq 1\ 000$	+ 3	+ 3
	- 1	- 1
$1\ 000 < D_n \leq 1\ 500$	+ 4	+ 4
	- 1	- 1
$1\ 500 < D_n \leq 2\ 000$	+ 6	+ 4
	- 1	- 1
$2\ 000 < D_n \leq 3\ 000$	+ 8	+ 6
	- 1	- 1
$3\ 000 < D_n \leq 4\ 000$	+ 11	+ 7
	- 1	- 1

For rolled sheets the minimum length shall be the nominal length.

### 4.2.3 Rectangularity

For any individual sheet, selected at random from any delivery, the rectangularity tolerance expressed as the difference between the length of the diagonals ( $|d_1 - d_2|$ , see figure 1) shall be in accordance with table A.1 of annex A (normative)

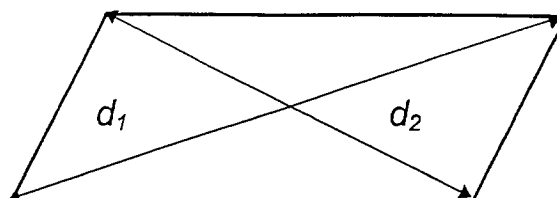


Figure 1: Difference between diagonals ( $|d_1 - d_2|$ )

Testing shall be in accordance with 5.4.3.

### 4.2.4 Bow of sheets in rolled form

For sheets in rolled form, a maximum bow of 20 mm in 10 metres length is permissible. Testing shall be in accordance with 5.4.4.

## 4.3 Properties

### 4.3.1 Mechanical and thermal properties

Table 2: Mechanical and thermal properties

Properties	Unit	Requirements (average values)				Test method subclause
		PE-HD sheet group				
		1 <sup>1)</sup>	2	3	4	
Density	g/cm <sup>3</sup>	0,95 to 0,96	0,94 to 0,96	0,95 to 0,96	≥ 0,96	5.5
Tensile stress at yield	MPa	≥ 20	≥ 15	≥ 20	≥ 25	5.6
Tensile strain at yield	%	≥ 10	≥ 8	≥ 8	≥ 8	5.6
Modulus of elasticity in tension	MPa	≥ 700	≥ 700	≥ 900	≥ 1200	5.7
Charpy impact strength of notched specimens	kJ/ m <sup>2</sup>	≥ 10	≥ 6	≥ 10	≥ 15	5.8
MFR 190 °C / 5 kg	g/ 10 min	0,4 to 0,7	0,1 to 2,0	0,1 to 2,0	0,1 to 2,0	5.9

<sup>1)</sup>Sheets of group 1 shall be manufactured from extrusion compounds (black, UV-stabilized with >2 % carbon black) complying with specific requirements for creep rupture strength defined in accordance with ISO/ TR 9 080 and shall be approved by all interested parties.

### 4.3.2 Behaviour after heating

#### 4.3.2.1 Maximum shrinkage for general applications

For general applications, the maximum shrinkage in the direction of extrusion shall be less than three percent after heating. Testing shall be in accordance with 5.10 and table 5.

### 4.3.2.2. Maximum shrinkage for thermoforming applications

The maximum shrinkage in the direction of extrusion shall not exceed the values given in table 3 when measured using the method in 5.10 and the conditions given in table 6.

**Table 3: Maximum shrinkage for thermoforming applications**

Nominal thickness, $h_n$ (mm)	0,5	1	2	4	6	8	10	> 10
Maximum shrinkage in the direction of extrusion (%)	75	70	60	50	40	35	30	not applicable

### 4.3.3 Physiological behaviour

Relevant legislation concerning physiological behaviour shall be taken into consideration.

## 5 Test methods

### 5.1 Test specimens

#### 5.1.1 Preparation of test specimens

Representative test specimens shall be cut longitudinally and transversely from locations evenly distributed over the length and width of the sheet.

From a sheet in roll form, a two metre sample shall be cut from the end of the roll to provide test specimens.

Surfaces of the test specimens shall be free from damage and other defects in order to avoid notch effects. Should any burrs occur on the test specimens during production these shall be eliminated without damaging the surfaces of the test specimen. If required, the cut edges shall be finished with abrasive paper (grain number 220 or finer), the direction of abrasion being along the length of the test specimens. If it is necessary to machine the sheet to reduce it to the thickness required, one original surface shall be left intact. In particular, test specimens over 4,2 mm thick intended to be used in the tests described in 5.6 to 5.8 shall be machined down on one side to a thickness of 4,0 mm  $\pm$  0,2 mm in accordance with EN ISO 2 818.

#### 5.1.2 Conditioning

All test specimens shall be conditioned for at least 16 hours at standard atmosphere (23) in accordance with EN ISO 291. Shorter conditioning times shall be used by agreement between the interested parties when it can be shown that there is no significant difference in the results obtained.

#### 5.1.3 Testing

Testing shall be carried out at standard atmosphere (23) in accordance with EN ISO 291, unless agreed differently between the interested parties or specified differently in the individual testing standards.

### 5.2 Delivery condition

Sheets should be visually examined when delivered to ensure freedom from mechanical damage or other obvious defects. Sheets can be inspected by means of ultrasonics or X-rays where required.

### 5.3 Appearance

Where possible, sheets shall be examined for visual defects by transmitted light using a suitable light source. Otherwise, sufficiently bright reflected light should be used. Any defects thus identified shall be compared with the agreed specification (either in written or sample form) and sentenced accordingly.



## 5.4 Dimensions

### 5.4.1 Thickness ( $h$ )

The thickness,  $h$ , shall be measured using a suitable calibrated equipment according to table 4:

**Table 4: Accuracy of equipment**

Dimensions in millimetres	
Nominal thickness, $h_n$	Accuracy
$0,50 \leq h_n \leq 1,00$	$\leq + 0,01$
$1,00 < h_n \leq 10,00$	$\leq + 0,05$
$10,00 < h_n \leq 40,00$	$\leq + 0,10$

### 5.4.2 Length ( $l$ ) and width ( $b$ )

The length,  $l$ , and width,  $b$ , shall be measured to the nearest 1 mm using a suitable calibrated equipment. Measurements shall be made directly on the surface of the sheet and along the cut edge.

### 5.4.3 Rectangularity

For flat sheets, the rectangularity expressed as the difference between the length of the diagonals according to figure 1,  $|d_1 - d_2|$ , shall be measured to the nearest 1 mm using a calibrated ruler or tape measure.

### 5.4.4 Bow of sheets in rolled form

For sheets in rolled form, the bow shall be determined after the sheets have been pulled freely from the rolls and measured against a straight line. The bow shall be measured to the nearest 1 mm using a suitable calibrated equipment.

## 5.5 Density

Density shall be determined in accordance with ISO 1 183.

## 5.6 Tensile stress at yield ( $\sigma_y$ ) and tensile strain at yield ( $\varepsilon_y$ )

Tensile stress at yield,  $\sigma_y$ , and tensile strain at yield,  $\varepsilon_y$ , shall be determined using at least five type 1B test specimens in each direction in accordance with EN ISO 527- 1 and EN ISO 527- 2 using a test speed of 50 mm/min  $\pm$  5 mm/min.

## 5.7 Modulus of elasticity in tension ( $E_t$ )

Modulus of elasticity in tension,  $E_t$ , shall be determined using at least five type 1B test specimens in each direction in accordance with EN ISO 527- 1 and EN ISO 527-2 using a test speed of 1 mm/min  $\pm$  0,2 mm/min.

## 5.8 Charpy impact strength of notched specimens ( $a_{cn}$ )

Charpy impact strength of notched specimens,  $a_{cn}$ , for nominal thicknesses  $\geq$  4 mm shall be determined in accordance with EN ISO 179/ 1eA using at least 10 test specimens in each direction.