



**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST ISO 6328:1997

<https://standards.iteh.ai/catalog/standards/sist/e5f7624b-3fd7-43bf-865b-4ad6bddac7f0/sist-iso-6328-1997>

---

International Standard



6328

---

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

---

## Photography — Photographic materials — Determination of ISO resolving power

*Photographie — Surfaces sensibles — Détermination du pouvoir résolvant*

First edition — 1982-09-01

**ITeH STANDARD PREVIEW**  
**(standards.iteh.ai)**

[SIST ISO 6328:1997](https://standards.iteh.ai/catalog/standards/sist/e5f7624b-3fd7-43bf-865b-4ad6bddac7f0/sist-iso-6328-1997)

<https://standards.iteh.ai/catalog/standards/sist/e5f7624b-3fd7-43bf-865b-4ad6bddac7f0/sist-iso-6328-1997>

---

UDC 771.537.61

Ref. No. ISO 6328-1982 (E)

**Descriptors** : photography, photographic materials, tests, resolving power determination, definitions.

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards institutes (ISO member bodies). The work of developing International Standards is carried out through ISO technical committees. Every member body interested in a subject for which a technical committee has been set up has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council.

International Standard ISO 6328 was developed by Technical Committee ISO/TC 42, *Photography*, and was circulated to the member bodies in April 1980.

It has been approved by the member bodies of the following countries :

Australia	Italy	South Africa, Rep. of
Belgium	Japan	Spain
Canada	Korea, Dem. P. Rep. of	Switzerland
Czechoslovakia	Netherlands	USA
Egypt, Arab Rep. of	Romania	USSR

The member bodies of the following countries expressed disapproval of the document on technical grounds :

France  
United Kingdom

## Contents

	Page
0 Introduction .....	1
1 Scope and field of application .....	1
2 References .....	1
3 Definitions .....	1
4 Sampling and storage .....	2
5 Method of test .....	2
5.1 Principle .....	2
5.2 Apparatus .....	2
5.3 Optimum exposure test .....	6
5.4 Optimum focus test .....	8
5.5 Maximum resolving power .....	8
5.6 Alternative test procedure .....	9
6 Product classification .....	9
6.1 Resolving power scale .....	9
6.2 Resolving power of a product .....	9
7 Product marking and labelling .....	9

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/sist/6328-1997-3fd7-43bf-865b-4ad6bddac7f0/sist-iso-6328-1997>

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)

This page intentionally left blank

SIST ISO 6328:1997

<https://standards.iteh.ai/catalog/standards/sist/e5f7624b-3fd7-43bf-865b-4ad6bddac7f0/sist-iso-6328-1997>

# Photography — Photographic materials — Determination of ISO resolving power

## 0 Introduction

The resolving power of a photographic material is an estimate of the smallest detail that may be visually observable when recorded on the material, and combines the effects of modulation transfer function, graininess and contrast, all of which contribute to overall image quality, and human observers, each of whom may differ in their assessment of quality. The method is particularly useful for appraising materials that will be viewed at high magnification such as microfilm, 8 mm and 16 mm motion picture film, etc. However, resolving power should not be expected to predict overall image quality in every situation, because image quality is too complex to be described by a single factor. This is particularly the case for low contrast continuous-tone products.

Resolving power as measured by photographing suitable test charts is very dependent on conditions of measurement and the structure of the test pattern. It depends markedly on the photographic conditions employed and on the presence of background glare from the illuminated target. It is affected by such factors as the colour of the light used, the exposure level, the focus, processing procedures, the lens aperture at which the test is made, the contrast of the target and the magnification of the camera lens and that through which the images are observed, etc.

The judgement exercised by the human observer in determining resolving power can be a source of significant experimental error. The criterion of resolution given in this International Standard was selected as it appeared to admit less latitude in interpretation than others.

## 1 Scope and field of application

This International Standard specifies a method for determining the resolving power of photographic films, plates and papers, including black-and-white films, black-and-white printing papers, colour reversal films, colour negative films, and colour printing papers. Materials designed for X-ray and other high-

energy radiation are excluded, as are materials having photopolymer, diazo, etc. light-sensitive layers.

## 2 Reference

ISO 497, *Guide to the choice of preferred numbers and of series containing more rounded values of preferred numbers.*

## 3 Definitions

For the purpose of this International Standard, the following definitions apply :

**3.1 test pattern** : Three parallel bars of equal width and separated by interspaces of the same width.

**3.2 test chart** : Array of test patterns, each identical in form but decreasing sequentially in size.

**3.3 spatial period** : Distance between successive corresponding points on a periodic pattern.

**3.4 spatial frequency** : Reciprocal of the spatial period expressed as cycles per millimetre (c/mm). It denotes the number of identical line pairs that can be contained within an overall width of 1 mm.

**3.5 contrast ratio** : Ratio of the luminance of the bars of the test pattern to the luminance of the surround.

**3.6 camera** : Optical system by which the test chart is imaged and recorded, with suitable reduction in size, on the photographic material being tested.

**3.7 reference surface** : Flat surface against which the emulsion side of the photographic material is pressed during exposure.

## ISO 6328-1982 (E)

**3.8 qualification** (of a camera) : The attainment of the necessary high optical performance of a camera, essential for its use in determining resolving power.

**3.9 replicate set** : Series of images of the chart made at the same focus and exposure settings.

**3.10 exposure series** : Series of images made at different exposure settings.

**3.11 focus series** : Series of images of the resolution chart made at different focus settings.

**3.12 resolving power** : Ability of a photographic material to maintain in the developed image the separate identity of parallel bars when their separation is small. Numerically equal to the spatial frequency of the smallest pattern that can be resolved.

**3.13 resolving power of a replicate set** : Median of the resolving powers of the test material in images of the replicate set.

**3.14 maximum resolving power** : Resolving power of the test material under conditions of optimum focus and exposure.

## 4 Sampling and storage

### 4.1 Product sampling

In determining the ISO resolving power of a product, it is important that the samples evaluated are representative of those used by the consumer. No fewer than three samples shall be obtained from the plant of the manufacturer or from an accredited distributor if they cannot be obtained directly from the manufacturer. In any case, the samples should be taken from products stored according to the manufacturer's recommendations and available in the market. Each sample shall represent a different batch of product.

### 4.2 Storage of samples

After procurement from the manufacturer or distributor, all samples of a product shall be stored in the unopened package for 2 to 4 months under conditions recommended by the manufacturer. When no specific recommendation is made, storage shall be at  $23 \pm 5^\circ\text{C}$  and a relative humidity of  $(50 \pm 20)\%$ . At the end of this storage period, samples should be tested. The basic objective in selecting and storing samples as described above is to ensure the film characteristics obtained are representative of those obtained by a consumer at the time of use.

## 5 Method of test

### 5.1 Principle

The resolving power of a material is determined by visual inspection of the image of the test chart recorded on the test material by means of a suitable camera system. It depends on

exposure, and passes through a maximum as the exposure is increased from a value at the toe of the characteristic curve to a value toward the shoulder. Furthermore, the resolving power passes through a maximum as the focus setting is given successive values that vary from one side of the correct focus to the other.

In brief, the procedure is to first determine the exposure for which the resolving power is maximized; the focus setting used is that found to be optimal during the qualification test. Then with the exposure so determined, the focus is changed by a series of small increments, and the resolving power at the best focus is determined. This is the ISO resolving power of the material.

Because of the variable effect of granularity, a set of pictures made with the same exposure and same focus setting often yields a range of resolving power values. To mitigate the effect of this variable, the International Standard resolving power is defined below in terms of the median value of a set of not less than nine replicated measurements.

Lacking definitive guidance, the criterion that the observer uses to decide whether a given test is or is not resolved is highly individual. Some observers, particularly inexperienced ones, tends to require clear separation of the bars while others are satisfied with much less distinct separation. Experience indicates that without a carefully defined and agreed upon criterion, observers may differ by as much as a factor 2, or even more, in the resolving power value they assign to the same image. However, with training, experienced observers should agree to within  $\pm$  one pattern or about  $\pm 12\%$  in terms of cycles per millimetre.

Describing a resolving power criterion in such a way that the same criterion is used by all observers is difficult. The criterion used in this International Standard is arbitrary, as any criterion must be, but was selected because it appears to admit less latitude in interpretation than any other criterion.

## 5.2 Apparatus

### 5.2.1 Test pattern

The test pattern shall be the three-bar pattern inscribed in a square as shown in figure 1. The shaded part of figure 1 represents the darker portion, and the unshaded part the lighter portion, of the field of view. In terms of displacement  $L$  of the bars, the dimensions of the square are  $2,5 L \times 2,5 L$ . The shaded part of figure 1 is termed the "surround".

The overall width and length of the pattern in figure 1 shall be within 5 % of the nominal value  $2,5 L$ . The width of the bars and the width of the interspaces shall be the same within 5 %.

The spatial frequency of the test patterns shall be calculated by measuring the overall pattern width ( $2,5 L$ ) and using the formula :

$$\text{Spatial frequency (cycles per millimetre)} = \frac{2,5}{\text{Overall pattern width, in millimetres}}$$



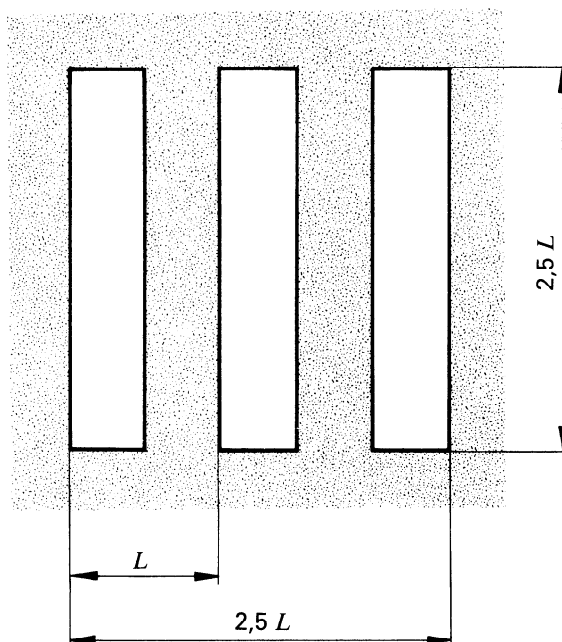


Figure 1 – Three-bar square test pattern

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

## 5.2.2 Test chart

The test chart may be an array of test patterns as illustrated in figure 2. The cycles of the test patterns in the array may be as shown in table 1. The change in spatial frequency between successive patterns shall be equal to  $20\sqrt{10}$ . This corresponds to increments of about 12 %.

The test chart shall be a non-selective neutral transparency.

The array of test patterns in figure 2 is approximately 100 mm square and is centered in a surround that is about 125 mm square. The two horizontal lines are  $100 \pm 0,5$  mm apart and are used to determine the magnification.

The luminance of the three bars of each test pattern and the luminance of the surround shall be measured<sup>1)</sup> at the position of the eyepiece which serves as the imaging lens.

This International Standard defines two different kinds of resolving power corresponding to test charts of two different contrast ratios.

### 5.2.2.1 High-contrast test chart

For the high-contrast test chart, the common logarithm of the

contrast ratio shall be at least 2,0. This is equivalent to a contrast ratio of 100.

### 5.2.2.2 Low-contrast test chart

For the low-contrast test chart, the common logarithm of the contrast ratio shall be  $0,20 \pm 0,02$ . This is equivalent to a contrast ratio of 1,6.

### 5.2.2.3 Illumination of the test chart

The test chart shall be transilluminated by a diffuse light source and the illuminance shall not vary more than 5 % over the area of the chart. The light transmitted by the test chart shall have spectral characteristics similar to those for which the material is designed, and be specified when quoting International Standard resolving power.

The luminance of the surround of the low-contrast test chart shall be as uniform as the state-of-the-art permits when the test chart is placed before a uniform diffuse source of light. In particular, the luminance shall be uniform to within  $\pm 5$  % up to a distance of 10 mm outwards from the edges of the test pattern.

1) A spot photometer may be used to measure the luminance of the surround and that of the largest bars to verify contrast ratio of the test chart in position in the resolving power test instrument. Since it will not be feasible to measure the luminance of the smaller bars with the spot photometer, a micro-densitometer may be used to verify the contrast uniformity of the test chart from the largest to the smallest test patterns.