

INTERNATIONAL STANDARD

NORME INTERNATIONALE



BASIC SAFETY PUBLICATION

PUBLICATION FONDAMENTALE DE SÉCURITÉ

Fire hazard testing – *STANDARD PREVIEW*
Part 2-11: Glowing/hot-wire based test methods – Glow-wire flammability test method for end-products (GWEPT)
(standards.iteh.ai)

IEC 60695-2-11:2014
Essais relatifs aux risques du feu –
Partie 2-11: Essais au fil incandescent/chauffant – Méthode d'essai d'inflammabilité pour produits finis (GWEPT)





THIS PUBLICATION IS COPYRIGHT PROTECTED
Copyright © 2014 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de l'IEC ou du Comité national de l'IEC du pays du demandeur. Si vous avez des questions sur le copyright de l'IEC ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de l'IEC de votre pays de résidence.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
Fax: +41 22 919 03 00
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

IEC Catalogue - webstore.iec.ch/catalogue

The stand-alone application for consulting the entire bibliographical information on IEC International Standards, Technical Specifications, Technical Reports and other documents. Available for PC, Mac OS, Android Tablets and iPad.

IEC publications search - www.iec.ch/searchpub

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and also once a month by email.

Electropedia - www.electropedia.org

The world's leading online dictionary of electronic and electrical terms containing more than 30 000 terms and definitions in English and French, with equivalent terms in 14 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Glossary - std.iec.ch/glossary

More than 55 000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: csc@iec.ch.

A propos de l'IEC

La Commission Electrotechnique Internationale (IEC) est la première organisation mondiale qui élabore et publie des Normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications IEC

Le contenu technique des publications IEC est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

Catalogue IEC - webstore.iec.ch/catalogue

Application autonome pour consulter tous les renseignements bibliographiques sur les Normes internationales, Spécifications techniques, Rapports techniques et autres documents de l'IEC. Disponible pour PC, Mac OS, tablettes Android et iPad.

Recherche de publications IEC - www.iec.ch/searchpub

La recherche avancée permet de trouver des publications IEC en utilisant différents critères (numéro de référence, texte, comité d'études,...). Elle donne aussi des informations sur les projets et les publications remplacées ou retirées.

IEC Just Published - webstore.iec.ch/justpublished

Restez informé sur les nouvelles publications IEC. Just Published détaille les nouvelles publications parues. Disponible en ligne et aussi une fois par mois par email.

Electropedia - www.electropedia.org

Le premier dictionnaire en ligne de termes électroniques et électriques. Il contient plus de 30 000 termes et définitions en anglais et en français, ainsi que les termes équivalents dans 14 langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International (IEV) en ligne.

Glossaire IEC - std.iec.ch/glossary

Plus de 55 000 entrées terminologiques électrotechniques, en anglais et en français, extraites des articles Termes et Définitions des publications IEC parues depuis 2002. Plus certaines entrées antérieures extraites des publications des CE 37, 77, 86 et CISPR de l'IEC.

Service Clients - webstore.iec.ch/csc

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions contactez-nous: csc@iec.ch.



IEC 60695-2-11

Edition 2.0 2014-02

INTERNATIONAL STANDARD

NORME INTERNATIONALE



BASIC SAFETY PUBLICATION

PUBLICATION FONDAMENTALE DE SÉCURITÉ

Fire hazard testing – Part 2-11: Glowing/hot-wire based test methods – Glow-wire flammability test method for end-products (GWEPT)

Essais relatifs aux risques du feu – Partie 2-11: Essais au fil incandescent/chauffant – Méthode d'essai d'inflammabilité pour produits finis (GWEPT)

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

COMMISSION
ELECTROTECHNIQUE
INTERNATIONALE

PRICE CODE
CODE PRIX

P

ICS 13.220.40, 29.020

ISBN 978-2-8322-1373-5

**Warning! Make sure that you obtained this publication from an authorized distributor.
Attention! Veuillez vous assurer que vous avez obtenu cette publication via un distributeur agréé.**

CONTENTS

FOREWORD	3
INTRODUCTION	5
1 Scope	6
2 Normative references	6
3 Terms and definitions	6
4 Test specimens	8
4.1 General	8
4.2 Complete end product	8
4.3 Partial end product (alternative)	8
4.4 Test considerations and limitations associated with the specimen configuration	9
5 Test apparatus	10
6 Verification of the temperature measuring system	10
7 Conditioning	10
7.1 Conditioning of test specimens	10
7.2 Conditioning of specified layers	10
7.3 Testing conditions	10
8 Test procedure	10
8.1 General	10
8.2 Test temperatures	11
8.3 Number of test specimens	11
9 Observations and measurements	11
10 Evaluation of test results	12
11 Test report	12
12 Information to be given in the relevant product standard	12
Annex A (informative) Suggested GWEPT temperatures	13
Bibliography	14
Figure 1 – Small parts	9
Figure A.1 – Suggested GWEPT temperatures	13
Table 1 – Test temperatures	11

INTERNATIONAL ELECTROTECHNICAL COMMISSION

FIRE HAZARD TESTING –

**Part 2-11: Glowing/hot-wire based test methods –
Glow-wire flammability test method for end-products (GWEPT)**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 60695-2-11 has been prepared by IEC technical committee 89: Fire hazard testing.

The text of this standard is based on the following documents:

FDIS	Report on voting
89/1197/FDIS	89/1206/RVD

Full information on the voting for the approval of this standard can be found in the report on voting indicated in the above table.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

It has the status of a basic safety publication in accordance with IEC Guide 104 and ISO/IEC Guide 51.

This standard is to be used in conjunction with IEC 60695-2-10.

This second edition of IEC 60695-2-11 cancels and replaces the first edition of IEC 60695-2-11 published in 2000. It constitutes a technical revision.

The main changes with respect to the previous edition are listed below:

- The Introduction has been added to provide background and how it relates to the Scope.
- The Scope has been modified for greater clarity and reference to basic safety publications.
- Numerous terms and definitions relevant to this Standard have been added to Clause 3.
- The application of “small parts” and “insignificant mass” have been introduced and clarified.
- The different types of specimens, how to specify them, and limitations of the test method have been further clarified in Clause 4.
- Clarified in Clause 5 the distance to specified layer when unknown.
- The information from Clause 6 has been moved into the test procedure in Clause 8.
- The conditioning of the specified layer and the laboratory ambient test conditions were clarified in Clause 7.
- Measurement of the maximum flame height was removed from Clause 9.
- The reference to this test as “GWEPT” was introduced along with an applicable title change.
- Annex A has been revised to reflect current practice by prominent product committees.

The committee has decided that the contents of this publication will remain unchanged until the stability date indicated on the IEC web site under "http://webstore.iec.ch" in the data related to the specific publication. At this date the publication will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

INTRODUCTION

The purpose of this Introduction is to provide background regarding the basic guidance that prompted the preparation of this International Standard and how it relates to the Scope.

In the design of any electrotechnical product, the risk of fire and the potential hazards associated with fire need to be considered. In this respect the objective within the design of component, circuit, and product design, as well as the choice of the materials, is to reduce to acceptable levels the potential risks of fire during normal operating conditions, reasonable foreseeable abnormal use, malfunction, and/or failure. IEC Technical Committee 89 has developed IEC 60695-1-10, together with its companion, IEC 60695-1-11, to provide guidance on how this is to be accomplished.

The primary aims of IEC 60695-1-10 and IEC 60695-1-11 are to provide guidance on how:

- a) to prevent ignition caused by an electrically energized component part, and
- b) to confine any resulting fire within the bounds of the enclosure of the electrotechnical product in the event of ignition.

Secondary aims of these documents include the minimization of any flame spread beyond the product's enclosure and the minimization of harmful effects of fire effluents such as heat, smoke, toxicity and/or corrosivity.

Fires involving electrotechnical products can also be initiated from external non-electrical sources. Considerations of this nature should be dealt with in the overall fire hazard assessment.

In electrotechnical equipment, overheated metal parts can act as ignition sources. In glow-wire tests, a glowing wire is used to simulate such an ignition source.

IEC 60695-2-10 describes a glow-wire test apparatus and common test procedure, IEC 60695-2-12 describes a glow-wire flammability index (GWFI) test method for materials, and IEC 60695-2-13 describes a glow-wire ignition temperature (GWIT) test method for materials.

This standard is used to assess the reaction of end products to heat caused by contact with an electrically heated wire under controlled laboratory conditions. This may be useful for the evaluation of end products that may be exposed to excess thermal stress such as a fault current flowing through a wire, overloading of components, and/or poor electrical connections. It should not be used to solely describe or appraise the fire hazard or fire risk of products, or assemblies under actual fire conditions. However, results of this test may be used as elements of a fire hazard assessment which takes into account all of the factors which are pertinent to a particular end use.

This international standard may involve hazardous materials, operations, and equipment. It does not purport to address all of the safety problems associated with its use. It is the responsibility of the user of this international standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

FIRE HAZARD TESTING –

Part 2-11: Glowing/hot-wire based test methods – Glow-wire flammability test method for end-products (GWEPT)

1 Scope

This part of IEC 60695 specifies a test method on an end product. It is intended to simulate the effects of thermal stresses produced by an electrically heated source to represent a fire hazard.

This test method is used to check that, under defined test conditions, an end product exposed to an electrically heated source has either a limited ability to ignite or, if it ignites, a limited ability to propagate flame. However, the fire hazard analysis, the flammability aspects and the flame spreading to other products are not covered by the present standard.

This basic safety publication is intended for use by technical committees in the preparation of standards in accordance with the principles laid down in IEC Guide 104 and ISO/IEC Guide 51.

One of the responsibilities of a technical committee is, wherever applicable, to make use of basic safety publications in the preparation of its publications. The requirements, test methods or test conditions of this basic safety publication will not apply unless specifically referred to or included in the relevant publications.

[IEC 60695-2-11:2014](https://standards.iteh.ai/catalog/standards/sist/3573bc31-509b-4d54-ad2d-31165d401831/iec-60695-2-11-2014)

2 Normative references

<https://standards.iteh.ai/catalog/standards/sist/3573bc31-509b-4d54-ad2d-31165d401831/iec-60695-2-11-2014>

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60695-2-10, *Fire hazard testing – Part 2-10: Glowing/hot-wire based test methods – Glow-wire apparatus and common test procedure*

IEC Guide 104, *The preparation of safety publications and the use of basic safety publications and group safety publications*

ISO/IEC Guide 51, *Safety aspects – Guidelines for their inclusion in standards*

3 Terms and definitions

For the purpose of this document the following terms and definitions apply.

3.1

burn, intransitive verb
undergo combustion

[SOURCE: ISO/IEC 13943:2008, definition 4.28]

3.2

combustible, adjective
capable of being ignited and burned

[SOURCE: ISO/IEC 13943:2008, definition 4.43]

3.3

combustion
exothermic reaction of a substance with an oxidizing agent

Note 1 to entry: Combustion generally emits fire effluent accompanied by flames and/or glowing.

[SOURCE: ISO/IEC 13943:2008, definition 4.46]

3.4

enclosure
(electrotechnical) external casing protecting the electrical and mechanical parts of apparatus

Note 1 to entry: The term excludes cables.

[SOURCE: ISO/IEC 13943:2008, definition 4.78]

3.5

end product
product that is ready for use without modification

Note 1 to entry: An end product can be a component of another end product.

[SOURCE: IEC 60695-4:2012, definition 3.2.7]

3.6

fire hazard
physical object or condition with a potential for an undesirable consequence from fire

[SOURCE: ISO/IEC 13943:2008, definition 4.112]

3.7

fire hazard assessment
evaluation of the possible causes of fire, the possibility and nature of subsequent fire growth, and the possible consequences of fire

[SOURCE: IEC 60695-4:2012, definition 3.2.10]

3.8

fire risk
probability of a fire combined with a quantified measure of its consequence

Note 1 to entry: It is often calculated as the product of probability and consequence.

[SOURCE: ISO/IEC 13943:2008, definition 4.124]

3.9

flame
rapid, self sustaining, sub-sonic propagation of combustion in a gaseous medium, usually with emission of light

[SOURCE: ISO/IEC 13943:2008, definition 4.133]

3.10

flame spread

propagation of a flame front

[SOURCE: ISO/IEC 13943:2008, definition 4.142]

3.11

flammability

ability of a material or product to burn with a flame under specified conditions

[SOURCE: ISO/IEC 13943:2008, definition 4.151]

3.12

glowing, adjective

emitting light without flame from the combustion of a material in the solid phase

3.13

ignition

sustained ignition (deprecated)
(general) initiation of combustion

[SOURCE: ISO/IEC 13943:2008, definition 4.187]

3.14

insignificant mass

insufficient combustible material to constitute a fire hazard

Note 1 to entry: A default value is 2 g, but product TCs may assign a different value appropriate to the product type and scale.

[SOURCE: IEC 60695-4:2012, definition 3.2.16]

3.15

small part

part with a dimension less than the minimum specified for the relevant test method

[SOURCE: IEC 60695-4:2012, definition 3.2.25]

4 Test specimens

4.1 General

It is not necessary to test end products or parts of end products which have insignificant mass. Additionally, this test method is not suitable for testing small parts (see 4.4).

4.2 Complete end product

It is preferred that the test specimen should be a complete end product as opposed to a partial end product (see 4.3). The test specimen shall be chosen so that the conditions of the test will not be significantly different from those occurring in normal use with regard to shape, ventilation, effect of thermal stresses, and eventually, the effects of burning or glowing particles falling from the test specimen.

4.3 Partial end product (alternative)

If the test cannot be made on a complete end product then, unless otherwise specified by the relevant product standard, it is acceptable to

- a) cut a piece containing the part under examination from a complete and assembled end product, or
- b) cut an aperture in the complete end product to allow the glow-wire access, or
- c) remove the part under examination in its entirety and test it separately.

Technical committees should define in their relevant product standards what may be removed to achieve access. So far as possible, these product standards should strive to replicate actual service locations and conditions.

4.4 Test considerations and limitations associated with the specimen configuration

When cutting an opening for access purposes, a small aperture may affect the results by leading to the ignition of the surroundings and/or reducing the temperature of the tip of the glow-wire. The opening should be large enough to supply an adequate supply of air for combustion.

If, during the test, any part of the equipment containing the test specimen is ignited by extraneous heat from the glow-wire which in turn influences the thermal conditions at the test specimen, the test shall be invalid.

The glow-wire flammability test method for end products shall not be used for testing small parts. This is because such parts cannot be effectively supported to avoid heat losses (see IEC 60695-2-10), and they are not able to accommodate the penetration of the glow-wire.

The following are considered to be small parts:

- a) where each surface lies completely within a circle of 15 mm in diameter; or
- b) where it is not possible to fit a circle of 8 mm in diameter completely on at least one of the surfaces while, at least one part dimension is > 15 mm.

See Figure 1.

When checking a surface,

- a) projections on the surface are disregarded and
- b) holes or recesses which are not greater than 2 mm in any dimension are disregarded.

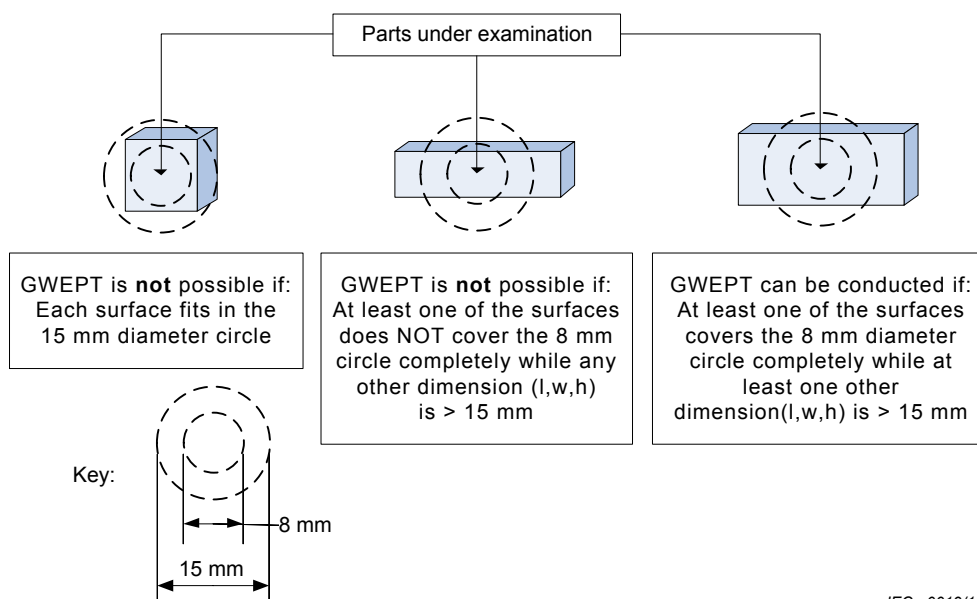


Figure 1 – Small parts

5 Test apparatus

The test apparatus is specified in IEC 60695-2-10.

To evaluate the possibility of the spread of fire, for example by burning or glowing particles falling from the test specimen, a specified layer as described in IEC 60695-2-10, or the material or components normally surrounding or situated underneath the test specimen, are placed underneath the test specimen. The distance between the test specimen and the specified layer representing the surrounding material or components, shall be equal to that which occurs in end use. If the test specimen is a component such that surrounding materials and distances are unknown, then the wrapping tissue / wooden board specified layer described in IEC 60695-2-10 shall be placed $200 \text{ mm} \pm 5 \text{ mm}$ below the glow wire point of contact.

If the test specimen is a complete free-standing equipment, it is placed in its normal position of use on the specified layer as described in IEC 60695-2-10 extending for at least 100 mm outside the base of the equipment in all directions.

If the test specimen is a complete wall-mounted equipment, it is fixed in its normal position of use $200 \text{ mm} \pm 5 \text{ mm}$ above the specified layer as described in IEC 60695-2-10.

6 Verification of the temperature measuring system

The method of verification of the temperature measuring system is specified in IEC 60695-2-10.

7 Conditioning

[IEC 60695-2-11:2014](#)

<https://standards.iteh.ai/catalog/standards/sist/3573bc31-509b-4d54-ad2d-311654491831/iec-60695-2-11-2014>

7.1 Conditioning of test specimens

Unless otherwise specified in the relevant product standard, the test specimens shall be conditioned for 24 h in an atmosphere having a temperature between $15 \text{ }^{\circ}\text{C}$ and $35 \text{ }^{\circ}\text{C}$ and a relative humidity between 45 % and 75 %.

7.2 Conditioning of specified layers

If the wrapping tissue / wooden board specified layer is used, the conditioning shall be carried out according to IEC 60695-2-10. If the material or components normally surrounding or situated underneath the test specimen is used, the material or components shall be conditioned in the same way as the test specimen (see 7.1).

7.3 Testing conditions

The test specimens shall be tested in a laboratory atmosphere having a temperature between $15 \text{ }^{\circ}\text{C}$ and $35 \text{ }^{\circ}\text{C}$ and a relative humidity less than or equal to 75 %. Testing shall be completed within 30 minutes after the specimen is removed from the conditions specified in 7.1.

8 Test procedure

8.1 General

In addition to the common test procedure specified in IEC 60695-2-10, if not otherwise specified, the test specimen shall be so arranged that the tip of the glow-wire is applied to the part of the surface of the test specimen which is likely to be subjected to thermal stresses in normal use. The glow-wire shall be maintained as close to the horizontal as is practicable.