



SLOVENSKI STANDARD
SIST ISO 4696-1:2000
01-junij-2000

Iron ores -- Static test for low-temperature reduction-disintegration -- Part 1: Reaction with CO, CO₂ and H₂

Iron ores -- Static test for low-temperature reduction-disintegration -- Part 1: Reaction with CO, CO₂ and H₂

iTeh STANDARD PREVIEW

Minerais de fer -- Essai statique de désagrégation par réduction à basse température -- Partie 1: Réaction avec CO, CO₂ et H₂

[SIST ISO 4696-1:2000](https://standards.iteh.ai/catalog/standards/sist/1adedad8-f3e4-41bb-be28-cc680360f300/sist-iso-4696-1-2000)

Ta slovenski standard je istoveten z: **ISO 4696-1:1996**

ICS:

73.060.10 Železove rude Iron ores

SIST ISO 4696-1:2000 en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST ISO 4696-1:2000

<https://standards.iteh.ai/catalog/standards/sist/1adedad8-f3e4-41bb-be28-cc68b380f300/sist-iso-4696-1-2000>

INTERNATIONAL
STANDARD

ISO
4696-1

First edition
1996-10-01

**Iron ores — Static test for low-temperature
reduction-disintegration —**

Part 1:
Reaction with CO, CO₂ and H₂

<https://standards.iteh.ai/catalog/standards/sist-iso-4696-1-2000>
Minerais de fer — Essai statique de désagrégation par réduction à basse température —

Partie 1: Réaction avec CO, CO₂ et H₂



Reference number
ISO 4696-1:1996(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

iTeh STANDARD PREVIEW

International Standard ISO 4696-1 was prepared by Technical Committee ISO/TC 102, *Iron ores*, Subcommittee SC 3, *Physical testing*. (standards.iteh.ai)

Together with part 2, this part of ISO 4696 cancels and replaces ISO 4696:1984, which has been technically revised. (<https://standards.iteh.ai/catalog/standards/sist/1adedad8-3e4-41bb-be28-cc68b380f300/sist-iso-4696-1-2000>)

ISO 4696 consists of the following parts, under the general title *Iron ores — Static test for low-temperature reduction-disintegration*:

- Part 1: *Reaction with CO, CO₂ and H₂*
- Part 2: *Reaction with CO*

Annex A forms an integral part of this part of ISO 4696. Annex B is for information only.

© ISO 1996

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Introduction

This part of ISO 4696 describes a test method for evaluating the disintegration behaviour of iron ores under specific conditions relevant to the low-temperature zone in the blast furnace for ironmaking.

It describes a test method for evaluating the disintegration behaviour of iron ore under specific conditions. The specific conditions are:

- a test sample having a specified size range;
- a specified test sample mass;
- isothermal reduction;
- reduction in a fixed bed;
- reduction with a specified gas composition and flow;
- tumbling in a drum having specified dimensions.

The results of this test should be considered in conjunction with the results of other reduction tests, e.g. ISO 4695, ISO 4698 and ISO 7215 (see annex B), particularly those conducted at high temperatures.

ISO 4696-2 describes an alternative method adopting different test conditions.

iTeh STANDARD PREVIEW
This page intentionally left blank
(standards.iteh.ai)

SIST ISO 4696-1:2000

<https://standards.iteh.ai/catalog/standards/sist/1adedad8-f3e4-41bb-be28-cc68b380f300/sist-iso-4696-1-2000>

Iron ores — Static test for low-temperature reduction-disintegration —

Part 1:

Reaction with CO, CO₂ and H₂

1 Scope

This part of ISO 4696 specifies a method for testing the disintegration of iron ores by tumbling, at room temperature, a test portion that has been reduced in a fixed bed at a temperature of 500 °C.

The method is applicable to sized iron ores and to iron-ore agglomerates such as pellets or sinter.

[SIST ISO 4696-1:2000](https://standards.iteh.ai/catalog/standards/sist/1adedad8-3e4-41bb-be28-cc68b380f300/sist-iso-4696-1-2000)

<https://standards.iteh.ai/catalog/standards/sist/1adedad8-3e4-41bb-be28-cc68b380f300/sist-iso-4696-1-2000>

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this part of ISO 4696. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this part of ISO 4696 are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 3081:1986, *Iron ores — Increment sampling — Manual method.*

ISO 3083:1986, *Iron ores — Preparation of samples — Manual method.*

3 Principle

A test portion with a specified size range is subjected to static reduction at a temperature of 500 °C using reducing gas consisting of CO, CO₂, H₂ and N₂.

After 1 h reduction time, the test portion is cooled to a temperature below 100 °C and tumbled by using a small tumbler drum for 300 revolutions in total. It is then sieved with test sieves having square mesh apertures of 6,30 mm, 3,15 mm and 500 µm.

The reduction-disintegration index (RDI-1) is calculated as a quantitative measure of the degree of disintegration of an iron ore that has been reduced and then tumbled: the percentage masses of material greater than 6,30 mm, less than 3,15 mm and less than 500 µm, respectively, are related to the total mass of the test portion after reduction and before tumbling.

4 Test conditions

Gas volumes and flow rates used in this part of ISO 4696 are as measured at a temperature of 0 °C and at atmospheric pressure (101,325 kPa)¹⁾.

4.1 Composition of reducing gas

The reducing gas shall consist of

CO	20 % (V/V) ± 0,5 % (V/V)
CO ₂	20 % (V/V) ± 0,5 % (V/V)
H ₂	2,0 % (V/V) ± 0,5 % (V/V)
N ₂	58 % (V/V) ± 0,5 % (V/V)

4.2 Purity of reducing gas

Impurities in the reducing gas shall not exceed

O ₂	0,1 % (V/V)
H ₂ O	0,2 % (V/V)

iTeh STANDARD PREVIEW
(standards.iteh.ai)

4.3 Flow rate of reducing gas

The reducing-gas flow rate shall, during the test period, be maintained at 20 l/min ± 1 l/min.

[SIST ISO 4696-1:2000](https://standards.iteh.ai/catalog/standards/sist/1adedad8-3e4-41bb-be28-cc68b380f300/sist-iso-4696-1-2000)

<https://standards.iteh.ai/catalog/standards/sist/1adedad8-3e4-41bb-be28-cc68b380f300/sist-iso-4696-1-2000>

4.4 Temperature of test

The reducing gas shall be preheated before entering the test portion to maintain the test portion at 500 °C ± 5 °C during the entire test period.

5 Apparatus

Figure 1 shows a schematic example of the test apparatus which shall consist of the following:

5.1 Gas supply system, capable of supplying the gases and regulating gas flow rates.

5.2 Reduction tube, made of non-scaling, heat-resisting metal to withstand a temperature of greater than 600 °C. The diameter of the sample bed shall be 75 mm ± 1 mm.

Figure 2 shows an example of such a reduction tube.

5.3 Electrically heated furnace, having a heating capacity sufficient to maintain the entire test portion and the gas entering the bed at 500 °C, and being equipped with a heating element suitable for the specified temperature.

1) 1 mmHg = 0,133 3 kPa; 1 atm = 0,101 325 MPa.

5.4 Tumbler drum, consisting of a vessel having an internal diameter of 130 mm and an inside length of 200 mm.

Two equally spaced steel lifters 200 mm long, 20 mm wide and 2 mm thick shall be mounted longitudinally inside the drum. These may be mounted on a frame that can be inserted inside the vessel from one end.

One end of the vessel shall be closed and the other open. A close-fitting lid shall be held in place on the opening to ensure a dust-tight seal.

Figure 3 shows an example of such a tumbler drum.

5.5 Test sieves, having square mesh apertures of the following nominal sizes:

16,0 mm; 12,5 mm; 10,0 mm; 6,30 mm; 3,15 mm and 500 μm .

5.6 Weighing device, of adequate load capacity and accurate to 0,1 g.

iTeh STANDARD PREVIEW (standards.iteh.ai)

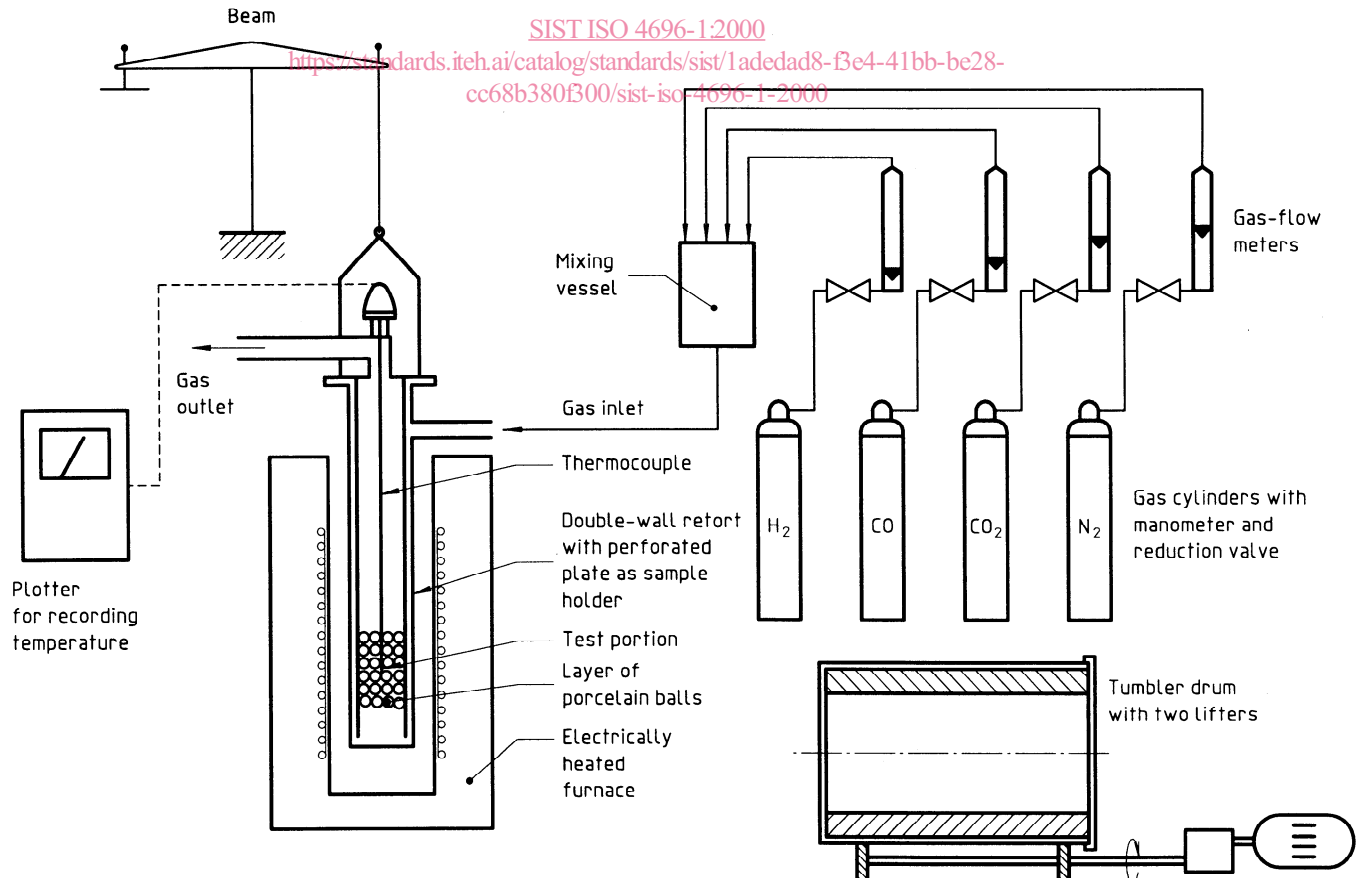


Figure 1 — Arrangement of a test unit