

INTERNATIONAL STANDARD

**IEC
60426**

Second edition
2007-01

**Electrical insulating materials –
Determination of electrolytic corrosion
caused by insulating materials –
Test methods**

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[IEC 60426:2007](#)

<https://standards.iteh.ai/catalog/standards/iec/d0c3c831-b175-4f31-a749-2a50ddfl398c/iec-60426-2007>



Reference number
IEC 60426:2007(E)

Publication numbering

As from 1 January 1997 all IEC publications are issued with a designation in the 60000 series. For example, IEC 34-1 is now referred to as IEC 60034-1.

Consolidated editions

The IEC is now publishing consolidated versions of its publications. For example, edition numbers 1.0, 1.1 and 1.2 refer, respectively, to the base publication, the base publication incorporating amendment 1 and the base publication incorporating amendments 1 and 2.

Further information on IEC publications

The technical content of IEC publications is kept under constant review by the IEC, thus ensuring that the content reflects current technology. Information relating to this publication, including its validity, is available in the IEC Catalogue of publications (see below) in addition to new editions, amendments and corrigenda. Information on the subjects under consideration and work in progress undertaken by the technical committee which has prepared this publication, as well as the list of publications issued, is also available from the following:

- **IEC Web Site** (www.iec.ch)
- **Catalogue of IEC publications**
The on-line catalogue on the IEC web site (www.iec.ch/searchpub) enables you to search by a variety of criteria including text searches, technical committees and date of publication. On-line information is also available on recently issued publications, withdrawn and replaced publications, as well as corrigenda.
- **IEC Just Published**
This summary of recently issued publications (www.iec.ch/online_news/justpub) is also available by email. Please contact the Customer Service Centre (see below) for further information.
- **Customer Service Centre**
If you have any questions regarding this publication or need further assistance, please contact the Customer Service Centre:

Email: custserv@iec.ch
Tel: +41 22 919 02 11
Fax: +41 22 919 03 00

INTERNATIONAL STANDARD

IEC 60426

Second edition
2007-01

Electrical insulating materials – Determination of electrolytic corrosion caused by insulating materials – Test methods

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[IEC 60426:2007](https://standards.iteh.ai/catalog/standards/iec/d0c3c831-b175-4f31-a749-2a50ddfl398c/iec-60426-2007)

<https://standards.iteh.ai/catalog/standards/iec/d0c3c831-b175-4f31-a749-2a50ddfl398c/iec-60426-2007>

© IEC 2007 — Copyright - all rights reserved

No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Electrotechnical Commission, 3, rue de Varembé, PO Box 131, CH-1211 Geneva 20, Switzerland
Telephone: +41 22 919 02 11 Telefax: +41 22 919 03 00 E-mail: inmail@iec.ch Web: www.iec.ch



Commission Electrotechnique Internationale
International Electrotechnical Commission
Международная Электротехническая Комиссия

PRICE CODE

U

For price, see current catalogue

CONTENTS

FOREWORD.....	4
INTRODUCTION.....	6
1 Scope.....	7
2 Normative references	7
3 Terms and definitions	7
4 General description of the test method	8
5 Test specimens	8
5.1 General.....	8
5.2 Cut surfaces of rigid materials (blocks, plates, sheets or semi-finished materials).....	9
5.3 Cast, moulding, injection and pressed materials.....	9
5.4 Cut surfaces of flexible films, foils and thin sheets.....	9
5.5 Adhesive tapes.....	10
5.6 Flexible sleeving and tubing	10
5.7 Lacquers and insulating varnishes.....	10
5.8 Cleanliness of contact surfaces	10
5.9 Number of test specimens	11
6 Test strips	11
6.1 General.....	11
6.2 Preparation of the test strips	11
6.3 Cleanliness of test strips	12
7 Test device.....	12
8 Test conditions	14
9 Test procedure	14
10 Evaluation	14
10.1 General evaluation	14
10.2 Visual inspection of the test strips	15
10.3 Tensile strength of test strips	15
11 Evaluation of corrosion on copper strips	16
12 Test report.....	17
Annex A (normative) Tables for the evaluation of corrosion on brass and aluminium strips	18
Annex B (informative) Notes on visual evaluation	20
Annex C (informative) Copper wire tensile strength method	21
Figure 1 – Test specimen of rigid material, for example textile laminate.....	8
Figure 2 – Test specimen of flexible material, for example flexible films, foils etc.....	10
Figure 3 – Test strip.....	12
Figure 4 – Test device for determining electrolytic corrosion.....	13
Figure C.1 – Apparatus for determining electrolytic corrosion of rigid insulating material	23
Figure C.2 – Apparatus for determining electrolytic corrosion of flexible insulating material	23

Table 1 – Degrees of corrosion of copper strips	16
Table A.1 – Degrees of corrosion of brass strips	18
Table A.2 – Degrees of corrosion of aluminium strips	19

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[IEC 60426:2007](#)

<https://standards.iteh.ai/catalog/standards/iec/d0c3c831-b175-4f31-a749-2a50ddfl398c/iec-60426-2007>

INTERNATIONAL ELECTROTECHNICAL COMMISSION

**ELECTRICAL INSULATING MATERIALS –
DETERMINATION OF ELECTROLYTIC CORROSION CAUSED BY
INSULATING MATERIALS –
TEST METHODS****FOREWORD**

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of the IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC provides no marking procedure to indicate its approval and cannot be rendered responsible for any equipment declared to be in conformity with an IEC Publication.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 60426 has been prepared by IEC technical committee 112: Evaluation and qualification of electrical insulating materials and systems.

This second edition cancels and replaces the first edition, published in 1973, and constitutes a technical revision.

The main changes with respect to the previous edition are listed below:

- experience has indicated the need for improved description of the experimental method. It describes a revised procedure for the visual and tensile strength test method that overcomes the limitations of the first edition;
- one older method of the first edition has partly been maintained in the informative annex.

The text of this standard is based on the following documents:

FDIS	Report on voting
112/45/FDIS	112/55/RVD

Full information on the voting for the approval of this standard can be found in the report on voting indicated in the above table.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

A bilingual version of this publication may be issued at a later date.

The committee has decided that the contents of this publication will remain unchanged until the maintenance result date indicated on the IEC web site under “<http://webstore.iec.ch>” in the data related to the specific publication. At this date, the publication will be

- reconfirmed;
- withdrawn;
- replaced by a revised edition, or
- amended.

iTeh Standards
(<https://standards.itih.ai>)
Document Preview

[IEC 60426:2007](#)

<https://standards.itih.ai/catalog/standards/iec/d0c3c831-b175-4f31-a749-2a50ddfl398c/iec-60426-2007>

INTRODUCTION

Electrical insulating materials at high atmospheric humidity and under influence of electric stress may cause corrosion of metal parts being in contact with them. Such electrolytic corrosion is dependent upon the composition of the insulating material and the character of the metal; it is influenced by temperature, relative humidity, nature of the voltage and the time of exposure. Direct voltage produces much more rapid and extensive corrosion than alternating voltage. Corrosion is more pronounced at the positive electrode.

Not only copper but also most other metals, except the noble metals such as platinum or gold, are subject to electrolytic corrosion. Electrolytic corrosion, however, is usually determined with insulating materials in contact with copper, brass or aluminium. Copper, however, is a basic metal and most frequently used in electrotechnical, teletechnical and electronic equipment, especially for current conducting parts and therefore it was chosen as a basic test metal. Other metals may be used when needed for special purposes, but the results may differ from those described in this method.

Electrolytic corrosion may cause open-circuit failure in electrical conductors and devices. It may promote low resistance leakage path across or through electrical insulation and the products of corrosion may otherwise interfere with the operation of electrical devices, i.e. may prevent operation of contacts, etc.

Electronic equipment operating under conditions of high humidity and elevated temperature may be particularly subjected to failure from electrolytic corrosion. Therefore, the selection of insulating materials, which do not produce electrolytic corrosion, is important for such applications.

The test method described in this second edition replaces two separate methods of the first edition – visual and tensile strength method. The former tensile strength method of the first edition, using copper wires, has been maintained in an informative annex. It must be emphasized that the advantage of this new method is that the same strip used for visual inspection is next used for the tensile strength test in opposite to the method described in the first edition. Therefore the correlation between tensile strength and visual examination is more obvious.

ELECTRICAL INSULATING MATERIALS –

DETERMINATION OF ELECTROLYTIC CORROSION CAUSED BY INSULATING MATERIALS – TEST METHODS

1 Scope

This standard determines the ability of insulating materials to produce electrolytic corrosion on metals being in contact with them under the influence of electric stress, high humidity and elevated temperature.

The effect of electrolytic corrosion is assessed in one test by using consecutively two methods:

- visual semi-quantitative method consisting in comparing visually the corrosion appearing on the anode and cathode metal strips, with those given in the reference figures.

This method consists of the direct visual assessment of the degree of corrosion of two copper strips, acting as anode and cathode respectively, placed in contact with the tested insulating material under a d.c. potential difference at specified environmental conditions. The degree of corrosion is assessed by visually comparing the corrosion marks on the anode and cathode metal strips with those shown in the reference figures;

- quantitative method, which involves the tensile strength measurement, carried out on the same anode and cathode metal strips after visual inspection.

An additional quantitative test method for determining electrolytic corrosion, which involves tensile strength measurement of copper wire, is described in the informative Annex C.

<https://standards.iteh.ai/catalog/standards/iec/d0c3c831-b175-4b31-a749-2a50ddfd1398c/iec-60426-2007>

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60068-3-4:2001, *Environmental testing – Part 3-4: Supporting documentation and guidance – Damp heat tests*

IEC 60454-2:—, *Pressure-sensitive adhesive tapes for electrical purposes – Part 2: Methods of test*¹

3 Terms and definitions

For the purposes of this document the following terms and definitions apply:

3.1

electrolytic corrosion

kind of galvanic corrosion caused by joint action of external source of d.c. potential and some substances included in some organic materials in presence of high humidity and elevated temperature

¹ To be published

3.2

test strip

a) positive

a metal strip connected with positive pole of direct current source which forms the anode in the contact system: metal – insulating material

b) negative

a metal strip connected with negative pole of direct current source which forms the cathode in the contact system: metal – insulating material

3.3

surface of contact

a) of tested material

part of insulating material specimen which is in direct contact with metal strips

b) of metal strip

part of metal strip (positive or negative) which is in direct contact with insulating material specimen

4 General description of the test method

The test consists of applying specified environmental conditions and a d.c. potential difference to two parallel copper strips 3 mm apart, acting as the anode and the cathode respectively. The insulating material under test (test specimen) is placed across these two strips. In order to obtain a good and uniform contact between the metal strips and the material under test, the test specimen is pressed to the strips by a cylindrical loading tube.

5 Test specimens

5.1 General

The preparation of the specimens depends on the type of material and the form in which it is supplied. The shape and dimensions of the test specimen are shown in Figure 1. Procedures for the preparation of the test specimen are reported beneath (5.2 to 5.7).

Dimensions in millimetres

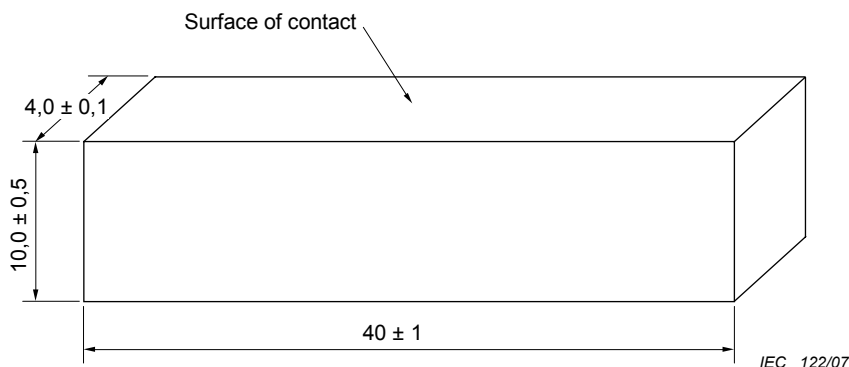


Figure 1 – Test specimen of rigid material, for example textile laminate

5.2 Cut surfaces of rigid materials (blocks, plates, sheets or semi-finished materials)

The test specimens shall be cut out or machined from the tested material to a thickness of 4 mm, by means of a dry method without the use of cutting oils or lubricants and without overheating or damaging them. It is recommended to take several test specimens from various layers of the product.

It is permissible to use the test specimens of thickness smaller than 4 mm, but not smaller than 2 mm.

The contact surface of the test specimen shall be smoothed using abrasive paper. Care should be taken to keep parallelism of the opposite surfaces of the test specimen, in order to assure a good contact of the test specimen to the metal strips. The surface of contact should not show any flaws, cracks, inclusions or bubbles.

The abrasive paper shall not contain any contaminations causing a bad corrosion index, for example halogen components.

5.3 Cast, moulding, injection and pressed materials

From insulating materials delivered in the form of liquid resin, moulding powder or granules, the test specimens shall be made in shapes and dimensions as shown in Figure 1. The specimens shall be made by casting or pressing in a special mould, following exactly the technological instruction recommended by the manufacturer of the tested material.

The test specimen and surface of contact shall be prepared as given in 5.2.

5.4 Cut surfaces of flexible films, foils and thin sheets

Test specimens of these products shall be made up in layers to form small packs placed between suitable holding plates of insulating material not causing electrolytic corrosion itself, for example polymethylmethacrylate (Plexiglas®²). The preferred thickness of holding plates is 1 mm ± 0,2 mm.

The thickness of a pack should be approximately of 4 mm or 2 mm, depending on the thickness of the tested foils. The value of 4 mm is recommended in the case of the single foil thickness being less than 2 mm and more than 0,5 mm, whereas that one of 2 mm is recommended if the single foil thickness is less than 0,5 mm.

These test blocks shall be compressed with screws made of the same material as holding plates and then machined to the appropriate shape as shown in Figure 2. The material to be tested should protrude 0,2 mm to 0,5 mm beyond the holding plates.

² Plexiglas® is an example of a suitable product available commercially. This information is given for the convenience of users of this document and does not constitute an endorsement by IEC of this product.