

SLOVENSKI STANDARD SIST ISO 7404-3:1998

01-februar-1998

A YhcXY'dYhfc[fUZg_j\ 'UbU']n'V]hi a]bcnbY[UdfYa c[U]b'UbhfUV]hU!' "XY. 8 c`c Ub^Y'g_i d]b'a UWYfU]^

Methods for the petrographic analysis of bituminous coal and anthracite -- Part 3: Method of determining maceral group composition

iTeh STANDARD PREVIEW

Méthodes d'analyse pétrographique des charbons bitumineux et de l'anthracite -- Partie 3: Détermination de la composition en groupes de macéraux

SIST ISO 7404-3:1998

ICS:

73.040 Premogi Coals

SIST ISO 7404-3:1998 en

SIST ISO 7404-3:1998

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST ISO 7404-3:1998

https://standards.iteh.ai/catalog/standards/sist/85c3cf8b-8d71-45a4-b182-3aa334beb18c/sist-iso-7404-3-1998

SIST ISO 7404-3:1998

INTERNATIONAL STANDARD

ISO 7404-3

> Second edition 1994-10-01

Methods for the petrographic analysis of bituminous coal and anthracite —

Part 3:

iTeh Swethod of determining maceral group (compositioniteh.ai)

SIST ISO 7404-3:1998

https://standards.ite/Methodes d'analyse pétrographique des charbons bitumineux et de l'anthracité cisis-iso-7404-3-1998

Partie 3: Détermination de la composition en groupes de macéraux



Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting vote.

International Standard ISO 7404-3 was prepared by Technical Committee ISO/TC 27, Solid mineral fuels.

SIST ISO 7404-3:1998

This second edition cancels/standrds replaces log the darfirsts / 8 edition - 8 d71-45 a 4-b182-(ISO 7404-3:1984), which has been technically revised 8 c/sist-iso-7404-3-1998

ISO 7404 consists of the following parts, under the general title *Methods* for the petrographic analysis of bituminous coal and anthracite:

- Part 1: Vocabulary
- Part 2: Method of preparing coal samples
- Part 3: Method of determining maceral group composition
- Part 4: Method of determining microlithotype, carbominerite and minerite composition
- Part 5: Method of determining microscopically the reflectance of vitrinite

Annex A of this part of ISO 7404 is for information only.

© ISO 1994

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Introduction

Petrographic analyses have been recognized internationally as important in the context of the genesis, vertical and lateral variation, continuity, metamorphism and usage of coal. The International Committee for Coal and Organic Petrology (ICCP) has made recommendations concerning nomenclature and analytical methods and has published an extensive handbook describing in detail the characteristics of a wide range of coals. The text of this part of ISO 7404 agrees substantially with the text of the handbook and incorporates many useful comments made by members of the ICCP and by member bodies of ISO/TC 27, Solid mineral fuels.

Petrographic analyses of a single coal provide information about the rank, the maceral and microlithotype compositions and the distribution of minerals in the coal. The reflectance of vitrinite is a useful measure of coal rank and the distribution of the reflectance of vitrinite in a coal blend, together with a maceral group analysis, can provide information about some important chemical and technological properties of the blend.

ISO 7404 Sis concerned with the methods of petrographic analysis curhttps://standards.itelrentlyalemployed/int/characterizing4bituminous coal and anthracite in the 3context of their technological use. It establishes a system for petrographic analysis and comprises five parts, as follows:

Part 1: Vocabulary.

Part 2: Method of preparing coal samples.

Part 3: Method of determining maceral group composition.

Part 4: Method of determining microlithotype, carbominerite and minerite composition.

Part 5: Method of determining microscopically the reflectance of vitrinite.

For information on the nomenclature and analysis of brown coals and lignites, reference should be made to the *International Handbook of Coal Petrography*^[1] published by the ICCP.

Macerals are microscopically recognizable organic constituents of coal, and can be grouped together into three maceral groups: vitrinite, liptinite and inertinite.

Maceral groups and their subdivisions are listed in ISO 7404-1. The properties of a given coal are determined by the proportions and associations of the macerals and minerals present and by the rank of the coal. The method of determining maceral group composition described in this part of ISO 7404 applies only to determinations made in reflected white light. Further analysis by other techniques, such as fluorescence microscopy, can be used to assist in maceral identification.

ISO 7404-3:1994(E)

© ISO

In addition to the macerals, it is possible to identify certain minerals in coal and these may either be determined as separate categories or be ignored. As some of the minerals cannot be satisfactorily identified under the microscope, an estimate of the total mineral matter content may be obtained from the ash.

iTeh STANDARD PREVIEW (standards.iteh.ai)

<u>SIST ISO 7404-3:1998</u> https://standards.iteh.ai/catalog/standards/sist/85c3cf8b-8d71-45a4-b182-3aa334beb18c/sist-iso-7404-3-1998

Methods for the petrographic analysis of bituminous coal and anthracite —

Part 3:

Method of determining maceral group composition

iTeh STANDARD PREVIEW

Scope

(standards.it maintain registers of currently valid International Standards.

This part of ISO 7404 specifies a method of determining the proportions of the maceral groups (and the determinations made on polished particulate blocks iso-74 Vocabulary. using reflected white light. If needed, the proportions of the individual macerals may be determined by the same procedure. It is not concerned with the determination of the proportions of naturally occurring maceral associations (i.e. microlithotypes, ISO 7404-4).

Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this part of ISO 7404. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this part of ISO 7404 are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO

404-3:1|**SO** 7404-1:1994, Methods for the petrographic minerals if desired) in coals. It is concerned only with a real sist analysis of bituminous coal and anthracite — Part 1:

> ISO 7404-2:1985, Methods for the petrographic analysis of bituminous coal and anthracite — Part 2: Method of preparing coal samples.

> ISO 7404-4:1988. Methods for the petrographic analysis of bituminous coal and anthracite — Part 4: Method of determining microlithotype, carbominerite and minerite composition.

> ISO 7404-5:1994, Methods for the petrographic analysis of bituminous coal and anthracite — Part 5: Method of determining microscopically the reflectance of vitrinite.

3 Definitions

For the purposes of this part of ISO 7404, the definitions given in ISO 7404-1 apply.

ISO 7404-3:1994(E) © ISO

4 Principle

A representative sample of coal is used to prepare a particulate block as described in ISO 7404-2. This is examined using a reflected light microscope and the maceral groups are identified under an immersion medium by their relative reflectance, colour, size and morphology. Their proportions are determined by a point count procedure.

5 Material

Immersion medium, having a suitable refractive index and compatible with the microscope objective.

NOTE 1 It is recommended that an oil with a refractive index of 1,518 0 as specified in ISO 7404-5 be used, especially if the reflectance of the macerals is to be measured.

6 Apparatus

6.1 Reflected light microscope, having an immersion objective of magnification between × 25 and × 60 and an eyepiece of magnification between × 8 and × 12. The eyepiece incorporates a fine crossline DA graticule.

6.2 Mechanical stage, capable of advancing the specimen laterally by equal steps of such length that TISO only a negligibly small proportion stofd the inparticles systand examined receives more than one count on the same b18c/sis particle. The step length is equal to half the maximum particle diameter, i.e. 0,5 mm to 0,6 mm for samples with a standard top particle size of 1 mm. The stage also permits a similar stepped advance in the perpendicular direction. The lateral movement is actuated preferably by the counter mechanism, whereas the perpendicular movement may be satisfactorily performed manually.

- **6.3 Counter**, capable of registering the counts in each category and preferably the grand total of petrographic components.
- **6.4 Sample mounting equipment**, comprising slides, modelling clay and levelling device.

7 Preparation of coal sample

Prepare and polish a particulate block as described in ISO 7404-2.

8 Procedure

Crosslines on

maceral or a void


Adjust the microscope (6.1) for Köhler illumination. Set up the levelled particulate block on the stage, place the immersion medium (clause 5) on the surface of the block, focus and observe the image in the microscope. Identify the material lying under the intersection of the crosslines and carry out the point count procedure as follows.

Action


Vitrinite (V), liptinite (L) or inertinite (I)	Operate the counter for appropriate maceral group.
Mounting medium	Ignore the point.
Minerals (M) RD PREVI	Operate the counter for pyrite, shale, etc. or ignore the point (see, the last three paragraphs of the introduction and clause 10).
Boundary between macerals or between 74maceral and mount-daing medium f8b-8d71-4 ist-iso-7404-3-1998	Examine in turn the material lying immediately adjacent to crossline intersection in the top aright, bottom right, bottom left and top left quadrants. Take the first of these which does not have a boundary in it, and operate the counter for this material (see figure 1).
Empty pore in a	Ignore the point

Advance the block by one step in the left-to-right direction, and continue counting and traversing the specimen. At the end of a traverse, advance the block by a step of at least equal length in the perpendicular direction to start the next parallel traverse. Choose the step length to ensure a uniform counting of points over the surface of the block.


Count a total of at least 500 points.

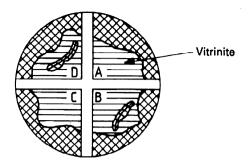


a) Normal case - count point A (vitrinite)

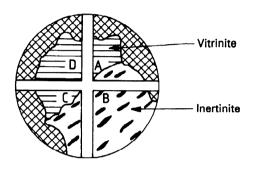

b) Boundary case — count point B (inertinite) iTeh STANDARD PREVIEW

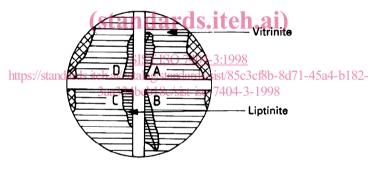

c) Boundary case - count point C (liptinite)

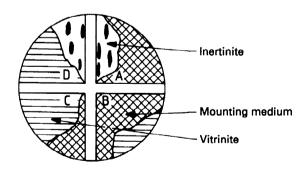

d) Boundary case - the point is not counted

NOTE — Width of crosslines exaggerated for clarity.

Figure 1 — Normal and boundary cases between macerals or between maceral and mounting medium