

INTERNATIONAL STANDARD

NORME INTERNATIONALE

Flexible insulating sleeving –
Part 3: Specifications for individual types of sleeving – Sheet 246: Heat-
shrinkable polyolefin sleeving, dual wall, non-flame retarded

Gaines isolantes souples –
Partie 3: Spécifications pour types particuliers de gaines – Feuille 246: Gaines
thermorétractables en polyoléfine, à double paroi, non retardées à la flamme



THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2007 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester.

If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de la CEI ou du Comité national de la CEI du pays du demandeur.

Si vous avez des questions sur le copyright de la CEI ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de la CEI de votre pays de résidence.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland
Email: inmail@iec.ch
Web: www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

- Catalogue of IEC publications: www.iec.ch/searchpub

The IEC on-line Catalogue enables you to search by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, withdrawn and replaced publications.

- IEC Just Published: www.iec.ch/online_news/justpub

Stay up to date on all new IEC publications. Just Published details twice a month all new publications released. Available on-line and also by email.

[IEC 60684-3-246:2007](mailto:IEC.60684-3-246:2007)

- Electropedia: www.electropedia.org www.iec.ch/catalog/standards/sist/23edbb29-58a1-4669-8985-

The world's leading online dictionary of electronic and electrical terms containing more than 20 000 terms and definitions in English and French, with equivalent terms in additional languages. Also known as the International Electrotechnical Vocabulary online.

- Customer Service Centre: www.iec.ch/webstore/custserv

If you wish to give us your feedback on this publication or need further assistance, please visit the Customer Service Centre FAQ or contact us:

Email: csc@iec.ch

Tel.: +41 22 919 02 11

Fax: +41 22 919 03 00

A propos de la CEI

La Commission Electrotechnique Internationale (CEI) est la première organisation mondiale qui élabore et publie des normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications CEI

Le contenu technique des publications de la CEI est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

- Catalogue des publications de la CEI: www.iec.ch/searchpub/cur_fut-f.htm

Le Catalogue en-ligne de la CEI vous permet d'effectuer des recherches en utilisant différents critères (numéro de référence, texte, comité d'études,...). Il donne aussi des informations sur les projets et les publications retirées ou remplacées.

- Just Published CEI: www.iec.ch/online_news/justpub

Restez informé sur les nouvelles publications de la CEI. Just Published détaille deux fois par mois les nouvelles publications parues. Disponible en-ligne et aussi par email.

- Electropedia: www.electropedia.org

Le premier dictionnaire en ligne au monde de termes électroniques et électriques. Il contient plus de 20 000 termes et définitions en anglais et en français, ainsi que les termes équivalents dans les langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International en ligne.

- Service Clients: www.iec.ch/webstore/custserv/custserv_entry-f.htm

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions, visitez le FAQ du Service clients ou contactez-nous:

Email: csc@iec.ch

Tél.: +41 22 919 02 11

Fax: +41 22 919 03 00



IEC 60684-3-246

Edition 3.0 2007-02

INTERNATIONAL STANDARD

NORME INTERNATIONALE

**Flexible insulating sleeving –
Part 3: Specifications for individual types of sleeving – Sheet 246: Heat-
shrinkable polyolefin sleeving, dual wall, non-flame retarded**

**Gaines isolantes souples –
Partie 3: Spécifications pour types particuliers de gaines – Feuille 246: Gaines
thermorétractables en polyoléfine, à double paroi, non retardées à la flamme**

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

COMMISSION
ELECTROTECHNIQUE
INTERNATIONALE

PRICE CODE
CODE PRIX



ICS 29.035.20

ISBN 978-2-88910-248-8

CONTENTS

FOREWORD.....	3
INTRODUCTION.....	5
1 Scope.....	6
2 Normative references.....	6
3 Designation	7
4 Conditions of test.....	7
5 Requirements	7
6 Sleeving conformance.....	7
7 Sealing performance test method.....	7
Figure 1 – Clamping tool for sealing performance test	8
Table 1 – Dimensional requirements.....	8
Table 2 – Property requirements	9
Table 3 – Additional property requirements.....	10
Table 4 – Requirements for breakdown voltage	10
Table 5 – Resistance to selected fluids.....	11

<https://standards.iteh.ai/catalog/standards/sist/23edbb29-58a1-4669-8985-0edd0a8a6368/iec-60684-3-246-2007>

INTERNATIONAL ELECTROTECHNICAL COMMISSION

FLEXIBLE INSULATING SLEEVING –

**Part 3: Specifications for individual types of sleeving –
Sheet 246: Heat-shrinkable polyolefin sleeving,
dual wall, non-flame retarded**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC provides no marking procedure to indicate its approval and cannot be rendered responsible for any equipment declared to be in conformity with an IEC Publication.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 60684-3-246 has been prepared by IEC technical committee 15: Solid electrical insulating materials.

This third edition cancels and replaces the second edition published in 2001, and constitutes a technical revision.

The major technical changes with regard to the second edition concern a better alignment with existing national specifications.

This bilingual version, published in 2009-06, corresponds to the English version.

The text of this standard is based on the following documents:

FDIS	Report on voting
15C/358/FDIS	15C/371/RVD

Full information on the voting for the approval of this standard can be found in the report on voting indicated in the above table.

The French version of this standard has not been voted upon.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all parts of the IEC 60684 series, published under the general title *Flexible insulating sleeving*, can be found on the IEC website.

The committee has decided that the contents of this publication will remain unchanged until the maintenance result date indicated on the IEC web site under "<http://webstore.iec.ch>" in the data related to the specific publication. At this date, the publication will be

- reconfirmed;
- withdrawn;
- replaced by a revised edition, or
- amended.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[IEC 60684-3-246:2007](#)

<https://standards.iteh.ai/catalog/standards/sist/23edbb29-58a1-4669-8985-0edd0a8a6368/iec-60684-3-246-2007>

INTRODUCTION

This International Standard is one of a series which deals with flexible insulating sleeving for electrical purposes.

The series consists of three parts:

Part 1: Definitions and general requirements (IEC 60684-1)

Part 2: Methods of test (IEC 60684-2)

Part 3: Specifications for individual types of sleeving (IEC 60684-3)

This standard comprises one of the sheets of Part 3 as follows:

Sheet 246: Heat-shrinkable polyolefin sleeving, dual wall, non-flame retarded

iTeh STANDARD PREVIEW **(standards.iteh.ai)**

[IEC 60684-3-246:2007](https://standards.iteh.ai/catalog/standards/sist/23edbb29-58a1-4669-8985-0edd0a8a6368/iec-60684-3-246-2007)

<https://standards.iteh.ai/catalog/standards/sist/23edbb29-58a1-4669-8985-0edd0a8a6368/iec-60684-3-246-2007>

FLEXIBLE INSULATING SLEEVING –

Part 3: Specifications for individual types of sleeving – Sheet 246: Heat-shrinkable polyolefin sleeving, dual wall, non-flame retarded

1 Scope

This part of IEC 60684 defines requirements for dual wall, non-flame retarded, heat shrinkable, polyolefin sleeving. This sleeving has been found suitable for use up to 110 °C.

The sleeving consists of an outer layer made of a semi-rigid cross-linked material.

The inner layer is a substantially non-cross-linked polyolefin that flows and fuses during the shrinkage process to provide a seal.

It is normally offered for sale with an internal diameter up to 25 mm in the following colours: black, white, red, yellow, blue and translucent.

Sizes or colours other than those listed in this standard may be available as custom items. These items are considered to comply with this standard if they comply with the property requirements listed in Tables 2, 3, 4 and 5, excluding dimensions.

Materials which conform to this specification meet established levels of performance. However, the selection of a material by a user for a specific application should be based on the actual requirements necessary for adequate performance in that application and not based on this specification alone.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60684-1:2003, *Flexible insulating sleeving – Part 1: Definitions and general requirements*

IEC 60684-2:1997, *Flexible insulating sleeving – Part 2: Methods of test*¹⁾
Amendment 1 (2003)
Amendment 2 (2005)

IEC 60757:1983, *Code for designation of colours*

ISO 1817:2005, *Rubber, vulcanized – Determination of the effect of liquids*

1) A consolidated edition 2.1 exists, including IEC 60684-2:1997 and its Amendment 1 (2003).

3 Designation

The sleeving shall be identified by the following designation, as shown in the following example:

Description	IEC publication number	IEC part number	IEC sheet number	Size (expanded/ recovered internal diameter, in millimetres)	Colour
↓	↓	↓	↓	↓	↓
Sleeving	- IEC 60684	- 3	- 246	- 12,7/5,0	- NC

NOTE NC is used for "Natural colour" / "No colour pigmentation".

Any abbreviation of colour shall comply with IEC 60757. Where no abbreviation is given, the colour shall be written in full.

4 Conditions of test

Unless otherwise specified, the sleeving shall be shrunk in a forced air circulation oven for (10 ± 1) min at 200 °C ± 5 K prior to testing.

(standards.iteh.ai)

5 Requirements

[IEC 60684-3-246:2007](#)

In addition to the general requirements given in IEC 60684-1, the sleeving shall comply with the requirements in Tables 1, 2, 3, 4 and 5.

6 Sleeving conformance

Conformance to the requirements of this specification shall normally be based on the results from 12,7 mm/5,0 mm black sleeving. The colour fastness to light shall be determined for all colours.

7 Sealing performance test method

Condition a nominal 150 mm length of sleeving at 200 °C ± 5 K for (5 ± 1) min and condition a pair of pliers (clamping tool, see Figure 1) at the same temperature for at least 10 min. Within 5 s after removal from the oven, grip approximately 6 mm of one end of the sleeving with the pliers with sufficient pressure so that the inner surfaces of the sleeving are in full contact. Hold the pressure for at least 40 s, then release the pressure and condition the sleeving at a temperature of 23 °C ± 2 K for at least 10 min.

Submerge the sealed end of the sleeving in at least 25 mm of water and pressurize the open end with at least 20,7 kPa of air pressure for at least 5 s.

Observe whether any air bubbles escape from the sealed end of the sleeving.

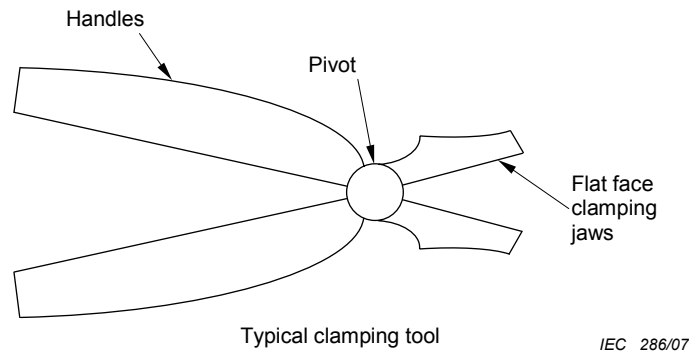


Figure 1 – Clamping tool for sealing performance test

Table 1 – Dimensional requirements

Size code ^{a)}	Internal diameter mm		Total recovered wall thickness ^{b)} mm
	Expanded min.	Recovered ^{c)} max.	
3,2/0,6	3,2	0,6	0,95 ± 0,20
4,7/1,5	4,7	1,5	1,10 ± 0,20
6,4/2,0	6,4	2,0	1,20 ± 0,25
9,5/3,4	9,5	3,4	1,30 ± 0,25
12,7/5,0	12,7	5,0	1,40 ± 0,25
19,1/8,0	19,1	8,0	1,65 ± 0,25
25,4/10,2	25,4	10,2	1,90 ± 0,25
7,6/1,3	7,6	1,3	2,50 ± 0,25

^{a)} These sizes are based on past industry practices for this type of sleeving.

^{b)} The ratio of the inner wall thickness to the total wall thickness will typically lie between 0,3 and 0,7 .

^{c)} In those cases where the inner wall distorts or flows during recovery, it may not be possible to determine the recovered inside diameter accurately. In such cases, the sleeving may be recovered over a mandrel or gauge of the specified diameter for the size being measured, and then shall be examined for complete contact with the mandrel or plug gauge to establish compliance with the requirements for the recovered diameter.

Table 2 – Property requirements

Property	IEC 60684-2 clause or subclause	Units	Max. or min.	Requirements	Remarks
Dimensions	3				
– internal diameter	3.1.2	mm		Table 1	
– wall thickness	3.3.2	mm		Table 1	
Density	4	g/cm ³	Max.	1,0	Test specimens shall be cut from full sections of sleeving
Heat shock	6	–	–	No observable dripping, cracking or flowing of the outer wall	Heat at 250 °C ± 5 K
Longitudinal change	9	%	Max.	+1 –10	Heat the expanded sleeving at 200 °C ± 5 K for (10 ± 1) min. The final measurement shall be on the outer wall only
Brittleness temperature	15	–	–	No visible cracking or breaking	Test at –40 °C ± 3 K after conditioning at the same temperature. The test shall be carried out on specimens taken from sleeving in the expanded (as supplied) form
Dimensional stability on storage	16	–	–	The dimensions shall be as specified in Table 1	
Tensile strength	19.1 and 19.2	MPa	Min.	10	Test in the expanded form. Use a jaw separation rate of 100 mm/min. For internal diameters <6,5 mm, use sleeving samples for testing. At internal nominal diameters ≥6,5 mm, use dumb-bell samples cut from sleeving. The cross-sectional area shall be calculated based on the jacket only
Elongation at break	19.1 and 19.2	%	Min.	200	
Secant modulus at 2 % elongation	19.4	MPa	Min.	175	Test in the expanded form. The cross-sectional area shall be calculated based on the jacket only
Breakdown voltage	21	kV	Min.	See Table 4	
Volume resistivity at room temperature	23 23.4.2	Ω·m	Min.	10 ¹²	
Copper corrosion	33	%	Max.	None above the allowable 8 %	Heat the specimens for (16 ± 0,5) h at 130 °C ± 2 K