



SLOVENSKI STANDARD

SIST EN 13900-5:2005

01-julij-2005

Pigmenti in polnila - Metode disperzije in ocenjevanje disperzivnosti v polimernih materialih - 5. del: Ugotavljanje vrednosti tlaka s preskusom na filtru

Pigments and extenders - Methods of dispersion and assessment of dispersibility in plastics - Part 5: Determination by filter pressure value test

Pigmente und Füllstoffe - Dispergiervverfahren und Beurteilung der Dispergierbarkeit in Kunststoffen - Teil 5: Bestimmung mit dem Druckfiltertest

Pigments et matières de charge - Méthodes de dispersion et évaluation de l'aptitude à la dispersion dans les plastiques - Partie 5: Détermination de la valeur de pression du filtre lors d'un essai

Ta slovenski standard je istoveten z: EN 13900-5:2005

ICS:

83.040.30	Pomožni materiali in aditivi za polimerne materiale	Auxiliary materials and additives for plastics
-----------	---	--

SIST EN 13900-5:2005

en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 13900-5:2005

<https://standards.iteh.ai/catalog/standards/sist/ac24f2ba-472e-40ba-ad2e-854bfe4ea50a/sist-en-13900-5-2005>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN 13900-5

May 2005

ICS 83.040.30

English version

**Pigments and extenders - Methods of dispersion and
assessment of dispersibility in plastics - Part 5: Determination by
filter pressure value test**

Pigments et matières de charge - Méthodes de dispersion
et évaluation de l'aptitude à la dispersion dans les
plastiques - Partie 5 : détermination de la valeur de
pression du filtre lors d'un essai

Pigmente und Füllstoffe - Dispergiervfahren und
Beurteilung der Dispergierbarkeit in Kunststoffen - Teil 5:
Bestimmung mit dem Druckfiltertest

This European Standard was approved by CEN on 21 March 2005.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

EN 13900-5:2005 (E)**Foreword**

This European Standard (EN 13900-5:2005) has been prepared by Technical Committee CEN/TC 298 "Pigments and extenders", the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by November 2005, and conflicting national standards shall be withdrawn at the latest by November 2005.

This document includes a Bibliography.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 13900-5:2005](https://standards.iteh.ai/catalog/standards/sist/ac24f2ba-472e-40ba-ad2e-854bfe4ea50a/sist-en-13900-5-2005)

<https://standards.iteh.ai/catalog/standards/sist/ac24f2ba-472e-40ba-ad2e-854bfe4ea50a/sist-en-13900-5-2005>

1 Scope

This part of EN 13900 specifies a method of assessing the degree of dispersion of a colorant in a thermoplastic polymer.

The method is suitable for testing colorants in the form of colour concentrates in all polymers used for extrusion and melt-spinning processes.

The filter pressure value (FPV) determined according to this method is valid only for the equipment, conditions and test polymer being used. The use of test conditions differing from those specified might give different results. The method of preparing the colour concentrate is not specified in this European Standard. The results obtained for individual colorants are therefore comparable only when the same method of preparation for colour concentrates is used.

Annex A is normative and gives a model for the breaker plate.

Annex B is informative and provides a model test report containing a result of the round-robin-tests carried out in preparing this European Standard.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 10088-1, *Stainless steels – Part 1: List of stainless steels*.

3 Terms and definitions

For the purposes of this European Standard, the following term and definition applies.

3.1

filter pressure value

FPV

pressure difference between the start pressure and the maximum pressure generated by extrusion in front of a screen pack related to the amount of colorant tested

4 Principle

The test mixture, consisting of a colour concentrate and a basic test polymer, is passed through an extruder fitted with melt pump and screen pack with breaker plate. In front of the screen pack is a melt pressure transducer. The pressure difference between the start pressure and the maximum pressure is used to calculate the filter pressure value [FPV].

5 Material

5.1 Colour concentrate

Homogeneous preparation of a colorant in an appropriate thermoplastic polymer.

5.2 Basic test polymer

Thermoplastic polymer, of a grade and type to be agreed between the interested parties.

EN 13900-5:2005 (E)

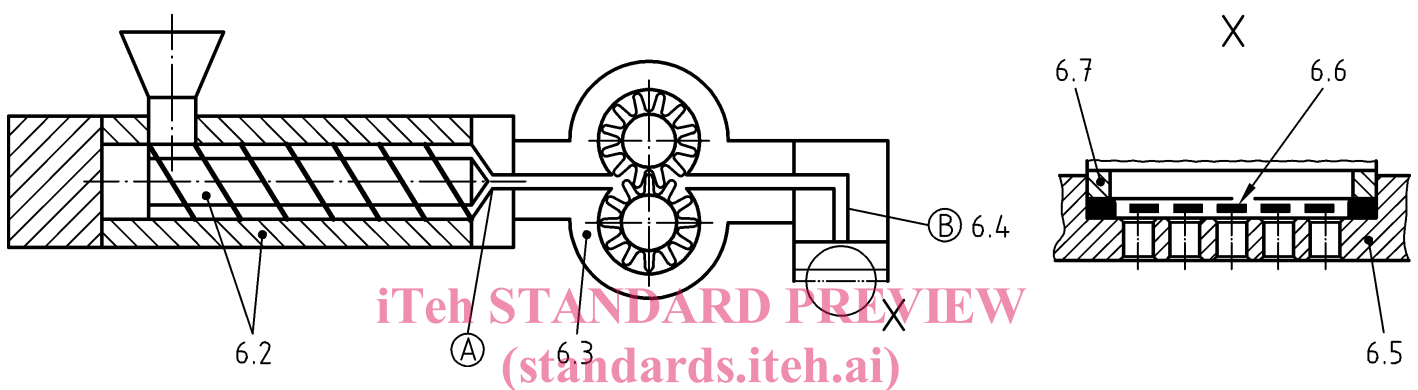
NOTE The development work on this European Standard was carried out in polypropylene (PP).

5.3 Test mixture

A homogeneous mixture of a colour concentrate (5.1) and the basic test polymer (5.2) as specified in Clause 7.

6 Apparatus**6.1 General**

Figure 1 illustrates the principle construction of the apparatus (see 6.2 to 6.7).

**Key**

- A Melt pressure transducer in front of the melt pump
 B Melt pressure transducer in front of the filter

Figure 1 — Apparatus

6.2 Extruder

A single screw extruder with non-grooved barrel and a screw without dispersing elements shall be used. A screw with a diameter between 19 mm and 30 mm and with a length of 20 L/D to 30 L/D (length/diameter) is recommended. It is necessary to have a melt pressure transducer in front of the melt pump (A) to measure the pressure of the melt. An electronic controller with screw speed/pressure feedback loop is necessary in order to maintain this pressure constant, preferably at a level between 30 bar and 60 bar, to ensure that the melt pump is completely filled and to ensure optimum homogeneity of the melt.

6.3 Melt pump

The melt pump, preferably a metering pump, shall provide a constant throughput of 50 cm³/min to 60 cm³/min.

6.4 Melt pressure transducer

The pressure range shall be preferably between 0 bar and 100 bar for mixture 1 (7.2) and between 0 bar and 350 bar for mixture 2 (7.3). The accuracy of the melt pressure transducer (B) shall be within $\pm 1\%$ with a repeatability of less than $\pm 0,1\%$.

NOTE The resolution of the pressure measurement should be 0,1 bar.

6.5 Breaker plate

A breaker plate is used to support the screen-pack and defines its free area (see Annex A).

6.6 Filter

6.6.1 General

The filter media is that part of the system which influences the differential pressure used as the basic data for determining the results of the test.

The differential pressure increase is dependent on the retention characteristics of the filter media.

In order to have comparable results it is important that the filter media is defined in detail and assembled exactly to specification.

Screen-packs are used as filter media. The screen-pack is assembled from ultrasonically cleaned filter discs, having a filter diameter of 33,8 mm ($\pm 0,1$ mm), in a multi-layer construction, preferably held together in an aluminium frame. All screens shall be made from a suitable material appropriate to the polymer used, e.g. stainless steel in accordance with EN 10088-1, Type 1.4404. Any change in specification (e. g. weaving pattern, surface condition, number of apertures per unit length or aperture width) can lead to a different test result.

6.6.2 Screen-pack 1

Two-layer construction, where the first layer is a reverse plain dutch weave 615/108 warp/weft per 25,4 mm with a wire diameter of 0,042 mm/0,14 mm and the second layer (support mesh) is a square mesh plain weave 0,63 mm aperture width with a wire diameter of 0,40 mm calendered (for further details see ISO 9044).

6.6.3 Screen-pack 2

Two-layer construction, where the first layer is a reverse plain dutch weave 615/132 warp/weft per 25,4 mm with a wire diameter of 0,042 mm/0,13 mm and the second layer (support mesh) is a square mesh plain weave 0,63 mm aperture width with a wire diameter of 0,40 mm calendered (for further details see ISO 9044).

6.6.4 Screen-pack 3

Three-layer construction, where the first layer is a twilled dutch weave 165/1400 warp/weft per 25,4 mm with a wire diameter of 0,071 mm/0,040 mm and the second layer (support mesh) is a square mesh plain weave 0,25 mm aperture width with a wire diameter of 0,16 mm and the third layer (support mesh) is a square mesh plain weave 0,63 mm aperture width with a wire diameter of 0,40 mm calendered (for further details see ISO 9044).

NOTE 1 The use of further finer screen-packs than described in 6.6.2 may be agreed between the interested parties.

NOTE 2 It is recommended to request confirmation from the supplier that the above specifications are used for the screen-pack. Especially the number of apertures per unit length and the wire diameters of the individual layers are extremely critical for the result of the filter pressure value test.

6.7 Sealing ring

The sealing ring or aluminium frame of the filter disc should have a diameter of 33,8 mm $\pm 0,1$ mm and an inside diameter of 28 mm $\pm 0,1$ mm.

If the screen-pack has no aluminium frame a sealing ring is to be used.

7 Preparation of test mixtures

7.1 General

The colour concentrate (5.1) and the basic test polymer (5.2) are mixed together, for example in a glass or plastics container, to provide the homogeneous test mixture.

NOTE 1 Mixture 1 is recommended for colour pigments and mixture 2 is recommended for white and carbon black pigments.

EN 13900-5:2005 (E)

NOTE 2 The use of other mixtures may be agreed between the interested parties.

NOTE 3 Colorant quantities below 5,0 g will lead to insufficient accuracy.

7.2 Mixture 1

A test mixture of 200 g (100 %), including 5,0 g colorant (2,5 %) is used.

NOTE If the colour concentrate contains 40% colorant the quantities are: 12,5 g colour concentrate and 187,5 g basic test polymer.

7.3 Mixture 2

A test mixture of 1000 g (100 %), including 80,0 g colorant (8 %) is used.

NOTE If the colour concentrate contains 40% colorant the quantities are: 200 g colour concentrate and 800 g basic test polymer.

8 Procedure**8.1 Pre-conditioning**

The complete apparatus (Clause 6) should be pre-heated to the processing temperature appropriate for the basic test polymer.

The equipment should be cleaned or adequately purged with the basic test polymer (5.2) before each test is started.

8.2 Determination

<https://standards.iteh.ai/catalog/standards/sist/ac24f2ba-472e-40ba-ad2e-854bfe4ea50a/sist-en-13900-5-2005>

Mount a new screen-pack (6.6.2 to 6.6.4) in front of the breaker plate (6.5) and the measuring equipment in such a way that the melt flows through the finer screen first and through the breaker plate last. A sealing ring (6.7) shall prevent leakage of the mixture around the edge of the screen-pack.

Allow sufficient time for the screen-pack and the breaker plate to reach the temperature of the equipment. This time will depend on the equipment being used. The basic test polymer (5.2) is then plasticized in the extruder and passed through the screen-pack with a defined melt volume throughput until the melt temperature and pressure remain constant. The machine conditions should guarantee a constant melt temperature, with temperature deviations of less than $\pm 2^{\circ}\text{C}$.

Measure the start pressure p_s developed by the basic test polymer directly in front of the screen-pack. The start pressure p_s should be constant. When the hopper is empty and the extruder screw is just visible, add the test mixture (5.3).

NOTE A pressure drop can occur because of different rheological properties of basic test polymer and test mixture.

After feeding of the test mixture is completed, 100 g basic test polymer are added just as the extruder screw becomes visible again.

The test is finished as soon as the extruder screw once again becomes visible. Use the recorded data to evaluate the maximum pressure p_{\max} and to calculate the filter pressure value.

Remove the screen-pack while still hot and purge the apparatus thoroughly with basic test polymer for the next test.

9 Evaluation

The filter pressure value [FPV], defined as the increase of pressure per gram colorant, is calculated by using the following equation:

$$FPV = \frac{(p_{\max} - p_s)}{m_c}$$

where

FPV filter pressure value, in bar per gram [bar/g];

p_s start pressure, in bar;

p_{\max} maximum pressure, in bar;

m_c colorant quantity used in the test, in gram.

It is recommended to express the filter pressure value accurate to one decimal place.

Figure 2 illustrates an example of a typical pressure curve.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 13900-5:2005](https://standards.iteh.ai/catalog/standards/sist/ac24f2ba-472e-40ba-ad2e-854bfe4ea50a/sist-en-13900-5-2005)

<https://standards.iteh.ai/catalog/standards/sist/ac24f2ba-472e-40ba-ad2e-854bfe4ea50a/sist-en-13900-5-2005>