



SLOVENSKI STANDARD
SIST EN 13511:2004

01-januar-2004

Footwear - Test methods for uppers - Resistance to damage on lasting

Footwear - Test methods for uppers - Resistance to damage on lasting

Schuhe - Prüfverfahren für Obermaterialien - Aufzwickbarkeit

Chaussures - Méthodes d'essai des tiges - Aptitude au montage

Ta slovenski standard je istoveten z: EN 13511:2001

[SIST EN 13511:2004](https://standards.iteh.ai/catalog/standards/sist/8b1ec042-8ab3-4b3b-8867-8fd41c7ebed4/sist-en-13511-2004)

<https://standards.iteh.ai/catalog/standards/sist/8b1ec042-8ab3-4b3b-8867-8fd41c7ebed4/sist-en-13511-2004>

ICS:

61.060

Obuvala

Footwear

SIST EN 13511:2004

en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 13511:2004](#)

<https://standards.iteh.ai/catalog/standards/sist/8b1ec042-8ab3-4b3b-8867-8fd41c7ebed4/sist-en-13511-2004>

EUROPEAN STANDARD

EN 13511

NORME EUROPÉENNE

EUROPÄISCHE NORM

November 2001

ICS 61.060

English version

Footwear - Test methods for uppers - Resistance to damage on lasting

Chaussures - Méthodes d'essai des tiges - Aptitude au montage

Schuhe - Prüfverfahren für Schäfte - Aufzwickbarkeit

This European Standard was approved by CEN on 3 October 2001.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

[SIST EN 13511:2004](https://standards.iteh.ai/catalog/standards/sist/8b1ec042-8ab3-4b3b-8867-8fd41c7ebed4/sist-en-13511-2004)

<https://standards.iteh.ai/catalog/standards/sist/8b1ec042-8ab3-4b3b-8867-8fd41c7ebed4/sist-en-13511-2004>



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Contents

	page
Foreword.....	3
1 Scope	4
2 Normative references	4
3 Terms and definitions.....	4
4 Apparatus and material	4
5 Sampling and conditioning.....	6
6 Test method.....	7
6.1 Principle	7
6.2 Procedure	7
7 Expression of results	8
8 Test report	8

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 13511:2004](https://standards.iteh.ai/catalog/standards/sist/8b1ec042-8ab3-4b3b-8867-8fd41c7ebed4/sist-en-13511-2004)

<https://standards.iteh.ai/catalog/standards/sist/8b1ec042-8ab3-4b3b-8867-8fd41c7ebed4/sist-en-13511-2004>

Foreword

This European Standard has been prepared by Technical Committee CEN/TC 309 "Footwear", the secretariat of which is held by AENOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by May 2002, and conflicting national standards shall be withdrawn at the latest by May 2002.

This draft European Standard is based on the IUP 9 method (ISO 3379:1976 "Leather - Determination of distension and strength of grain - Ball burst test").

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST EN 13511:2004](#)

<https://standards.iteh.ai/catalog/standards/sist/8b1ec042-8ab3-4b3b-8867-8fd41c7ebed4/sist-en-13511-2004>

EN 13511:2001 (E)

1 Scope

This European Standard specifies a test method to determine the lastability of uppers or complete upper assembly irrespective of the material in order to assess the suitability for the end use.

2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text, and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies (including amendments).

EN 12222, *Footwear - Standard atmospheres for conditioning and testing of footwear and components for footwear.*

prEN ISO 2418, *Leather - Chemical, physical, mechanical and fastness tests – Sampling.*

3 Terms and definitions

For the purposes of this European Standard, the following terms and definitions apply.

3.1

resistance to damage on lasting

ability of a material to be stretched simultaneously in all directions (distended) without being damaged

3.2

upper

materials forming the outer face of the footwear which is attached to the sole assembly and covers the upper dorsal surface of the foot. In the case of boots this also includes the outer face of the material covering the leg. Only the materials that are visible are included, no account should be taken of underlying materials

3.3

complete upper assembly

finished upper, fully seamed, joined or laminated together as appropriate, comprising the centre material and any lining(s) together with all components such as interlinings, adhesives, membranes, foams or reinforcements, but excluding toe puffs and stiffeners

NOTE The complete upper assembly can be flat, 2- dimensional or comprise lasted upper in the final footwear.

4 Apparatus and material

The following apparatus and material shall be used:

4.1 Test machine (see Figures 1 and 2), including the following:

4.1.1 Means of clamping the test specimen round its edge leaving a central circular free area of diameter 25,00 mm \pm 0,5 mm. The design of the clamping system of the machine shall ensure that the test specimen does not slip during the test, and shall neither stretch nor compress the central area of the test specimen as it is clamped.

Dimensions in millimetres


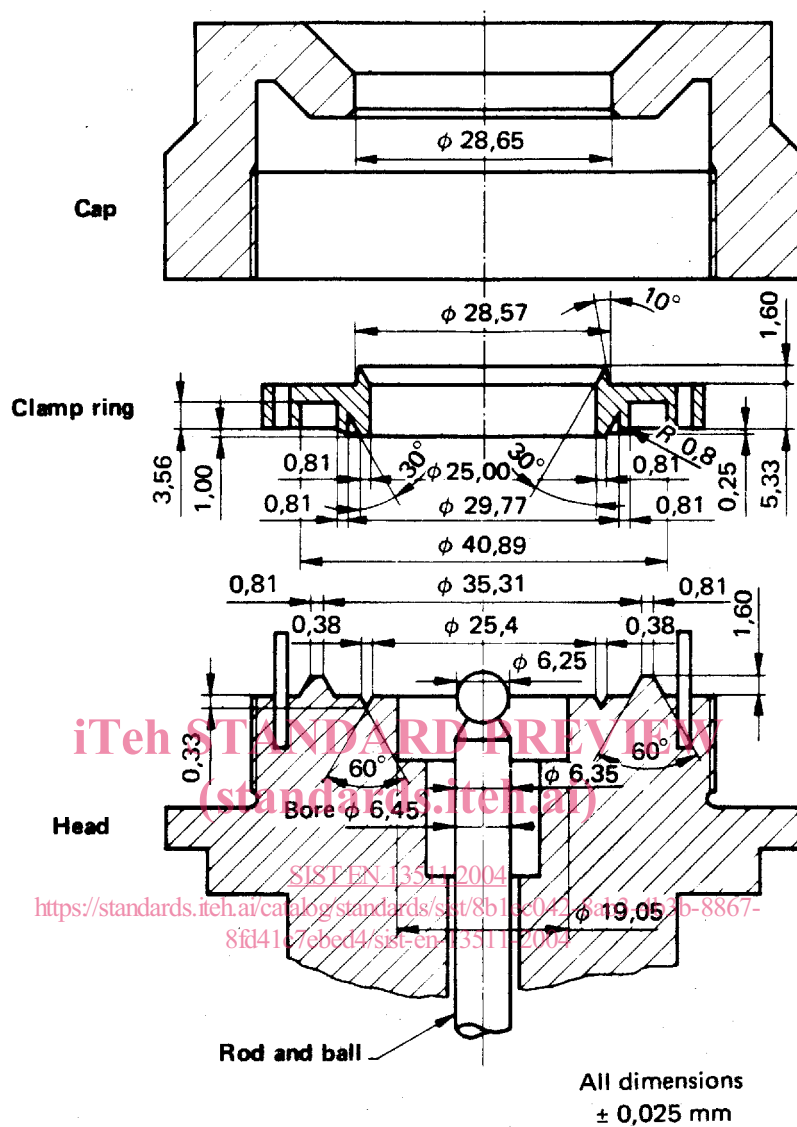


Figure 1 — Details of clamp and head

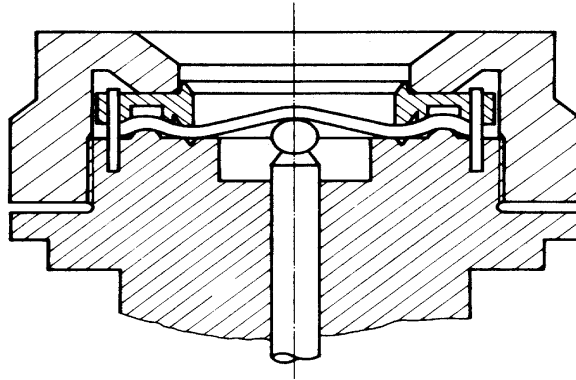

iTeh STANDARD PREVIEW

Figure 2 — Cross Section of clamping head with test piece in position

SIST EN 13511:2004

- 4.1.2 Moveable plunger with a $6,25 \text{ mm} \pm 0,05 \text{ mm}$ diameter spherical ball on the end.
- 4.1.3 Means of moving the plunger relative to the test specimen clamp at a speed of $0,20 \text{ mm/s} \pm 0,05 \text{ mm/s}$.
- 4.1.4 Means of monitoring the distension (travel of the plunger from zero) to an accuracy of $\pm 0,05 \text{ mm}$.
- 4.1.5 Means of monitoring the force on the plunger within the range 0 N to 800 N to an accuracy of $\pm 10 \text{ N}$.
- 4.2 **Press knife** or similar means for cutting test specimens.

5 Sampling and conditioning

5.1 Test specimens shall be of a sufficient size to allow them to be clamped firmly on the test machine (see 4.1), so that they do not slip during the test.

In the case of leather use prEN ISO 2418 to select the sampling position from the butt region of the skin or side.

For non-leather materials cut 3 test specimens from a range of positions across the full usable width and length of the sheet material. For a material with a woven structure this shall prevent any two test specimens containing the same warp or weft threads.

5.2 For test specimens from footwear uppers, they shall not be cut from any areas containing seams or perforations and any other design features which mean that the test specimen will not be of uniform thickness across its entire surface area. Furthermore, no test specimens shall be cut from areas of finished shoe uppers which are subjected to strains during lasting, especially the toe and backpart areas. Test specimens shall be prepared from complete upper assemblies when the lining material is permanently attached to the upper material.

It can be that it is impossible to cut a test specimen of sufficient size from certain types of footwear especially children's and the test specimen size shall not be reduced. If it is not possible to cut the correct size test specimen from a shoe upper the materials themselves shall be tested.

5.3 Place the test specimens in a conditioned environment as specified in EN 12222 for 24 h prior to test and carry out the test in this atmosphere.

6 Test method

6.1 Principle

A circular test specimen is clamped round its edge and is gradually distended by forcing a small metal ball attached to a plunger through the test specimen. At a certain distension, measured in terms of distance travelled by the plunger, either cracks appear in the surface of the material or a layer of the material sustains permanent physical damage; this distension is recorded as the first damage point.

At a higher distension the material usually bursts and this distension can also be recorded. Throughout the test the travel of, and force on the plunger is monitored so that if required a plot of force against distension can be produced.

6.2 Procedure

6.2.1 Ensure the test machine is set with the central plunger retracted to zero or minimum distension. If it has a maximum force pointer turn it to zero.

6.2.2 Tightly clamp the test specimen into the test machine so that the ball ended plunger acts on the reverse side of the test specimen (i.e. when testing grain leathers, the ball ended plunger will press against the flesh side of the leather).

6.2.3 For some thick test specimens a very high clamping force may be necessary whereas with thin test specimens care is required to avoid cutting into the test specimen.

6.2.4 Force the plunger into the test specimen at a rate of 0,20 mm/s \pm 0,05 mm/s.

6.2.5 Record the point of first damage as the plunger stretches the test specimen as follows:

- a) When testing leathers the first damage usually occurs in the finish or the surface of the grain. Hence during the test continually observe the surface of the test specimen, at the centre where the maximum distension is taking place. At the first sign of surface cracking, record the force on the plunger and the distension of the test specimen. However, if the grain is still intact, continue until grain crack occurs and record also the distension and force at this point.

Patent leather is a special case because often the grain of the leather cracks before the patent surface film. Particular care is therefore required when observing patent leather test specimens. Two indications of the grain cracking are a small shallow depression in the surface of the film above the crack and a momentary drop in the force on the plunger. If the patent film cracks this shall also be regarded as a "grain crack" whether or not a crack in the grain is visible.

- b) When testing non-leather materials such as coated fabrics the first damage usually occurs within the material, with no visible damage at the surface. Hence during the test continually observe the force on the plunger as the test specimen is stretched. When damage occurs to a layer of the test specimen the force on the plunger either stops rising, or falls, however this may only be momentary. Record this value and the distension of the test specimen at this point.

6.2.6 If the bursting point is required then continue to observe the test specimen and record the distension and force when the spherical end first appears through the sample.

6.2.7 Retract the plunger and remove the test specimen.