



**SLOVENSKI STANDARD**  
**SIST EN 13514:2004**  
**01-januar-2004**

---

**Footwear - Test methods for uppers - Delamination resistance**

Footwear - Test methods for uppers - Delamination resistance

Schuhe - Prüfverfahren für Obermaterialien - Beständigkeit gegen Schichtentrennung

Chaussures - Méthodes d'essai des tiges - Résistance au délaminage

**Ta slovenski standard je istoveten z: EN 13514:2001**

[SIST EN 13514:2004](https://standards.iteh.ai/catalog/standards/sist/80217a1a-7169-4dcb-9c27-86494612488f/sist-en-13514-2004)

<https://standards.iteh.ai/catalog/standards/sist/80217a1a-7169-4dcb-9c27-86494612488f/sist-en-13514-2004>

**ICS:**

61.060

Obuvala

Footwear

**SIST EN 13514:2004**

**en**

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[SIST EN 13514:2004](#)

<https://standards.iteh.ai/catalog/standards/sist/80217a1a-7169-4dcb-9c27-86494612488f/sist-en-13514-2004>

EUROPEAN STANDARD  
NORME EUROPÉENNE  
EUROPÄISCHE NORM

**EN 13514**

November 2001

ICS 61.060

English version

## Footwear - Test methods for uppers - Delamination resistance

Chaussures - Méthodes d'essai des tiges - Résistance au délamination

Schuhe - Prüfverfahren für Schäfte - Beständigkeit gegen Schichtentrennung

This European Standard was approved by CEN on 3 October 2001.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

**STANDARD PREVIEW**  
**(standards.iteh.ai)**  
SIST EN 13514:2004  
<https://standards.iteh.ai/catalog/standards/sist/80217a1a-7169-4dcb-9c27-86494612488f/sist-en-13514-2004>



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

## Contents

	page
Foreword.....	3
1 Scope .....	4
2 Normative references .....	4
3 Term and definition.....	4
4 Apparatus and material .....	4
5 Sampling .....	5
6 Test method.....	6
6.1 Principle .....	6
6.2 Procedure .....	6
7 Expression of results .....	9
8 Test report .....	9

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST EN 13514:2004](#)

<https://standards.iteh.ai/catalog/standards/sist/80217a1a-7169-4dcb-9c27-86494612488f/sist-en-13514-2004>

## Foreword

This European Standard has been prepared by Technical Committee CEN/TC 309 "Footwear", the secretariat of which is held by AENOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by May 2002, and conflicting national standards shall be withdrawn at the latest by May 2002.

This European Standard is based on the IULTCS/IUF 470 method (ISO 11644:1993 "Leather - Test for adhesion of finish").

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST EN 13514:2004](#)

<https://standards.iteh.ai/catalog/standards/sist/80217a1a-7169-4dcb-9c27-86494612488f/sist-en-13514-2004>

## EN 13514:2001 (E)

### 1 Scope

This European Standard specifies a test method for determining the delamination resistance of uppers irrespective of the material, in order to assess the suitability for the end use.

### 2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text, and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies (including amendments).

EN 12222, *Footwear - Standard atmospheres for conditioning and testing of footwear and components for footwear.*

EN 12749, *Footwear - Ageing conditioning.*

EN 13400, *Footwear - Sampling location, preparation and duration of conditioning of samples and test pieces.*

EN ISO 3696, *Water for analytical laboratory use - Specification and test method.*

EN ISO 7500-1, *Metallic materials – Verification of static uniaxial testing machines. Part 1: Tension/compression testing machines.*

ITEH STANDARD PREVIEW  
(standards.iteh.ai)

### 3 Term and definition

SIST EN 13514:2004

<https://standards.iteh.ai/catalog/standards/sist/80217a1a-7169-4dcb-9c27-864946124861/sist-en-13514-2004>

For the purposes of this European Standard, the following term and definition applies.

#### 3.1

##### **delamination resistance**

strength of adhesion between a coating and its base material

### 4 Apparatus and material

The following apparatus and material shall be used:

**4.1 Tensile testing machine** with: a jaw separation rate of 100 mm/min  $\pm$  10 mm/min, a force range appropriate to the specimen under test (normally a range of 0 N to 200 N is suitable for test specimens of polyurethane coated fabric) and the capability of measuring the force to an accuracy greater than 2 % as specified by Class 2 in EN ISO 7500-1.

**4.2 Autographic recorder** or similar means of continuously recording the force.

**4.3 Rapid acting platen press** capable of applying a pressure of 550 kPa  $\pm$  50 kPa on an area of 50 mm x 70 mm.

**4.4 Rubber pad** of thickness at least 10 mm and hardness 40 IRHD  $\pm$  10 IRHD.

**4.5 Radiant heater** capable of heating a dry adhesive film on resin rubber to 80 °C to 90 °C within 15 s, normally mounting the adhesive film from 100 mm to 150 mm from a heater element of power approximately 3 kW and area of approximately 0,06 m<sup>2</sup> is satisfactory. Commercial equipment used for reactivating soles and uppers in footwear production is suitable.

**4.6 Means** of checking that the temperature of the adhesive film is within the range 80 °C to 90 °C. Heat sensitive crayons are suitable, preferably with a melting temperature of 83 °C. Also suitable are infra-red temperature measuring guns.

**4.7 Resin rubber**, thickness 3,5 mm ± 0,2 mm and hardness 95 IRHD ± 2 IRHD with a surface peel tear strength greater than that of the test specimen.

**4.8 A solvent-borne polyurethane adhesive** which will bond well to resin rubber and the coated surface of the test specimen.

**4.9 An adhesion primer**, such as a halogenating solution used in footwear manufacture for rubber can be helpful in producing satisfactory bonds.

**4.10 Cutting device** such as a press knife or scissors capable of cutting rectangular test specimens of dimensions (50 mm ± 1 mm) x (70 mm ± 1 mm). In addition, if carrying out the test on hydrolysed test specimens, a second cutting device is required to cut square test specimens (70 mm ± 1 mm) x (70 mm ± 1 mm).

**4.11 Cutting device** such as a sharp knife or rotary disc cutter for cutting test specimens from bonded test assemblies. This device shall neither unduly compress nor force apart the layers of the test assembly at the edges during cutting and therefore a press knife is unsuitable.

**4.12** If testing the wet adhesion strength, **distilled or deionised water** complying with grade 3 of EN ISO 3696.

**4.13 Timer** capable of recording times up to 30 s to the nearest 0,5 s.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

### 5 Sampling

**5.1** For the dry tests, mark six rectangular boxes (70 mm ± 1 mm) x (50 mm ± 1 mm): two with their longer edges parallel to the along direction of sheet material (machine or backbone direction) or X-axis (as defined in EN 13400) of the upper, and four with their longer edges perpendicular to this, on the reverse of the sheet material or uppers.

**5.2** For the wet tests mark either a further two rectangular boxes (70 mm ± 1 mm) x (50 mm ± 1 mm), putting the 50 mm edge in the direction with the lowest dry peel strength (if already known), or a further six boxes as described in 5.1 on the reverse of the material or uppers.

**5.3** Make further marks on the material to divide each of the rectangles marked in 5.1 and 5.2 into two equal halves (35 mm ± 0,5 mm) x (50 mm ± 1 mm). Mark the along direction or X-axis in each of the smaller rectangles. Use an arrow and ensure that the arrow heads point in the same direction. For uppers, the arrow head shall point towards the toe.

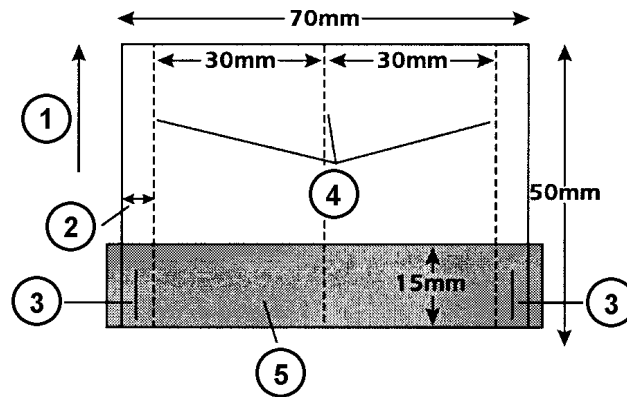
**5.4** For hydrolysis tests, mark a further two 70 mm ± 1 mm square boxes with their edges parallel to the along direction or X-axis. Mark the along direction or X-axis using an arrow as in 5.3.

**NOTE** Since ink marks can be removed by the wetting or hydrolysis treatments it is advisable to also use a code of cut off corners.

**5.5** Cut from the sheet material or uppers, the rectangular boxes marked in 5.1 and 5.2 and the squares marked in 5.4. Each piece of material is later cut to give two test specimens 30 mm ± 0,5 mm x 50 mm ± 1 mm, see Figure 1. After bonding to resin rubber, each piece of material is later cut to give two peel test specimens. With some shoe styles it will not be possible to cut the correct size pieces of material. In such cases it will be necessary to reduce the size of the pieces to a minimum of (40 mm ± 1 mm) x (50 mm ± 1 mm). In all such cases, the pieces will give one test specimen only and shall not be further sub-divided as in 5.3.

**5.6** Cut a rectangular piece of resin rubber (see 4.7) measuring (50 mm ± 1 mm) x (70 mm ± 1 mm) for each piece of material cut in 5.5. If the setting of the radiant heater unit (see 4.5) needs to be checked cut one or two additional pieces of rubber.

## EN 13514:2001 (E)

**Key**

- 1 Direction of peel
- 2 Approximately 5 mm
- 3 Staple
- 4 Cut lines
- 5 Paper strip

**Figure 1 — Test specimen assembly**

NOTE Specimens can be taken from materials likely to be used for uppers or from made-up uppers or finished footwear.

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)

**6 Test method****6.1 Principle**

[SIST EN 13514:2004](https://standards.iteh.ai/catalog/standards/sist/80217a1a-7169-4dcb-9c27-b09d188a19ca-953152004)

<https://standards.iteh.ai/catalog/standards/sist/80217a1a-7169-4dcb-9c27-b09d188a19ca-953152004>

The coated surface of a test specimen is bonded to a piece of resin rubber using a strong adhesive. The force required to peel the test specimen from the resin rubber leaving the coating attached to the rubber is measured using a tensile testing machine. The test can also be carried out on wet and hydrolysed test specimens.

**6.2 Procedure**

**6.2.1** Place a strip of paper ( $75 \text{ mm} \pm 5 \text{ mm}$ ) x ( $15 \text{ mm} \pm 3 \text{ mm}$ ) to the coated side of each piece of material cut in 5.5 so that it is against one of the longer edges. Attach the paper strips with a staple (or similar) at each end so that the staples are positioned as shown in Figure 1. With the four test specimens cut for the dry test where the arrow points toward a longer edge, two shall have the paper strip attached along the edge to which the arrow is pointing and two shall have the paper strip along the opposite edge.

**6.2.2** If an adhesion primer (see 4.9) is available, apply this in accordance with the suppliers instructions to the whole area of the reverse side of each piece of resin rubber cut in 5.6.

**6.2.3** Allow the resin rubber pieces to dry full in accordance with the suppliers recommendations.

**6.2.4** Apply the polyurethane adhesive (see 4.8) in accordance with the suppliers instructions to the whole area of the reverse of each piece of resin rubber.

**6.2.5** Similarly apply adhesive to the coated surface of each piece of material under test so that it just overlaps the paper strip.

**6.2.6** Allow the adhesive to dry for at least 1 h.

**6.2.7** If the time required to heat the adhesive film to a temperature of between  $80 \text{ }^\circ\text{C}$  and  $90 \text{ }^\circ\text{C}$  using the radiant heater is not known, then measure this time using the extra pieces of rubber cut in 5.6 and the means of checking the temperature of the adhesive film (see 4.6). If this time is found to be longer than 15 s then either



increase the temperature of the heating element or reduce the distance between the element and the resin rubber until the time is below 15 s. Record the time taken to heat the adhesive film to the desired temperature as  $T_a$  to the nearest 1 s.

#### 6.2.8 Preparation of bonded assemblies:

**6.2.8.1** Place a piece of adhesive coated resin rubber in the radiant heater with the adhesive surface facing the heater element so that it is subjected to heat for  $T_a$  (in seconds).

**6.2.8.2** Carefully and quickly place the adhesive coated surface of a piece of upper material (5.5) in contact with the adhesive coating on the piece of resin rubber so that the edges of both surfaces are aligned. This will subsequently be referred to as a test assembly.

**6.2.8.3** Immediately place the test assembly into the platen press (see 4.3) so that the resin rubber is lowermost and resting on the rubber pad (see 4.4). Apply a pressure of 550 kPa  $\pm$  50 kPa to the assembly for 15 s  $\pm$  1 s.

It is important that the time between removing the resin rubber from the heater unit in 6.2.8.1 to placing the assembly in the press and applying pressure in 6.2.8.3 shall be no more than 7 s.

**6.2.9** Store the bonded assemblies in a conditioned standard atmosphere as specified in EN 12222 for at least 24 h.

**6.2.10** Use the cutting device (see 4.11) to make three cuts in each test assembly parallel to the 50 mm edges so that the centre portions form two test specimens of width 30,0 mm  $\pm$  0,5 mm and length 50 mm  $\pm$  1 mm and the two outer portions are waste strips of width approximately 5 mm, see Figure 1.

**6.2.11** Open the unbonded portion of each test specimen, taking care not to weaken the bond line, and centrally clamp it between the jaws of the tensile tester (see 4.1) so that the unbonded tab of resin rubber is in one jaw and the unbonded tab of upper material is in the other jaw (see Figure 2).

<https://standards.iteh.ai/catalog/standards/sist/80217a1a-7169-4dcb-9c27-86494612488f/sist-en-13514-2004>