



SLOVENSKI STANDARD
SIST EN ISO 22774:2005

01-april-2005

Obutev - Preskusne metode za dodatke: vezalke - Odpornost proti odrgnjenju (ISO 22774:2004)

Footwear - Test methods for accessories: shoe laces - Abrasion resistance (ISO 22774:2004)

Schuhe - Prüfverfahren für Zubehör: Schnürsenkel - Scheuerbeständigkeit (ISO 22774:2004)

Chaussures - Méthodes d'essai pour accessoires: lacets - Résistance à l'abrasion (ISO 22774:2004)

SIST EN ISO 22774:2005
<https://standards.iteh.ai/catalog/standards/sist/5e767c6-3073-419c-bd41-97c21e819ce1/sist-en-iso-22774-2005>

Ta slovenski standard je istoveten z: EN ISO 22774:2004

ICS:

61.060

Obuvala

Footwear

SIST EN ISO 22774:2005

en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 22774:2005

<https://standards.iteh.ai/catalog/standards/sist/f5e767c6-3073-419c-bd41-97c21e819ce1/sist-en-iso-22774-2005>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN ISO 22774

December 2004

ICS 61.060

English version

Footwear - Test methods for accessories: shoe laces - Abrasion resistance (ISO 22774:2004)

Chaussures - Méthodes d'essai pour accessoires: lacets et oeillets - Résistance à l'abrasion (ISO 22774:2004)

Schuhe - Prüfverfahren für Zubehör: Schnürsenkel - Scheuerbeständigkeit (ISO 22774:2004)

This European Standard was approved by CEN on 23 August 2004.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

[SIST EN ISO 22774:2005](https://standards.iteh.ai/catalog/standards/sist/15e767c6-3073-419c-bd41-97c21e819ce1/sist-en-iso-22774-2005)

<https://standards.iteh.ai/catalog/standards/sist/15e767c6-3073-419c-bd41-97c21e819ce1/sist-en-iso-22774-2005>



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Contents	Page
Foreword.....	3
1 Scope	4
2 Normative references	4
3 Terms and definitions	4
4 Principle.....	4
5 Apparatus and materials.....	5
5.1 General.....	5
6 Test specimens.....	7
6.1 Method 1	7
6.2 Methods 2 and 3.....	7
7 Conditioning.....	7
8 Procedure	7
8.1 Method 1	7
8.2 Method 2	8
8.3 Method 3	8
9 Calculation and expression of results.....	8
10 Test report	9
Annex ZA (normative) Normative references to International publications with their corresponding European publications.....	10

iTech STANDARD PREVIEW

(standards.itech.ai)

SIST EN ISO 22774:2005

[https://standards.itech.ai/catalog/standards/sist/5e767c6-3073-419c-bd41-](https://standards.itech.ai/catalog/standards/sist/5e767c6-3073-419c-bd41-97c21e819ce1/sist-en-iso-22774-2005)[97c21e819ce1/sist-en-iso-22774-2005](https://standards.itech.ai/catalog/standards/sist/5e767c6-3073-419c-bd41-97c21e819ce1/sist-en-iso-22774-2005)

Foreword

This document (EN ISO 22774:2004) has been prepared by CEN/TC 309, "Footwear", the secretariat of which is held by AENOR, in collaboration with Technical Committee ISO/TC 216 "Footwear".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2005, and conflicting national standards shall be withdrawn at the latest by June 2005.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST EN ISO 22774:2005](https://standards.iteh.ai/catalog/standards/sist/f5e767c6-3073-419c-bd41-97c21e819ce1/sist-en-iso-22774-2005)

<https://standards.iteh.ai/catalog/standards/sist/f5e767c6-3073-419c-bd41-97c21e819ce1/sist-en-iso-22774-2005>

EN ISO 22774:2004 (E)

1 Scope

This document specifies three test methods for determining the abrasion resistance of a shoe lace to repeated rubbing:

- Method 1: lace to lace abrasion;
- Method 2: lace to standard eyelet abrasion;
- Method 3: lace to eyelet (from footwear) abrasion.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 12222, *Footwear — Standard atmospheres for conditioning and testing of footwear and components for footwear*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

abrasion resistance of shoe laces

ability of the shoe lace to resist to repeated rubbing against either a similar shoe lace or a lace carrier

3.2

number of cycles to failure

arithmetic mean of the number of cycles to failure for the test specimens submitted to test

3.3

type of failure

expressed as failure of the shorter lace or failure of the longer lace, together with a description of the respective amount of wear in the covering and core of each lace

4 Principle

A shoe lace is threaded through a loop formed by:

- a piece of similar lace held open by a spacer (Method 1);
- a lace carrier (Methods 2 and 3).

The shoe lace is bent through a fixed acute angle at the point of contact with the loop. It is then held under a standard tension while it is repeatedly drawn back and forth through the loop until it fails.

5 Apparatus and materials

5.1 General

5.1.1 A test machine with one or more test stations, see Figure 1, each having:

NOTE Test machines with less than six stations are also acceptable to conduct this test. In which case the test should be repeated until six test specimens have been tested (see 8.1.6).

5.1.2 A moveable clamp which has a means of firmly holding:

- both ends of a piece of shoe lace (Method 1);
- one end of the metal strip (see 5.1.8) (Methods 2 and 3).

5.1.3 A stationary clamp which is mounted in the horizontal same plane as the moveable clamp (5.1.1) and is capable of holding one end of a shoe lace. The stationary clamp should be $280 \text{ mm} \pm 50 \text{ mm}$ from the moveable clamp (5.1.2) when the clamps are at their minimum separation, this distance will subsequently be referred to as *D*.

5.1.4 A tensioning device with a method of holding the end of a piece of shoe lace at a point $35 \text{ mm} \pm 5 \text{ mm}$ to one side of, and in the same horizontal plane as, the stationary clamp (5.1.3) and applying a tensioning force of $2,45 \text{ N} \pm 0,03 \text{ N}$, see Figure 1. This can be achieved by passing the shoe lace over a pulley and suspending a mass of $250 \text{ g} \pm 3 \text{ g}$ from the lower end of the vertical portion of the lace.

5.1.5 A means of moving the moveable clamp (5.1.2) with a simple harmonic reciprocating motion through a distance of $35 \text{ mm} \pm 2 \text{ mm}$ and back to the original starting position at a rate of $60 \text{ cycles per minute} \pm 6 \text{ cycles per minute}$.

[SIST EN ISO 22774:2005](https://standards.iteh.ai/catalog/standards/sist/5e767c6-3073-419c-bd41-)

<https://standards.iteh.ai/catalog/standards/sist/5e767c6-3073-419c-bd41->


5.1.6 A means of counting the number of abrasion cycles up to failure of the lace or lace carrier.

5.1.7 For Method 1:

- a rigid spacer device of width $25 \text{ mm} \pm 5 \text{ mm}$. This is used to hold the two legs of the loop of lace which is clamped in the moveable clamp (5.1.2) apart (see Figure 1), so that when it is under tension the end of the loop forms an isosceles triangle with the spacer as its base and the two parts of the lace are at an angle of $52,5^\circ \pm 5,0^\circ$;
- a template with an angle of $52,5^\circ$ marked on it, for setting the position of the spacer device.

5.1.8 For Method 2, a metal strip of width approximately 25 mm , thickness approximately 1 mm and length approximately $D - 60 \text{ mm}$. One end of the strip should fit into the moveable clamp (5.1.2) and the other end should be capable of holding the test lace carrier.

EN ISO 22774:2004 (E)

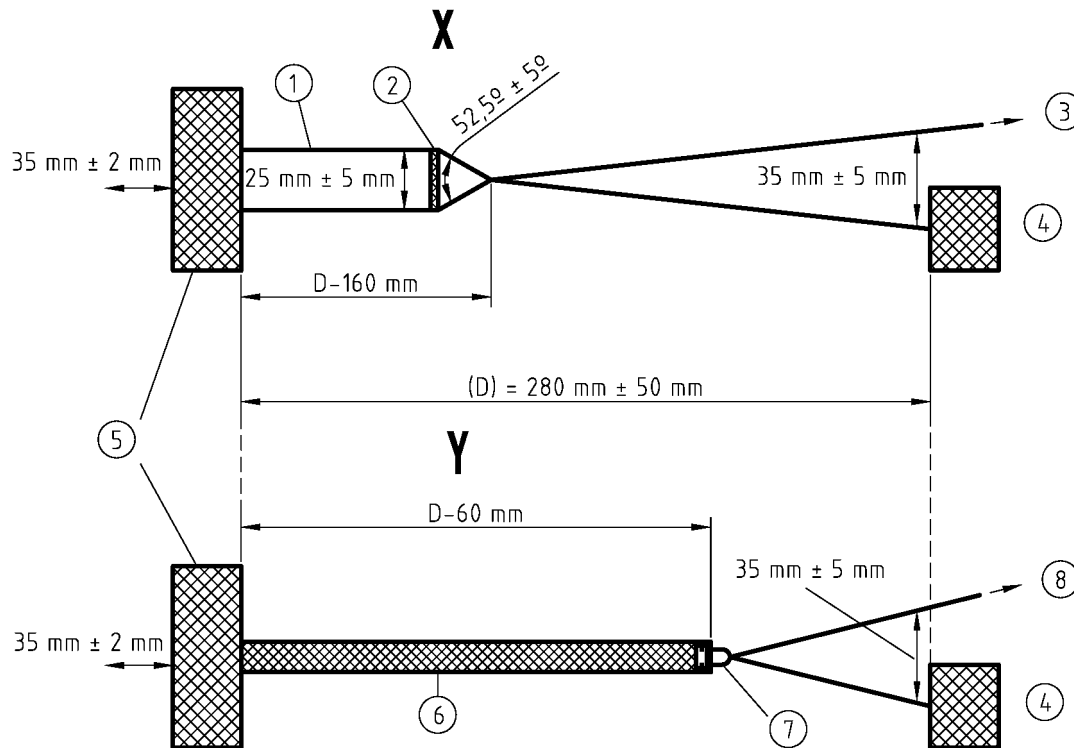

iTeh STANDARD PREVIEW (standards.iteh.ai)

X = Method 1: Lace – lace abrasion

Y = Methods 2 and 3: Lace – carrier abrasion

- 1 Lace loop
- 2 Spacer
- 3 Force (2,45 N ± 0,03 N)
- 4 Stationary clamp
- 5 Moveable clamp
- 6 Metal strip
- 7 Lace carrier
- 8 Force (2,45 N ± 0,03 N)

[SIST EN ISO 22774:2005](https://standards.iteh.ai/catalog/standards/sist/f5e767c6-3073-419c-bd41-97c21e819ce1/sist-en-iso-22774-2005)

<https://standards.iteh.ai/catalog/standards/sist/f5e767c6-3073-419c-bd41-97c21e819ce1/sist-en-iso-22774-2005>

Figure 1 — Plan view of abrasion geometry

5.2 Standard eyelets, with the following characteristics (method 2):

- Construction: Visible (standard/flat) type;
- Material type: brass;
- Nominal internal barrel diameter: 4,5 mm;
- Nominal overall length: 5,5 mm;

5.3 Six test lace carriers (for methods 2 and 3)

5.3.1 Method 2

Mounting board: rigid fibreboard 3,0 mm ± 0,5 mm thick. Eyelet is clenched in drilled hole 5,0 mm ± 0,2 mm diameter (board with eyelet cut to size to fit mounting in machine) and fixed to the metal strip (see Figure 1).

5.3.2 Method 3

Cut from the footwear a sample including the eyelet and fix it to the metal strip (see Figure 1).

6 Test specimens

6.1 Method 1

6.1.1 Cut six pieces of shoe lace each of minimum length $2 \times (D - 160)$ mm.

If sufficient made shoe laces are available, cut each test specimen from a separate lace.

6.1.2 Cut six pieces of shoe lace each of length $500 \text{ mm} \pm 10 \text{ mm}$.

If sufficient made shoe laces are available, cut each test specimen from a separate lace.

For some equipment it is possible to use pieces of lace as short as 100 mm by tying string to each end to lengthen them, provided only the lace test specimen (6.1.1) rubs against the lace test specimen (6.1.2).

6.2 Methods 2 and 3

Cut six pieces of shoe lace each of length $300 \text{ mm} \pm 10 \text{ mm}$.

If sufficient made shoe laces are available, cut each test specimen from a separate lace.

For some equipment it is possible to use pieces of lace as short as 100 mm by tying string to each end to lengthen them, provided only the lace test specimen rubs against the test lace carrier (5.3).

[SIST EN ISO 22774:2005](https://standards.iteh.ai/catalog/standards/sist/5e767c6-3073-419c-bd41-97c21e819ce1/sist-en-iso-22774-2005)

<https://standards.iteh.ai/catalog/standards/sist/5e767c6-3073-419c-bd41-97c21e819ce1/sist-en-iso-22774-2005>

7 Conditioning

Store the shoe laces and the test lace carriers in a standard atmosphere in accordance with EN 12222 for at least 48 h before testing and carry out the test in this atmosphere.

8 Procedure

8.1 Method 1

8.1.1 Secure both ends of one of the pieces of lace (6.1.1) in a moveable clamp (5.1.2) so that it forms a loop of length approximately $2 \times (D - 160)$ mm.

8.1.2 Secure one end of a piece of the lace (6.1.2) in the corresponding stationary clamp (5.1.3).

8.1.3 Thread the free end of the piece of lace (6.1.2) through the loop formed by the piece of lace (6.1.1) in subclause 8.1.1.

8.1.4 Apply a tensioning force of $2,45 \text{ N} \pm 0,03 \text{ N}$ to the free end of the piece of lace (6.1.2).

8.1.5 Fit a spacer (5.1.7) into the loop formed by the piece of lace (6.1.1) and slide it towards the point of contact with the piece of lace (6.1.2) until the template (5.1.7) indicates that the tip of the loop of lace (6.1.1) forms an angle of $52,5^\circ \pm 5,0^\circ$ (see Figure 1).

8.1.6 Repeat the procedure in 8.1.1 to 8.1.5 for the other 5 pairs of test laces (6.1.1 and 6.1.2). For equipment with less than six test stations this will require steps 8.1.1 to 8.1.4 to be repeated until all six pieces have been tested.