

INTERNATIONAL  
STANDARD

**ISO**  
**12307-1**

First edition  
1994-12-15

---

---

**Plain bearings — Wrapped bushes —**

**Part 1:**

Checking the outside diameter

iTeh STANDARD PREVIEW

(standards.iteh.ai)

*Paliers lisses — Bagues roulées —*

*Partie 1: Contrôle du diamètre extérieur*

<https://standards.iteh.ai/catalog/standards/sist/bc68ecb8-8b2a-4726-b715-2b8f56279715/iso-12307-1-1994>



Reference number  
ISO 12307-1:1994(E)

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 12307-1 was prepared by Technical Committee ISO/TC 123, *Plain bearings*, Subcommittee SC 5, *Quality analysis and assurance*.

<https://standards.iteh.ai/catalog/standards/sist/bc68ecb8-8b2a-4726-b715-1994>

ISO 12307 consists of the following parts, under the general title *Plain bearings — Wrapped bushes*:

- *Part 1: Checking the outside diameter*
- *Part 2: Checking the inside diameter*

Annexes A, B and C of this part of ISO 12307 are for information only.

© ISO 1994

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization  
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

# Plain bearings — Wrapped bushes —

## Part 1: Checking the outside diameter

### 1 Scope

This part of ISO 12307 specifies in accordance with ISO 12301 the checking of the outside diameter of wrapped bushes (methods A and B specified in ISO 3547) and describes the necessary checking methods and measuring equipment.

Wrapped bushes in the free condition are flexible but, after insertion, they adapt largely to the shape of the housing bore due to the oversize between the outside diameter of the bush and the housing bore. For this reason, checking of the outside diameter of wrapped bushes can only be carried out under a constraining load by use of specialized measuring equipment.

#### NOTES

- 1 All dimensions in this part of ISO 12307 are given in millimetres.
- 2 The dimensions and tolerances of wrapped bushes are given in ISO 3547. Checking the wall thickness is the subject of ISO 12306.

### 2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this part of ISO 12307. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this part of ISO 12307 are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 286-1:1988, *ISO system of limits and fits — Part 1: Bases of tolerances, deviations and fits.*

ISO 286-2:1988, *ISO system of limits and fits — Part 2: Tables of standard tolerance grades and limit deviations for holes and shafts.*

ISO/R 1938:1971, *ISO system of limits and fits — Part II: Inspection of plain workpieces.*

ISO 3547:1976, *Plain bearings — Wrapped bushes — Dimensions, tolerances and methods of checking.*

### 3 Symbols and units


For the purposes of this part of ISO 12307, the symbols and units are as given in table 1.

Table 1 — Symbols and units

Symbol	Parameter	SI unit
$a_c$	Distance between checking block halves	mm
$B$	Width of the bush	mm
$b_{c,1}$	Width of the checking block	mm
$b_{c,2}$	Width of the setting plug ( $b_{c,2} = b_{c,1} + 5$ )	mm
$D_o$	Outside diameter of the bush	mm
$d_{c,1}$	Diameter of the checking block bore (see ISO 3547)	mm
$d_{c,2}$	Diameter of the setting plug	mm
$d_{c,a,1}$	Actual diameter of the checking block	mm
$d_{c,a,2}$	Actual diameter of the setting plug	mm
$E_{red}$	Elastic reduction of the outside diameter under the checking load $F_c$	mm
$F_c$	Checking load	N
$C$	Correction factor	mm
$n$	Number of test pieces	
$P_{zw}$	Confidence level, on both sides	%
$R_a$	Surface roughness (in accordance with ISO 468)	$\mu\text{m}$
$T$	Tolerance on $D_o$	mm
$t_1 \dots t_6$	Tolerances of form and position	mm
$u$	Uncertainty of measurement ( $P_{zw} = 95\%$ )	mm
$u_E$	Uncertainty of measurement of the measuring equipment	mm
$\Delta x$	Difference in measured values between first and second readings	mm
$\overline{\Delta x}$	Arithmetic mean of $\Delta x$	mm
$\sigma$	Standard deviation	mm
$\sigma_{\Delta x}$	Standard deviation of $\Delta x$	mm

#### 4 Outside diameter, $D_o$

For the outside diameter of a wrapped bush, see figure 1.

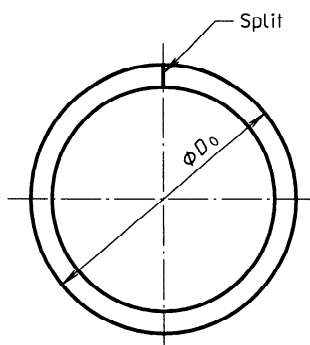

NOTE — The free diameter of a wrapped bush is not measured directly because of the flexible nature of the component.

Figure 1 — Outside diameter of a wrapped bush

## 5 Purpose of checking

The outside diameter shall be checked to guarantee the designated mounting compression (interference fit) for the wrapped bush in the housing bore.

## 6 Methods of checking

### 6.1 Checking method A: Measurement of outside diameter, $D_o$ (see ISO 3547)

Check the outside diameter of a wrapped bush using measuring equipment as shown in figure 2, with a checking block consisting of upper and lower halves (see figures 3 and 4) and setting plugs (see figures 5 and 6), at a determined checking load of  $F_c$ .

Measure the outside diameter indirectly as the difference in the value of  $a_c$  ( $\Delta a_c$ ).

The checking load is calculated such that the bush outside diameter is reduced only elastically during checking and that there is no permanent deformation.

### 6.2 Checking method B: Gauging of outside diameter, $D_o$ (see ISO 3547)

Check the outside diameter of a wrapped bush in "GO" and "NOT-GO" ring gauges.

The checking result is of an attributive nature, i.e. "GO" or "NOT-GO".

## 7 Selection of checking method for outside diameter

Method A is a precise method involving complex tooling. Method B is an attributive method using simpler tooling. Both methods are in general use. Method A is generally unsuitable for small bushes up to 10 mm outside diameter but is preferred for bushes over 10 mm outside diameter.


## 8 Test ISO 3547 — A: Outside diameter, $D_o$

### 8.1 Measuring equipment

See tables 2 to 4.

Typical equipment for measuring the bush consists essentially of the following components:

- base plate used as fixture and guiding device for the split checking block;
- aggregate to generate the checking load;
- upper plate;
- system transferring the distance  $a_c$  of both checking block halves to the measuring pin (see figure 2);
- measuring pin with indicating instrument;
- checking block (see figures 3 and 4) with setting plug (see figures 5 and 6);
- correlation compression (load table).

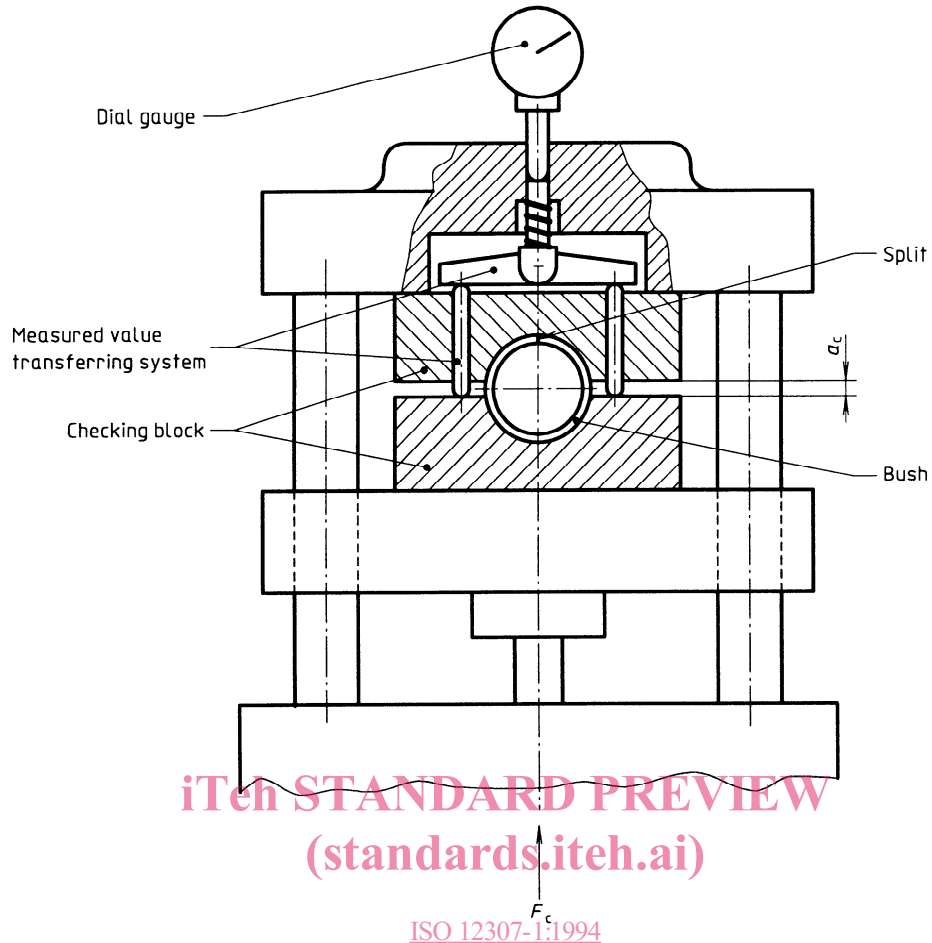

iTeh STANDARD PREVIEW  
 (standards.iteh.ai)  
 ISO 12307-1:1994  
<https://standards.iteh.ai/catalog/standards/sist/bc68ecb8-8b2a-4726-b715-208256279715/iso-12307-1-1994>  
**Figure 2 — Typical outside diameter measuring system**

Figure 2 shows hydraulically operated equipment. Pneumatically or mechanically operated equipment may also be used.

The force  $F_c$  may be applied from the top or from below.

The bush split shall be in the vertical direction and pointing towards the upper checking block.

**Table 2 — Checking loads, limiting deviations, speeds of approach and temperatures**

Checking load $F_c$ N	Permissible limiting deviations %	Maximum speed of approach to apply the checking load $F_c$ mm/s	Test temperature <sup>1)</sup> °C
$F_c \leq 2\,000$	$\pm 1,25$	$10 \pm 2$ without impact	20 to 25
$2\,000 < F_c \leq 5\,000$	$\pm 1$		
$5\,000 < F_c \leq 10\,000$	$\pm 0,75$		
$10\,000 < F_c \leq 50\,000$	$\pm 0,5$		

1) The difference in temperature between the checking block and the bush to be measured shall not exceed 1 °C.

**Table 3 — Deviations for dial gauge and electronic gauge**

Outside diameter $D_o$ mm	Scale graduation value		Total deviation <sup>1)</sup>	
	dial gauge	mm electronic gauge	dial gauge	mm electronic gauge
$D_o \leq 80$	0,001	0,001	0,001 2	0,5 % of measuring range
$D_o > 80$	0,005	0,001	0,006	

1) Maximum measuring value indication (full-scale  $\pm 500 \mu\text{m}$ ).

**Table 4 — Manufacturing tolerances for the upper and lower clamping surfaces of the measuring equipment**

Tolerance of parallelism between both clamping surfaces mm	Tolerance of flatness mm	Surface roughness, $R_a$ $\mu\text{m}$
0,01/100	0,005	0,2

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)

## 8.2 Requirements for measuring equipment

The requirements for the measuring equipment for measurement of the bush outside diameter,  $D_o$ , shall be as shown in figures 3 to 6 and given in table 5: [ISO 12307-1:1994](https://standards.iteh.ai/catalog/standards/sist/bc68ecb8-8b2a-4726-b715-2b8f56279715/iso-12307-1-1994)

<https://standards.iteh.ai/catalog/standards/sist/bc68ecb8-8b2a-4726-b715-2b8f56279715/iso-12307-1-1994>

$$d_{c,1} = D_{o,max} - E_{red}$$

$$E_{red} = 0,006 \text{ mm for } D_o < 12 \text{ mm}$$


$$E_{red} = 0,0012 \text{ mm for } D_o \geq 12 \text{ mm}$$

$$b_{c,1} \geq B + 2$$

$$h_{c,2} = h_{c,1} + 5$$


where  $E_{red}$  is the elastic reduction in accordance with ISO 3547.

Dimensions in millimetres,  
surface roughness values in micrometres

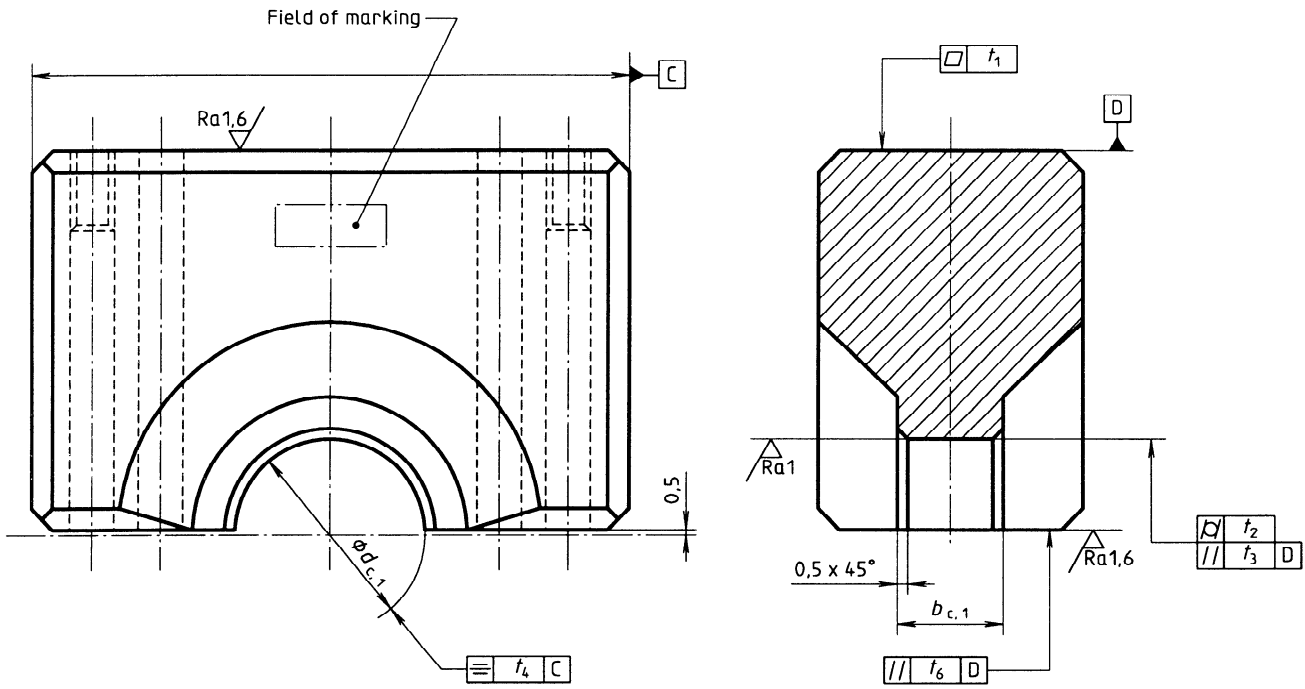

**Figure 3 — Upper half of checking block**  
(standards.iteh.ai)

ISO 12307-1:1994  
<https://standards.iteh.ai/catalog/standards/sist/bc68ecb8-8b2a-4726-b715-2b856279715/iso-12307-1-1994>  
 Dimensions in millimetres,  
surface roughness values in micrometres

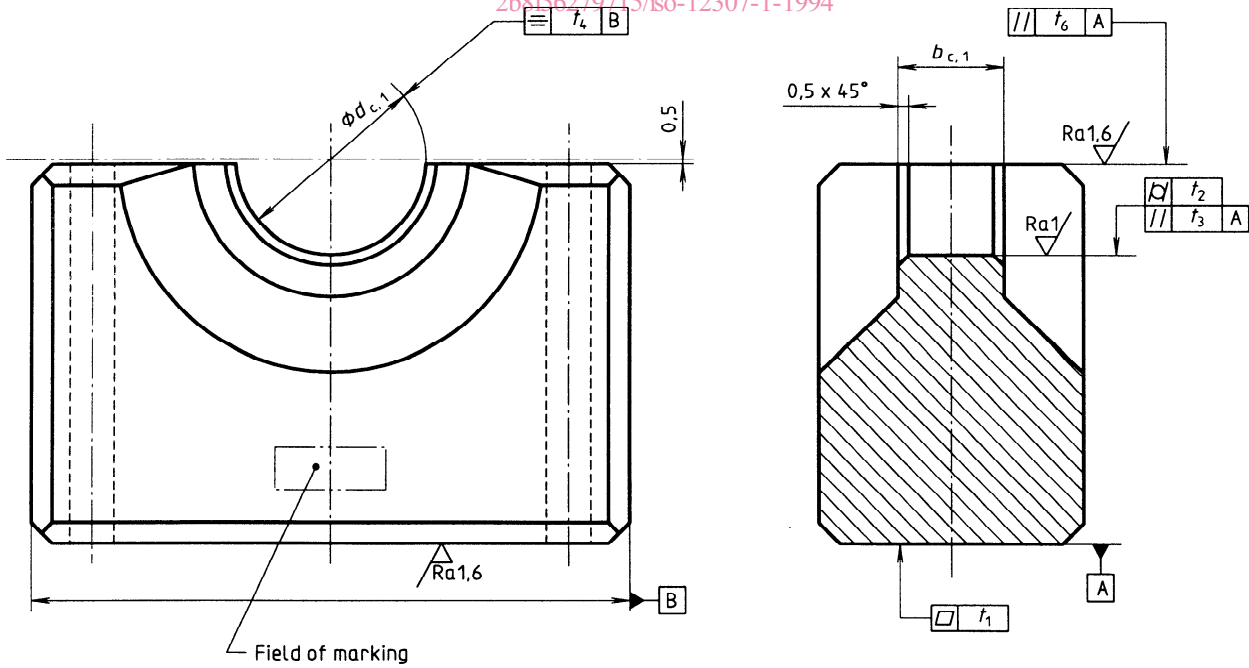

**Figure 4 — Lower half of checking block**



Dimensions in millimetres,  
surface roughness values in micrometres

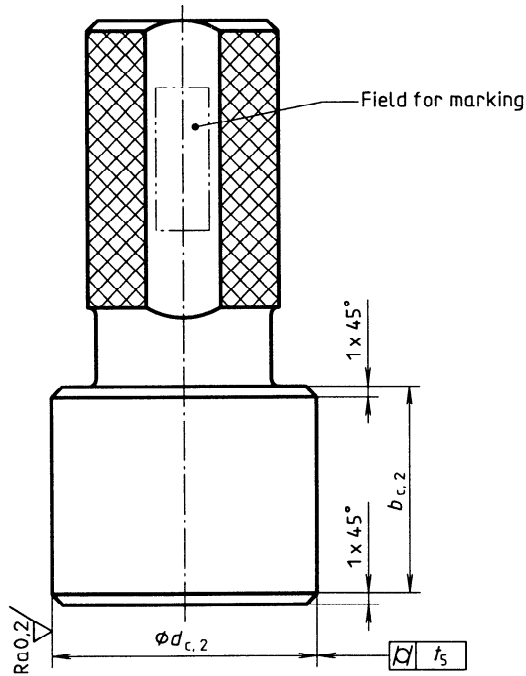


Figure 5 — Setting plug, solid, for  $d_{c,2} \leq 80$  mm  
(standards.iteh.ai)

ISO 12307-1:1994

<https://standards.iteh.ai/catalog/standards/sist/bc68ecb8-8b2a-4726-1511-2b8f56279715/iso-12307-1-1994>

Dimensions in millimetres,  
surface roughness values in micrometres

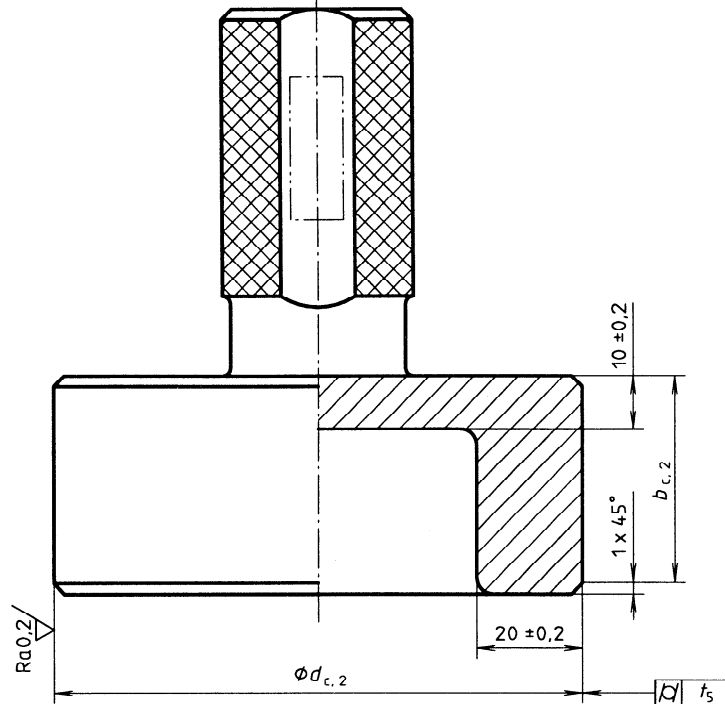


Figure 6 — Setting plug, for example with blind hole, for  $d_{c,2} > 80$  mm

**Table 5 — Manufacturing tolerances and wearing limits for checking block and setting plug**

Outside diameter $D_o$	Limits of manufacturing tolerances or wearing limits	$d_{c,2}$	$d_{c,1}$	$t_1$	$t_2$	$t_3$	$t_4$	$t_5$	$t_6$
$D_o \leq 80$	manufacture	$\begin{matrix} 0 \\ -0,003 \end{matrix}$	$\begin{matrix} +0,003 \\ 0 \end{matrix}$	0,002	0,002	0,003	0,05	0,002	0,03
	wear	- 0,005	+ 0,005	0,004	0,004	0,005	0,05	0,004	0,05
$80 < D_o \leq 150$ 1)	manufacture	$\begin{matrix} 0 \\ -0,005 \end{matrix}$	$\begin{matrix} +0,005 \\ 0 \end{matrix}$	0,003	0,003	0,004	0,05	0,003	0,03
	wear	- 0,007	+ 0,007	0,005	0,005	0,006	0,05	0,005	0,05

1) For  $D_o > 150$  mm, agreement shall be reached between the manufacturer and customer.

Checking block halves (see figures 3 and 4) and setting plugs (see figures 5 and 6) shall be made from hardened (60 HRC to 64 HRC) and non-ageing steel.

The checking block halves shall be of rigid construction so that only negligible deformations are caused by the forces arising during measurement of the bushes.

The bore of the checking block halves and the checking surface of the setting plug shall not be chromium plated.

The checking block and the setting plug may be marked with their nominal diameter,  $d_{c,1}$ .

The setting plugs shall be additionally marked with their correction factor  $C$ .

**8.3 Determination of correction factor  $C$**  ISO 12307-1:1994

<https://standards.iteh.ai/catalog/standards/sist/bc68ecb8-8b2a-4726-b715-2f66701307-1-1994>

The correction factor,  $C$ , is calculated from the following formula:

$$C = \frac{\pi}{2} (d_{c,a,1} - d_{c,1}) - (d_{c,a,1} - d_{c,a,2})$$

**EXAMPLE**

$$d_{c,1} = 20,050 \text{ mm}$$

$$d_{c,a,1} = 20,052 \text{ mm}$$

$$d_{c,a,2} = 20,048 \text{ mm}$$

Therefore

$$C = \frac{\pi}{2} (20,052 - 20,050) - (20,052 - 20,048)$$

$$C = - 0,001 \text{ mm}$$

If the actual diameter  $d_{c,a,1}$  of the checking block deviates from the  $d_{c,1}$  diameter of the bushes to be checked, these checking blocks may still be used provided that the deviation  $|d_{c,a,1} - d_{c,1}| \leq 0,03$  mm. The tolerances of the setting plug according to table 4 are not affected.

**EXAMPLE**

$$d_{c,1} = 20,062 \text{ mm}$$

$$d_{c,a,1} = 20,052 \text{ mm}$$

$$d_{c,a,2} = 20,048 \text{ mm}$$

$$|d_{c,a,1} - d_{c,1}| = 0,010 \text{ mm} = < 0,030 \text{ mm}$$

Therefore

$$C = \frac{\pi}{2} (20,052 - 20,062) - (20,052 - 20,048)$$

$$C = -0,020 \text{ mm}$$

#### 8.4 Procedure

Perfect positioning of both checking block halves to each other is given when the lower half is inserted first and fixed centrally to the bush measuring equipment. Then press the loosely mounted upper checking block half under a given checking load against the lower checking block half with the setting plug inserted. Fix it in this state and adjust the correction factor  $C$  in accordance with 8.3, and take the reading  $\Delta\alpha_c$ . Then insert the bushes centrally.

#### 8.5 Measuring errors

The most frequent errors are given in 8.5.1 to 8.5.3.

##### 8.5.1 Errors due to measuring equipment

- a) The upper and lower checking block halves are not lined up to each other.
- b) The checking block halves are not correctly fixed in the measuring equipment.
- c) Tightness [too much clearance, damage of the transmission system (see figure 2), dial gauge, measuring pin, etc.].
- d) Damage to or wear of the checking block or setting plug.
- e) The width of the checking block bore,  $b_{c,1}$ , is less than the width of the bush,  $B$ .
- f) The checking load,  $F_c$ , does not correspond to the calculated load.

##### 8.5.2 Errors due to the bush

Presence of grease, dirt, burrs, etc. on the outside diameter (back surface) and/or in the split, and damage or deformation of the outside diameter and/or the split.

##### 8.5.3 Errors due to human factors

- a) Wrong setting of the checking load.
- b) The bush is measured eccentrically to the width of the checking block bore,  $b_{c,1}$ .
- c) The split in the bush inserted in the checking block does not point vertically towards the upper checking block.
- d) Incorrect reading taken at measurement of the actual diameters  $d_{c,a,1}$  and  $d_{c,a,2}$ .
- e) Wrong calculation and/or setting of the correction value.
- f) Wrong conversion of the outside diameter,  $D_o$ .