

INTERNATIONAL STANDARD

NORME INTERNATIONALE

**Winding wires – Test methods –
Part 5: Electrical properties**

**Fils de bobinage – Méthodes d'essai –
Partie 5: Propriétés électriques**

IEC 60851-5:2008

<https://standards.iteh.ai/catalog/standards/iec/db3ef4c5-ec44-4320-b327-baa3410f575b/iec-60851-5-2008>



THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2011 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester.

If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de la CEI ou du Comité national de la CEI du pays du demandeur.

Si vous avez des questions sur le copyright de la CEI ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de la CEI de votre pays de résidence.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland
Email: inmail@iec.ch
Web: www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

- Catalogue of IEC publications: www.iec.ch/searchpub

The IEC on-line Catalogue enables you to search by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, withdrawn and replaced publications.

- IEC Just Published: www.iec.ch/online_news/justpub

Stay up to date on all new IEC publications. Just Published details twice a month all new publications released. Available on-line and also by email.

- Electropedia: www.electropedia.org

The world's leading online dictionary of electronic and electrical terms containing more than 20 000 terms and definitions in English and French, with equivalent terms in additional languages. Also known as the International Electrotechnical Vocabulary online.

- Customer Service Centre: www.iec.ch/webstore/custserv

If you wish to give us your feedback on this publication or need further assistance, please visit the Customer Service Centre FAQ or contact us:

Email: csc@iec.ch

Tel.: +41 22 919 02 11

Fax: +41 22 919 03 00

A propos de la CEI

La Commission Electrotechnique Internationale (CEI) est la première organisation mondiale qui élabore et publie des normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications CEI

Le contenu technique des publications de la CEI est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

- Catalogue des publications de la CEI: www.iec.ch/searchpub/cur_fut-f.htm

Le Catalogue en-ligne de la CEI vous permet d'effectuer des recherches en utilisant différents critères (numéro de référence, texte, comité d'études,...). Il donne aussi des informations sur les projets et les publications retirées ou remplacées.

- Just Published CEI: www.iec.ch/online_news/justpub

Restez informé sur les nouvelles publications de la CEI. Just Published détaille deux fois par mois les nouvelles publications parues. Disponible en-ligne et aussi par email.

- Electropedia: www.electropedia.org

Le premier dictionnaire en ligne au monde de termes électroniques et électriques. Il contient plus de 20 000 termes et définitions en anglais et en français, ainsi que les termes équivalents dans les langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International en ligne.

- Service Clients: www.iec.ch/webstore/custserv/custserv_entry-f.htm

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions, visitez le FAQ du Service clients ou contactez-nous:

Email: csc@iec.ch

Tél.: +41 22 919 02 11

Fax: +41 22 919 03 00



IEC 60851-5

Edition 4.1 2011-08

INTERNATIONAL STANDARD

NORME INTERNATIONALE

**Winding wires – Test methods –
Part 5: Electrical properties**

**Fils de bobinage – Méthodes d'essai –
Partie 5: Propriétés électriques**

IEC 60851-5:2008

<https://standards.iteh.ai/catalog/standards/iec/db3ef4c5-ec44-4320-b327-baa3410f575b/iec-60851-5-2008>

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

COMMISSION
ELECTROTECHNIQUE
INTERNATIONALE

ICS 29.060.10

ISBN 978-2-88912-611-8

CONTENTS

FOREWORD.....	4
INTRODUCTION.....	6
1 Scope.....	7
2 Normative references	7
3 Test 5: Electrical resistance.....	7
4 Test 13: Breakdown voltage	8
4.1 Principle.....	8
4.2 Equipment.....	8
4.3 Enamelled round wire with a nominal conductor diameter up to and including 0,100 mm	9
4.3.1 Grade 1 to grade 3 with a nominal diameter up to and including 0,100 mm.....	9
4.3.2 Grade of FIW 3 to FIW 9 with a nominal conductor diameter up to and including 1,600 mm.....	10
4.4 Enamelled round wire with a nominal conductor diameter over 0,100 mm up to and including 2,500 mm, grade 1 to grade 3	11
4.4.1 Test at room temperature	11
4.4.2 Test at elevated temperature	12
4.5 Round wire with a nominal conductor diameter over 2,500 mm.....	13
4.5.1 Test at room temperature	13
4.5.2 Test at elevated temperature.....	15
4.6 Fibre wound round wire	15
4.6.1 Test at room temperature	15
4.6.2 Test at elevated temperature	16
4.7 Rectangular wire	17
4.7.1 Test at room temperature	17
4.7.2 Test at elevated temperature.....	17
5 Test 14: Continuity of insulation (applicable to enamelled round and tape wrapped round wire).....	17
5.1 General.....	17
5.2 Low-voltage continuity (nominal conductor diameter up to and including 0,050 mm, grade 1 to grade 3)	18
5.3 High-voltage continuity (nominal conductor diameter over 0,050 mm up to and including 1,600 mm, grade 1 to grade 3, and over 0,035 mm, up to and including 1,600 mm, grade 3 of FIW 3 to FIW 9).....	19
5.3.1 Principle	19
5.3.2 Equipment.....	19
5.3.3 Procedure.....	24
5.3.4 Result.....	25
5.4 Inline high-voltage continuity (wires in accordance with grade of FIW 3 to FIW 10 with nominal conductor diameter over 0,035 mm up to and including 1,600 mm)	25
5.4.1 Principle	25
5.4.2 Equipment.....	26
5.4.3 Procedure.....	26
5.4.4 Result.....	27

6	Test 19: Dielectric dissipation factor (applicable to enamelled wire and bunched wire).....	27
6.1	Principle.....	27
6.2	Equipment.....	28
6.3	Specimen.....	29
6.3.1	Specimen for a metal bath electrode.....	29
6.3.2	Specimen for a conductive suspension electrode.....	29
6.4	Procedure.....	29
6.5	Result.....	29
7	Test 23: Pin hole test.....	29
	Annex A (informative) Dissipation factor methods.....	31
	Figure 1 – Arrangement of cylinder and specimen for the breakdown voltage test.....	10
	Figure 2 – Device for twisting the specimen for breakdown voltage test.....	12
	Figure 3 – U-bend specimen for the breakdown voltage test (specimen placed in shot bath).....	14
	Figure 4 – Coil-wound specimen for the breakdown voltage test.....	16
	Figure 5 – Apparatus for testing the low-voltage continuity of covering.....	18
	Figure 6 – High-voltage d.c. continuity – Pulleys for wire size 0,050 mm to 0,250 mm.....	21
	Figure 7 – Pulley dimensions and spacing for wire size 0,250 mm to 1,600 mm.....	21
	Figure 8a – Graphite fibre single brush electrode assembly.....	22
	Figure 8b – Graphite fibre dual brush electrode assembly.....	23
	Figure 8 – Graphite fibre single or dual brush electrode assembly.....	23
	Figure 9 – Suitable electrode arrangement for testing the dielectric dissipation factor.....	28
	Figure A.1 – Example of linear method for sole coating.....	33
	Figure A.2 – Example of logarithmic method for sole coating.....	33
	Table 1 – Rates of test voltage increase.....	8
	Table 2 – Loads applied to the wire.....	9
	Table 3 – Loads applied to the wire and number of twists.....	12
	Table 4 – Off-line HVC fault currents.....	20
	Table 5 – Test voltages.....	24
	Table 5.1 – Off-line HVC test voltages for grades 1 – 3.....	24
	Table 5.2 – Off-line HVC test voltages for grade of FIW 3 – FIW 9.....	25
	Table 6 – In-line HVC fault currents.....	26
	Table 7 – In-line HVC test voltages.....	27

INTERNATIONAL ELECTROTECHNICAL COMMISSION

WINDING WIRES – TEST METHODS –

Part 5: Electrical properties

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as “IEC Publication(s)”). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

This consolidated version of IEC 60851-5 consists of the fourth edition (2008) [documents 55/1069/FDIS and 55/1078/RVD] and its amendment 1 (2011) [documents 55/1223/FDIS and 55/1251/RVD]. It bears the edition number 4.1.

The technical content is therefore identical to the base edition and its amendment and has been prepared for user convenience. A vertical line in the margin shows where the base publication has been modified by amendment 1. Additions and deletions are displayed in red, with deletions being struck through.

International Standard IEC 60851-5 has been prepared by IEC technical committee 55: Winding wires.

Significant revisions to the previous edition include the following points:

- in Subclause 5.3, the addition of the use of carbon brush electrodes for the counting discontinuities during the high voltage continuity test, as an alternative to the V-groove pulley electrode;
- clarifications in the breakdown voltage test for round wires larger than 2,500 mm and for fibrous covered wires.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all the parts in the IEC 60851 series, under the general title *Winding wires – Test methods*, can be found on the website.

The amendment 1 includes

- in Clause 4 the addition of dielectric breakdown requirements for fully insulated (FIW) zero-defect enamelled round copper wires;
- in Clause 5 the addition of continuity requirements for fully insulated (FIW) zero-defect enamelled round copper wires.

The committee has decided that the contents of the base publication and its amendments will remain unchanged until the stability date indicated on the IEC web site under "<http://webstore.iec.ch>" in the data related to the specific publication. At this date, the publication will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or [IEC 60851-5:2008](#)
- amended.

<https://standards.tech.ai/catalog/standards/iec/db3ef4c5-ec44-4320-b327-baa3410f575b/iec-60851-5-2008>

IMPORTANT – The “colour inside” logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this publication using a colour printer.

INTRODUCTION

This part of IEC 60851 forms an element of a series of standards which deals with insulated wires used for windings in electrical equipment. The series has three groups describing

- a) winding wires – Test methods (IEC 60851);
- b) specifications for particular types of winding wires (IEC 60317);
- c) packaging of winding wires (IEC 60264).

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[IEC 60851-5:2008](#)

<https://standards.iteh.ai/catalog/standards/iec/db3ef4c5-ec44-4320-b327-baa3410f575b/iec-60851-5-2008>

WINDING WIRES – TEST METHODS –

Part 5: Electrical properties

1 Scope

This part of IEC 60851 specifies the following tests:

- Test 5: Electrical resistance;
- Test 13: Breakdown voltage;
- Test 14: Continuity of insulation;
- Test 19: Dielectric dissipation factor;
- Test 23: Pin hole.

For definitions, general notes on methods of test and the complete series of methods of test for winding wires, see IEC 60851-1.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60851-1, *Winding wires – Test methods – Part 1: General*

[IEC 60851-5:2008](#)

<http://standards.iteh.org/catalog/iec/standards/iec-60851-5-2008>

3 Test 5: Electrical resistance

Electrical resistance is the d.c. resistance at 20 °C of 1 m of wire.

The method used shall provide a precision of 0,5 %.

For bunched wires a length of up to 10 m shall be used and the ends shall be soldered before the measurement. When measuring the resistance to check for an excessive number of broken wires, a length of 10 m of bunched wire shall be used.

If the resistance R_t is measured at a temperature t other than 20 °C, the resistance R_{20} at 20 °C shall be calculated by means of the following formula:

$$R_{20} = \frac{R_t}{1 + \alpha (t - 20)}$$

where

t is the actual temperature in degrees Celsius during the measurement;

α is the temperature coefficient in K⁻¹.

In the temperature range from 15 °C to 25 °C, the temperature coefficient to be used shall be:

- for copper: $\alpha_{20} = 3,96 \times 10^{-3} \text{ K}^{-1}$;
- for aluminium: $\alpha_{20} = 4,07 \times 10^{-3} \text{ K}^{-1}$.

One test shall be made. The electrical resistance shall be reported.

4 Test 13: Breakdown voltage

4.1 Principle

The test voltage shall be an a.c. voltage of 50 Hz or 60 Hz nominal frequency. The test voltage shall be applied at zero and increased at a uniform rate according to Table 1.

Table 1 – Rates of test voltage increase

Breakdown voltage V		Rate of increase V/s
Over	Up to and including	
–	500	20
500	2 500	100
2 500	–	500

4.2 Equipment

The following equipment shall be used:

- test transformer with a rated power of at least 500 VA providing an a.c. voltage of an undistorted sine waveform under test conditions, with a peak factor being within the limits of $\sqrt{2} \pm 5 \%$ (1,34 to 1,48) and with a capacity to supply a current of 5 mA with a maximum voltage drop of 2 %;
- fault detection circuit, which operates at a current of 5 mA or more;
- arrangement to provide a uniform rise of the test voltage at the specified rate;
- oven with forced air circulation;
- polished metal cylinder, 25 mm \pm 1 mm in diameter, mounted with its axis horizontal (see Figure 1) and electrically connected to one terminal of the test voltage supply;
- twisting device according to Figure 2, that allows to twist two pieces of wire for a length of 125 mm;
- strips of metal foil, 6 mm in width and pressure sensitive tape, 12 mm in width;
- container with metal shot of stainless steel or nickel-plated iron. The diameter of the shot shall not exceed 2 mm. The shot shall be cleaned periodically by suitable means;
- metal mandrel, 50 mm \pm 2 mm in diameter;
- metal mandrel, 25 mm \pm 1 mm in diameter;
- metal mandrel, 80 mm \pm 3 mm in diameter.

4.3 Enamelled round wire ~~with a nominal conductor diameter up to and including 0,100 mm~~

4.3.1 Grade 1 to grade 3 with a nominal diameter up to and including 0,100 mm

~~A straight piece of wire with the insulation removed at one end shall be connected to the upper terminal as shown in Figure 1 and wound once around the cylinder. A load as specified in Table 2 shall be applied to the lower end of the wire to keep the specimen in close contact with the cylinder.~~


The test is carried out on a cylinder with a diameter of 25 mm ± 1 mm. A straight piece of wire with the insulation removed at one end shall be connected to the upper terminal as shown in Figure 1 and wound once around the cylinder. A load as specified in Table 2.1 shall be applied to the lower end of the wire to keep the specimen in close contact with the cylinder.

The test voltage shall be applied according to 4.1 between the conductor of the wire and the cylinder. The test shall be carried out at room temperature.

Five specimens shall be tested. The five single values shall be reported.

Table 2.1 – Loads applied to the wire

Nominal conductor diameter mm		Load N
Over	Up to and including	
–	0,018	0,013
0,018	0,020	0,015
0,020	0,022	0,020
0,022	0,025	0,025
0,025	0,028	0,030
0,028	0,032	0,040
0,032	0,036	0,050
0,036	0,040	0,060
0,040	0,045	0,080
0,045	0,050	0,100
0,050	0,056	0,120
0,056	0,063	0,150
0,063	0,071	0,200
0,071	0,080	0,250
0,080	0,090	0,300
0,090	0,100	0,400

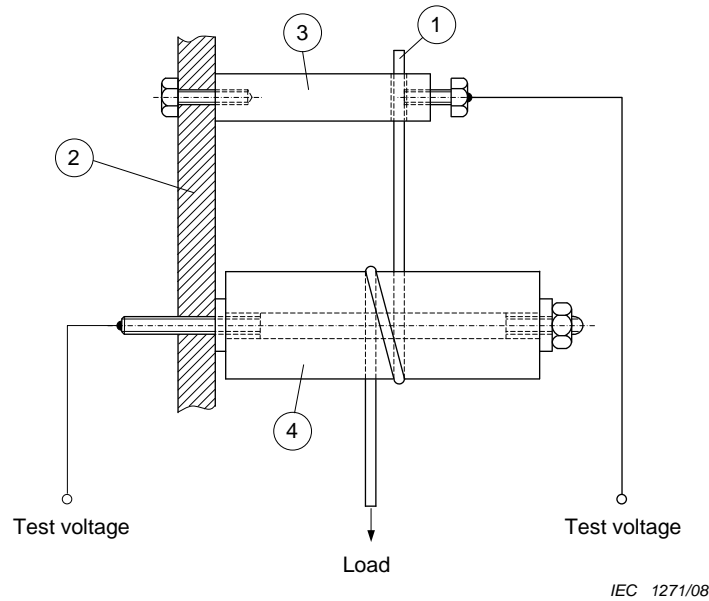

- 1 specimen
- 2 insulating material
- 3 upper terminal
- 4 cylinder

Figure 1 – Arrangement of cylinder and specimen for the breakdown voltage test

4.3.2 Grade of FIW 3 to FIW 9 with a nominal conductor diameter up to and including 1,600 mm

The test is carried out on a cylinder with a diameter as set out in Table 2.2.

A straight piece of wire with the insulation removed at one end shall be connected to the upper terminal as shown in Figure 1 and wound once around the cylinder. A load as specified in Table 2.2 shall be applied to the lower end of the wire to keep the specimen in close contact with the cylinder.

The test voltage shall be applied according to 4.1 between the conductor of the wire and the cylinder. The test shall be carried out at room temperature. Five specimens shall be tested. The five single values shall be reported.

Table 2.2 – Loads and diameters of test cylinders applied to wire

Nominal diameter mm	Nominal diameter mm	Load N	Diameter of test cylinder mm
Over	Up to and including		
-	0,040	0,080	25 ± 1
0,040	0,045	0,100	25 ± 1
0,045	0,050	0,130	25 ± 1
0,050	0,056	0,160	25 ± 1
0,056	0,063	0,200	25 ± 1
0,063	0,071	0,260	25 ± 1
0,071	0,080	0,330	25 ± 1
0,080	0,090	0,400	25 ± 1
0,090	0,100	0,500	25 ± 1
0,100	0,160	0,600	25 ± 1
0,160	0,250	0,850	25 ± 1
0,250	0,355	1,700	25 ± 1
0,355	0,500	3,400	25 ± 1
0,500	0,710	7,000	50 ± 2
0,710	1,060	13,500	50 ± 2
1,060	1,400	27,000	80 ± 3
1,400	1,600	54,000	80 ± 3

IEC 60851-5:2008

<https://standards.iteh.ai/catalog/standards/iec/db3ef4c5-ec44-4320-b327-baa3410f575b/iec-60851-5-2008>

4.4 Enamelled round wire with a nominal conductor diameter over 0,100 mm up to and including 2,500 mm, **grade 1 to grade 3**

4.4.1 Test at room temperature


A straight piece of wire, approximately 400 mm in length, with the insulation removed at both ends, shall be twisted back on itself for a distance of (125 ± 5) mm on the twisting device as shown in Figure 2. The ends of the wire shall be joined, and the load applied with the number of twists, as given in Table 3. The loop at the end of the twisted section shall be cut at two places to provide a maximum spacing between the cut ends. Any bending to ensure adequate separation between the two wire ends shall avoid sharp bends or damage to the coating.

The test voltage shall be applied according to 4.1 between the conductors of the wires.

Five specimens shall be tested. The five single values shall be reported.

Table 3 – Loads applied to the wire and number of twists

Nominal conductor diameter mm		Load N	Number of twists
Over	Up to and including		
0,100	0,250	0,85	33
0,250	0,355	1,70	23
0,355	0,500	3,40	16
0,500	0,710	7,00	12
0,710	1,060	13,50	8
1,060	1,400	27,00	6
1,400	2,000	54,00	4
2,000	2,500	108,00	3

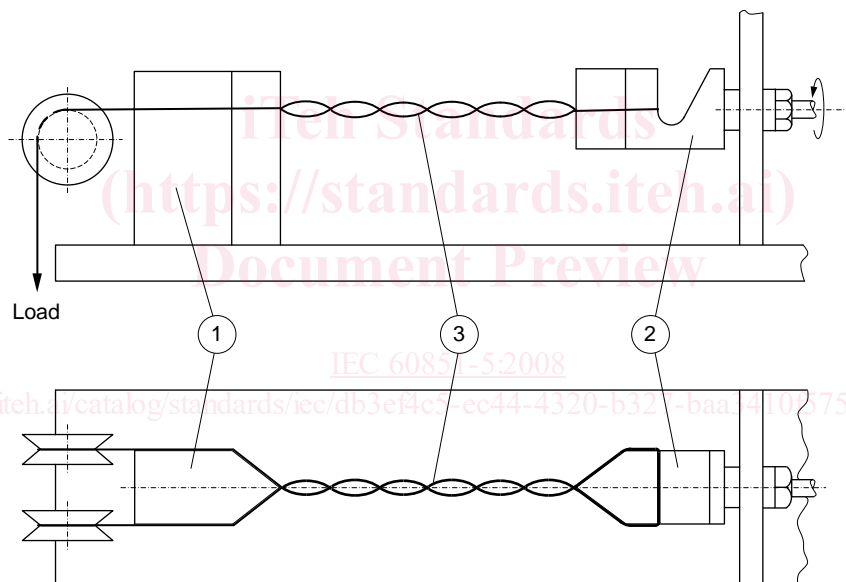

IEC 1272/08

- 1 spacer
- 2 rotary hook
- 3 specimen

Figure 2 – Device for twisting the specimen for breakdown voltage test

4.4.2 Test at elevated temperature

A specimen prepared according to 4.4.1 shall be placed in the oven preheated to the specified test temperature ± 3 °C. The test voltage shall be applied according to 4.1 between the conductors of the wires in not less than 15 min after placing the specimen in the oven. The test shall be completed within 30 min.

Five specimens shall be tested. The five single values shall be reported.