



Designation: A 934/A 934M – 00a

Standard Specification for Epoxy-Coated Prefabricated Steel Reinforcing Bars¹

This standard is issued under the fixed designation A 934/A 934M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reappraisal.

1. Scope

1.1 This specification covers deformed and plain steel reinforcing bars which prior to surface preparation are prefabricated and then coated with a protective fusion-bonded epoxy coating by electrostatic spray or other suitable method.

1.2 Prefabricated steel reinforcing bars coated with fusion-bonded epoxy formulations in accordance with this specification are not intended to be bent or rebent.

NOTE 1—Experience has shown epoxy-coated prefabricated steel reinforcing bars have limited capability to be successfully field bent or rebent (see 9.3.1). If the construction project requires epoxy-coated steel reinforcing bars that must be able to sustain field bending or rebending, the use of coated bars conforming to Specification A 775/A 775M should be considered.

1.3 Organic coatings other than epoxy may be used provided they meet the requirements of this specification.

1.4 Requirements for epoxy coatings are contained in Annex A1.

1.5 Guidelines for application process and product test procedures of epoxy coatings for steel reinforcing bars are presented in Appendix X1.

1.6 Guidelines for construction practices at the job-site for coated steel reinforcing bars are presented in Appendix X2.

1.7 This specification is applicable for orders in either SI (metric) units (as Specification A 934M) or inch-pound units [as Specification A 934].

1.8 The values stated in either SI or inch-pound units are to be regarded as standard. Within the text, the inch-pound units are shown in brackets. The values stated in the two systems are not exact equivalents: therefore, each system must be used independently of the other. Combining values from the systems may result in nonconformance with this specification.

1.9 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:

¹ This specification is under the jurisdiction of ASTM Committee A01 on Steel, Stainless Steel, and Related Alloys and is the direct responsibility of Subcommittee A01.05 on Steel Reinforcement.

Current edition approved Oct. 10, 2000. Published December 2000. Originally published as A 934/A 934M – 95. Last previous edition A 934/A 934M – 00.

A 615/A 615M Specification for Deformed and Plain Billet-Steel Bars for Concrete Reinforcement²

A 706/A 706M Specification for Low-Alloy Steel Deformed and Plain Bars for Concrete Reinforcement²

A 775/A 775M Specification for Epoxy-Coated Reinforcing Steel Bars²

A 944 Test Method for Comparing Bond Strength of Steel Reinforcing Bars to Concrete Using Beam-End Specimens²

A 996/A 996M Specification for Rail-Steel and Axle-Steel Deformed Bars for Concrete Reinforcement²

B 117 Practice for Operating Salt Spray (Fog) Testing Apparatus³

D 4060 Test Method for Abrasion Resistance of Organic Coatings by the Taber Abraser⁴

G 8 Test Methods for Cathodic Disbonding of Pipeline Coatings⁵

G 12 Test Method for Nondestructive Measurement of Film Thickness of Pipeline Coatings on Steel⁵

G 14 Test Method for Impact Resistance of Pipeline Coatings (Falling Weight Test)⁵

G 20 Test Method for Chemical Resistance of Pipeline Coatings⁵

G 42 Test Method for Cathodic Disbonding of Pipeline Coatings Subjected to Elevated Temperatures⁵

G 62 Test Methods for Holiday Detection in Pipeline Coatings⁵

2.2 *NACE International Standard:*⁶

RP 0287 Field Measurement of Surface Profile of Abrasive Blast Cleaned Steel Surfaces Using a Replica Tape

2.3 *Society for Protective Coatings Specifications:*⁷

SSPC-SP 10 Near-White Blast Cleaning

SSPC-VIS 1 Pictorial Surface Preparation Standards for Painting Steel Surfaces

2.4 *American Concrete Institute Specification:*⁸

ACI 301 Specifications for Structural Concrete

² Annual Book of ASTM Standards, Vol 01.04.

³ Annual Book of ASTM Standards, Vol 03.02.

⁴ Annual Book of ASTM Standards, Vol 06.01.

⁵ Annual Book of ASTM Standards, Vol 06.02.

⁶ Available from NACE International, 1440 South Creek, Houston, TX 77084.

⁷ Available from Society for Protective Coatings, 40 24th Street, Pittsburgh, PA 15222.

⁸ Available from American Concrete Institute, 38800 International Way, P.O. Box 9094, Farmington Hills, MI 48333-9094.

2.5 Concrete Reinforcing Steel Institute:⁹

“Voluntary Certification Program for Fusion-Bonded Epoxy Coating Applicator Plants”

3. Terminology

3.1 Definitions of Terms Specific to This Standard:

3.1.1 *conversion coating*—a preparation of the blast-cleaned metal surface prior to coating application that is designed to pretreat the metal to promote coating adhesion, reduce metal coating reactions, improve corrosion resistance, and increase blister resistance.

3.1.2 *disbonding*—loss of adhesion between the fusion-bonded epoxy coating and the steel reinforcing bar.

3.1.3 *fusion-bonded epoxy coating*—a product containing pigments, thermosetting epoxy resins, crosslinking agents, and other additives, which is applied in the form of a powder onto a clean, heated metallic substrate and fuses to form a continuous barrier coating.

3.1.4 *holiday*—a discontinuity in a coating that is not discernible to a person with normal or corrected vision.

3.1.5 *patching material*—a liquid two-part epoxy coating, formulated to be compatible with the fusion-bonded epoxy powder coating, used to repair damaged areas and cut ends.

3.1.6 *prefabricated bars*—steel reinforcing bars that are cut to specified lengths and bent to the required shapes prior to coating.

3.1.7 *wetting agent*—a material that lowers the surface tension of water allowing it to penetrate more effectively into small discontinuities in the coating, giving a more accurate indication of the holiday count.

4. Ordering Information

4.1 It shall be the responsibility of the purchaser to specify all requirements that are necessary for the coated steel reinforcing bars under this specification. Such requirements to be considered include, but are not limited to, the following:

4.1.1 Reinforcing bar specification and year of issue,

4.1.2 Quantity and bend types of bars,

4.1.3 Size and grade of bars,

4.1.4 Requirements for the powder coating and provision of test data (5.2),

4.1.5 Requirements for patching material (5.3),

4.1.6 Quantity of patching material,

4.1.7 Whether a report on tests performed on the coated steel reinforcing bars being furnished is required (15.1),

4.1.8 Method for temperature reduction of hot, freshly coated bars (unforced air cool down or forced air/water quench) (8.3).

NOTE 2—A typical ordering description is as follows: Deformed Grade 420 bars to ASTM A 615M—____; 6000 m, No. 19; cut to specified lengths and fabricated prior to coating; epoxy-coated to ASTM A 934M—____; including written certifications for the powder coating and coated bars and 1 L of patching material.

[Deformed Grade 60 bars to ASTM A 615—____; 20 000 ft, No. 6; cut to specified lengths and fabricated prior to coating; epoxy-coated to

ASTM A 934—____; including written certifications for the powder coating and coated bars and 1 qt. of patching material.

5. Materials

5.1 Steel reinforcing bars to be coated shall meet the requirements of one of the following specifications: A 615M, A 706M, or A 996M [A 615, A 706, or A 996] as specified by the purchaser and shall be free of contaminants such as oil, grease, or paint.

NOTE 3—Prior to coating, the steel reinforcing bars should be inspected for their suitability for coating. Bars with sharp edges on the deformations, rolled-in slivers, or other surface imperfections are difficult to coat properly. The coating will flow away from the sharp edges and may result in inadequate coating thickness at these points.

5.2 The powder coating shall meet the requirements of Annex A1. Upon request, the purchaser shall be provided with test data for review.

5.2.1 A written certification shall be furnished to the purchaser that properly identifies the lot designation of the powder coating used in the order, material quantity represented, date of manufacture, name and address of the powder coating manufacturer, and a statement that the supplied powder coating is the same composition as that qualified according to Annex A1 of this specification. The powder coating shall be used within the powder coating manufacturer’s written recommended shelf life.

5.2.2 If specified in the order, a representative 0.2-kg [8-oz] sample of the powder coating shall be supplied to the purchaser from each batch. The sample shall be packaged in an airtight container and identified by the batch designation.

5.2.3 The powder coating shall be maintained in a temperature-controlled environment following the written recommendations of the powder coating manufacturer until ready for use, at which point the powder coating shall be given sufficient time to reach approximate plant ambient temperature.

5.3 If specified in the order, patching material, compatible with the coating, inert in concrete, and recommended by the powder coating manufacturer, shall be supplied to the purchaser.

6. Prefabrication of Steel Reinforcing Bars

6.1 The steel reinforcing bars to be coated shall have been prefabricated in accordance with the purchaser’s requirements or project specifications prior to surface preparation.

NOTE 4—Drive rolls on shear beds and backup barrels on benders should be protected with a suitable covering to minimize crushing or creating rollover damage to the steel reinforcing bar deformations during the fabrication process.

7. Surface Preparation of Steel Reinforcing Bars

7.1 The surface of the steel reinforcing bars shall be cleaned by abrasive blast steel grit to near-white metal in accordance with SSPC-SP10.

7.1.1 The final surface condition shall be defined according to SSPC-VIS1.

7.1.2 Average blast profile roughness depth readings of 37 to 100 μm [1.5 to 4.0 mils], as determined by replica tape measurements using RP0287 or other methods acceptable to the purchaser, shall be considered suitable as an anchor pattern.

⁹ Available from Concrete Reinforcing Steel Institute, 933 N. Plum Grove Rd., Schaumburg, IL 60173.

NOTE 5—The use of a profilometer type surface measurement instrument that measures the peak count as well as the maximum profile depth is recommended.

7.2 A steel grit of Rockwell Hardness C50 or higher shall be used. A maximum of 5 % steel shot is allowable in the media.

NOTE 6—Recycled steel grit abrasive should be maintained so as to minimize contaminants such as oil, salt, and dust caused by the blasting operation.

7.3 Multidirectional, high-pressure dry air knives shall be used after blast cleaning to remove dust, grit, and other foreign matter from the steel surface. The air knives shall not deposit oil on the steel reinforcing bars.

NOTE 7—It is recommended that incoming steel reinforcing bars and blast media be checked for salt contamination prior to use. Blast media found to be salt contaminated should be rejected. Steel reinforcing bars found to be salt contaminated from exposure to deicing salts or salt spray should be cleaned by acid washing or other suitable methods to remove salt contaminants from the surface prior to blast cleaning.

7.4 It shall be permissible for the manufacturer to use a chemical wash or conversion of the steel reinforcing bar surface, or both, to enhance coating adhesion. This pretreatment shall be applied after abrasive cleaning and before coating, in accordance with the written application instructions specified by the pretreatment manufacturer.

8. Coating Application

8.1 Cleaned, uncoated steel reinforcing bars shall be handled by personnel wearing clean gloves to prevent contamination of the steel surface.

8.2 If pretreatment is used in the preparation of the surface the powder coating shall be applied to the cleaned and pretreated steel reinforcing bar surface as soon as possible after surface treatments have been completed, and before visible oxidation of the surface occurs as discernible to a person with normal or corrected vision. In no case shall application of the coating be delayed more than 3 h after cleaning.

8.3 The fusion-bonded epoxy powder coating shall be applied in accordance with the written recommendations of the manufacturer of the powder coating for initial steel surface temperature range and post application cure requirements. The temperature of the surface immediately prior to coating shall be measured using infrared guns or temperature-indicating crayons at least once every 30 min during continuous operations.

NOTE 8—The use of infrared and temperature-indicating crayon measurement of the steel reinforcing bars is recommended.

8.4 The powder coating shall be applied by electrostatic spray or other suitable method.

9. Requirements for Coated Steel Reinforcing Bars

9.1 Coating Thickness:

9.1.1 The coating thickness after curing shall be 175 to 300 μm [7 to 12 mils].

9.1.2 For acceptance purposes, at least 90 % of all recorded coating thickness measurements shall be within the specified range. Thickness measurements below 125 μm [5 mils] shall be considered cause for rejection. The upper thickness limit does not apply to repaired areas of damaged coating.

9.1.3 A single recorded steel reinforcing bar coating thick-

ness measurement is the average of three individual readings obtained between three consecutive deformations. A minimum of five recorded measurements shall be obtained approximately evenly spaced along each side of the test bar (a minimum of ten recorded measurements per bar).

9.1.4 Measurements shall be made in accordance with Test Method G 12 following the instructions for calibration and use recommended by the thickness gage manufacturer. Pull-off or fixed probe gages shall be used. Pencil-type pull-off gages that require the operator to observe the readings at the instant the magnet is pulled from the surface shall not be used.

9.1.5 The coating thickness shall be measured on the body of a straight length of coated steel reinforcing bar between the deformations or ribs.

9.2 Coating Continuity:

9.2.1 Holiday checks to determine the acceptability of the coated steel reinforcing bars prior to shipment shall be made at the manufacturer's plant with a hand-held 67.5-V, 80 000- Ω , wet-sponge-type dc holiday detector.

9.2.2 There shall not be on average more than three holidays per metre [one holiday per linear foot] on the coated steel reinforcing bars. For coated bars less than 0.3 m [1 ft] in length, the maximum shall be one holiday.

9.2.3 A wetting agent shall be used in accordance with Test Methods G 62 in the inspection for holidays on the coated steel reinforcing bars.

9.2.4 The coated steel reinforcing bars shall be inspected at a maximum rate of 0.05 m/s [0.2 ft/s], wiping one side of the coated bar and then the other with the wetted sponge or an equivalent method.

NOTE 9—Care should be taken that contact of the sponge along the entire steel surface being tested is maintained in order to obtain an accurate holiday count.

9.3 Coating Flexibility:

9.3.1 Coating flexibility shall be evaluated by bending production-coated steel reinforcing bars around a mandrel eight times the nominal diameter (d) of the bar at a uniform rate and within 5 s. The exception to the $8d$ mandrel requirement shall be Nos. 43 and 57 [Nos. 14 and 18] bars. A 430-mm [17-in.] mandrel (9.71*d*) shall be used when evaluating No. 43 [No. 14] bar, and a 580-mm [23-in.] mandrel (10.22*d*) shall be used with No. 57 [No. 18] bar. For Nos. 10 to 16 [Nos. 3 to 5] coated steel reinforcing bars, the bend angle after rebound shall be 9°. For No. 19 to 57 [Nos. 6 to 18] coated steel reinforcing bars, the bend angle after rebound shall be 6°. The two longitudinal deformations shall be placed in a plane perpendicular to the mandrel radius. The temperature of the test specimens shall be between 20 and 30°C [68 and 86°F].

9.3.2 No cracking or disbonding of the coating shall be discernible to a person with normal or corrected vision on the outside radius of the bent bar. Except as specified in 11.1, evidence of cracking or disbonding of the coating shall be considered cause for rejection of the coated steel reinforcing bars represented by the bend test sample.

9.4 Coating Adhesion:

9.4.1 Coating adhesion shall be evaluated by cathodic disbondment testing of production-coated steel reinforcing bars. Test Method G 42 shall be followed except, (*I*) the

cathode shall be a 200-mm [8-in.] long coated steel reinforcing bar; (2) the anode shall be a 150-mm [6-in.] long solid platinum electrode (1.6-mm [0.06-in.] nominal diameter) or platinized wire (3-mm [0.12-in.] nominal diameter); (3) a calomel reference electrode shall be used; (4) the electrolyte solution shall be 3 % NaCl by mass dissolved in distilled water; (5) the electrolyte solution temperature shall be $65 \pm 2^\circ\text{C}$ [$150 \pm 3.6^\circ\text{F}$]; (6) the drilled coating defect shall be 3 mm [0.12 in.] in diameter; (7) a potential of -3 V measured against the calomel reference electrode shall be applied and a 10-ohm shunt resistor used, and; (8) the test duration shall be 24 h.

9.4.2 Following the 24-h exposure and prior to coating evaluation, the coated steel reinforcing bar shall be given a minimum of a 1-h cooling-off period to allow the bar to reach 20 to 30°C [68 to 86°F].

9.4.3 Measurements of the cathodic disbondment radius shall be obtained at 0° , 90° , 180° , and 270° . The average of the four values shall not exceed 6 mm [0.24 in.] when measured from the edge of the intentional coating defect.

9.4.4 Approximately even numbers of straight and bent sections of coated steel reinforcing bars shall be evaluated (approximately half of these tests shall be made on the inside radius and half on the outside radius on the bent bar sections).

10. Frequency of Tests

10.1 Tests for coating thickness shall be made on a minimum of two bars of straight section and two bars of bent section of each size from each production hour.

10.2 Tests for coating continuity shall be conducted on a minimum of two bars of each size from each production hour.

10.3 Tests for coating flexibility shall be made on a minimum of one bar of each bar size from each four production hours.

10.4 Tests for coating adhesion shall be made on a minimum of two bars from each 8-h production shift: one straight bar section and one bent bar section. If there are no bent bars being coated during the production period, a second straight bar section shall be substituted for the test.

11. Retests

11.1 If any test specimen for coating thickness, continuity, flexibility, or adhesion fails to meet the specified requirements, the bar from which the test specimen was taken shall be rejected and two further coated steel reinforcing bars from the same lot shall be subjected to the test or tests in which the original bar failed. If both additional coated steel reinforcing bars pass the retest, the lot from which they were taken shall be deemed to meet the requirements of this specification. If either of them fails, the lot shall be deemed not to comply with this specification.

11.2 If the lot does not comply with this specification, two coated steel reinforcing bars shall be selected from the lot immediately preceding and immediately following the non-compliant lot and subjected to the test or tests in which the original bars failed. If all bars pass the retests, then the lots shall be deemed to meet the requirements of this specification. If any bar fails a retest, the lot from which it originated shall be deemed not to comply with this specification.

11.3 In the case of a second noncompliant lot, the untested

lot immediately next to it, which may be preceding or following, shall be subjected to retest. This procedure shall be repeated until a compliant lot is tested.

NOTE 10—In the use of the Retest provision of this specification, a “lot” is defined as the coated steel reinforcing bars that are represented by the sample which has been tested. A certain number of coated steel reinforcing bars will have been produced since the last acceptance test was performed and accepted. The steel reinforcing bars that have been coated since that last test should be divided into four equal time period groups according to when they were produced. Each lot should then be further defined as those coated steel reinforcing bars that have been produced in a given time period since the last accepted test.

12. Permissible Amount of Damaged Coating and Repair of Damaged Coating

12.1 Damaged coating discernible to a person with normal or corrected vision shall be repaired with patching material meeting the requirements of 5.3 in accordance with the written recommendations of the patching material manufacturer. Any rust shall be removed by suitable means before application of the patching material.

12.2 The maximum amount of repaired damaged coating shall not exceed 1 % of the total surface area in each 0.3-m [1-ft] length.

NOTE 11—If the amount of repaired damaged coating in any 0.3-m [1-ft] length of a coated bar exceeds 1 %, that section should be removed from the coated steel reinforcing bar and discarded. In patching damaged coating, care should be taken not to apply the patching material over an excessive area of the intact coating during the repair process. Too large an area of thick patching material, especially on smaller-size reinforcing bars, is likely to cause a reduction in bond strength of the bars to concrete.

12.3 Repaired areas shall have a minimum thickness of 250 μm [10 mils].

13. Inspection

13.1 The inspector representing the owner/purchaser shall have free entry at all times, while work on the contract of the purchaser is being performed, to the parts of the manufacturer's coating line that concern the manufacture of the coated steel reinforcing bar ordered. The manufacturer shall provide access to all reasonable facilities to satisfy the inspector that the coated steel reinforcing bar is being furnished in accordance with this specification. All tests and inspections shall be made at the place of manufacture prior to shipment unless otherwise specified, and shall be conducted so as not to interfere unnecessarily with the operation of the coating line. At a mutually agreed upon frequency, the purchaser or the purchaser's representative shall be permitted to take lengths of coated steel reinforcing bar from the production run for testing.

14. Rejection

14.1 Coated steel reinforcing bars represented by test specimens that do not meet the requirements of this specification shall be rejected and marked with a contrasting color paint or other suitable identification. At the manufacturer's option, the affected lot shall be replaced or, alternately, stripped of coating, recleaned, recoated, and resubmitted for acceptance testing in accordance with the requirements of this specification.

NOTE 12—If the coating is not to be stripped from the rejected steel

reinforcing bars, the bars should be scrapped.

15. Certification

15.1 The purchaser shall be furnished, at the time of shipment, written certification that samples representing each lot of coated steel reinforcing bars have been either tested or inspected as directed in this specification and the requirements have been met. When specified in the purchase order or contract, a report of the test results shall be furnished.

16. Handling and Identification

16.1 Coated steel reinforcing bars shall be transported and handled with care. All systems for handling coated steel reinforcing bars shall have padded contact areas. All bundling bands shall be padded, or suitable banding used to prevent damage to the coating. All bundles of coated steel reinforcing bars shall be lifted with a strong back, spreader bar, multiple supports, or a platform bridge to prevent bar-to-bar abrasion from sags in the bundles. The coated steel reinforcing bars or bundles shall not be dropped or dragged.

16.2 Smaller pieces of coated steel reinforcing bars, such as stirrups and ties, shall be packaged in such a way as to minimize damage to the coating during shipping and handling.

16.3 If circumstances require storing coated steel reinforcing bars outdoors for more than two months, protective storage measures shall be implemented to protect the material from sunlight, salt spray, and weather exposure. If the manufacturer

stores coated steel reinforcing bars outdoors without cover, the date on which the coated bars are placed outdoor shall be recorded on the identification tag of the bundled steel. Coated steel reinforcing bars stored in severe corrosive environments will require protection sooner. Coated steel reinforcing bars or bundles shall be covered with opaque polyethylene sheeting or other suitable opaque protective material. For stacked bundles, the protective covering shall be draped around the perimeter of the stack. The covering shall be secured adequately, and allow for air circulation around the bars to minimize condensation under the covering.

16.4 All coated steel reinforcing bars or bundles shall be stored off the ground on protective cribbing.

16.5 The identification of all steel reinforcing bars shall be maintained throughout the fabrication and coating process to the point of shipment.

16.6 Quality assurance codes that certify compliance to this specification shall be placed on all identification tags of the coated steel reinforcing bars or bundles. These codes shall include references to the date of fabrication, the date of coating, the powder coating lot designation and the quality assurance testing performed.

17. Keywords

17.1 concrete reinforcement; corrosion resistance; epoxy coating; prefabrication; steel reinforcing bars

(<https://standards.iteh.ai>)
Document Preview

ANNEX

(Mandatory Information)

A1. REQUIREMENTS FOR FUSION-BONDED EPOXY POWDER COATINGS FOR PREFABRICATED STEEL REINFORCING BARS

A1.1 Epoxy Powder Coatings

A1.1.1 This annex covers qualification requirements for fusion-bonded epoxy powder coatings for protecting steel reinforcing bars from corrosion.

A1.1.2 Other organic coatings may be used provided they meet the requirements of this specification.

A1.2 Test Materials

A1.2.1 A 0.5-kg [1-lb] sample of the powder coating with its generic description and its fingerprint (including the method such as infrared spectroscopy or thermal analysis) shall be submitted to the testing agency. The fingerprint and generic description shall become an integral part of the qualification test report.

A1.2.2 A sample of patching material shall be submitted to the testing agency. The product name and a description of the patching material shall be given in the test report.

A1.2.3 Test Specimens:

A1.2.3.1 The following specimens shall be submitted as a minimum for testing:

(1) Fourteen 1.2-m [4-ft] long No. 19 [No. 6], Grade 420 [Grade 60] deformed steel reinforcing bars, with a coating

thickness of 175 to 300 μm [7 to 12 mils].

(2) Six uncoated and uncleaned No. 19 [No. 6] steel reinforcing bars, 1.2 m [4 ft] long, from the same lot of steel as the coated bars.

(3) Four 100 by 100 by 1.3-mm [4 by 4 by 0.05-in.] thick steel plates with center holes for Taber abrasers with a coating thickness of $250 \pm 50 \mu\text{m}$ [10 ± 2 mils].

(4) Four 100 by 100-mm [4 by 4-in.] free films of coating material with a thickness of 175 to 225 μm [7 to 9 mils].

(5) Twelve coated No. 19 [No. 6] steel reinforcing bars, 0.25-m [10-in.] long, with a coating thickness of 175 to 300 μm [7 to 12 mils]. The coated bars shall have their ends sealed with a minimum of 250 μm [10 mils] of patching material.

(6) Ten coated No. 19 [No. 6] steel reinforcing bars, 0.20-m [8-in.] long, with a coating thickness of 175 to 300 μm [7 to 12 mils]. The coated bars shall have their ends sealed with a minimum of 250 μm [10 mils] of patching material.

A1.2.3.2 Steel reinforcing bars with a nominal diameter within $\pm 1 \text{ mm}$ [0.04 in.] of No. 19 [No. 6] bars shall be acceptable for qualification testing.

A1.2.3.3 The coating on the bars and films tested shall be free of holes, voids, contamination, cracks, and damaged areas.

The coated bars shall be checked for holidays using a 67.5-V, 80 000- Ω , wet-sponge-type dc holiday detector in accordance with Test Method G 62. The total number of coating holidays found on the bar specimens tested shall be reported.

A1.2.3.4 The powder coating manufacturer shall specify the method and grade of metal surface preparation and the coating application procedures for the test specimens and for contract production of coated steel reinforcing bars. These procedures shall be listed in the test report. Note that production-coated steel reinforcing bars shall be required to be manufactured in the same manner as the qualification bars. Therefore, it is necessary that the qualification coated steel reinforcing bars be prepared in the same manner proposed for production. Variations in the critical preparation, thermal treatment, coating procedures and cure methods known to be allowable without a compromise in quality shall also be detailed in the qualification report.

A1.3 Coating Requirements

A1.3.1 *Chemical Resistance*—The chemical resistance of the coating shall be evaluated in accordance with Test Method G 20 by immersing coated steel reinforcing bars in each of the following: distilled water, a 3-M aqueous solution of CaCl_2 , a 3-M aqueous solution of NaOH , and a solution saturated with $\text{Ca}(\text{OH})_2$. Specimens without holidays and specimens with an intentional 6-mm [0.25-in.] diameter hole drilled through the coating shall be tested. The temperature of the test solutions shall be $24 \pm 2^\circ\text{C}$ [$75 \pm 3.6^\circ\text{F}$]. The immersion shall last 45 days. The coating must not blister, soften, lose bond, or develop holidays during this period. The coating surrounding the intentionally made hole shall exhibit no undercutting during the 45-day period.

A1.3.2 *Cathodic Disbondment*—The effects of electrical and electrochemical stresses on the bond of the coating to steel and on the film integrity shall be assessed in elevated and

Test Bar Preparation

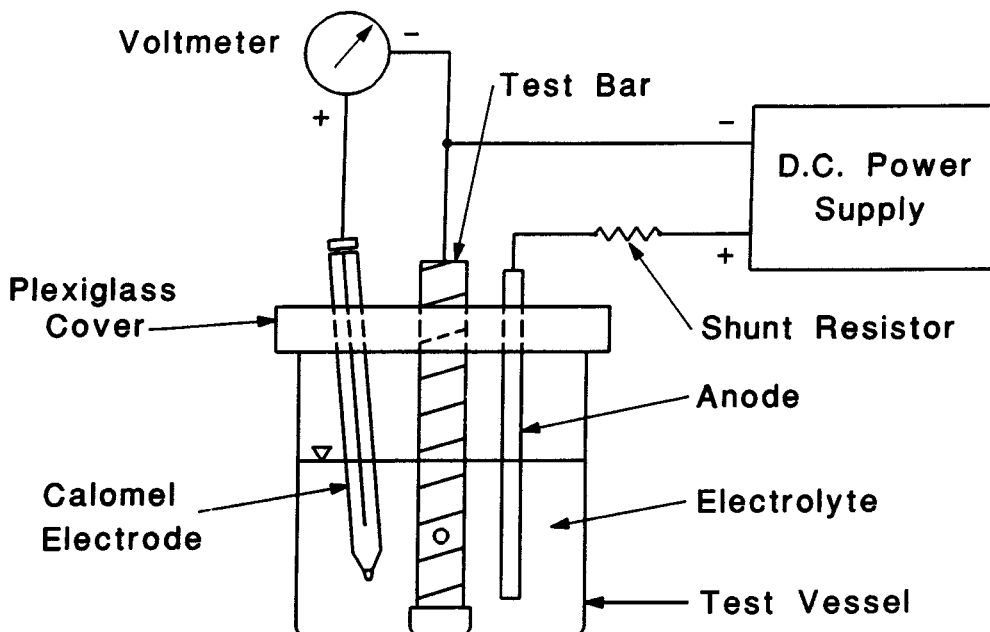
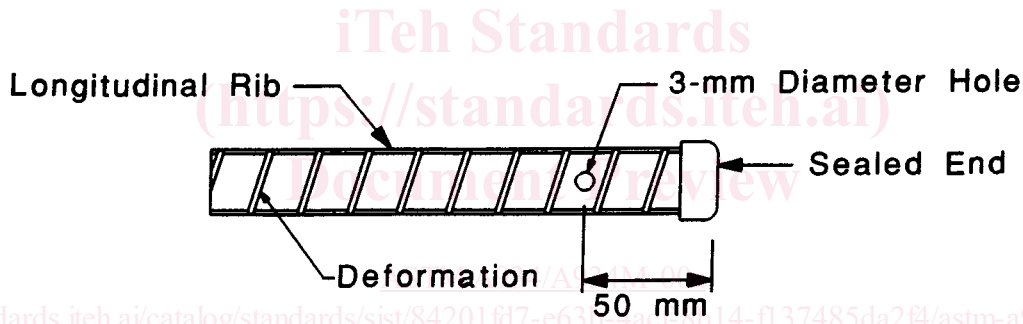


FIG. A1.1 Cathodic Disbondment Test Equipment Configuration