
**Plastics piping systems — Glass-reinforced
thermosetting plastics (GRP) pipes —
Determination of longitudinal tensile
properties**

*Systèmes de canalisations en plastiques — Tubes en plastiques
thermodurcissables renforcés de verre (PRV) — Détermination des
propriétés en traction longitudinale*
(standards.iteh.ai)

ISO 8513:2000

<https://standards.iteh.ai/catalog/standards/sist/3c282f29-7b76-4ad9-b167-391d82deb453/iso-8513-2000>



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 8513:2000

<https://standards.iteh.ai/catalog/standards/sist/3c282f29-7b76-4ad9-b167-391d82deb453/iso-8513-2000>

© ISO 2000

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.ch
Web www.iso.ch

Printed in Switzerland

Contents

	Page
1 Scope	1
2 Terms and definitions	1
3 Principle	2
4 Apparatus	2
5 Test pieces	4
6 Conditioning	7
7 Test temperature	7
8 Procedure (methods A, B and C)	7
9 Calculation	8
10 Test report	11

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 8513:2000](#)

<https://standards.iteh.ai/catalog/standards/sist/3c282f29-7b76-4ad9-b167-391d82deb453/iso-8513-2000>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this International Standard may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

International Standard ISO 8513 was prepared by Technical Committee ISO/TC 138, *Plastics pipes, fittings and valves for the transport of fluids*, Subcommittee SC 6, *Reinforced plastics pipes and fittings for all applications*.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 8513:2000](https://standards.iteh.ai/catalog/standards/sist/3c282f29-7b76-4ad9-b167-391d82deb453/iso-8513-2000)

<https://standards.iteh.ai/catalog/standards/sist/3c282f29-7b76-4ad9-b167-391d82deb453/iso-8513-2000>

Plastics piping systems — Glass-reinforced thermosetting plastics (GRP) pipes — Determination of longitudinal tensile properties

1 Scope

This International Standard specifies three test methods for determining the longitudinal tensile properties of pipes of glass-reinforced thermosetting plastics (GRP). The properties which can be determined are:

- the longitudinal tensile strength
- the percentage ultimate elongation
- the longitudinal modulus of elasticity.

Method A uses for the test piece(s) a longitudinal strip cut from a pipe.

Method B uses a specified length of the full cross-section of the pipe.

Method C uses a notched plate cut from a pipe wall section.

Method A is applicable to pipes with a nominal size of DN 50 or greater with circumferentially wound filaments, with or without chopped glass and/or woven rovings and/or fillers, and to centrifugally cast pipes. It is applicable to those pipes with helically wound filaments with a nominal size of DN 200 or greater.

Method B is applicable to all types of GRP pipe. It is usually used for pipes with a nominal size up to and including DN 150.

Method C is primarily intended for use for helically wound pipes with a winding angle other than approximately 90°. This method may also be used for other types of pipe.

Results from one method are not necessarily equal to the results derived from any of the alternative methods. However, all methods have equal validity.

2 Terms and definitions

For the purposes of this International Standard, the following terms and definitions apply.

2.1

initial longitudinal tensile strength

σ_{LA}^* , σ_{LB}^* , σ_{LC}^*

maximum tensile force in the longitudinal direction per unit mean circumference (see 2.6) at failure (the subscripts A, B and C denote the method of test used)

NOTE It is expressed in newtons per millimetre of circumference (N/mm).

2.2

ultimate longitudinal tensile stress

σ_L

maximum longitudinal tensile force per unit cross-sectional area at failure

NOTE It is expressed in newtons per square millimetre (N/mm).

2.3 ultimate elongation

ε_L
elongation coincident with the ultimate longitudinal tensile stress (see 2.2)

NOTE It is expressed as a percentage of an initial gauge length or free length of a test piece.

2.4 longitudinal modulus of elasticity

E_L
longitudinal tensile force per unit cross-sectional area divided by the strain

NOTE It is expressed in newtons per square millimetre (N/mm²).

2.5 mean diameter

d_m
diameter of the circle corresponding with the middle of the pipe wall cross-section

NOTE 1 It is given by any of the following:

- the average of the external diameter of the pipe minus the average of the wall thickness;
- the external circumference of the pipe divided by π ($\pi \approx 3,141\ 6$) minus the average of the wall thickness;
- the average of the internal diameter of the pipe plus the average of the wall thickness.

NOTE 2 It is expressed in millimetres.

2.6 mean circumference

circumference corresponding to the mean diameter (see 2.5) multiplied by π ($\pi \approx 3,141\ 6$)

NOTE It is expressed in millimetres.

ITeH STANDARD PREVIEW
(standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/sist/3c282f29-7b76-4ad9-b167-391d82deb453/iso-8513-2000>

3 Principle

Test pieces comprising either strips cut longitudinally from a pipe wall segment (method A), a specified length of pipe (method B) or a notched plate cut from a pipe wall section (method C) are subjected to extension in the longitudinal direction at a constant speed such that fracture occurs within a specified time.

The tensile properties are determined using the initial dimensions of the test piece, the tensile force and the elongation.

NOTE It is assumed that the following test parameters are set by the standard making reference to this International Standard:

- the methods to be used, i.e. method A, method B or method C;
- the number of test pieces (see 5.5);
- if applicable, the requirements for conditioning, e.g. temperature, humidity, time and associated tolerances (see clause 6);
- the test temperature and its tolerance (see clause 7);
- the properties to be measured (see clause 8).

4 Apparatus


4.1 Tensile-testing machine, of the constant rate of cross-head movement type, incorporating the following features:

- a fixed part, fitted with a grip to hold one end of the test piece without permitting any longitudinal movement thereof, and a moveable part, incorporating a grip to hold the other end of the test piece during extension (the

fixed and moving parts and their associated grips (see 4.2) shall enable the test piece to be aligned when a force is applied so that its longitudinal axis coincides with the direction of this force);

- b) a drive mechanism, capable of imparting a constant speed of 1 mm/min to the moving part;
- c) a force indicator, capable of measuring the force applied to a test piece which is held in the grips (the mechanism shall be free from significant inertia lag at the necessary speed of testing and shall indicate or record force, or consequent stress, with an accuracy of within $\pm 1\%$ of the value to be measured).

4.2 Grips, for holding the test piece. Each of the two the grips shall be capable of holding one end of the test piece without slip or crushing to an extent that will affect the results obtained. Grips which tighten automatically may be suitable. Typical grips for a pipe section test piece (see 5.3) are shown in Figure 1.

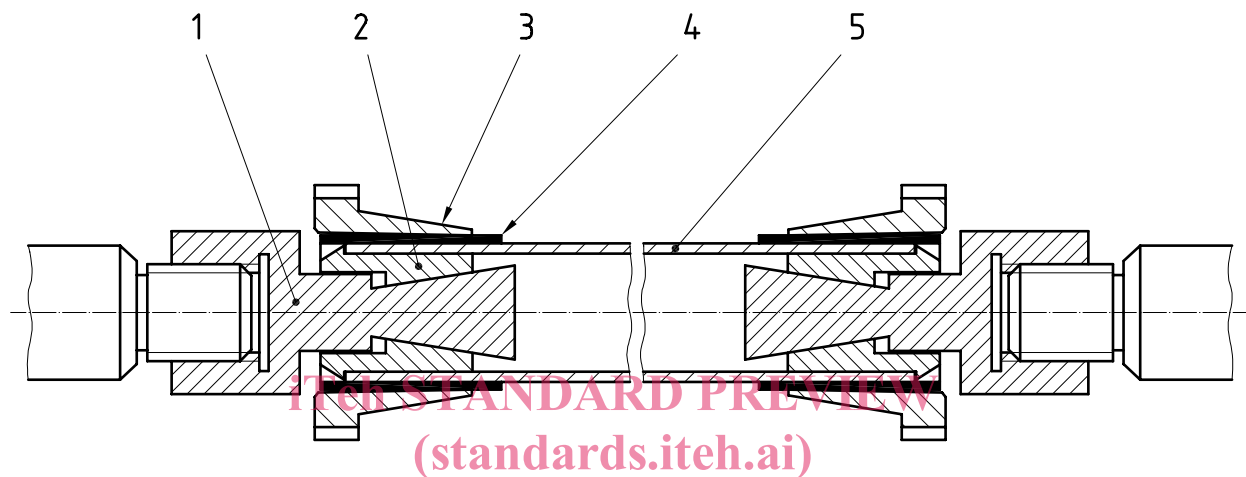

Key

- 1 Mandrel
- 2 Segmented grips
- 3 Sleeve
- 4 Reinforcing band
- 5 Test piece

ISO 8513:2000

<https://standards.iteh.ai/catalog/standards/sist/3c282f29-7b76-4ad9-b167-391d82deb453/iso-8513-2000>

Figure 1 — Typical grips for a pipe section test piece (method B)

4.3 Dimension measurement devices, capable of measuring the necessary dimensions of the test piece (e.g. length, width, wall thickness) to an accuracy of half the accuracy required in clause 8 for measurements, e.g. a measuring accuracy $\pm 0,1$ mm requires a device accuracy of $\pm 0,05$ mm.

4.4 Extension indicator, if required, capable of measuring the distance between two fixed points located within the gauge length of the test piece so that the elongation in the gauge section can be determined. The device shall be free of any significant inertia lag at the relevant speed of testing (see 8.4) and shall be accurate to within $\pm 1\%$ of the indicated value.

If strain gauges are used, these shall be mounted on both sides of the test piece, on the centreline, and the average value shall be used for the calculation of the modulus and the percentage elongation.

NOTE 1 An extension indicator is only necessary if the referring standard specifies that the elongation and/or any modulus of elasticity of the test piece is to be determined.

NOTE 2 It is desirable, but not essential, that this instrument automatically records this distance (or any change in it) as a function of the load on the test piece or of the elapsed time from the start of the test, or both. If only the latter is obtained, load/time data should be recorded as well.

5 Test pieces

5.1 General

The test piece shall be a strip or dumb-bell conforming to 5.2, or a pipe section conforming to 5.3, or a plate conforming to 5.4.

The test piece shall be obtained in such a way that it is not damaged.

5.2 Strip test piece (method A)

5.2.1 Shape

Each test piece shall be a strip cut in the longitudinal direction of the pipe and either shaped to the dimensions of the applicable dumb-bell as shown in Figure 2 or a parallel-sided (rectangular plan) test piece as shown in Figure 3.

NOTE The test pieces may be cut from a ring previously used for the determination of the initial specific ring stiffness.

5.2.2 Dimensions

5.2.2.1 Length

The length, l , of the test piece shall be (300 ± 15) mm (see Figure 2 and Figure 3).

5.2.2.2 Shaped strip

The gauge length, l_G , of the test piece shall be as follows (see Figure 2):

$$100 \text{ mm} \leq l_G \leq 150 \text{ mm}$$

The radius, R , shall be machined to conform to the following limits (see Figure 2):

$$50 \text{ mm} \leq R \leq 70 \text{ mm}$$

The width, b_G , of the test piece within the gauge length, shall conform to the following requirements, as applicable (see Figure 2 and 5.2.1):

$$b_G = (10 \pm 1) \text{ mm for } DN \leq 150;$$

$$b_G = (25 \pm 1) \text{ mm for } DN > 150.$$

The total width, b , of the test piece shall conform to the following requirements (see Figure 2):

$$b = (18 \pm 2) \text{ mm for } DN \leq 150;$$


$$b = (40 \pm 2) \text{ mm for } DN > 150;$$

5.2.2.3 Parallel-sided strip

The width, b_G , of the test piece shall be as follows (see Figure 3):

$$b_G = (10 \pm 1) \text{ mm for } DN \leq 150;$$

$$b_G = (25 \pm 1) \text{ mm for } DN > 150.$$

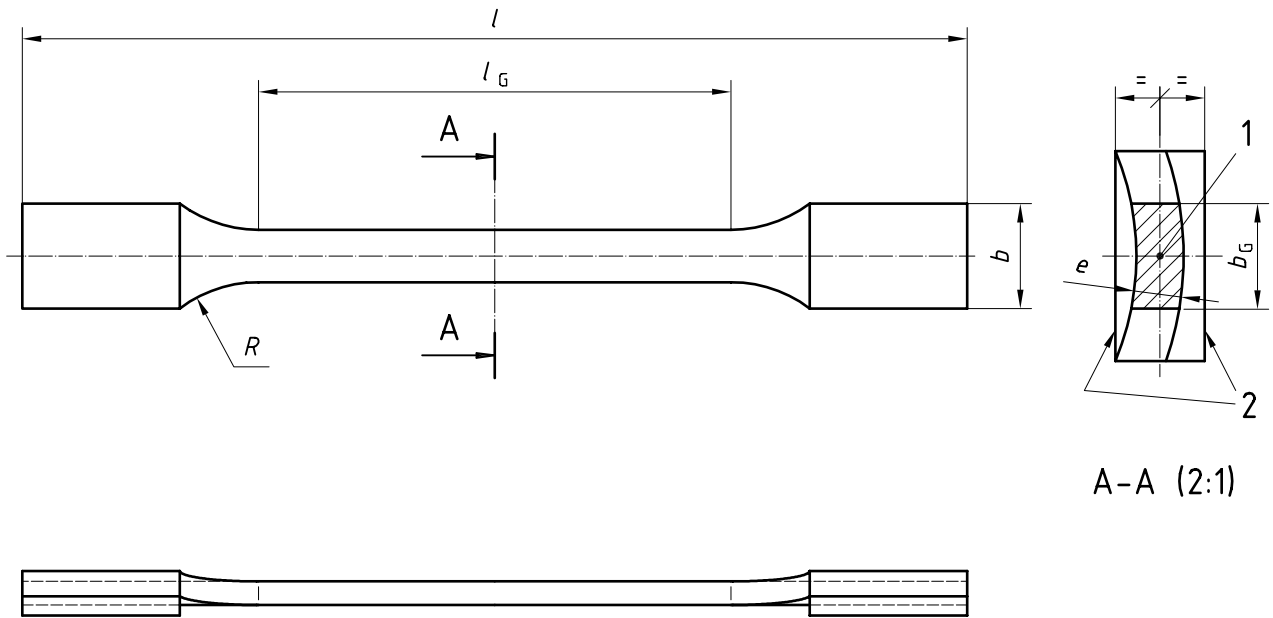


Key

- 1 Centroid of gauge length cross-section
- 2 Ends built up with plain or reinforced thermoset resin and trimmed flat and parallel, if required
- e* Wall thickness

(standards.iteh.ai)
Figure 2 — Shaped test piece dimensions (method A)

ISO 8513:2000

<https://standards.iteh.ai/catalog/standards/sist/3c282f29-7b76-4ad9-b167-391d82deb453/iso-8513-2000>

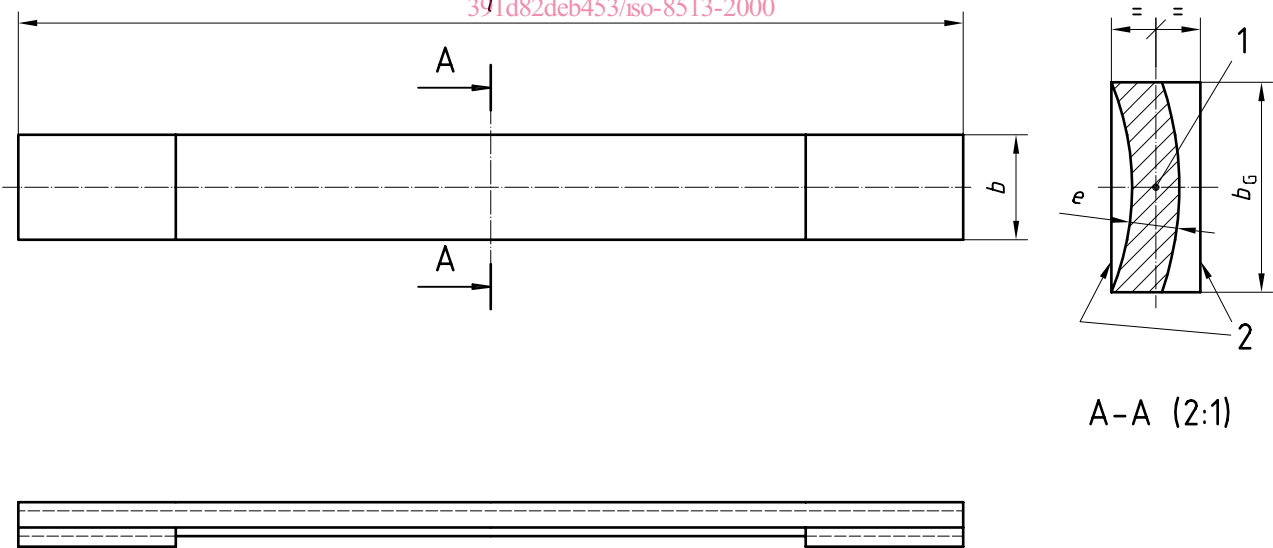

Key

- 1 Centroid of gauge length cross-section
- 2 Ends built up with plain or reinforced thermoset resin and trimmed flat and parallel, if required
- e* Wall thickness

Figure 3 — Parallel-sided strip test piece dimensions (method A)