



## Designation: C 198 – 91 (Reapproved 1996)<sup>ε1</sup>

AMERICAN SOCIETY FOR TESTING AND MATERIALS  
100 Barr Harbor Dr., West Conshohocken, PA 19428  
Reprinted from the Annual Book of ASTM Standards. Copyright ASTM

# Standard Test Method for Cold Bonding Strength of Refractory Mortar<sup>1</sup>

This standard is issued under the fixed designation C 198; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

<sup>ε1</sup> NOTE—Keywords were added editorially in September 1996.

## 1. Scope

1.1 This test method covers the determination of the bonding strength of air-setting refractory mortar by determining the flexural strength (modulus of rupture) at room temperature of oven-dried brick-mortar joints.

1.2 The values stated in inch-pound units are to be regarded as the standard. The values stated in SI units are for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

### 2.1 ASTM Standards:

- C 78 Test Method for Flexural Strength of Concrete (Using Simple Beam With Third-Point Loading)<sup>2</sup>
- C 133 Test Methods for Cold Crushing Strength and Modulus of Rupture of Refractories<sup>3</sup>
- C 651 Test Method for Flexural Strength of Manufactured Carbon and Graphite Articles Using Four-Point Loading at Room Temperature<sup>3</sup>
- E 4 Practices for Force Verification of Testing Machines<sup>4</sup>

## 3. Significance and Use

3.1 The data developed by this test method show the bonding strength and intrinsic strength of different qualities of air-setting mortar. The procedures described in this test method measure the bonding strength and intrinsic strength of air-setting mortars when used with specific brands or lots of refractory brick.

3.2 Note that it is possible to obtain results with these methods for brick and mortar combinations which are incompatible for use at high operating temperatures. The user must determine this compatibility. Only brick and mortar combina-

tions known or intended to be compatible for a particular use should be tested.

3.3 Properties of the brick, including its strength, apparent porosity, and pore size distribution, can affect the measurement of both the bonding strength of the brick-mortar composite and the intrinsic strength of the mortar. The average modulus of rupture of the test brick, as determined by Test Method C 133, should exceed that expected for the mortar being tested. The testing of specific brands or lots of brick and mortar is preferred.

3.4 Three modes of failure are available: the break may occur within the brick itself, at the brick-mortar interface, or within the mortar itself. The latter provides a practical measurement of the strength of the mortar itself and is the predominant mode of failure with the four-point flexure test described. The three-point flexure test measures the failure strength of the brick-mortar composite. Failure within the brick itself suggests that either the particular brick contained a serious flaw, or that the mortar joint strength is of the same magnitude or greater than that of the refractory brick. The mode of failure should always be reported in the final report.

3.5 A ruggedness test for this test method<sup>5</sup> performed in 1985 found the following variables to be rugged: specimen size (2.5 to 3.0 in.), mortared surface (cut versus uncut), joint thickness ( $\frac{1}{16}$  to  $\frac{1}{8}$  in.), pulling of rods (fast versus slow), the loading rate (500 to 1000 lbf/min), the method of load application (3- versus 4-point), and the operator.

3.6 The cold bonding strengths of refractory mortars obtained by this test method are suitable for use in research and development, quality control, and for establishing and evaluating compliance with specifications between producers and consumers.

## 4. Apparatus

4.1 *Brick*—At least five 9 by 4¼ by 2½-in. (230 by 114 by 65-mm) straight brick having plane surfaces and true rectangular shape and an average modulus of rupture higher than that expected from the mortar under test, when determined in accordance with Test Methods C 133, compose a sample.

4.2 *Spacing Rods*—Two joint-thickness spacing rods made

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee C-8 on Refractories and is the direct responsibility of Subcommittee C08.09 on Monolithic Refractories.

Current edition approved Jan. 25, 1991. Published August 1991. Originally published as C 198 – 45 T. Last previous edition C 198 – 83.

<sup>2</sup> *Annual Book of ASTM Standards*, Vol 04.02.

<sup>3</sup> *Annual Book of ASTM Standards*, Vol 15.01.

<sup>4</sup> *Annual Book of ASTM Standards*, Vol 03.01.

<sup>5</sup> Supporting data on ruggedness testing is available from ASTM. Request RR:C-8-1008.

of 1/16-in. (2-mm) diameter drill rod cut into 4-in. (102-mm) lengths.

4.3 *Oven*—A drying oven to accommodate at least five 9-in. (230-mm) straight brick standing on end, and for use at 220 to 230°F (105 to 110°C).

4.4 *Testing Machine*—A standard mechanical or hydraulic compression testing machine conforming to the requirements of Practices E 4 and having a sensitivity of 20 lbf or less in the range from 0 to 4000 lbf (17.8 kN) may be used.

4.5 *Loading Fixture*—The fixtures shall provide load bearing blocks which ensure that the forces are applied normal to the beam without eccentricity. The directions of loads and reactions may be maintained parallel by judicious use of linkages, roller bearings, and flexure plates. Eccentricity of loading can be avoided by the use of spherical bearings.

4.5.1 Test Methods C 133 provide illustrations of three-point loading fixtures which meet the above requirements. One acceptable four-point loading fixture is illustrated in Test Method C 78. Another is illustrated in Test Method C 651. The span length,  $L$ , of the support blocks shall be  $7.00 \pm 0.05$  in. ( $178 \pm 1$  mm). The span length,  $l$ , of the load-applying blocks for four-point loading shall be  $2.33 \pm 0.05$  in. ( $59 \pm 1$  mm) (see Figs. 1 and 2).

5. Sampling

5.1 *Wet Mortars*—The sample of mortar shall be a prepared test sample of about 10 lb (4.5 kg) (approximately 1/2 gal (1.89 L)). If the weight of the commercial container is appreciably more than 10 lb, the contents of the container shall be thoroughly mixed in the container, or transferred without loss to a clean impervious receptacle of larger size and mixed thoroughly to a uniform consistency. 1b test sample shall then be taken and placed in a suitable covered container resistant to the possible corrosive action of the mortar.

5.2 *Dry Mortars*—The sample of mortar submitted shall be a prepared test sample of 10 lb (4.5 kg) or a larger quantity,


such as a 50 or 100-lb (23 or 45-kg) bag from which a 10-lb (4.5 kg) sample may be obtained using acceptable sampling procedures. The 10-lb (4.5 kg) sample should be thoroughly mixed with water to a uniform, troweling consistency and stored in a covered container (resistant to possible corrosive action by the mortar) for at least 16 h prior to the test.

NOTE 1—Reaction of phosphoric acid or aluminum phosphate with metallics may cause the development of hydrogen gas in some mortars. Therefore, the container should be covered only to minimize moisture loss, not tightly sealed.

6. Procedure

6.1 Cut each of the bricks of the sample (see Note 2) into two equal parts on a plane parallel to the 2 1/2 by 4 1/4-in. (65 by 114-mm) face. Use the uncut 2 1/2-by-4 1/4 in. face of each dry half-brick to form the mortar joint. The test mortar shall be of troweling consistency; this may require the addition of small amounts of water, followed by thorough mixing. Place approximately double the quantity of mortar required to form a joint 1/16 in. (2 mm) in thickness on the uncut and horizontally placed face of one half-brick. Place two spacing rods in the mortar parallel to the 2 1/2-in. (65 mm) edges of the brick and 3/4-in. (19 mm) from each edge. Then place the uncut face of the other half-brick on the mortar. Force out the excess mortar in the joint by pressing on the top half-brick and at the same time moving it with a to-and-fro motion in the direction of the 4 1/2 in. (114 mm) dimension of the brick, using the spacing rods as rollers.

6.1.1 A total of five movements in each direction shall be given, and the distance of travel for the top half-brick should be 1/4 in. (6 mm) from center in each direction. Withdraw the rods and clean the excess mortar from the surface of the joint. Allow the joints, prepared in this manner, to air-dry undisturbed at room temperature for 24 h, and then oven-dry at 220 to 230°F (105 to 110°C) for 18 h (overnight). Upon removal from the

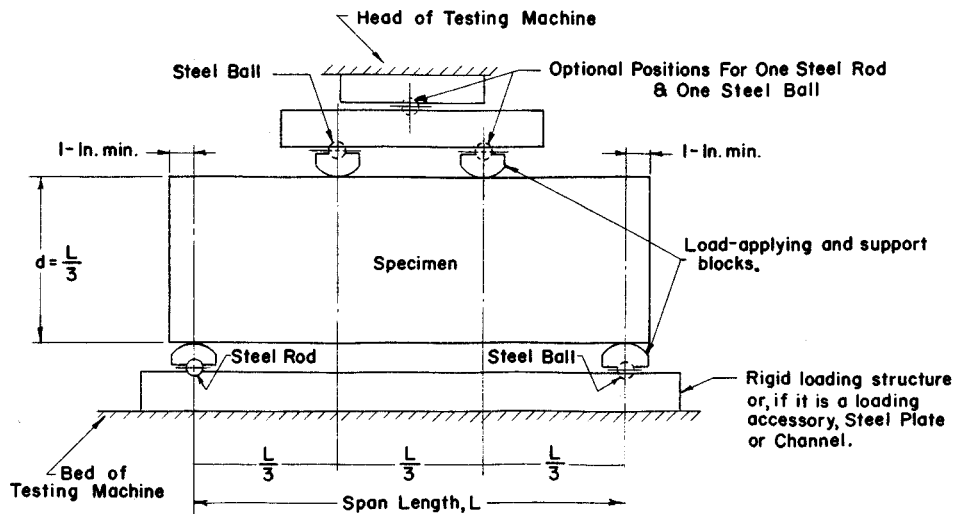

NOTE 1—This apparatus may be used inverted. If the testing machine applies a force through a spherically sealed head, the center pivot may be omitted, provided one load-applying block pivots on a rod and the other on a ball.

NOTE 2—1 in. = 25.4 mm.

FIG. 1 Diagrammatic View of a Suitable Apparatus for Flexure Test of Refractory Mortar Joints, Four-Point Loading Method