

# INTERNATIONAL STANDARD

**Optical fibres –  
Part 1-47: Measurement methods and test procedures – Macrobending loss**

IEC 60793-1-47:2009  
<https://standards.iteh.ai/catalog/standards/sist/4eb4af6-2728-4a32-a134-698a30fc0665/iec-60793-1-47-2009>



## THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2009 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester.

If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Central Office  
3, rue de Varembe  
CH-1211 Geneva 20  
Switzerland  
Email: [inmail@iec.ch](mailto:inmail@iec.ch)  
Web: [www.iec.ch](http://www.iec.ch)

### About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

### About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

- Catalogue of IEC publications: [www.iec.ch/searchpub](http://www.iec.ch/searchpub)

The IEC on-line Catalogue enables you to search by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, withdrawn and replaced publications.

- IEC Just Published: [www.iec.ch/online\\_news/justpub](http://www.iec.ch/online_news/justpub)

Stay up to date on all new IEC publications. Just Published details twice a month all new publications released. Available on-line and also by email.

- Electropedia: [www.electropedia.org](http://www.electropedia.org)

The world's leading online dictionary of electronic and electrical terms containing more than 20 000 terms and definitions in English and French, with equivalent terms in additional languages. Also known as the International Electrotechnical Vocabulary online.

- Customer Service Centre: [www.iec.ch/webstore/custserv](http://www.iec.ch/webstore/custserv)

If you wish to give us your feedback on this publication or need further assistance, please visit the Customer Service Centre FAQ or contact us:

Email: [csc@iec.ch](mailto:csc@iec.ch)  
Tel.: +41 22 919 02 11  
Fax: +41 22 919 03 00

# INTERNATIONAL STANDARD

**Optical fibres –  
Part 1-47: Measurement methods and test procedures – Macrobending loss**

<https://standards.iteh.ai/catalog/standards/sist/4eb4af6-2728-4a32-a134-698a30fc0665/iec-60793-1-47-2009>

INTERNATIONAL  
ELECTROTECHNICAL  
COMMISSION

PRICE CODE

P

ICS 33.180.10

ISBN 978-2-88910-289-1

## CONTENTS

|   |    |
|---|----|
| FOREWORD.....   | 3  |
| INTRODUCTION.....                                       | 5  |
| 1 Scope.....  | 6  |
| 2 Normative references .....                            | 6  |
| 3 Specimen .....  | 7  |
| 3.1 Specimen length.....                                | 7  |
| 3.1.1 Method A – Fibre winding .....                    | 7  |
| 3.1.2 Method B – Quarter circle bends .....             | 7  |
| 3.2 Specimen end face.....                              | 7  |
| 4 Apparatus.....  | 7  |
| 4.1 Method A – Fibre winding .....                      | 7  |
| 4.2 Method B – Quarter circle bends .....               | 7  |
| 5 Procedure .....                                       | 8  |
| 5.1 Method A – Fibre winding .....                      | 8  |
| 5.1.1 General .....                                     | 8  |
| 5.1.2 Single-mode fibres .....                          | 9  |
| 5.1.3 Multimode (A1) fibres .....                       | 10 |
| 5.2 Method B – Quarter circle bends .....               | 10 |
| 6 Calculations .....                                    | 12 |
| 7 Results .....   | 12 |
| 7.1 Information available with each measurement .....   | 12 |
| 7.2 Information available upon request.....             | 12 |
| 8 Specification information .....                       | 13 |
| Annex A (informative) Small bend radius phenomena ..... | 14 |
| Bibliography.....                                       | 16 |
| <br>  |    |
| Figure 1 – Quarter circle guide groove in plate.....    | 8  |
| Figure 2 – Multiple bends using stacked plates .....    | 11 |
| Figure A.1 – Loss curves versus curve fits.....         | 14 |

## INTERNATIONAL ELECTROTECHNICAL COMMISSION

## OPTICAL FIBRES –

**Part 1-47: Measurement methods and test procedures –  
Macrobending loss**

## FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC provides no marking procedure to indicate its approval and cannot be rendered responsible for any equipment declared to be in conformity with an IEC Publication.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 60793-1-47 has been prepared by subcommittee 86A: Fibres and cables, of IEC technical committee 86: Fibre optics.

This third edition cancels and replaces the second edition published in 2006. It constitutes a technical revision. The main change is listed below:

- Introduction of the Annex A describing small bend radius phenomena.

This standard is to be read in conjunction with IEC 60793-1-1.

The text of this standard is based on the following documents:

| CDV          | Report on voting |
|--------------|------------------|
| 86A/1207/CDV | 86A/1240/RVC     |

Full information on the voting for the approval of this standard can be found in the report on voting indicated in the above table.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all parts of IEC 60793 series, published under the general title *Optical fibres*, can be found on the IEC website.

The committee has decided that the contents of this publication will remain unchanged until the maintenance result date indicated on the IEC web site under "<http://webstore.iec.ch>" in the data related to the specific publication. At this date, the publication will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

A bilingual version of this publication may be issued at a later date.

## INTRODUCTION

Publications in the IEC 60793-1 series concern measurement methods and test procedures as they apply to optical fibres.

Within the same series, several different areas are grouped, but all numbers are possibly not used, as follows:

- Parts 1-10 to 1-19: General
- Parts 1-20 to 1-29: Measurement methods and test procedures for dimensions
- Parts 1-30 to 1-39: Measurement methods and test procedures for mechanical characteristics
- Parts 1-40 to 1-49: Measurement methods and test procedures for transmission and optical characteristics
- Parts 1-50 to 1-59: Measurement methods and test procedures for environmental characteristics

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

IEC 60793-1-47:2009

<https://standards.iteh.ai/catalog/standards/sist/4eb4af6-2728-4a32-a134-698a30fc0665/iec-60793-1-47-2009>

## OPTICAL FIBRES –

### Part 1-47: Measurement methods and test procedures – Macrobending loss

#### 1 Scope

This part of IEC 60793 establishes uniform requirements for measuring the macrobending loss of single-mode fibres (category B) at 1 550 nm or 1 625 nm, category A1 multimode fibres at 850 nm or 1 300 nm, and category A3 and A4 multimode fibres at 650 nm, 850 nm or 1 300 nm, thereby assisting in the inspection of fibres and cables for commercial purposes.

The standard gives two methods for measuring macrobending sensitivity:

- Method A – Fibre winding, pertains to category B single-mode fibres and category A1 multimode fibres.
- Method B – Quarter circle bends, pertains to category A3 and A4 multimode fibres.

For both of these methods, the optical power is measured using either the power monitoring or the cut-back technique.

Methods A and B are expected to produce different results if they are applied to the same fibre. This is because the key difference between the two methods is the deployment, including the bend radius and amount of fibre that is bent. The reason for the difference is that A3 and A4 multimode fibres are expected to be deployed in short lengths with relatively fewer bends compared to single-mode and category A1 multimode fibres.

In the following text, the “curvature radius” is defined as the radius of the suitable circular shaped support (e.g. mandrel or guiding groove on a flat surface) on which the fibre can be bent.

#### 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60793-1-1: *Optical fibres – Part 1-1: Measurement methods and test procedures – General and guidance*

IEC 60793-1-40: *Optical fibres – Part 1-40: Measurement methods and test procedures – Attenuation*

IEC 60793-1-46: *Optical fibres – Part 1-46: Measurement methods and test procedures – Monitoring of changes in optical transmittance*

IEC 61280-4-1: *Fibre-optic communication subsystem test procedures – Part 4-1: Cable plant and links – Multimode fibre-optic cable plant attenuation measurement*



### 3 Specimen

#### 3.1 Specimen length

##### 3.1.1 Method A – Fibre winding

The specimen shall be a known length of fibre, as specified in the detail specification. In particular, the length of the sample tested for loss is determined by the measurement set-up, i.e. curvature radius ( $R$ ) and number of turns ( $N$ ); any further fibre length does not affect the measurement results, provided that the signal to noise ( $S/N$ ) ratio is optimised.

##### 3.1.2 Method B – Quarter circle bends

The specimen length shall be determined according to the details shown in 5.2.

#### 3.2 Specimen end face

Prepare a flat end face, orthogonal to the fibre axis, at the input and output ends of each test specimen.

### 4 Apparatus

#### 4.1 Method A – Fibre winding

The apparatus consists of a tool (e.g. a mandrel or a guiding groove on a flat surface) able to hold the sample bent with a radius as stated in the specification (e.g. 30 mm for single-mode fibres and 37,5 mm for multimode fibres) and a loss-measurement instrument. Determine the macrobending loss at the wavelength as stated in the specification (e.g. 850 nm or 1 300 nm for multimode fibres, 1 550 nm or 1 625 nm for singlemode fibre) by using either the transmitted power monitoring technique (method A of IEC 60793-1-46) or the cut-back technique (method A of IEC 60793-1-40), taking care of the appropriate launch condition for the specific fibre type.

#### 4.2 Method B – Quarter circle bends

The apparatus consists of one or more plates, each containing one or more “guide grooves,” and a loss-measurement instrument. The plates shall be designed to be stacked during the test without contacting the sample fibre in a lower or higher plate; such contact will affect the measurement results. Each guide groove shall have a quarter circle segment (i.e. 90°) as shown in Figure 1. The bend radius  $r$ , i.e. the radius of the quarter circle segment, shall be stated in the detail specification. The width of each guide groove shall be at least 0,4 mm greater than the diameter of the fibre.

Determine the macrobending loss at the wavelength as stated in the specification (e.g. 650 nm, 850 nm, or 1 300 nm) by using either the transmitted power monitoring technique (method A of IEC 60793-1-46) or the cut-back technique (method A of IEC 60793-1-40), taking care of the appropriate launch condition for the specific fibre type.

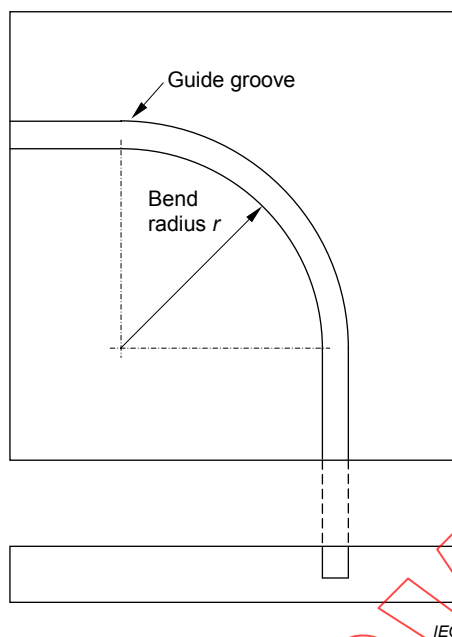


Figure 1 – Quarter circle guide groove in plate

## 5 Procedure

### 5.1 Method A – Fibre winding

#### 5.1.1 General

Loosely wind the fibre on the tool, avoiding excessive fibre twist. The number of turns, curvature radius and wavelength at which loss is to be measured are discussed in the following paragraphs.

Since the actual curvature radius is critical, a maximum tolerance of  $\pm 0,1$  mm (for radii lower than or equal to 15 mm) or  $\pm 0,5$  mm to 1,0 mm (for larger radii) is accepted: a tighter tolerance on small radii is required for higher measurement sensitivity.

Both for single-mode and for multimode fibres, two optical powers can be measured using:

- the power-monitoring technique, which measures the fibre attenuation increase due to a change from the straight condition to a bent condition, or
- the cut-back technique, which measures the total attenuation of the fibre in the bent condition. In order to determine the induced attenuation due to macrobending, this value should be corrected for the intrinsic attenuation of the fibre.

The fibre length outside the mandrel and the reference cut-back length shall be free of bends that might introduce a significant change in the measurement result. Collection of excess fibre in a bend radius of at least 140 mm is recommended.

It is also possible to rewind the fibre from a mandrel with a large radius (introducing negligible macrobend loss) to the mandrel with the required radius. In this case, the macrobend loss can be determined directly by using the power-monitoring technique (without the correction for the intrinsic attenuation of the fibre).

Care must be taken in order not to introduce torsion on any fibre part during the measurements, as this would affect the result.

### 5.1.2 Single-mode fibres

Different applications may require different deployment conditions: fibre types have been developed which exhibit bending performances optimized for each condition.

Two typical environments are recognized for (possibly) different fibre types, for which different measurement set-ups should be considered when characterizing fibre performances.

- a) Long distance networks: far from urban areas, space occupancy is not typically an issue, and bends imposed to the fibres can be limited to relatively large radii. Fibres designed for this application should be tested in similar conditions, i.e. with the samples wrapped around relatively large radius mandrels, e.g. in the range 25 mm to 30 mm.

This measurement set-up is mainly affected by errors related to low *S/N* ratio and by unwanted tension, torsions or kinks on the relatively long fibre length used for the measurement.

- b) Access networks: operating conditions require bending radii as small as possible, compatible with lifetime expectations and acceptable losses. Fibres designed for this application should be tested in similar conditions, i.e. with the samples bent at small radii, e.g. in the range 7,5 mm to 15 mm (see Annex A).

The measurement can be affected by different sources, one of which is reflections. The reflection of light at the coating/air or coating/glass, at surrounding surfaces (including, when used, the mandrel surface), or at connectors are some examples.

The test can be carried out on samples either making complete (360 °) turn(s), in open air or around a suitable support (mandrel), or making an equivalent number of partial turns, for example u-turns (180 °) or quarter turns (90 °), in open air or around suitable supports. The length under test is different for complete and partial turns, for example the length of a complete turn being twice the length of a u-turn or four times the length of a quarter turn. In the following, the term "coil" refers to one complete turn. One coil could also be made of, for example two consecutive u-turns<sup>1</sup> or four consecutive quarter turns. This should be taken into account while normalizing the results to the length of the sample (number of coils).

The following recommendations apply to test conditions in both cases (items a) and b) above):

#### Number of turns

The number of turns should be in accordance with the values stated in the product specification.

For single-mode fibres, the attenuation increases in a linear fashion with the number of turns.

For each radius, the number of turns shall be chosen in such a way that:

- the induced loss is significantly higher than the detection limit of the set-up; when necessary, for example for low bend loss fibres, tests may be carried out with more turns than the specification requires – followed by linear normalization to the specified number;
- the induced loss is significantly lower than the onset of the non-linear region in the set-up; for bending radii in the range 5 mm to 10 mm this may imply that not more than 5 to 10 turns should be used.

#### Bend radius

<sup>1</sup> If there is excessive displacement between successive u-turns, the length of the sample arranged on two u-turns can be shorter than one coil. A maximum displacement between adjacent u-turns of 0,5 mm is therefore suggested.