

INTERNATIONAL STANDARD

NORME INTERNATIONALE

Rubber insulated cables – Rated voltages up to and including 450/750 V –
Part 1: General requirements

(standards.iteh.ai)

Conducteurs et câbles isolés au caoutchouc – Tension assignée au plus égale
à 450/750 V –

Partie 1: Exigences générales

<https://standards.iteh.ai/catalog/standards/sist/0245853a-92ea-444f-bd5d-1e0e/iec-60245-1-2003amd1-2007-csv>



THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2008 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester.

If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de la CEI ou du Comité national de la CEI du pays du demandeur.

Si vous avez des questions sur le copyright de la CEI ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de la CEI de votre pays de résidence.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland
Email: inmail@iec.ch
Web: www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

- Catalogue of IEC publications: www.iec.ch/searchpub

The IEC on-line Catalogue enables you to search by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, withdrawn and replaced publications.

- IEC Just Published: www.iec.ch/online_news/justpub

Stay up to date on all new IEC publications. Just Published details twice a month all new publications released. Available on-line and also by email.

- Electropedia: www.electropedia.org

The world's leading online dictionary of electronic and electrical terms containing more than 20 000 terms and definitions in English and French, with equivalent terms in additional languages. Also known as the International Electrotechnical Vocabulary online.

- Customer Service Centre: www.iec.ch/webstore/custserv

If you wish to give us your feedback on this publication or need further assistance, please visit the Customer Service Centre FAQ or contact us:

Email: csc@iec.ch
Tel.: +41 22 919 02 11
Fax: +41 22 919 03 00

A propos de la CEI

La Commission Electrotechnique Internationale (CEI) est la première organisation mondiale qui élabore et publie des normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications CEI

Le contenu technique des publications de la CEI est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

- Catalogue des publications de la CEI: www.iec.ch/searchpub/cur_fut-f.htm

Le Catalogue en-ligne de la CEI vous permet d'effectuer des recherches en utilisant différents critères (numéro de référence, texte, comité d'études,...). Il donne aussi des informations sur les projets et les publications retirées ou remplacées.

- Just Published CEI: www.iec.ch/online_news/justpub

Restez informé sur les nouvelles publications de la CEI. Just Published détaille deux fois par mois les nouvelles publications parues. Disponible en-ligne et aussi par email.

- Electropedia: www.electropedia.org

Le premier dictionnaire en ligne au monde de termes électroniques et électriques. Il contient plus de 20 000 termes et définitions en anglais et en français, ainsi que les termes équivalents dans les langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International en ligne.

- Service Clients: www.iec.ch/webstore/custserv/custserv_entry-f.htm

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions, visitez le FAQ du Service clients ou contactez-nous:

Email: csc@iec.ch
Tél.: +41 22 919 02 11
Fax: +41 22 919 03 00

INTERNATIONAL STANDARD

NORME INTERNATIONALE

**Rubber insulated cables – Rated voltages up to and including 450/750 V –
Part 1: General requirements**

**Conducteurs et câbles isolés au caoutchouc – Tension assignée au plus égale
à 450/750 V –**
Partie 1: Exigences générales

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

COMMISSION
ELECTROTECHNIQUE
INTERNATIONALE

CONTENTS

FOREWORD.....	3
1 General	5
1.1 Scope.....	5
1.2 Normative references	5
2 Terms and definitions	6
2.1 Definitions relating to insulating and sheathing materials.....	6
2.2 Definitions relating to the tests	7
3 Marking	7
3.1 Indication of origin and cable identification	7
3.2 Durability.....	8
3.3 Legibility.....	8
4 Core identification	8
4.1 Core identification by colours	8
4.2 Core identification by numbers	9
5 General requirements for the construction of cables	10
5.1 Conductors.....	10
5.2 Insulation	11
5.3 Filler.....	13
5.4 Textile braid	14
5.5 Sheath	14
5.6 Tests on completed cables.....	17
6 Guide to use of the cables.....	20
Annex A (normative) Code designation	21
Annex B (normative) Calculation method for determination of the thickness of sheath of cable types 60245 IEC 53, 57 and 66 of IEC 60245-4	23
Bibliography.....	25
Figure 1 – Arrangement of marking	10
Table 1 – Requirements for non-electrical tests for cross-linked rubber insulation.....	12
Table 2 – Requirements for non-electrical tests for cross-linked rubber sheath	15
Table 3 – Requirements for electrical tests for cross-linked rubber insulated cables	18
Table 4 – Requirements for the static flexibility test for arc-welding electrode cables.....	19
Table 5 – Requirements for the static flexibility test for lift cables	19
Table B.1 – Fictitious diameter per nominal cross-sectional area	24

ITeH STANDARD PREVIEW

(standards.iteh.ai)

IEC 60245-1:2003+AMD1:2007 CSV

<https://standards.iteh.ai/catalog/standards/sist/0245853a-92ea-444f-bd5d-9ccf7c0dce0e/iec-60245-1-2003amd1-2007-csv>

INTERNATIONAL ELECTROTECHNICAL COMMISSION

**RUBBER INSULATED CABLES –
RATED VOLTAGES UP TO AND INCLUDING 450/750 V –****Part 1: General requirements**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC provides no marking procedure to indicate its approval and cannot be rendered responsible for any equipment declared to be in conformity with an IEC Publication.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 60245-1 has been prepared by IEC technical committee 20: Electric cables.

The principal change with respect to the previous edition is the replacement of insulation IE 1 with IE 4. This fourth edition does not constitute a full technical revision.

This consolidated version of IEC 60245-1 consists of the fourth edition (2003) [documents 20/659/FDIS and 20/679/RVD] and its amendment 1 (2007) [documents 20/902/FDIS and 20/909/RVD].

The technical content is therefore identical to the base edition and its amendment and has been prepared for user convenience.

It bears the edition number 4.1.

A vertical line in the margin shows where the base publication has been modified by amendment 1.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

IEC 60245 consists of the following parts, under the general title *Rubber insulated cables – Rated voltages up to and including 450/750 V*:

Part 1: General requirements

Part 2: Test methods

Part 3: Heat resistant silicone insulated cables

Part 4: Cords and flexible cables

Part 5: Lift cables

Part 6: Arc welding electrode cables

Part 7: Heat resistant ethylene-vinyl-acetate rubber insulated cables

Part 8: Cords for applications requiring high flexibility

Parts 3 to 8 are for particular types of cable and should be read in conjunction with Part 1 and Part 2. Further parts may be added as other types are standardized.

The committee has decided that the contents of the base publication and its amendments will remain unchanged until the maintenance result date indicated on the IEC web site under "<http://webstore.iec.ch>" in the data related to the specific publication. At this date, the publication will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

[IEC 60245-1:2003+AMD1:2007 CSV](http://standards.iteh.ai/catalog/standards/sist/0245853a-92ea-444f-bd5d-7c01e0e/iec-60245-1-2003amd1-2007-csv)

[https://standards.iteh.ai/catalog/standards/sist/0245853a-92ea-444f-bd5d-](https://standards.iteh.ai/catalog/standards/sist/0245853a-92ea-444f-bd5d-7c01e0e/iec-60245-1-2003amd1-2007-csv)

[7c01e0e/iec-60245-1-2003amd1-2007-csv](https://standards.iteh.ai/catalog/standards/sist/0245853a-92ea-444f-bd5d-7c01e0e/iec-60245-1-2003amd1-2007-csv)

(standards.iteh.ai)

RUBBER INSULATED CABLES – RATED VOLTAGES UP TO AND INCLUDING 450/750 V –

Part 1: General requirements

1 General

1.1 Scope

This part of IEC 60245 applies to rigid and flexible cables with insulation, and sheath if any, based on vulcanized rubber of rated voltages U_0/U up to and including 450/750 V used in power installations of nominal voltage not exceeding 450/750 V a.c.

NOTE For some types of flexible cables the term 'cord' is used.

The particular types of cables are specified in IEC 60245-3, IEC 60245-4, etc. The code designations of these types of cables are given in Annex A.

The test methods specified in Parts 1 to 8 are given in IEC 60245-2, IEC 60332-1 and in the relevant parts of IEC 60811.

1.2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

[https://standards.iteh.ai/catalog/standards/sist/0245853a-92ea-444f-bd5d-](https://standards.iteh.ai/catalog/standards/sist/0245853a-92ea-444f-bd5d-7c01e9c07163/iec-60245-1-2007)

IEC 60173:1964, *Colours of the cores of flexible cables and cords*

IEC 60228:1978, *Conductors of insulated cables*

IEC 60245-2:1994, *Rubber insulated cables – Rated voltages up to and including 450/750 V – Part 2: Test methods*

IEC 60245-3:1994, *Rubber insulated cables – Rated voltages up to and including 450/750 V – Part 3: Heat resistant silicone insulated cables*

IEC 60245-4:1994, *Rubber insulated cables – Rated voltages up to and including 450/750 V – Part 4: Cords and flexible cables*

IEC 60245-7:1994, *Rubber insulated cables – Rated voltages up to and including 450/750 V – Part 7: Heat resistant ethylene-vinyl-acetate rubber insulated cables*

IEC 60332-1:1993, *Tests on electric cables under fire conditions – Part 1: Test on a single vertical insulated wire or cable*

IEC 60811-1-1:1993, *Common test methods for insulating and sheathing materials of electric cables – Part 1: Methods for general application – Section 1: Measurement of thickness and overall dimensions – Tests for determining the mechanical properties*

IEC 60811-1-2:1985, *Common test methods for insulating and sheathing materials of electric cables – Part 1: Methods for general application – Section Two: Thermal ageing methods*

IEC 60811-1-4:1985, *Common test methods for insulating and sheathing materials of electric cables – Part 1: Methods for general application – Section Four: Tests at low temperature*

IEC 60811-2-1:1998, *Insulating and sheathing materials of electric and optical cables – Common test methods – Part 2-1: Methods specific to elastomeric compounds – Ozone resistance, hot set and mineral oil immersion tests*

IEC 60811-3-1:1985, *Common test methods for insulating and sheathing materials of electric cables – Part 3: Methods specific to PVC compounds – Section One: Pressure test at high temperature – Tests for resistance to cracking*

IEC 62440, *Electric cables – Guide to use for cables with a rated voltage not exceeding 450/750V¹*

2 Terms and definitions

For the purposes of this document, the following terms and definitions apply:

2.1 Definitions relating to insulating and sheathing materials

2.1.1

type of compound

category in which a compound is placed according to its properties, as determined by specific tests

NOTE The type designation is not directly related to the composition of the compound.

2.1.2

rubber compound

combination of materials suitably selected, proportioned, treated and vulcanized, of which the characteristic constituent is a rubber and/or synthetic elastomer

NOTE Vulcanization is defined as a post-application treatment taking place after the insulation and/or sheath has been applied in order to induce permanent cross-linking of the elastomer.

2.1.3

polychloroprene compound (PCP) or other equivalent synthetic elastomer

vulcanized compound in which the elastomer is polychloroprene or other equivalent synthetic elastomer providing a compound with properties similar to PCP

2.1.4

ethylene-vinyl acetate rubber compound (EVA) or other equivalent synthetic elastomer

cross-linked compound in which the elastomer is ethylene-vinyl acetate or other equivalent synthetic elastomer providing a compound with properties similar to EVA

2.1.5

ethylene-propylene rubber compound (EPR) or equivalent synthetic elastomer

cross-linked compound in which the elastomer is ethylene-propylene or equivalent synthetic elastomer providing a compound with properties similar to EPR

2.1.6

cross-linked polyvinyl chloride (XLPVC)

combinations of materials of which polyvinyl chloride is the characteristic constituent, including adequate cross-linking agents, suitably selected, proportioned and treated which, when cross-linked, meet the requirements given in the particular specification

¹ In preparation.

2.2 Definitions relating to the tests

2.2.1

type tests

T

tests required to be made before supplying a type of cable covered by this standard on a general commercial basis, in order to demonstrate satisfactory performance characteristics to meet the intended application

NOTE These tests are of such a nature that, after they have been made, they need not be repeated, unless changes have been made in the cable materials or design which might change the performance characteristics.

2.2.2

sample tests

S

tests made on samples of completed cable, or components taken from a completed cable, adequate to verify that the finished product meets the design specifications

2.3

rated voltage

reference voltage for which the cable is designed, and which serves to define the electrical tests

NOTE 1 The rated voltage is expressed by the combination of two values: U_0/U expressed in volts (V):

U_0 being the r.m.s. value between any insulated conductor and "earth" (metal covering of the cable or the surrounding medium);

U being the r.m.s. value between any two phase conductors of a multicore cable or of a system of single-core cables.

In an alternating-current system, the rated voltage of a cable is at least equal to the nominal voltage of the system for which it is intended.

This condition applies both to the value U_0 and to the value U .

In a direct current system, the nominal voltage of the system is not higher than 1,5 times the rated voltage of the cable.

NOTE 2 The operating voltage of a system may permanently exceed the nominal voltage of such a system by 10 %. A cable can be used at a 10 % higher operating voltage than its rated voltage if the latter is at least equal to the nominal voltage of the system.

3 Marking

3.1 Indication of origin and cable identification

Cables shall be provided with an indication of the manufacturer, which shall be either an identification thread or a repetitive marking of the manufacturer's name or trademark.

Marking may be by printing or by reproduction in relief on, or in, the insulation or sheath, or by printing on a proofed tape or a separate marker tape.

3.1.1 Continuity of marks

Each specified mark shall be regarded as continuous if the distance between the end of the mark and the beginning of the next identical mark does not exceed

550 mm if the marking is on the outer sheath of the cable,

275 mm if the marking is

- on the insulation of an unsheathed cable, or
- on the insulation of a sheathed cable, or
- on a tape within a sheathed cable.

3.2 Durability

Printed markings shall be durable. Compliance with this requirement shall be checked by the test given in 1.8 of IEC 60245-2.

3.3 Legibility

All markings shall be legible.

The colours of the identification threads shall be easy to recognize or easily made recognizable, if necessary, by cleaning with petrol or other suitable solvent.

4 Core identification

Each core shall be identified as follows:

- in cables having up to and including five cores, by colour; see 4.1;
- in cables having more than five cores by colour or by number; see 4.1 and 4.2.

NOTE The colour scheme is under consideration.

4.1 Core identification by colours

4.1.1 General requirements

Identification of the cores of a cable shall be achieved by the use of coloured insulation or other suitable method.

Each core of a cable shall have only one colour, except the core identified by a combination of the colours green and yellow.

The colours green and yellow, when not in combination, shall not be used for any multicore cable.

NOTE The colours red and white should preferably be avoided.

4.1.2 Colour scheme

The preferred colour scheme is as follows:

single-core cable:	no preferred colour scheme;
two-core cable:	no preferred colour scheme;
three-core cable:	either green-and-yellow, blue, brown, or brown, black, grey
four-core cable:	either green-and-yellow, brown, black, grey, or blue, brown, black, grey
five-core cable:	either green-and-yellow, blue, brown, black, grey, or blue, brown, black, grey, black.
cables having more than five cores:	either in the outer layer one core green-and-yellow, one core blue, and the other cores of one and the same colour, however not green, yellow, blue or brown; in the other layers one core brown and the other cores of one and the same colour, however not green, yellow, blue or brown; or in the outer layer one core blue, one core brown and the other cores of one and the same colour, however not green, yellow, blue or brown; in the other layers one core brown and the other cores of one and the same colour, however not green, yellow, blue or brown.

iTeh STANDARD PREVIEW

The colours shall be clearly identifiable and durable. Durability shall be checked by the test given in 1.8 of IEC 60245-2. (standards.iteh.ai)

4.1.3 Colour combination green/yellow

The distribution of the colours for the core coloured green/yellow shall comply with the following condition (which is in accordance with IEC 60173): for every 15 mm length of core, one of these colours shall cover at least 30 % and not more than 70 % of the surface of the core, the other colour covering the remainder.

NOTE Information on the use of the colours green-and-yellow and blue.

It is understood that the colours green and yellow, when they are combined as specified above, are recognized exclusively as a means of identification of the core intended for use as earth connection or similar protection, and that the colour blue is intended for the identification of the core intended to be connected to neutral. If, however, there is no neutral, blue can be used to identify any core except the earthing or protective conductor.

4.2 Core identification by numbers

4.2.1 General requirements

The insulation of the cores shall be of the same colour and numbered sequentially, except for the core coloured green/yellow, if one is included.

The green/yellow core, if any, shall comply with the requirement of 4.1.3 and shall be in the outer layer.

The numbering shall start with the number "1" in the inner layer.

The numbers shall be printed in arabic numerals on the outer surfaces of the cores. All the numbers shall be of the same colour, which shall contrast with the colour of the insulation. The numerals shall be legible.

4.2.2 Preferred arrangement of marking

The numbers shall be repeated at regular intervals along the core, consecutive numbers being inverted in relation to each other.

When the number is a single numeral, a dash shall be placed underneath it. If the number consists of two numerals, these shall be positioned one below the other, and a dash placed below the lower numeral. The spacing d between consecutive numbers shall not exceed 50 mm.

The arrangement of the marks is shown in Figure 1 below.

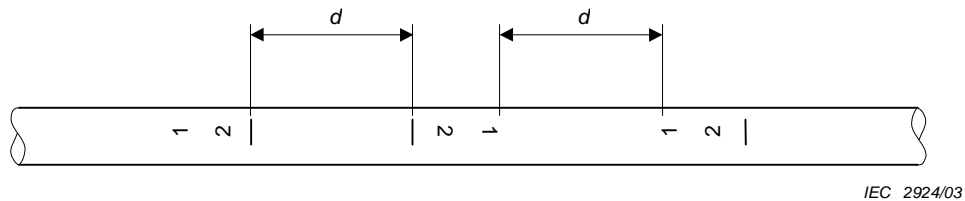


Figure 1 – Arrangement of marking by numbers

4.2.3 Durability

Printed numerals shall be durable. Compliance with this requirement shall be checked by the test given in 1.8 of IEC 60245-2 (standards.iteh.ai)

5 General requirements for the construction of cables

5.1 Conductors

5.1.1 Material

The conductors shall consist of annealed copper. Unless otherwise specified in the particular specifications (IEC 60245-3, IEC 60245-4, etc.), the wires of conductors may be plain or tinned. Tinned wires shall be covered with an effective layer of tin.

5.1.2 Construction

The maximum diameters of the wires of the conductors shall be in accordance with IEC 60228, unless otherwise specified in the particular cable specifications.

The classes of conductors relevant to the various types of cables are given in the particular specifications (IEC 60245-3, IEC 60245-4, etc.).

5.1.3 Separator between conductor and insulation

An optional separating tape made of suitable material may be placed between the plain or tinned conductor and the insulation.

5.1.4 Construction verification

Compliance with the requirements of 5.1.1 and 5.1.2, including the requirements of IEC 60228, shall be checked by inspection and by measurement.

5.1.5 Electrical resistance

Unless otherwise specified in the particular specifications (IEC 60245-3, IEC 60245-4, etc.), the resistance of each conductor at 20 °C shall be in accordance with the requirements of IEC 60228 for the given class of conductor.

Compliance shall be checked by the test given in 2.1 of IEC 60245-2.

5.2 Insulation

5.2.1 Material

The insulation shall be a cross-linked material of the type specified for each type of cable in the particular specification (IEC 60245-3, IEC 60245-4, etc.).

Type IE 2 in the case of cables insulated with silicone rubber compound.

Type IE 3 in the case of cables insulated with rubber compound based on ethylene vinyl-acetate or equivalent materials.

Type IE 4 in the case of cables insulated with ordinary ethylene-propylene rubber compound or equivalent materials.

The test requirements for these compounds are specified in Table 1.

NOTE For some cables belonging to IEC 60245-8, insulation type XP1 is given in that particular specification.

The maximum operating temperatures for cables insulated with any of the above types of compound and covered by the particular specifications (IEC 60245-3, IEC 60245-4, etc.) are given in those publications.

5.2.2 Application to the conductor

The insulation shall be closely applied to the conductor or separator. In the particular specifications (IEC 60245-3, IEC 60245-4, etc.) it is stated, for each type of cable, whether the insulation shall be applied in a single layer or in a number of layers, and whether it shall or shall not be covered with a proofed tape. It shall be possible to remove the insulation, without damage to the insulation itself, to the conductor, or to the tin or metal coating if any. Compliance shall be checked by inspection and by manual test.

5.2.3 Thickness

The mean value of the thickness of insulation shall be not less than the specified value for each type and size of cable shown in the tables of the particular specifications (IEC 60245-3, IEC 60245-4, etc.). However, the thickness at any one place may be less than the specified value, provided that the difference does not exceed 0,1 mm + 10 % of the specified value. Compliance shall be checked by the test given in 1.9 of IEC 60245-2.

5.2.4 Mechanical properties before and after ageing

The insulation shall have adequate mechanical strength and elasticity within the temperature limits to which it may be exposed in normal use.

Compliance shall be checked by carrying out the tests specified in Table 1.

The applicable test methods and the results to be obtained are specified in Table 1.

Table 1 – Requirements for non-electrical tests for cross-linked rubber insulation

1	2	3	4	5	6	7	
Ref. No.	Test	Unit	Type of compound			Test method described in	
			IE 2	IE 3	IE 4	IEC	Subclause
1	<i>Tensile strength and elongation at break</i>					60811-1-1	9.1
1.1	Properties in the state as delivered						
1.1.1	Values to be obtained for the tensile strength: - median, min.	N/mm ²	5,0	6,5	5,0		
1.1.2	Values to be obtained for the elongation at break: - median, min.	%	150	200	200		
1.2	Properties after ageing in air oven					60811-1-1	9.1
1.2.1	Ageing conditions ^{a, b} : - temperature - duration of treatment	°C h	200 ± 2 10 × 24	150 ± 2 7 × 24	100 ± 2 7 × 24	60811-1-2	8.1
1.2.2	Values to be obtained for the tensile strength: - median, min. - variation ^c , max.	N/mm ² %	4,0 -	- ± 30	4,2 ± 25		
1.2.3	Values to be obtained for the elongation-at-break: - median, min. - variation ^c , max.	% %	120 -	- ± 30	200 ± 25		
1.3	Spare						
1.4	Properties after ageing in an air bomb					60811-1-2	8.2
1.4.1	Ageing conditions ^a : - temperature - duration of treatment	°C h	- -	150 ± 3 7 × 24	127 ± 2 40		
1.4.2	Values to be obtained for the tensile strength: - median, min. - variation ^c , max.	N/mm ² %	- -	6,0 -	- ±30		
1.4.3	Values to be obtained for the elongation-at-break: - variation ^c , max.	%	-	-30 ^d	±30		

iTech STANDARD PREVIEW
(standards.iteh.ai)
IEC 60245-1:2003+AMD1:2007 CSV
<https://standards.iteh.ai/catalog/standards/sist/0245853a-92ea-444f-bc5d-9ccf7c0dce0e/iec-60245-1-2003amd1-2007-csv>

Table 1 (continued)

1	2	3	4	5	6	7	
Ref. No.	Test	Unit	Type of compound			Test method described in	
			IE 2	IE 3	IE 4	IEC	Subclause
2 2.1	<i>Hot set test</i> Test conditions: - temperature - time under load - mechanical stress	°C min N/mm ²	200 ± 3 15 0,20	200 ± 3 15 0,20	200 ± 3 15 0,20	60811-2-1	Clause 9
2.2	Values to be obtained: - elongation under load, max. - elongation after cooling, max.	% %	175 25	100 25	100 25		
3 3.1	<i>Pressure test at high temperature</i> Test conditions: - force exercised by the blade - duration of heating under load - temperature	°C	-	See IEC 60811-3-1 8.1.4 8.1.5 150 ± 2	- - -	60811-3-1	Clause 8
3.2	Result to be obtained: - median of the depth of penetration, max.	%	-	50	-		
4 4.1	<i>Ozone resistance test</i> Test conditions: - test temperature - test duration - ozone concentration	°C h %	- - -	- - -	25 ± 2 24 0,025 to 0,030	60811-2-1	Clause 8
4.2	Result to be obtained				No cracks		

IEC 60245-1:2003+AMD1:2007 CSV

^a Ageing of Type IE 4 shall be carried out with the conductor in place, or with not more than 30% of the conductor strands removed.

^b Unless otherwise specified in the relevant cable specifications, a rotating fan inside the oven is normally permissible when testing rubber compounds. However, in case of dispute, ageing shall be carried out in an oven which is designed to operate without a fan rotating inside it.

^c Variation: Difference between the median value after ageing and the median value without ageing, expressed as a percentage of the latter.

^d No limit for the positive tolerance.

5.3 Filler

5.3.1 Material

Unless otherwise specified in the particular specification (IEC 60245-3, IEC 60245-4, etc.), the fillers shall be composed of one of the following or of any combination of the following:

- a compound based on cross-linked or uncross-linked rubber, or
- natural or synthetic textiles, or
- paper.

There shall be no harmful interactions between the constituents of the filler and the insulation and/or the sheath.