

Edition 1.0 2012-03

INTERNATIONAL STANDARD

NORME INTERNATIONALE

Electric and optical fibre cables Test methods for hon-metallic materials – Part 511: Mechanical tests – Measurement of the melt flow index of polyethylene compounds

Câbles électriques et à fibres optiques – Méthodes d'essai pour les matériaux non-métalliques – 39d9f4aa0466/iec-60811-511-2012 Partie 511: Essais mécaniques – Mesure de l'indice de fluidité à chaud des mélanges polyéthylène





THIS PUBLICATION IS COPYRIGHT PROTECTED Copyright © 2012 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester.

If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de la CEI ou du Comité national de la CEI du pays du demandeur. Si vous avez des questions sur le copyright de la CEI ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de la CEI de votre pays de résidence.

IEC Central Office	Tel.: +41 22 919 02 11
3, rue de Varembé	Fax: +41 22 919 03 00
CH-1211 Geneva 20	info@iec.ch
Switzerland	www.iec.ch
Switzerland	www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

Useful links:

IEC publications search - www.iec.ch/searchpub

The advanced search enables you to find IEC publications rols. The world's leading online dictionary of electronic and by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, replaced endo811-511 additional languages. Also known as the International withdrawn publications. https://standards.iteh.ai/catalog/standards/stb/01eS/940-Dec/-4808-906/-

IEC Just Published - webstore.iec.ch/justpublished/4aa0466/icc-608 Customer/Service Centre - webstore.iec.ch/csc

Stay up to date on all new IEC publications. Just Published details all new publications released. Available on-line and also once a month by email.

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: csc@iec.ch.

A propos de la CEI

La Commission Electrotechnique Internationale (CEI) est la première organisation mondiale qui élabore et publie des Normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications CEI

Le contenu technique des publications de la CEI est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

Liens utiles:

Recherche de publications CEI - www.iec.ch/searchpub

La recherche avancée vous permet de trouver des publications CEI en utilisant différents critères (numéro de référence, texte, comité d'études,...).

Elle donne aussi des informations sur les projets et les publications remplacées ou retirées.

Just Published CEI - webstore.iec.ch/justpublished

Restez informé sur les nouvelles publications de la CEI. Just Published détaille les nouvelles publications parues. Disponible en ligne et aussi une fois par mois par email.

Electropedia - www.electropedia.org

Le premier dictionnaire en ligne au monde de termes électroniques et électriques. Il contient plus de 30 000 termes et définitions en anglais et en français, ainsi que les termes équivalents dans les langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International (VEI) en ligne.

Service Clients - webstore.iec.ch/csc

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions contactez-nous: csc@iec.ch.



Edition 1.0 2012-03

INTERNATIONAL STANDARD

NORME INTERNATIONALE

Electric and optical fibre cables A Test methods for non-metallic materials – Part 511: Mechanical tests – Measurement of the melt flow index of polyethylene compounds

IEC 60811-511:2012

Câbles électriques et à fibres optigues d'essai pour les matériaux non-métalliques – 39d9f4aa0466/iec-60811-511-2012 Partie 511: Essais mécaniques – Mesure de l'indice de fluidité à chaud des mélanges polyéthylène

INTERNATIONAL ELECTROTECHNICAL COMMISSION

COMMISSION ELECTROTECHNIQUE INTERNATIONALE

PRICE CODE CODE PRIX



ICS 29.035.01; 29.060.20

ISBN 978-2-88912-988-1

Warning! Make sure that you obtained this publication from an authorized distributor. Attention! Veuillez vous assurer que vous avez obtenu cette publication via un distributeur agréé.

 Registered trademark of the International Electrotechnical Commission Marque déposée de la Commission Electrotechnique Internationale

CONTENTS

FO	REWC	RD		3	
INT	RODU	JCTION		5	
1	Scope				
2	Normative references				
3	Terms and definitions				
4	Test method				
	4.1		al		
	4.2		tus		
	4.3 Test samples				
	4.4	Cleanir	ng and maintenance of the apparatus	9	
	4.5	Method	I A		
		4.5.1	General		
		4.5.2	Test procedure		
		4.5.3	Expression of results		
	4.6	Method	I B	11	
	4.7	Method	I C		
		4.7.1	GeneralSTANDARD PREVIEW Test procedure	11	
		4.7.2			
		4.7.3	Expression of (results and ards.iteh.ai)		
5					
Bib	liograp	ohy	IEC 60811-511:2012		
			https://standards.iteh.ai/catalog/standards/sist/6fe8794b-bee7-4808-90e7- 39d9f4aa0466/iec-60811-511-2012		
Fig	ure 1 -	- Appar	atus for determining melt flow index	8	
			-		
5					
Tab	ole 1 –	Definiti	on of types of polyethylene	6	
			ntervals (as a function of melt flow index) used in obtaining cut-offs charge put into the cylinder for methods A and C	11	

INTERNATIONAL ELECTROTECHNICAL COMMISSION

ELECTRIC AND OPTICAL FIBRE CABLES – TEST METHODS FOR NON-METALLIC MATERIALS –

Part 511: Mechanical tests – Measurement of the melt flow index of polyethylene compounds

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible 6 in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter. 39d9f4aa0466/iec-60811-511-2012
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 60811-511 has been prepared by IEC technical committee 20: Electric cables.

This Part 511 of IEC 60811 cancels and replaces Clause 10 of IEC 60811-4-1:2004, which is withdrawn. Full details of the replacements are shown in Annex A of IEC 60811-100:2012.

There are no specific technical changes with respect to the previous edition, but see the Foreword to IEC 60811-100:2012.

The text of this standard is based on the following documents:

FDIS	Report on voting
20/1307/FDIS	20/1356/RVD

Full information on the voting for the approval of this standard can be found in the report on voting indicated in the above table.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

This part of IEC 60811 shall be used in conjunction with IEC 60811-100.

A list of all the parts in the IEC 60811 series, published under the general title *Electric and optical fibre cables – Test methods for non-metallic materials*, can be found on the IEC website.

The committee has decided that the contents of this publication will remain unchanged until the stability date indicated on the IEC web site under "http://webstore.iec.ch" in the data related to the specific publication. At this date, the publication will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or ANDARD PREVIEW
- amended.

(standards.iteh.ai)

<u>IEC 60811-511:2012</u> https://standards.iteh.ai/catalog/standards/sist/6fe8794b-bee7-4808-90e7-39d9f4aa0466/iec-60811-511-2012

INTRODUCTION

The IEC 60811 series specifies the test methods to be used for testing non-metallic materials of all types of cables. These test methods are intended to be referenced in standards for cable construction and for cable materials.

NOTE 1 Non-metallic materials are typically used for insulating, sheathing, bedding, filling or taping within cables.

NOTE 2 These test methods are accepted as basic and fundamental and have been developed and used over many years principally for the materials in all energy cables. They have also been widely accepted and used for other cables, in particular optical fibre cables, communication and control cables and cables for ships and offshore applications.

iTeh STANDARD PREVIEW (standards.iteh.ai)

<u>IEC 60811-511:2012</u> https://standards.iteh.ai/catalog/standards/sist/6fe8794b-bee7-4808-90e7-39d9f4aa0466/iec-60811-511-2012

ELECTRIC AND OPTICAL FIBRE CABLES – TEST METHODS FOR NON-METALLIC MATERIALS –

Part 511: Mechanical tests – Measurement of the melt flow index of polyethylene compounds

1 Scope

This Part 511 of IEC 60811 describes the procedure for the measurement of the melt flow index for polyethylene compounds.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60811-100:2012, Electric and optical fibre cables – Test methods for non-metallic materials – Part 100: General STANDARD PREVIEW

IEC 60811-606, Electric and optical fibre cables it fest methods for non-metallic materials-Part 606: Physical tests – Methods for determining the density

IEC 60811-511:2012

For the purposes of this document, the terms and definitions given in IEC 60811-100 apply.

Additionally, for the purposes of this standard, a distinction is made between low-density, medium-density and high-density PE as shown in Table 1.

Type of polyethylene	Density at 23 °C ^a g/cm ³	
Low-density polyethylene	≤ 0,925	
Medium-density polyethylene	> 0,925 ≤ 0,940	
High-density polyethylene	> 0,940	
^a These densities refer to unfilled resins as determined by the method specified in IEC 60811-606.		

Table 1 – Definition of types of polyethylene

4 Test method

4.1 General

This part of IEC 60811 shall be used in conjunction with Part 100: General

All the tests shall be carried out not less than 16 h after the extrusion of the insulating or sheathing compounds.

The melt flow index (MFI) of polyethylene and polyethylene compounds is the quantity of material extruded in 1,5 min or 10 min at 190 °C through a specified die under the action of a load determined by the method used.

NOTE 1 The same method is also specified in ISO 1133.

NOTE 2 The melt flow index is not applicable to flame retarding polyethylene. Flame retardant PE is defined as PE containing additives intended to reduce flame propagation.

4.2 Apparatus

The apparatus consists basically of an extrusion plastometer, the general design being as shown in Figure 1. The compound, which is contained in a vertical cylinder, is extruded through a die by a loaded piston under controlled temperature conditions. All surfaces of the apparatus in contact with the material under test shall have a high polish.

The apparatus consists of the following parts:

a) Steel cylinder

A steel cylinder fixed in a vertical position and thermally insulated for operation at 190 °C. The cylinder shall be at least 115 mm long with an internal diameter of between 9,5 mm and 10 mm and complying with the requirements in item b) below. The base of the cylinder shall be thermally insulated if the area of the exposed metal exceeds 4 cm² and it is recommended that the insulating material used be polytetrafluoroethylene (thickness about 3 mm) in order to avoid the extruded material from sticking.

b) Steel hollow piston

A steel hollow piston with a length at least the same as that of the cylinder. The axes of the cylinder and of the piston shall coincide and the effective length of the piston shall be a maximum of 135 mm. There is a head of length $(6,35 \pm 0,10)$ mm. The diameter of the head shall be less than the internal diameter of the cylinder at all points along the working length of the cylinder by $(0,075\pm 0,015)$ mm on addition for calculating the load (see item c) this diameter should be known within $\pm 0,025$ mm. The lower edge of the head shall have a radius of 0,4 mm and the upper edge has its sharp edge removed. Above the head, the piston has a diameter of about 9 mm. A stud may be added at the top of the piston to support the removable load, but the piston is thermally insulated from this load.

c) Removable load on top of the piston

The combined masses of the load and the piston shall be such that the force *P* applied is:

- P = 21,2 N in the case of method A (see 4.5);
- P = 49,1 N in the case of method C (see 4.7);
- d) Heater

A heater to maintain the polyethylene in the cylinder at a temperature of (190 \pm 0,5) °C. An automatic temperature control is strongly recommended.

e) Temperature measuring device

A temperature measuring device located as closely as possible to the die, but situated within the body of the cylinder. The measuring device shall be calibrated to permit temperature measurement to an accuracy of \pm 0,1 °C.


f) Die

A die of length (8,000 \pm 0,025) mm made of hardened steel, the mean internal diameter being between 2,090 mm and 2,100 mm and uniform along its length to within \pm 0,005 mm (see Figure 2). The die shall not project beyond the base of the cylinder.

g) Balance

A balance accurate to \pm 0,000 5 g.


Dimensions in millimeters

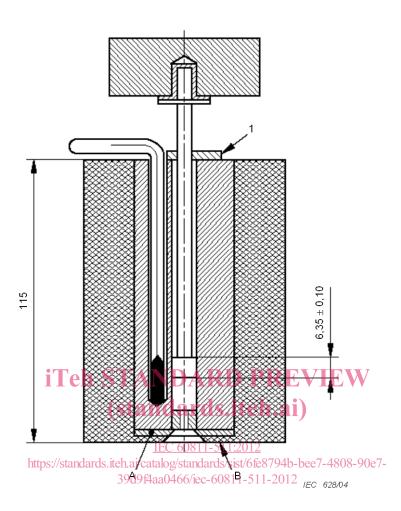

NOTE The figure shows the large external diameter cylinder, die-retaining plate A and insulating plate B. **Key**

1 guide collar



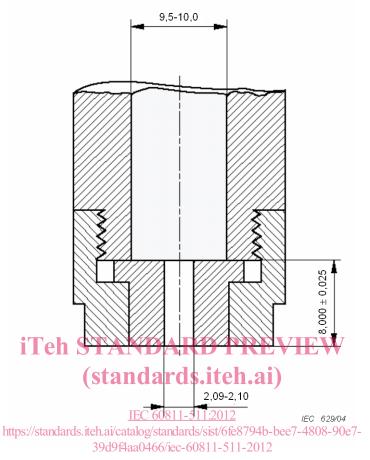

NOTE The figure shows the small external diameter cylinder with an example method of retaining the die.

Figure 2 – Die

4.3 Test samples

A sample of insulation or sheath of sufficient mass shall be taken from one end of the cable or wire. The sample shall be cut in pieces, the dimension of which shall not exceed 3 mm in any direction.

It is permitted to take material from different cores of the same cable.

4.4 Cleaning and maintenance of the apparatus

The apparatus shall be cleaned after each test.

On no account should abrasives or materials likely to damage the surfaces of the piston, cylinder or die be used in removing superficial polyethylene or in manipulating any part of the apparatus.

Suitable solvents for cleaning the apparatus are xylene, tetrahydronaphthalene or odourless kerosene. The piston shall be cleaned while still hot with a cloth dipped in the solvent; likewise, the cylinder shall also be cleaned while still hot, with a swab dipped in the solvent. The die shall be cleaned with a closely-fitting brass reamer or wooden peg and then immersed in boiling solvent.