

INTERNATIONAL STANDARD

ISO
9653

First edition
1991-12-15

Adhesives — Test method for shear impact strength of adhesive bonds

Adhésifs — Essai de tenue au choc par cisaillement du joint adhésif

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 9653:1991](#)

<https://standards.iteh.ai/catalog/standards/sist/38d323a4-4f00-4c5e-a877-2458d1598aa1/iso-9653-1991>



Reference number
ISO 9653:1991(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 9653 was prepared by Technical Committee ISO/TC 61, *Plastics*, Sub-Committee SC 11, *Products*.

[ISO 9653:1991](https://standards.iteh.ai/catalog/standards/sist/38d323a4-4f00-4c5e-a877-2458d1598aa1/iso-9653-1991)

<https://standards.iteh.ai/catalog/standards/sist/38d323a4-4f00-4c5e-a877-2458d1598aa1/iso-9653-1991>

© ISO 1991

All rights reserved. No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Adhesives — Test method for shear impact strength of adhesive bonds

1 Scope

1.1 This International Standard specifies a method for the determination of the comparative impact value of adhesive bonds in shear, when tested on standard specimens, and using specified conditions of preparation, conditioning and testing.

1.2 The method is intended to be used for wood-to-wood or metal-to-metal bonds, but may be extended to cover plastics-to-plastics bonds as well as bonds between combinations of these materials.

2 Definition

For the purposes of this International Standard, the following definition applies.

2.1 Impact value: Energy absorbed by a specimen of standard design when sheared by a single blow of a testing-machine hammer. The impact value is expressed in joules per square metre.

3 Principle

The impact value is determined by using a pendulum-type impact machine on a metal-to-metal or wood-to-wood specimen.

4 Apparatus

4.1 Pendulum-type impact machine, with a impact-head velocity of 3,4 m/s, comprising the elements specified in 4.1.1 to 4.1.3.

4.1.1 Impact head, with a flat striking face slightly wider than the specimen and aligned to strike the specimen full-face.

4.1.2 Specimen-holding fixture, as shown in figure 1. The fixture illustrated is not always suitable for use with all impact machines and vices. Dimensions and design of the fixture may be varied as required for adaptation to machines and vices available, provided the following general requirements are met:

The fixture shall be machined from a solid piece of steel and solidly bolted to the base of the testing machine. Corners shall be drilled to ensure that the specimen sets flush against the retaining end of the fixture. The drilled corners are provided to minimize dirt collection at the corners which could hold the end of the specimen away from the face of the fixture. The fixture shall be provided with a screw to tighten the specimen in the fixture to minimize the tendency of the specimen to overturn when struck. A metal plate may be placed between the end of the block and the end of the screw when non-metallic adherends are used. The fixture shall be so located that the specimen will be struck at the point of maximum head velocity.

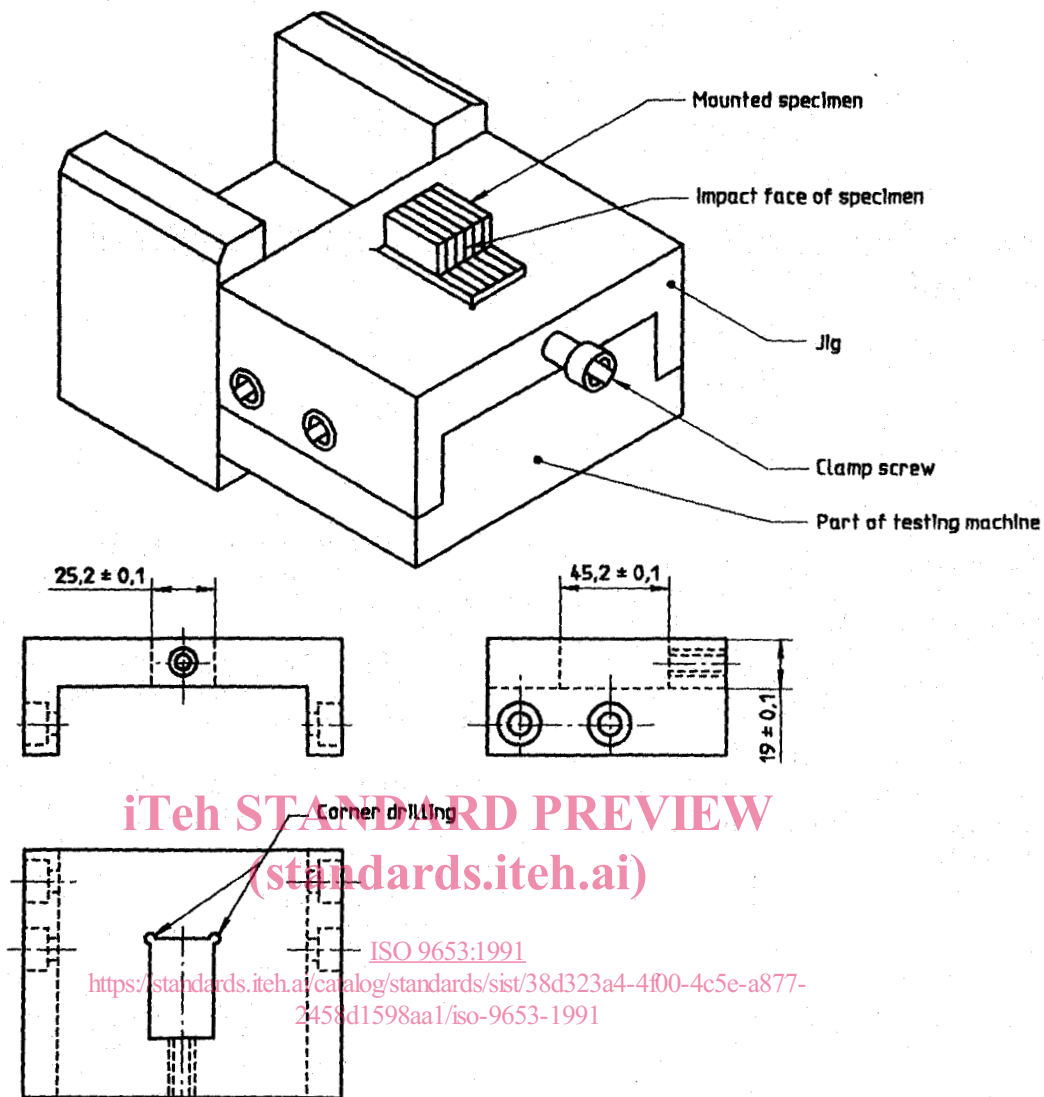


Figure 1 — Adapter fixture for impact machines

4.1.3 Vice or bolts, to hold the fixture firm and immobile under the stress of the testing-machine hammer. The total height of the vice fixture and specimen shall be such that the lower edge of the striking face of the impact head strikes the specimen as near the adhesive line as possible, preferably within 0,80 mm. Ordinarily, the distance between the top of the jaws of the vice of the machine and the bottom of the striking face of the head is 22 mm. The proper height of the specimen may be obtained by adjusting its height in the fixture.

NOTE 1 Additional information on impact-testing machines and their calibration may be found in ISO 178:1975, *Plastics — Determination of flexural properties of rigid plastics*, and ISO 179:1982, *Plastics — Determination of Charpy impact strength of rigid materials*.

4.2 Conditioning chamber, capable of maintaining a relative humidity of $(50 \pm 5) \%$ at $23 \text{ }^\circ\text{C} \pm 2 \text{ }^\circ\text{C}$.

NOTE 2 A saturated solution of calcium nitrate will give approximately 51 % relative humidity at the test temperature.

5 Specimens


5.1 The specimen for metal-to-metal adhesives shall conform to the dimensions given in figure 2 a) whenever possible. In cases where this specimen cannot be fractured in the testing machine available, the dimensions of the 25 mm by 25 mm block may be reduced to a smaller square, keeping the dimensions of the 25 mm by 45 mm block constant. The dimensions of the specimen and bonded area shall be clearly stated in the test report (clause 12). In any case, it is desirable that the specimen size

be such as to give impact strengths that fall somewhere near the middle range of the testing machine, since readings in the highest and lowest ranges are often unreliable. The specimen shall be assembled in such a way that the face receiving the impact load is at the point of maximum velocity of the impact head. The impact face of the specimen shall be

square and flat, perpendicular to the plane of the bond, and parallel to the striking face of the pendulum.


Tests on adhesives with high impact strength should be conducted on steel to minimize deformation. Specimens may be re-used after testing, provided that the face receiving the impact is not deformed.

Dimensions in millimetres

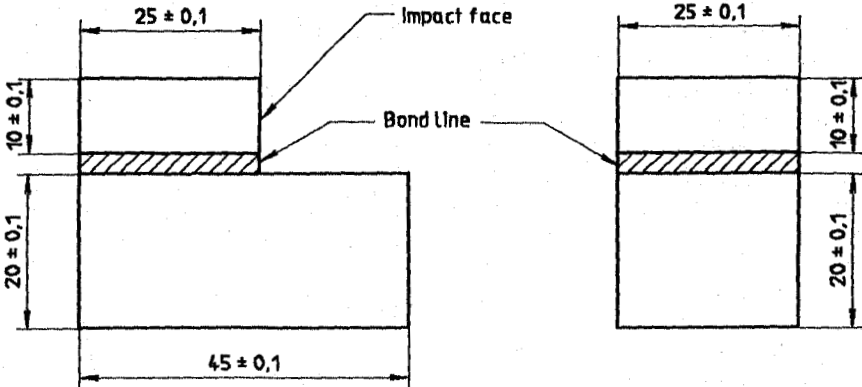

a) Metal-to-metal specimen

iTeh STANDARD PREVIEW
(standards.iteh.ai)

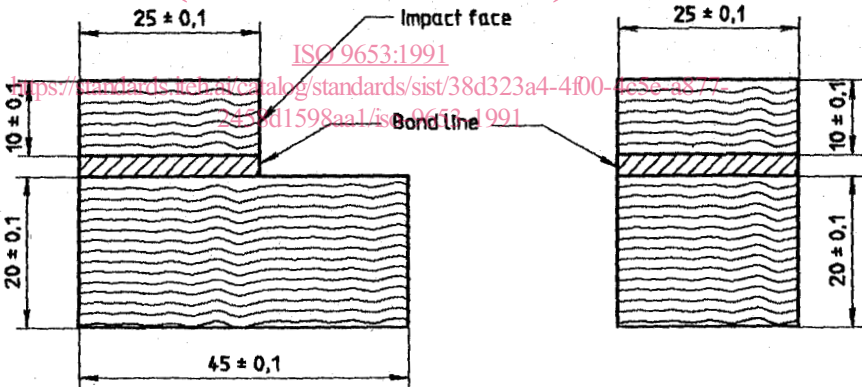

b) Wood-to-wood specimen showing grain direction

Figure 2 — Block shear impact specimen

5.2 Specimens for wood-to-wood adhesives shall conform to the dimensions shown in figure 2 b). The specimens shall be prepared by bonding blocks 10 mm thick by 25 mm wide, of convenient length, to blocks 20 mm thick by 45 mm wide, of the same convenient length, where the 25 mm and 45 mm dimensions, in each case, are those in the direction of the grain. Specimens, each 25 mm in width, may then be cut from the bonded assembly by cutting across the long dimension, in the grain direction. Wood having a minimum specific gravity of 0,65 based on oven-dry mass and volume shall be selected (see note 3). These blocks shall be of straight grain and free from defects, including knots, birdseye, short grain, decay, and any unusual discolorations within the test area. The blocks shall be at the equilibrium moisture content recommended by the manufacturer of the adhesive. In the absence of such recommendation, the moisture content shall be from 10 % to 12 %, based on oven-dry mass as determined on representative samples (see note 3). Just prior to bonding, the blocks shall be surfaced, preferably with a hand-feed jointer, and then weighed and assembled in pairs so that blocks of approximately the same specific gravity are bonded together. The surfaces shall remain unsanded and shall be free from dirt. Blocks shall be bonded as described in clause 7, after which specimens conforming to figure 2 b) shall be prepared.

NOTE 3 Suitable woods are listed in annex B of ISO 6237:1987, *Adhesives — Wood-to-wood adhesive bonds — Determination of shear strength by tensile loading*. In this annex, the moisture content determination process is described as well.

6 Number of specimens

6.1 At least 10 specimens shall be tested for each adhesive in the case of metal-to-metal specimens.

6.2 At least 20 specimens shall be tested, representing at least four different joints, in the case of wood-to-wood specimens.

6.3 Specimens that break at some obviously fortuitous flaw remote from the bond line shall be discarded and retests made, unless such flaws constitute a variable the effect of which it is desired to study.

7 Bonding

7.1 Bonding shall be in accordance with the procedure outlined by the manufacturer of the adhesive.

7.1.1 For metal-to-metal specimens, preparation of areas that are to be bonded shall be in accordance with the recommendations of the manufacturer of the adhesive.

7.1.2 For wood-to-wood specimens, the grain of the wood shall be parallel in the two pieces and parallel to the bond line, as shown in figure 2 b). If wood with a slight taper in the grain must be used, the pieces shall be assembled in such a way that the grain runs towards the bond line towards the back of the specimen. Thus, failures that start in the wood will be directed towards the bond line. Squeeze-out shall be removed when necessary to ensure proper positioning of the specimen in the fixture.

7.2 Excess adhesive at the impact face [see figure 2 a) and figure 2 b)] shall also be removed carefully to ensure proper striking of the impact head.

8 Conditioning

8.1 Preconditioning is not required for metal-to-metal bonds. The adhesive is ready for test purposes when it has been applied in accordance with clause 7, unless otherwise specified by the manufacturer or the purchaser.

8.2 All wood specimens shall be conditioned at a relative humidity of $(50 \pm 5) \%$, and at a temperature of $23 \text{ }^\circ\text{C} \pm 2 \text{ }^\circ\text{C}$ for a period of 7 days, or until specimens reach equilibrium as indicated by no progressive changes in mass, whichever is the shorter period.

8.3 Special conditioning procedures may be used by agreement between the manufacturer and the purchaser.

9 Procedure

9.1 Test in an atmosphere such that the moisture content of the wood specimens developed under the conditions prescribed in 8.2 is not noticeably altered during testing, and test as soon as possible after the conditioning period prescribed in 8.2.

9.2 Place the specimen in the fixture in the vice of the impact machine in such a way that the specimen butts squarely against the retaining end of the fixture. Rest the impact head of the machine gently against the specimen and adjust the fixture so that the head fits squarely against the impact face of the specimen.

9.3 Raise the impact head to a predetermined height and release the safety catch. The impact energy absorbed by the specimen may be read directly.

9.4 Record the following information:

9.4.1 Record, in joules, the energy absorbed in producing failure of the specimen.

9.4.2 Record the bonded area of the specimen.

9.4.3 In the case of metal-to-metal adhesives, record the percentages of cohesion, adhesion and contact failures. This will be based on visual inspection. Cohesion failure may be obtained by observing how much of the failure has occurred in the adhesive itself. That is, if the adhesive has adhered to the metal test pieces and no voids are visible, it represents a 100 % cohesion failure. Adhesion failure refers to the separation of adhesive layer from the metal being bonded. Contact failure refers to a lack of bond induced by uneven surfaces and poor pressure distribution.

9.4.4 In the case of wood-to-wood adhesives, record the percentages of wood failure, adhesive failure and contact failure. This will be based on visual inspection.

10 Expression of results

Calculate the impact value of the specimen as the energy absorbed in producing failure of the specimen divided by the bonded area of the specimen, and express in joules per square metre. Report the values to the nearest 100 J/m^2 . Unit results cannot be extended to surfaces different from those tested.

11 Precision

The precision of this test method is not known because inter-laboratory data are not available. When

inter-laboratory data are obtained, a precision statement will be added at the following revision.

12 Test report

The test report shall include the following:

- a) a reference to this International Standard;
- b) complete identification of the adhesive tested, including type, source, manufacturer's code numbers, form, etc.;
- c) the method used to prepare the specimens, the dimensions of the specimens and the materials bonded;
- d) the average thickness of the adhesive layer after formation of the joint, within 0,03 mm (the method of obtaining the thickness of the adhesive layer shall be described, including the procedure, location of measurements and range of measurements);
- e) the conditioning procedure used;
- f) the atmospheric conditions in the test chamber;
- g) the number of specimens tested;
- h) the actual bonded area;
- i) the maximum, minimum and average value of the impact strength, plus the average value of the percentages of wood, adhesive and contact failures for the wood specimens, or cohesion, adhesion and contact failures for the metal specimens.

iTech STANDARD PREVIEW
(standards.iteh.ai)
ISO 9653:1991
<https://standards.iteh.ai/catalog/standards/sist/38d3224e-419c-4591-8000-2458d1598aa1/iso-9653-1991>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 9653:1991

<https://standards.iteh.ai/catalog/standards/sist/38d323a4-4f00-4c5e-a877-2458d1598aa1/iso-9653-1991>

UDC 665.93:620.179.4

Descriptors: plastics, adhesives, tests, adhesion tests, impact tests, shear tests.

Price based on 5 pages
