
Penjeni polimerni materiali - Določevanje gorilnih lastnosti malih preskušancev, izpostavljenih majhnemu plamenu, s horizontalno metodo

Cellular plastics -- Determination of horizontal burning characteristics of small specimens subjected to a small flame

iTeh STANDARD PREVIEW

Plastiques alvéolaires -- Détermination des caractéristiques de combustion de petites éprouvettes en position horizontale, soumises à une petite flamme

[SIST ISO 9772:1996](https://standards.itih.ai/catalog/standards/sist/31c290e9-b958-4785-98a0-dc1c01ce466f/sist-iso-9772-1996)

Ta slovenski standard je istoveten z: ISO 9772:1994

ICS:

13.220.40	Sposobnost vžiga in obnašanje materialov in proizvodov pri gorenju	Ignitability and burning behaviour of materials and products
83.100	Penjeni polimeri	Cellular materials

SIST ISO 9772:1996**en**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST ISO 9772:1996

<https://standards.iteh.ai/catalog/standards/sist/31c290e9-b958-4785-98a0-dc1c01ce466f/sist-iso-9772-1996>

INTERNATIONAL
STANDARD

ISO
9772

First edition
1994-08-01

**Cellular plastics — Determination of
horizontal burning characteristics of small
specimens subjected to a small flame**

iTeh STANDARD PREVIEW

(standard.itih.ai)
*Plastiques alvéolaires — Détermination des caractéristiques de
combustion de petites éprouvettes en position horizontale, soumises à
une petite flamme*

SIST ISO 9772:1996

<https://standards.itih.ai/catalog/standards/sist/31c290e9-b958-4785-98a0-dc1c01ce466f/sist-iso-9772-1996>



Reference number
ISO 9772:1994(E)

ISO 9772:1994(E)**Contents**

	Page
1 Scope	1
2 Normative references	1
3 Definitions	1
4 Significance of test	2
5 Apparatus	2
6 Specimens	6
7 Conditioning	6
8 Test procedure	7
9 Calculations	9
10 Precision	9
11 Test report	10

Annex

A Classification system	11
--------------------------------------	-----------

ITeh STANDARD PREVIEW
(standards.iteh.ai)
 SIST ISO 9772:1996
<https://standards.iteh.ai/catalog/standards/sist/31c290e9-b958-4785-98a0-dc1c01ce466f/sist-iso-9772-1996>

© ISO 1994

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
 Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 9772 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 4, *Burning behaviour*.

Annex A of this International Standard is for information only.

<https://standards.iteh.ai/catalog/standards/sist/31c290e9-b958-4785-98a0-dc1c01ce466f/sist-iso-9772-1996>

iTeh STANDARD PREVIEW
This page intentionally left blank
(standards.iteh.ai)

SIST ISO 9772:1996

<https://standards.iteh.ai/catalog/standards/sist/31c290e9-b958-4785-98a0-dc1c01ce466f/sist-iso-9772-1996>

Cellular plastics — Determination of horizontal burning characteristics of small specimens subjected to a small flame

1 Scope

1.1 This International Standard specifies a small-scale laboratory screening procedure for comparing the relative burning characteristics of horizontally oriented, small cellular-plastic specimens having a density less than 250 kg/m³ determined in accordance with ISO 845, when exposed to a low-energy source of ignition.

NOTE 1 Another standard exists covering flexible cellular plastic and cellular rubber — ISO 3582:1978, *Cellular plastic and cellular rubber materials — Laboratory assessment of horizontal burning characteristics of small specimens subjected to a small flame*.

1.2 This method of test is intended for quality assurance and limited product evaluation of component cellular materials under controlled laboratory conditions, and is not intended to assess the fire behaviour of e.g. building materials or furnishings under actual fire conditions.

1.3 The optional classification system described in annex A is intended for the preselection of component materials for products.

1.4 The burning behaviour of cellular plastics is influenced by test specimen orientation (vertical or horizontal). This method of test evaluates specimens which are oriented horizontally.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publi-

cation, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 291:1977, *Plastics — Standard atmospheres for conditioning and testing*.

ISO 845:1988, *Cellular plastics and rubbers — Determination of apparent (bulk) density*.

ISO 1043-1:1987, *Plastics — Symbols — Part 1: Basic polymers and their special characteristics*.

ISO 1923:1981, *Cellular plastics and rubbers — Determination of linear dimensions*.

ISO 10093:—¹⁾, *Plastics — Fire tests — Standard ignition sources*.

3 Definitions

For the purposes of this International Standard, the following definitions apply.

3.1 afterflame time: The length of time for which a material continues to flame, under specified test conditions, after the ignition source has been removed.

3.2 afterglow time: The length of time for which a material continues to glow, under specified test conditions, after the ignition source has been removed and/or cessation of flaming.

1) To be published.

4 Significance of test

4.1 Tests conducted on a material under the conditions specified can be of considerable value when comparing the horizontal-burning characteristics of different materials, controlling manufacturing processes or assessing any changes in formulation or treatment prior to use.

4.2 Assessment of fire hazard requires consideration of such factors as fuel contribution, intensity of burning (rate of heat release), products of combustion and environmental factors such as intensity of source, orientation of exposed material and ventilation conditions.

4.3 Horizontal-burning characteristics, as measured by this test procedure, may be affected by such factors as density, any anisotropy of the cellular material, its melting characteristics, colour and the thickness.

4.4 Certain materials may shrink from the applied flame without igniting. In this event, test results are not valid and additional test specimens will be required to obtain 10 valid test results. If this proves impossible due to non-ignition of all the specimens, then this test is not suitable for these materials.

4.5 The horizontal-burning characteristics of some cellular-plastic materials may change with time and tests are therefore conducted before and after heat-ageing.

5 Apparatus

5.1 Laboratory fume hood (cupboard), having an inside volume of at least 0,5 m³. It shall permit observation and shall be draught-free while permitting normal thermal circulation of air past the specimen during burning. For safety and convenience, it is desirable to fit the enclosure with a device, such as an exhaust fan, to remove products of combustion that may be toxic. However, it is important to turn the device off during the actual test and start it again immediately after the test to remove the products of combustion.

NOTE 2 The amount of oxygen available to support combustion is naturally important for the conduct of these flame tests. For tests conducted by this method when

burning times are protracted, chamber sizes less than 1 m³ may not provide accurate results.

5.2 Laboratory burner, as specified in ISO 10093, designated P/PF2 and having a barrel length of 100 mm ± 10 mm and an internal diameter of 9,5 mm ± 0,3 mm. The barrel shall not be equipped with an end attachment, such as a stabilizer.

5.3 Burner wing top, having an opening of internal length 48 mm ± 1 mm and internal width 1,3 mm ± 0,05 mm (see figure 1).


5.4 Support gauze, approximately 215 mm long by 75 mm wide, having 13 mm of its length bent to form a right angle at one end as shown in figure 2. It shall consist of 6,4 mm mesh gauze constructed of 0,90 mm ± 0,05 mm diameter stainless-steel or low-carbon-steel wire. A different support gauze is necessary for each specimen unless means are provided to burn off any residue from a prior test.

5.5 Support-gauze holder, consisting of two laboratory ring stands with clamps adjustable to the desired angles and heights or a support-gauze holder constructed from aluminium or steel (see figure 3), and satisfying the following conditions:

- a) the long axis of the gauze is maintained to within 1° of the horizontal;
- b) the near end of the specimen is 13 mm ± 1 mm above the burner wing top (see figure 4);
- c) the space both above and below the specimen is not obstructed;
- d) a means is provided for positioning the burner in the correct location relative to the specimen, preferably with a sliding mechanism and a stop to allow fast movement of the burner flame towards and away from the specimen;
- e) the gauze is equidistant from the front and back, and from both sides, of the test chamber, and is 175 mm ± 10 mm above the base of the test chamber.

5.6 Two timing devices, accurate to 1 s.

5.7 Measuring scale, graduated in millimetres, to measure the length, width and thickness of the test specimen.

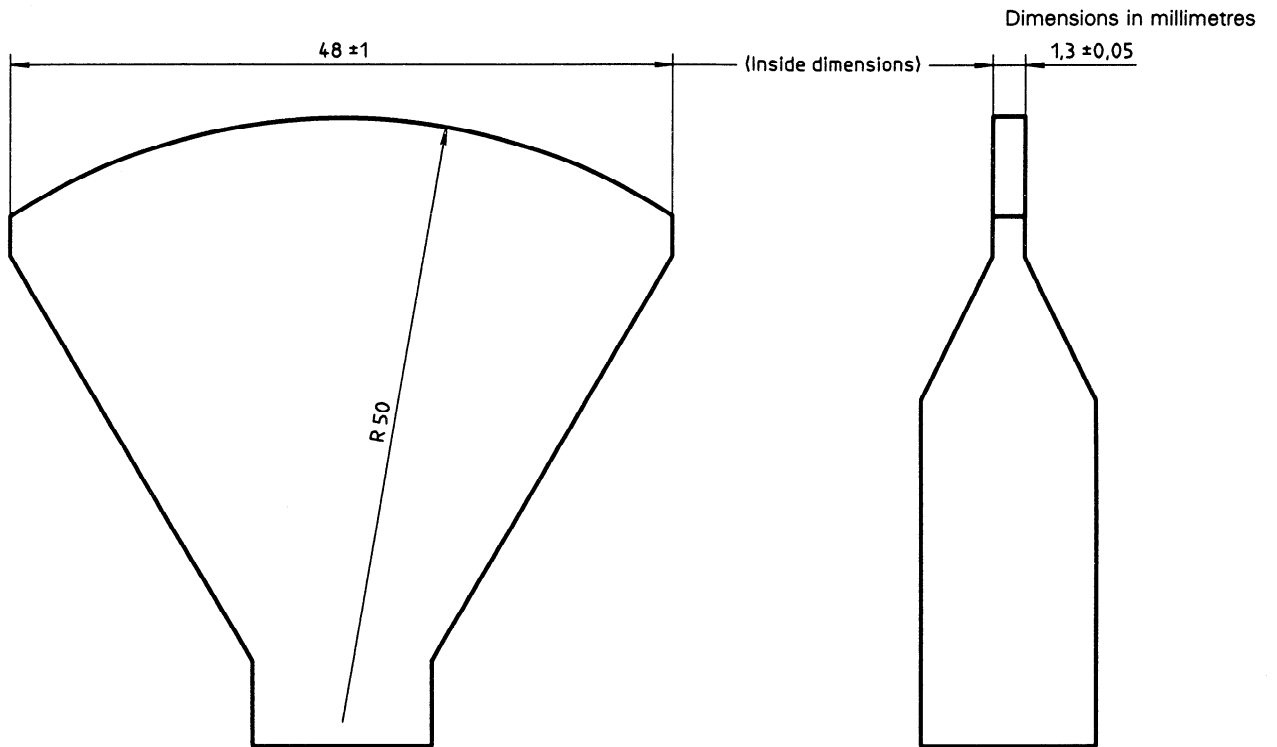

iTeh STANDARD PREVIEW
(standards.iteh.ai)



Material: copper or stainless steel

Figure 1 — Burner wing top (5.3)