



Standard Test Method for Tear-Propagation Resistance of Plastic Film and Thin Sheeting by a Single-Tear Method¹

This standard is issued under the fixed designation D 1938; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the determination of the force necessary to propagate a tear in plastic film and thin sheeting (thickness of 1 mm (0.04 in.) or less) by a single-tear method.

1.2 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

NOTE 1—This standard and ISO 6383-1 are technically equivalent. However, the specimen size is larger for ISO 6383-1.

2. Referenced Documents

2.1 ASTM Standards:

- D 374 Test Methods for Thickness of Solid Electrical Insulation²
- D 618 Practice for Conditioning Plastics and Electrical Insulating Materials for Testing³
- D 882 Test Methods for Tensile Properties of Thin Plastic Sheetings³
- D 883 Terminology Relating to Plastics³
- D 4000 Classification System for Specifying Plastic Materials⁴
- E 4 Practices for Load Verification of Testing Machines⁵
- E 691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method⁶

2.2 ISO Standard:

- ISO 6383-1 Film and Sheetings—Determination of Tear Resistance Part 1 Trouser Tear Method⁷

¹ This test method is under the jurisdiction of ASTM Committee D-20 on Plastics and is the direct responsibility of Subcommittee D20.10 on Mechanical Properties. Current edition approved Feb. 15, 1994. Published April 1994. Originally published as D 1938 – 62 T. Last previous edition D 1938 – 93.

² Annual Book of ASTM Standards, Vol 10.01.

³ Annual Book of ASTM Standards, Vol 08.01.

⁴ Annual Book of ASTM Standards, Vol 08.02.

⁵ Annual Book of ASTM Standards, Vol 03.01.

⁶ Annual Book of ASTM Standards, Vol 14.02.

⁷ Available from American National Standards Institute, 11 W. 42nd St., 13th Floor, New York, NY 10036.

3. Terminology

3.1 *Definitions:* Definitions of terms applying to this test method appear in Terminology D 883.

4. Summary of Test Method

4.1 The force to propagate a tear across a film or sheeting specimen is measured using a constant-rate-of-grip separation machine as described in Method A of Test Methods D 882. The force necessary to propagate the tear is interpreted from the load-time chart.

5. Significance and Use

5.1 This test method is of value in rating the tear-propagation force of various plastic films and thin sheeting of comparable thickness. The tear-propagation resistance in highly extensible film or sheeting is distinguished from the tear-propagation resistance in slightly extensible or nonextensible film or sheeting in Fig. 1 and Fig. 2 in 10.1 and 10.2, respectively.

5.2 This test method should be used for specification acceptance testing only after it has been demonstrated that the data for the particular material are acceptably reproducible.

5.3 The data obtained by this test method furnish information for ranking the tear-propagation resistance of plastic films and sheeting of similar composition. Actual use performance may not necessarily correlate with data from this test method. Sets of data from specimens of dissimilar thickness are usually not comparable.

5.4 For many materials, there may be a specification that requires the use of this test method, but with some procedural modifications that take precedence when adhering to the specification. Therefore, it is advisable to refer to that material specification before using this test method. Table 1 of Classification System D 4000 lists the ASTM materials standards that currently exist.

6. Apparatus

6.1 *Film-Testing Machine*, with a force-indicating head that can measure the load applied to tear the specimen. It should be equipped with a device for recording the load carried by the specimen and the amount of separation of the grips during the test. The testing machine shall be essentially free from inertia lag at the specified rate of testing and shall indicate the load



FIG. 1 Load-Time Chart for Low-Extensible Film

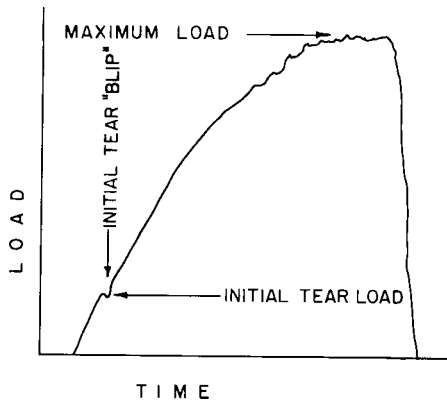


FIG. 2 Load-Time Chart for Highly Extensible Film

with an accuracy of $\pm 2\%$ of the indicated value or better. The accuracy of the testing machine shall be verified in accordance with Practices E 4. A device shall be included to control the grip-separation rate at $250 \text{ mm (10 in.)} \pm 5\%/ \text{min}$.

6.2 *Thickness-Measuring Devices*, in accordance with Test Methods D 374 or a method of equivalent accuracy.

6.3 *Cutter*—A sharp razor blade or the equivalent.

6.4 *Conditioning Apparatus*, in accordance with Procedure A of Practice D 618.

7. Test Specimens

7.1 The specimens shall be of the single-tear type and shall consist of strips 75 mm (3 in.) long by 25 mm (1 in.) wide and shall have a clean longitudinal slit $50 \text{ mm (2 in.)} \pm 2\%$ long cut with a sharp razor blade (Fig. 3) or the equivalent.

NOTE 2—The thickness of the test specimens shall be uniform to within 5% of the thickness over the length of the unslit portion of the specimen.

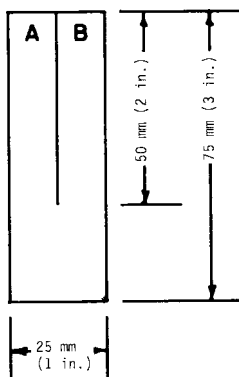


FIG. 3 Single-Tear Specimen

7.2 Measure the thickness of the specimen below the slit (see Fig. 3) in several places and record it in millimetres to the nearest $0.0025 \text{ mm (0.0001 in.)}$.

7.3 Cut enough specimens to provide a minimum of five tear-propagation force determinations each in the machine direction and in the transverse direction of the material being tested.

8. Conditioning

8.1 *Conditioning*—Condition the test specimens at $23 \pm 2^\circ\text{C (73.4} \pm 3.6^\circ\text{F)}$ and $50 \pm 5\%$ relative humidity for not less than 40 h prior to test in accordance with Procedure A of Practice D 618, for those tests where conditioning is required. In cases of disagreement, the tolerances shall be $\pm 1^\circ\text{C (}\pm 1.8^\circ\text{F)}$ and $\pm 2\%$ relative humidity.

8.2 *Test Conditions*—Conduct tests in the standard laboratory atmosphere of $23 \pm 2^\circ\text{C (73.4} \pm 3.6^\circ\text{F)}$ and $50 \pm 5\%$ relative humidity, unless otherwise specified in the test methods. In cases of disagreement, the tolerances shall be $\pm 1^\circ\text{C (}\pm 1.8^\circ\text{F)}$ and $\pm 2\%$ relative humidity.

9. Procedure

9.1 Secure Tongue A (Fig. 3) in one grip and Tongue B in the other grip of the constant-rate-of-grip separation-testing machine, using an initial grip separation of 50 mm (2 in.) . Align the specimen so that its major axis coincides with an imaginary line joining the centers of the grips.

9.2 Using a grip-separation speed of $250 \text{ mm (10 in.)/min}$, start the machine, and record the load necessary to propagate the tear through the entire unslit 25-mm (1-in.) portion.

9.3 Test not less than five specimens in each of the principal film or sheeting directions.

10. Calculation

10.1 For thin films and sheeting that have load-time charts characterized by Fig. 1, obtain the average tear propagation force by averaging the load indicated on the chart over the time period, disregarding the initial and final portions of the curve. This can be done with an integrator or a planimeter. In some cases, a fairly accurate estimate can be made by eye.

10.2 For thin films and sheeting that have load-time charts characterized by Fig. 2, obtain and report the initial force to continue the propagation of the slit and the maximum force from the chart. The initial force may be more readily detected by placing a dot approximately $3 \text{ mm (}\frac{1}{8} \text{ in.)}$ in a diameter at the base of the razor-blade slit with a china-marking wax pencil. As the load is applied to the sample, observe the dot area. When the load is just sufficient to begin the extension of the slit, introduce a “blip” on the chart (see Fig. 2) by pushing the appropriate button on the recorder or the equivalent to mark this point. The maximum load is the highest reading on the chart. Report both the initial load and the maximum load.

10.3 For each series of tests, report the mean of all values obtained to three significant figures and as the mean value of the particular property.

10.4 Calculate the estimated standard deviation as follows and report to the significant figures:

$$s = \sqrt{(\sum X^2 - n\bar{X}^2)/(n - 1)}$$