



**SLOVENSKI STANDARD**  
**SIST ISO 10251:2000**  
**01-junij-2000**

---

**Koncentrati sulfidov bakra, svinca in cinka - Ugotavljanje izgube mase nasutega materiala pri sušenju**

Copper, lead and zinc sulfide concentrates -- Determination of mass loss of bulk material on drying

**iTeh STANDARD PREVIEW**

Concentrés sulfurés de cuivre, de plomb et de zinc -- Détermination de la perte de masse au séchage du matériau en vrac

[SIST ISO 10251:2000](https://standards.iteh.ai/catalog/standards/sist/8cde3ef1-0693-455f-9176-5282875f4467/sist-iso-10251-2000)

**Ta slovenski standard je istoveten z: ISO 10251:1997**

---

**ICS:**

73.060.99      Druge rude      Other metalliferous minerals

**SIST ISO 10251:2000**      **en**

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[SIST ISO 10251:2000](#)

<https://standards.iteh.ai/catalog/standards/sist/8cde3ef4-0693-455f-9176-5282895f4467/sist-iso-10251-2000>

# INTERNATIONAL STANDARD

**ISO**  
**10251**

First edition  
1997-12-15

---

---

## **Copper, lead and zinc sulfide concentrates — Determination of mass loss of bulk material on drying**

*Concentrés sulfurés de cuivre, de plomb et de zinc — Détermination  
de la perte de masse au séchage du matériau en vrac*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[SIST ISO 10251:2000](https://standards.iteh.ai/catalog/standards/sist/8cde3ef4-0693-455f-9176-5282895f4467/sist-iso-10251-2000)

<https://standards.iteh.ai/catalog/standards/sist/8cde3ef4-0693-455f-9176-5282895f4467/sist-iso-10251-2000>



Reference number  
ISO 10251:1997(E)

**ISO 10251:1997(E)****Foreword**

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 10251 was prepared by Technical Committee ISO/TC 183, *Copper, lead and zinc ores and concentrates*.

Annexes A and B form an integral part of this International Standard. Annex C is for information only.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST ISO 10251:2000

<https://standards.iteh.ai/catalog/standards/sist/8cde3ef4-0693-455f-9176-5282895f4467/sist-iso-10251-2000>

© ISO 1997

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization  
Case postale 56 • CH-1211 Genève 20 • Switzerland  
Internet central@iso.ch  
X.400 c=ch; a=400net; p=iso; o=isocs; s=central

Printed in Switzerland

## Introduction

Reference to the percentage mass loss as moisture content is appropriate, because, although oxidation, decomposition or sublimation of elemental sulfur may contribute, most of the mass loss on drying is due to loss of moisture.

When oxidation, decomposition or sublimation of elemental sulfur has been shown to occur or volatile organic flotation reagents such as kerosene are present, the chemical analysis test sample should be prepared from the dried moisture test portions. Under these circumstances, the sampling scheme established in accordance with ISO 12743 must ensure that moisture samples and test portions are sufficiently representative for subsequent chemical analysis. When oxidation is a problem, an inert atmosphere may also be used during the drying stage. Annex A provides a procedure by which it can be determined whether or not a concentrate is susceptible to oxidation, decomposition or sublimation.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST ISO 10251:2000](https://standards.iteh.ai/catalog/standards/sist/8cde3ef4-0693-455f-9176-5282895f4467/sist-iso-10251-2000)

<https://standards.iteh.ai/catalog/standards/sist/8cde3ef4-0693-455f-9176-5282895f4467/sist-iso-10251-2000>

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST ISO 10251:2000

<https://standards.iteh.ai/catalog/standards/sist/8cde3ef4-0693-455f-9176-5282895f4467/sist-iso-10251-2000>

# Copper, lead and zinc sulfide concentrates — Determination of mass loss of bulk material on drying

## 1 Scope

This International Standard specifies methods for the determination of moisture content of a lot of copper, lead or zinc sulfide concentrate, defined as the percentage mass loss of the moisture test portion under the conditions of drying specified in this document.

NOTE 1 In order to obtain an unbiased estimate of the metal content of the lot, it is important that the same drying conditions are used for the determination of bulk and hygroscopic moisture or for preparing a predried test portion.

This International Standard is not applicable to drying samples used for determination of volatile elements such as mercury and sulfur. Such samples are allowed to dry at ambient temperature and a hygroscopic moisture determination is carried out in accordance with ISO 9599 at the time of chemical analysis.

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)

## 2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 9599: 1991, *Copper lead and zinc sulfide concentrates — Determination of hygroscopic moisture in the analysis sample — Gravimetric method.*

ISO 12743:—<sup>1)</sup>, *Copper, lead and zinc sulfide concentrates — Sampling procedures for determination of metal and moisture content.*

## 3 Definitions

For the purposes of this International Standard, the following definitions apply.

**3.1 representative sample:** A quantity of concentrate representing a larger mass of concentrate with both precision and bias within acceptable limits.

**3.2 lot:** A quantity of concentrate to be sampled.

**3.3 lot sample:** A quantity of concentrate which is representative of the lot.

<sup>1)</sup> To be published.

**3.4 sub-lot:** Subdivided parts of a lot which are processed separately, each of them producing a subsample which is analysed separately, e.g. for moisture determination.

**3.5 subsample:** A quantity of concentrate which is representative of the sub-lot.

**3.6 increment:** A quantity of concentrate selected by a sampling device in one operation.

**3.7 moisture sample:** A representative quantity of concentrate from which test portions are taken for moisture determination.

NOTE 2 Alternatively, the whole moisture sample may be dried to determine its moisture content.

**3.8 laboratory sample:** A sample that is processed so that it can be sent to the laboratory and used for further processing and selection of one or more test samples for chemical analysis.

**3.9 common sample:** A representative quantity of concentrate that is dried to determine its mass loss and subsequently used for further processing and selection of one or more test samples for chemical analysis.

**3.10 test sample:** A representative quantity of concentrate obtained for a laboratory sample when additional preparation, such as drying or hygroscopic moisture determination, is needed prior to selection of one or more test portions.

**3.11 test portion:** A representative quantity of concentrate taken from a moisture sample, a laboratory sample or a test sample which is submitted to moisture determination or analysis in its entirety.

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

## 4 Drying method

[SIST ISO 10251:2000](https://standards.iteh.ai/catalog/standards/sist/8cde3ef4-0693-455f-9176-5282895f4467/sist-iso-10251-2000)

### 4.1 General

<https://standards.iteh.ai/catalog/standards/sist/8cde3ef4-0693-455f-9176-5282895f4467/sist-iso-10251-2000>

Test portions are dried at  $105\text{ °C} \pm 5\text{ °C}$  until constant mass is obtained and the moisture content determined as the percentage mass loss on drying. However, drying to constant mass can be difficult or impossible if the concentrate is susceptible to oxidation, decomposition or sublimation of elemental sulfur or volatile organic flotation reagents such as kerosene are present (see annex A). Under these circumstances, a common sample for moisture determination and chemical analysis, drying in an inert atmosphere, or interruption of drying is applied. If a common sample is used, the moisture samples and test portions must be sufficiently representative for subsequent chemical analysis.

One of the following drying methods is selected to suit the particular concentrate. A flowsheet for selecting the correct drying method is given in figure 1.



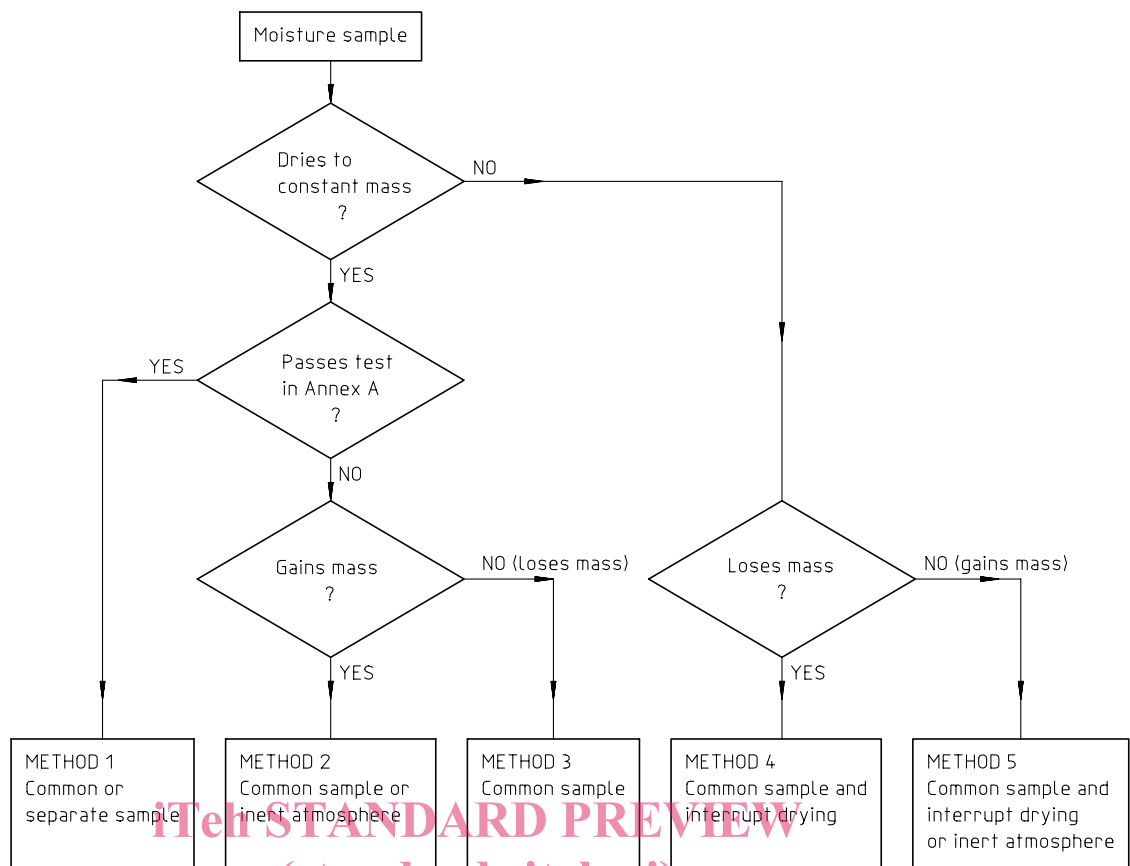


Figure 1 - Procedure for selection of appropriate drying method

SIST ISO 10251:2000

#### 4.2 Method 1

<https://standards.iteh.ai/catalog/standards/sist/8cde3ef4-0693-455f-9176-5282895f4467/sist-iso-10251-2000>

Where the test portion can be dried to constant mass and the concentrate passes the test in annex A, a separate sample for moisture determination or a common sample is dried to constant mass.

#### 4.3 Method 2

Where the test portion can be dried to constant mass, but the test in annex A results in a higher mass, indicating that the concentrate is susceptible to oxidation, moisture and chemical analysis samples are dried to constant mass in an inert atmosphere, or a common sample is dried to constant mass.

#### 4.4 Method 3

Where the test portion can be dried to constant mass, but the test in annex A results in a lower mass, indicating that the concentrate may be losing organics over an extended period, a common sample is dried to constant mass.

#### 4.5 Method 4

Where the test portion cannot be dried to constant mass and continues to lose mass over long periods, indicating that the concentrate may be losing hydrated water, decomposing or subliming, a common sample is used, with interruption of drying after a period determined in accordance with clause 8 for each concentrate type and no further drying prior to analysis.