

# INTERNATIONAL STANDARD

# NORME INTERNATIONALE



BASIC SAFETY PUBLICATION

PUBLICATION FONDAMENTALE DE SÉCURITÉ

**Fire hazard testing – Part 10-2: Abnormal heat – Ball pressure test method**  
**STANDARD PREVIEW**  
(standards.iteh.ai)

**Essais relatifs aux risques du feu –**  
**Partie 10-2: Chaleurs anormales – Essai à la bille**  
IEC 60695-10-2:2014  
<https://standards.iteh.ai/catalog/standards/sist/ac1a0c80-93a7-41c7-9af9-57d97bc8430a/iec-60695-10-2-2014>



## THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2014 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de l'IEC ou du Comité national de l'IEC du pays du demandeur. Si vous avez des questions sur le copyright de l'IEC ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de l'IEC de votre pays de résidence.

IEC Central Office  
3, rue de Varembe  
CH-1211 Geneva 20  
Switzerland

Tel.: +41 22 919 02 11  
Fax: +41 22 919 03 00  
[info@iec.ch](mailto:info@iec.ch)  
[www.iec.ch](http://www.iec.ch)

### About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

### About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

#### IEC Catalogue - [webstore.iec.ch/catalogue](http://webstore.iec.ch/catalogue)

The stand-alone application for consulting the entire bibliographical information on IEC International Standards, Technical Specifications, Technical Reports and other documents. Available for PC, Mac OS, Android Tablets and iPad.

#### IEC publications search - [www.iec.ch/searchpub](http://www.iec.ch/searchpub)

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, replaced and withdrawn publications.

#### IEC Just Published - [webstore.iec.ch/justpublished](http://webstore.iec.ch/justpublished)

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and also once a month by email.

#### Electropedia - [www.electropedia.org](http://www.electropedia.org)

The world's leading online dictionary of electronic and electrical terms containing more than 30 000 terms and definitions in English and French, with equivalent terms in 14 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

#### IEC Glossary - [std.iec.ch/glossary](http://std.iec.ch/glossary)

More than 55 000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

#### IEC Customer Service Centre - [webstore.iec.ch/csc](http://webstore.iec.ch/csc)

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: [csc@iec.ch](mailto:csc@iec.ch).

### A propos de l'IEC

La Commission Electrotechnique Internationale (IEC) est la première organisation mondiale qui élabore et publie des Normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

### A propos des publications IEC

Le contenu technique des publications IEC est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

#### Catalogue IEC - [webstore.iec.ch/catalogue](http://webstore.iec.ch/catalogue)

Application autonome pour consulter tous les renseignements bibliographiques sur les Normes internationales, Spécifications techniques, Rapports techniques et autres documents de l'IEC. Disponible pour PC, Mac OS, tablettes Android et iPad.

#### Recherche de publications IEC - [www.iec.ch/searchpub](http://www.iec.ch/searchpub)

La recherche avancée permet de trouver des publications IEC en utilisant différents critères (numéro de référence, texte, comité d'études,...). Elle donne aussi des informations sur les projets et les publications remplacées ou retirées.

#### IEC Just Published - [webstore.iec.ch/justpublished](http://webstore.iec.ch/justpublished)

Restez informé sur les nouvelles publications IEC. Just Published détaille les nouvelles publications parues. Disponible en ligne et aussi une fois par mois par email.

#### Electropedia - [www.electropedia.org](http://www.electropedia.org)

Le premier dictionnaire en ligne de termes électroniques et électriques. Il contient plus de 30 000 termes et définitions en anglais et en français, ainsi que les termes équivalents dans 14 langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International (IEV) en ligne.

#### Glossaire IEC - [std.iec.ch/glossary](http://std.iec.ch/glossary)

Plus de 55 000 entrées terminologiques électrotechniques, en anglais et en français, extraites des articles Termes et Définitions des publications IEC parues depuis 2002. Plus certaines entrées antérieures extraites des publications des CE 37, 77, 86 et CISPR de l'IEC.

#### Service Clients - [webstore.iec.ch/csc](http://webstore.iec.ch/csc)

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions contactez-nous: [csc@iec.ch](mailto:csc@iec.ch).



IEC 60695-10-2

Edition 3.0 2014-02

# INTERNATIONAL STANDARD

## NORME INTERNATIONALE



BASIC SAFETY PUBLICATION

PUBLICATION FONDAMENTALE DE SÉCURITÉ

**Fire hazard testing – Part 10-2: Abnormal heat – Ball pressure test method**  
**STANDARD PREVIEW**  
(standards.iteh.ai)

**Essais relatifs aux risques du feu – Partie 10-2: Chaleurs anormales – Essai à la bille**  
IEC 60695-10-2:2014  
http://standards.iteh.ai/catalog/standards/sist/80-93a7-41c7-9af9-57d97bc8430a/iec-60695-10-2-2014

INTERNATIONAL  
ELECTROTECHNICAL  
COMMISSION

COMMISSION  
ELECTROTECHNIQUE  
INTERNATIONALE

PRICE CODE  
CODE PRIX

P

ICS 13.220.40, 29.020

ISBN 978-2-8322-1393-3

**Warning! Make sure that you obtained this publication from an authorized distributor.**  
**Attention! Veuillez vous assurer que vous avez obtenu cette publication via un distributeur agréé.**

## CONTENTS

FOREWORD.....	3
INTRODUCTION.....	5
1 Scope.....	6
2 Normative references .....	6
3 Terms and definitions .....	7
4 General description of the test method .....	7
5 Apparatus.....	7
5.1 Loading device.....	7
5.2 Test specimen support.....	8
5.3 Heating oven .....	8
5.4 Optical measuring instrument.....	9
5.5 Temperature measuring equipment.....	9
6 Test specimens .....	9
6.1 End product test method .....	9
6.2 Material Test method .....	9
6.2.1 Test specimen preparation .....	9
6.2.2 Test specimen dimensions.....	9
7 Conditioning .....	9
8 Test procedure .....	10
8.1 Selection of the test temperature.....	10
8.1.1 Method A – End product test method.....	10
8.1.2 Method B – Material performance test method .....	10
8.2 Heating oven and test apparatus setup .....	11
8.3 Test setup.....	11
8.4 Test specimen post conditioning .....	11
8.5 Measurements .....	12
9 Evaluation of test results .....	12
10 Information to be given in the relevant product standard .....	13
11 Test Report .....	13
Annex A (informative) Correlation between the ball pressure test and the Vicat test of ISO 306 .....	14
Annex B (informative) Depth indentation method .....	15
Bibliography.....	16
Figure 1 – Loading device (example) .....	8
Figure 2 – Measurement of dimension $d$ (example) .....	12
Table 1 – Suggested initial test temperatures .....	10

## INTERNATIONAL ELECTROTECHNICAL COMMISSION

## FIRE HAZARD TESTING –

## Part 10-2: Abnormal heat – Ball pressure test method

## FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.  
<http://standards.iteh.ai/catalog/standards/sist/60695-10-2/iec-60695-10-2:2014>
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 60695-10-2 has been prepared by IEC technical committee 89: Fire hazard testing.

This third edition cancels and replaces the second edition of IEC 60695-10-2 published in 2003. It constitutes a technical revision.

It has the status of a basic safety publication in accordance with IEC Guide 104 and ISO/IEC Guide 51.

The main changes with respect to the previous edition are listed below:

- The addition of an introduction introduces the user to the basic guidance documents published by TC 89
- Addition of a reference to IEC Guide 104 and ISO/IEC Guide 51 in the Scope
- Additional relevant Terms and Definitions in new Clause 3

- 5.2: Additional requirements to the test specimen support at the suggestion of IECEE-CTL to improve reproducibility
- 5.3: Clarification of heating oven requirements at the suggestion of IECEE-CTL to improve reproducibility
- 5.4: Specification of minimum resolution consistent with method requirements for optical measurement instrument
- New Test Procedure in in Clauses 6 and 8 which introduces separate methods for End Product proof testing (Method A) and material performance testing (Method B)
- Updated Clause 11 Test Report to be consistent with other IEC 60695 documents.

The text of this standard is based on the following documents:

FDIS	Report on voting
89/1203/FDIS	89/1210/RVD

Full information on the voting for the approval of this standard can be found in the report on voting indicated in the above table.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all the parts in the IEC 60695 series, under the general title *Fire hazard testing*, can be found on the IEC web site.

The committee has decided that the contents of this publication will remain unchanged until the stability date indicated on the IEC web site under "http://webstore.iec.ch" in the data related to the specific publication. At this date, the publication will be

IEC 60695-10-2:2014

- reconfirmed, <https://standards.iteh.ai/catalog/standards/sist/aefa6e80-93a7-41c7-9a9f-57d97bc8430a/iec-60695-10-2-2014>
- withdrawn,
- replaced by a revised edition, or
- amended.

**IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.**

## INTRODUCTION

In the design of any electrotechnical product, the risk of abnormal heat and the potential hazards associated with abnormal heat need to be considered. In this respect the objective of component, circuit, and product design, as well as the choice of materials, is to reduce to acceptable levels the potential risks during normal operating conditions, reasonable foreseeable abnormal use, malfunction and/or failure. IEC/TC 89 has developed IEC 60695-1-10, together with its companion, IEC 60695-1-11, to provide guidance on how this is to be accomplished.

The primary aims of IEC 60695-1-10 and IEC 60695-1-11 are to provide guidance on how:

- a) to prevent ignition caused by an electrically energized component part, and
- b) to confine any resulting fire within the bounds of the enclosure of the electrotechnical product in the event of ignition.

Secondary aims of IEC 60695-1-10 and IEC 60695-1-11 include the minimization of any flame spread beyond the product's enclosure and the minimization of the harmful effects of fire effluents such as heat, smoke, toxicity and/or corrosivity.

Fires involving electrotechnical products can also be initiated from external non-electrical sources. Considerations of this nature should be dealt with in the overall fire hazard assessment.

This part of IEC 60695 describes a test method where the softening and accelerated material flow under load of a polymeric material is evaluated using a weighted ball-bearing in a heating oven. It should be used to measure, describe, and rank a property of a material in response to elevated temperatures under controlled laboratory conditions. This may be useful for the evaluation of materials for use in products that may be exposed to excess thermal stress. It should also be used for the evaluation of materials used in end products. It should not be used to solely describe or appraise the fire hazard or fire risk of materials, products, or assemblies under actual abnormal conditions. However, results of this test method may be used as elements of a fire hazard assessment which takes into account all of the factors pertinent to a particular end use.

This International Standard may involve hazardous materials, operations, and equipment. It does not purport to address all of the safety problems associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

## FIRE HAZARD TESTING –

### Part 10-2: Abnormal heat – Ball pressure test method

#### 1 Scope

This part of IEC 60695 specifies the ball pressure test as a method for evaluating the softening temperature and accelerated material flow under load of polymeric materials and parts of end products in their ability to resist abnormal heat. It is applicable to the materials used in electrotechnical equipment, subassemblies and components, and to solid electrical insulating materials except ceramics.

NOTE The Ball Pressure test method is not appropriate for certain elastomers, foamed materials, and other materials that tend to be soft at room temperature. Product Committees are encouraged to evaluate these materials using other methods such as IEC 60695-10-3.

This basic safety publication is intended for use by technical committees in the preparation of standards in accordance with the principles laid down in IEC Guide 104 and ISO/IEC Guide 51.

One of the responsibilities of a technical committee is, wherever applicable, to make use of basic safety publications in the preparation of its publications. The requirements, test methods or test conditions of this basic safety publication will not apply unless specifically referred to or included in the relevant publications.

#### 2 Normative references

[IEC 60695-10-2:2014](https://standards.iteh.ai/catalog/standards/sist/aefa6e80-93a7-41c7-9a9f-57d97bc8430a/iec-60695-10-2-2014)

<https://standards.iteh.ai/catalog/standards/sist/aefa6e80-93a7-41c7-9a9f-57d97bc8430a/iec-60695-10-2-2014>

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60216-4-1, *Electrical insulating materials – Thermal endurance properties – Part 4-1: Ageing ovens – Single-chamber ovens*

ISO/IEC 13943:2008, *Fire safety – Vocabulary*

ISO 3290-1, *Rolling bearings – Balls – Part 1: Steel balls*

IEC Guide 104, *The preparation of safety publications and the use of basic safety publications and group safety publications*

ISO/IEC Guide 51, *Safety aspects – Guidelines for inclusion in standards*

ISO 293, *Plastics – Compression moulding of test specimens of thermoplastic materials*

ISO 294 (All Parts), *Plastics – Injection moulding of test specimens of thermoplastic materials*

ISO 295, *Plastics – Compression moulding of test specimens of thermosetting materials*



### 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO/IEC 13943:2008, one of which is reproduced below for the users' convenience, as well as the following apply.

#### 3.1

##### **abnormal heat**

<electrotechnical> heat that is additional to that resulting from use under normal conditions, up to and including that which causes a fire

[SOURCE: ISO/IEC 13943:2008, definition 4.1]

#### 3.2

##### **end product**

product that is ready for use without modification

Note 1 to entry: An end product can be a component of another end product.

[SOURCE: IEC 60695-4:2012, definition 3.2.7]

#### 3.3

##### **proof test**

any predetermined and specified test required of an end product to verify its suitability for its intended purpose

### 4 General description of the test method


To measure and to verify the dimension  $d$  of the indentation left by a steel ball applied on a test specimen with a specified force and at a specified temperature.

### 5 Apparatus

#### 5.1 Loading device

The loading device shall consist of a  $5 \text{ mm} \pm 0,05 \text{ mm}$  diameter pressure ball (a finished steel ball for rolling bearings in accordance with ISO 3290-1) attached to a system of weights designed to apply a downward force equivalent to a  $20 \text{ N} \pm 0,2 \text{ N}$  load including the mass of the pressure ball.

An example of a typical loading device is shown in Figure 1.

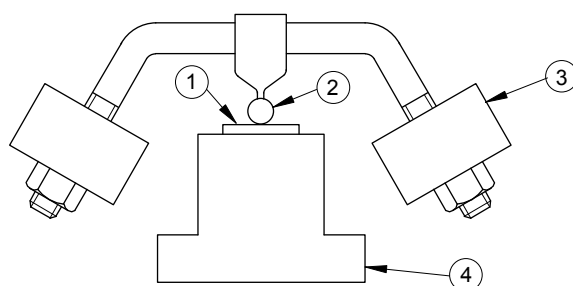


IEC 0314/14

**Key**

- 1 Test specimen
- 2 Pressure ball
- 3 Weight
- 4 Test specimen support

**Figure 1a**

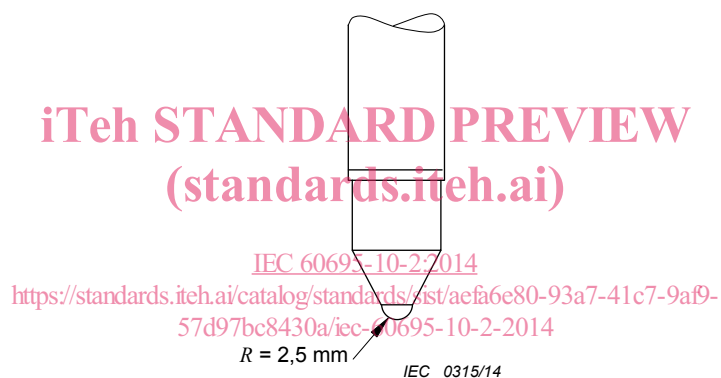

**Figure 1b**

**Figure 1 – Loading device (example)**

**5.2 Test specimen support**

The test specimen support shall be such that

- a) it rigidly supports the test specimen in a horizontal position;
- b) it has sufficient strength to support the loading device;
- c) it has a smooth flat surface;
- d) it has sufficiently large mass to prevent a significant reduction in temperature of the apparatus during the installation and removal of the test specimen from the heating oven.

NOTE It has been found useful to mount a separate thermocouple in the centre of the test specimen support approximately 3 mm below the surface to check that the temperature of the test specimen support does not significantly deviate from the test temperature.

**5.3 Heating oven**

The heating oven shall be a single chamber type in accordance with IEC 60216-4-1 with regard to temperature differences, fluctuation, and variations appropriate to the test temperature.

In addition, the heating oven shall be capable of returning to the set temperature in accordance with the requirements in 8.3 after the heating oven door is closed after inserting the test specimen.

#### 5.4 Optical measuring instrument

The optical measuring instrument shall have an optical magnification of at least  $10\times$  and shall incorporate a calibrated reticule or cross-travel measuring table with a resolution of not more than 0,1 mm. A lighting device can be used to illuminate the surface where the pressure ball was applied.

#### 5.5 Temperature measuring equipment

The temperature shall be measured using equipment with a accuracy of  $\pm 2$  K below 100 °C and  $\pm 3$  % at 100 °C and above. It is preferable to measure the temperature by a thermocouple type K or J inserted in the test specimen support.

### 6 Test specimens

#### 6.1 End product test method

A test specimen is cut from the end product in such a way that a piece at least 2,5 mm thick with approximately parallel upper and lower surfaces is obtained. If necessary, the thickness may be attained by stacking two or more sections so long as there is no noticeable movement between the surfaces prior to testing. If it is not possible to cut a test specimen with parallel surfaces, care shall be taken to support the area of the test specimen directly under the pressure ball. The test specimen shall be a square with a minimum of 10 mm sides or a circle with a diameter of at least 10 mm.

IEC 60695-10-2:2014

If it is impracticable to use a test specimen from the end product, then a plaque of identical material may be used as the test specimen as described in 6.2.

NOTE Three test specimens may be necessary.

#### 6.2 Material Test method

##### 6.2.1 Test specimen preparation

Test specimens shall be fabricated using the appropriate ISO method, e.g. casting and injection moulding in accordance with the ISO 294 series, compression moulding in accordance with ISO 293 or ISO 295, or transfer moulding to the necessary shape.

##### 6.2.2 Test specimen dimensions

The dimensions of the planar sections of the test specimens shall be at least 10 mm in length and 10 mm in width, or a circle with a diameter of at least 10 mm and shall be provided in a thickness of  $3,0\text{ mm} \pm 0,5\text{ mm}$ .

NOTE 15 test specimens may be necessary.

### 7 Conditioning

The test specimen shall be stored for at least 24 h in an atmosphere having a temperature between 15 °C and 35 °C and a relative humidity between 45 % and 75 %.

NOTE For materials, the mechanical characteristics of which are significantly affected by moisture content or temperature, a more precise conditioning may be specified.

## 8 Test procedure

### 8.1 Selection of the test temperature

#### 8.1.1 Method A – End product test method

The Method A test method (proof test method) generally entails testing at a single temperature as defined below in order to determine if the pass requirement of Clause 9 is obtained.

Unless otherwise specified in the relevant product specification, conduct the test method at a temperature as defined below:

- a) For parts supporting live parts, the test temperature shall be 40 °C plus the maximum allowable temperature rise of the part under consideration as defined in the product specification, or
- b) For other parts, the test temperature shall be the ambient temperature plus the maximum allowable temperature rise (as defined in the product specification) of the part under consideration.

Unless otherwise specified in the relevant product specification, the test temperature shall not be less than 125 °C for parts supporting live parts or 75 °C for all other parts under consideration.

#### 8.1.2 Method B – Material performance test method

The Method B test method (material performance test method) entails multiple tests to find the maximum temperature at which the pass requirement of Clause 9 is obtained.

Select an appropriate initial test temperature

NOTE Generally, for many engineering thermoplastics, a starting temperature 10 °C lower than the VST<sub>A50</sub> temperature (in accordance with ISO 306) has been found to be a useful starting point. The VST<sub>A50</sub> temperature is the Vicat Softening Temperature as determined using the A50 method of ISO 306, which uses a force of 10 N and a heating rate of 50 °C/h.

Subsequent test temperatures will be determined by the procedures outlined in 8.2 to 8.5. Test temperatures shall be in multiples of 5 °C.

Table 1 provides guidance regarding the initial test temperature.

**Table 1 – Suggested initial test temperatures**

Material	Initial test temperature (°C)
PA6	200
PA66	240
PA46	280
PBT	200
PET	240
PC	140
PC+ABS	90
PP	120

If the initial test temperature results complies with the pass requirement of Clause 9, repeat the test procedure (8.2 to 8.4) with a new test specimen at a higher temperature than the