



SLOVENSKI STANDARD
SIST EN 23927:2000
01-december-2000

Metallic powders, excluding powders for hardmetals - Determination of compactibility (Compressibility) in uniaxial compression (ISO 3927:1985)

Metallic powders, excluding powders for hardmetals - Determination of compactibility (Compressibility) in uniaxial compression (ISO 3927:1985)

Metallpulver, mit Ausnahme von Hartmetallpulvern - Bestimmung der Verdichtbarkeit bei einachsigen Pressen (ISO 3927:1985)

Poudres métalliques, à l'exclusion des poudres pour métaux-durs - Détermination de la compressibilité sous compression uniaxiale (ISO 3927:1985)

<https://standards.iteh.ai/catalog/standards/sist/e82f6958-424f-4c23-9e9b-b8be66703fa1/sist-en-23927-2000>

Ta slovenski standard je istoveten z: EN 23927:1993

ICS:

77.160 Metalurgija prahov Powder metallurgy

SIST EN 23927:2000 **en**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 23927:2000

<https://standards.iteh.ai/catalog/standards/sist/e82f6958-424f-4c23-9e9b-b8be66703fa1/sist-en-23927-2000>

EUROPEAN STANDARD

EN 23927:1993

NORME EUROPÉENNE

EUROPÄISCHE NORM

April 1993

UDC 621.762:669-492.2:620.1:539.58

Descriptors: Powder metallurgy, metallic powder, compressibility, mechanical tests, compression tests

English version

**Metallic powders, excluding powders for
hardmetals - Determination of compactibility
(Compressibility) in uniaxial compression
(ISO 3927:1985)**

Poudres métalliques, à l'exclusion des poudres pour métaux-durs - Détermination de la compressibilité sous compression uniaxiale (ISO 3927:1985)

Metallpulver, mit Ausnahme von Hartmetallpulvern - Bestimmung der Verdichtbarkeit bei einachsiger Pressen (ISO 3927:1985)

STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 23927:2000

<https://standards.iteh.ai/catalog/standards/sist/e82f6958-424f-4c23-9e9b-b8b66703fa1/sist-en-23927-2000>

This European Standard was approved by CEN on 1993-04-02. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member..

The European Standards exist in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Page 2
EN 23927:1993

Foreword

In 1992 ISO 3927:1985 "Metallic powders, excluding powders for hardmetals - Determination of compactibility (Compressibility) in uniaxial compression" was submitted to the CEN Primary Questionnaire procedure.

Following the positive result of the CEN/CS Proposal ISO 3927:1985 was submitted to the CEN Formal Vote. The result of the Formal Vote was positive.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 1993, and conflicting national standards shall be withdrawn at the latest by October 1993.

According to the Internal Regulations of CEN/CENELEC, the following countries are bound to implement this European Standard :

Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Endorsement notice

SIST EN:23927:2000

[https://standards.iteh.ai/catalog/standards/sist/e82f6958-424f-4c23-9e9b-](https://standards.iteh.ai/catalog/standards/sist/e82f6958-424f-4c23-9e9b-38b6670381/sist-en-23927-2000)

[38b6670381/sist-en-23927-2000](https://standards.iteh.ai/catalog/standards/sist/e82f6958-424f-4c23-9e9b-38b6670381/sist-en-23927-2000)

The text of the International Standard ISO 3927:1985 was approved by CEN as a European Standard without any modification.

International Standard



3927

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

Metallic powders, excluding powders for hardmetals — Determination of compactibility (compressibility) in uniaxial compression

Poudres métalliques, à l'exclusion des poudres pour métaux-durs — Détermination de la compressibilité sous compression uniaxiale

Second edition — 1985-07-01

(standards.iteh.ai)

SIST EN 23927:2000

<https://standards.iteh.ai/catalog/standards/sist/e82f6958-424f-4c23-9e9b-b8be66703fa1/sist-en-23927-2000>

UDC 621.762.4 : 539.58

Ref. No. ISO 3927-1985 (E)

Descriptors : powder metallurgy, metallic powder, tests, compression tests, determination, compressibility, test equipment.

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council. They are approved in accordance with ISO procedures requiring at least 75 % approval by the member bodies voting.

International Standard ISO 3927 was prepared by Technical Committee ISO/TC 119, *Powder metallurgy*.

ISO 3927 was first published in 1977. This second edition cancels and replaces the first edition, of which it constitutes a minor revision.

SIST EN 23927:2000
<https://standards.iteh.ai/catalog/standards/sist/e82f6958-424f-4c23-9e9b-b8be66703fa1/sist-en-23927-2000>

Metallic powders, excluding powders for hardmetals — Determination of compactibility (compressibility) in uniaxial compression

1 Scope and field of application

This International Standard specifies methods to measure the extent to which a metallic powder is compacted when subjected to uniaxial compressive loading in a confining die under specified conditions.

The method is not applicable to powders for hardmetals.

2 Principle

Compaction of a powder uniaxially in a confining die by double action pressing. Samples of the powder may be pressed either at a single specified pressure or at a series of specified pressures. After ejection from the die, determination of the density of the compacts.

The density obtained in the former case represents the compactibility of the powder at the specified pressure. The densities obtained in the latter case can be utilized for drawing the compactibility (compressibility) curve of the powder, i.e. a plot of the density as a function of the compacting pressure.

3 Symbols and designations

Symbol	Designation	Unit
ρ_p	Compactibility	g/cm ³
m	Mass of the compact	g
V	Volume of the compact	cm ³

If the compactibility is measured at one pressure only, for example 400 N/mm², the symbol becomes $\rho_{p(400)}$.

4 Apparatus

4.1 Die, preferably of cemented carbide, or alternatively of tool steel, and **two punches** for producing either cylindrical or rectangular compacts.

4.1.1 The cylindrical die should be capable of making compacts of diameter 20 to 26 mm and a height to diameter ratio between 0,8 and 1. An example of a design for tooling is shown in figure 1.

4.1.2 The rectangular die should be capable of making compacts 30 mm × 12 mm and of thickness 5 to 7 mm. An example for a design for tooling is shown in figure 2.

4.2 Press, capable of applying forces up to about 500 kN with a minimum accuracy of ±2 % and adjustable to permit an even increase of the force at a rate not higher than 50 kN/s.

4.3 Balance, capable of weighing at least 100 g to an accuracy of ±0,01 g.

4.4 Micrometer or other suitable measuring device for measuring the dimensions of the compacts to an accuracy of ±0,01 mm.

5 Sampling

The quantity of the test sample shall be chosen to give the required number of test pieces (see clause 7) with the dimensions specified in 4.1. If necessary, preliminary tests should be made in order to establish the quantity of powder which is needed for fulfilling this requirement.

6 Procedure

6.1 Cleaning of the die and punches

Wipe the die cavity and the punches with soft and clean paper towelling soaked with an appropriate solvent such as acetone. Allow the solvent to evaporate.

6.2 Powder testing conditions

6.2.1 Powders which do not contain a lubricant can be tested:

- in a dry die (**warning**: seizure and excessive die wear may occur, particularly at high compacting pressures);
- in a die with lubricated walls (see 6.3.1);
- after admixing a lubricant (see 6.3.2) and in a dry die.

ISO 3927-1985 (E)

6.2.2 Powders which contain a lubricant can be tested:

- a) in a dry die;
- b) after admixing additional lubricant (see 6.3.2) and in a dry die.

6.3 Lubrication

Use one of the two following methods of lubrication.

6.3.1 Die wall lubrication

Apply to the die walls a mixture or a solution of a lubricant in a volatile organic liquid, for example 100 g of zinc stearate in 1 000 cm³ of acetone. After any excess liquid has drained away, allow the solution adhering to the walls to evaporate leaving a thin layer of lubricant.

6.3.2 Lubrication of powder

Lubricate the powder to be tested by thoroughly mixing into it a quantity (for example 0,5 to 1,5 %) of a suitable solid lubricant (for example zinc stearate or stearic acid).

6.4 Compacting and ejection

Insert the lower punch into the die cavity. Position the die to the desired filling height by using supporting spacers between the die and the foot of the lower punch. Pour the sample into the die cavity, taking the usual precautions to ensure that the powder is uniformly distributed in the die cavity. Position the upper punch and place the die with the punches between the platens of the press. Apply and release a preliminary force of approximately 20 kN. Remove the spacers supporting the die. If the die is supported by springs, or in some similar way, it is not necessary to apply the preliminary force.

Apply the final force at a constant rate which shall not exceed 50 kN/s.

Eject the compact from the die by means of the lower punch.

The procedure of compacting and ejection is exemplified in figure 3.

After ejection and, if necessary, deburring, weigh the compact to the nearest 0,01 g. Measure its dimensions to the nearest 0,01 mm.

6.5 Compacting pressures

For determining the compactibility curve of a powder at a series of pressures, the applied pressures shall be 200, 400, 500, 600 and 800 N/mm². If compactibility is to be determined at a single pressure only, it shall be measured at one of the pressures above.

7 Expression of results

7.1 The density of the compact is given by the formula

$$\rho_p = \frac{m}{V}$$

Report the density to the nearest 0,01 g/cm³.

7.2 Report the compactibility as the average of the three density figures, calculated to the nearest 0,01 g/cm³, obtained at the specified compacting pressure.

7.3 The compactibility curve of a powder is drawn through points representing single determinations of ρ_p at the specified compacting pressures.

8 Test report

The test report shall include the following information:

- a) reference to this International Standard;
- b) all details necessary for the identification of the test sample;
- c) the type of test piece;
- d) the type, nature and amount of the lubricant, if it has been added to the powder; in certain cases it may be desirable to report how the lubricant was added;
- e) the compacting pressures;
- f) the result obtained;
- g) all operations not specified in this International Standard, or regarded as optional;
- h) details of any occurrence which may have affected the result.

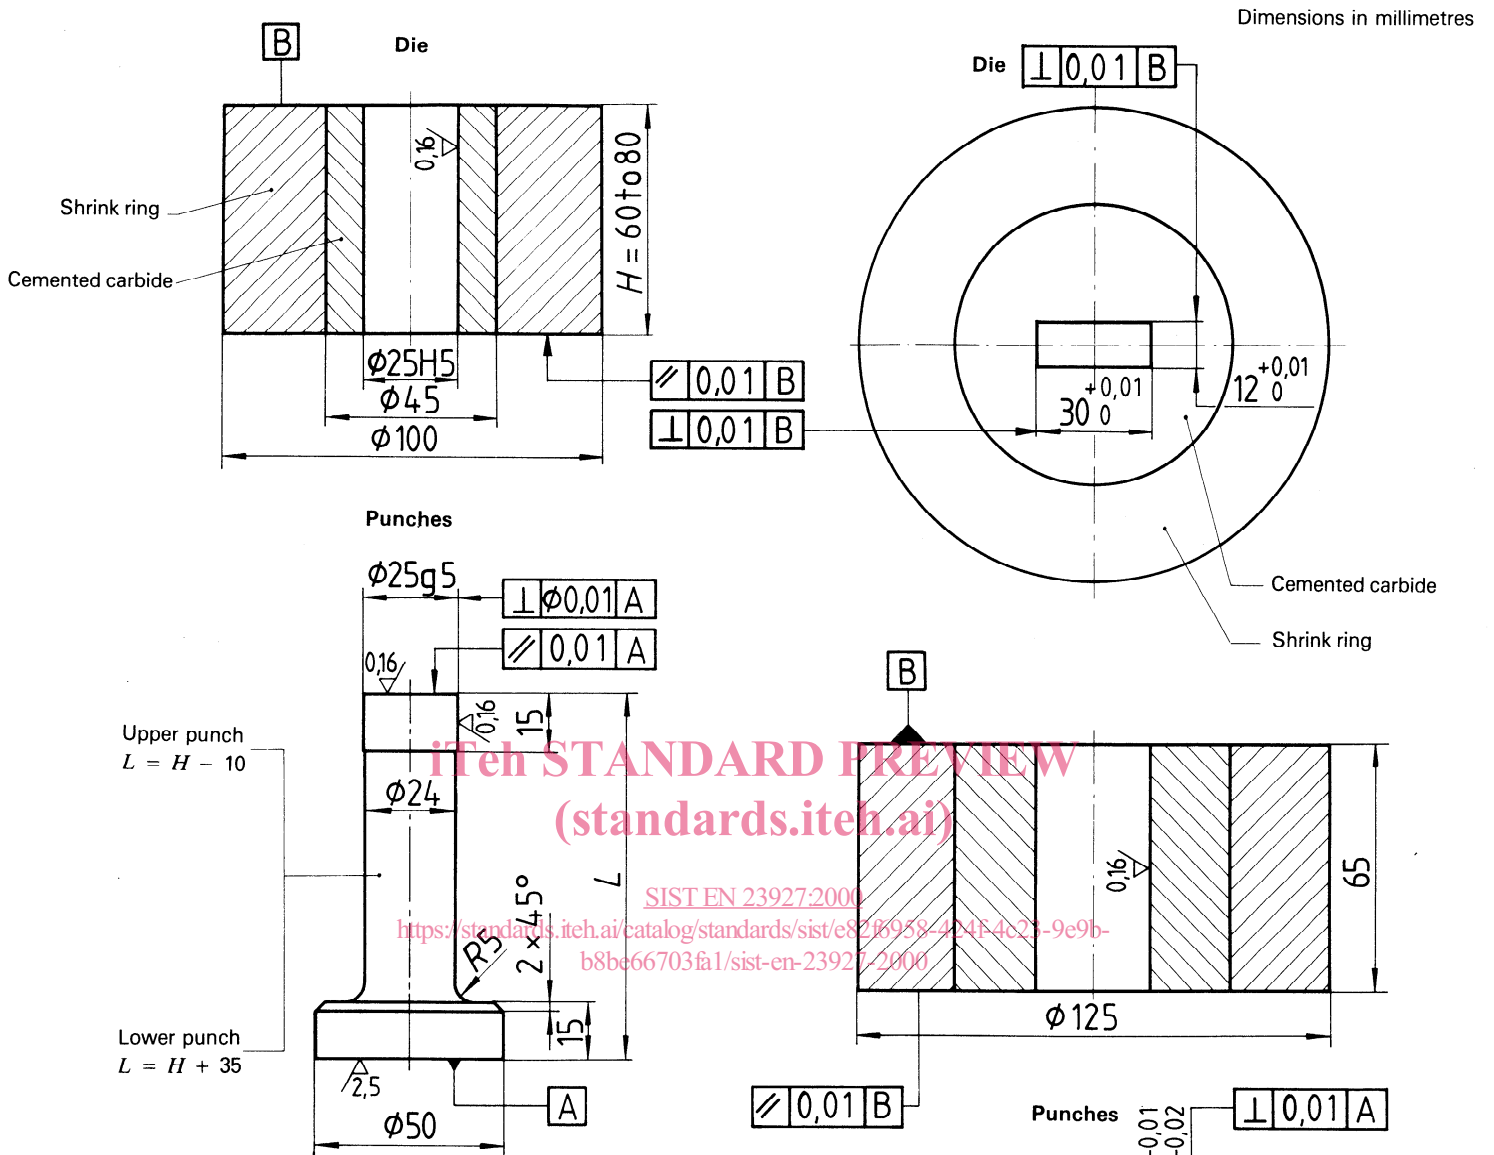


Figure 1 — Example of tooling to produce a cylindrical test piece

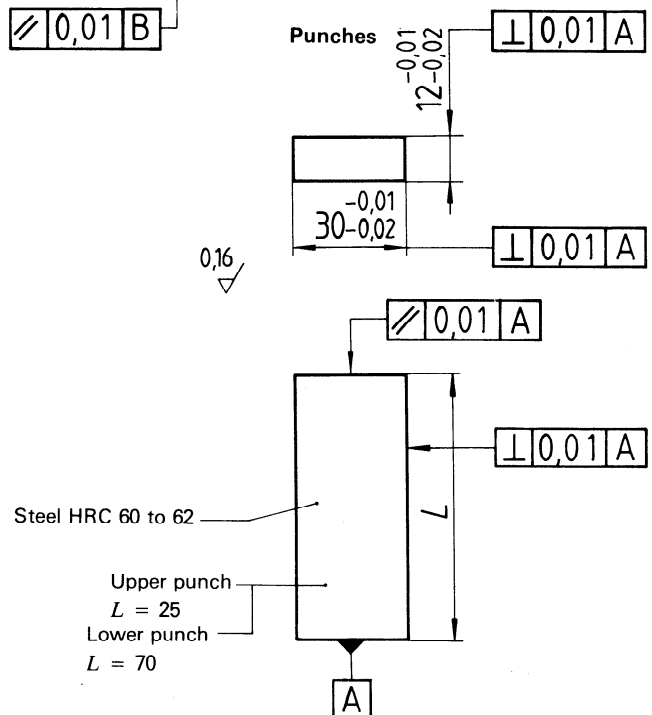


Figure 2 — Example of tooling to produce a rectangular test piece

NOTE — Mating parts shall be fitted and lapped.