SLOVENSKI STANDARD

SIST EN ISO 4022:2007

01-januar-2007

Prepustne sintrane kovine - Ugotavljanje prepuġļ anja tekoļ in (ISO 4022:1987)

Permeable sintered metal materials - Determination of fluid permeability (ISO 4022:1987)

Durchlässige Sintermetallwerkstoffe - Bestimmung der Flüssigkeitsdurchlässigkeit (ISO 4022:1987)

Matériaux métalliques frittés perméables - Détermination de la perméabilité aux fluides (ISO 4022:1987)

Ta slovenski standard je istoveten z: **EN ISO 4022:2006**

ICS:

77.160	Metalurgija prahov	Powder metallurgy

SIST EN ISO 4022:2007 **en**

EUROPEAN STANDARD

NORME EUROPÉENNE

EUROPÄISCHE NORM

EN ISO 4022

April 2006

ICS 77.160

English Version

Permeable sintered metal materials - Determination of fluid permeability (ISO 4022:1987)

Matériaux métalliques frittés perméables - Détermination de la perméabilité aux fluides (ISO 4022:1987)

Durchlässige Sintermetallwerkstoffe - Bestimmung der Flüssigkeitsdurchlässigkeit (ISO 4022:1987)

This European Standard was approved by CEN on 9 March 2006.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Ref. No. EN ISO 4022:2006: E

Foreword

The text of ISO 4022:1987 has been prepared by Technical Committee ISO/TC 119 "Powder metallurgy" of the International Organization for Standardization (ISO) and has been taken over as EN ISO 4022:2006 by Technical Committee CEN/SS M11 "Powder metallurgy", the secretariat of which is held by CMC.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2006, and conflicting national standards shall be withdrawn at the latest by October 2006.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

Endorsement notice

The text of ISO 4022:1987 has been approved by CEN as EN ISO 4022:2006 without any modifications.

INTERNATIONAL STANDARD

ISO 4022

Second edition
1987-10-01

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION
ORGANISATION INTERNATIONALE DE NORMALISATION
МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ

Permeable sintered metal materials — Determination of fluid permeability

Matériaux métalliques frittés perméables — Détermination de la perméabilité aux fluides

Reference number
ISO 4022 : 1987 (E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council. They are approved in accordance with ISO procedures requiring at least 75 % approval by the member bodies voting.

International Standard ISO 4022 was prepared by Technical Committee ISO/TC 119, *Powder metallurgy.*

This second edition cancels and replaces the first edition (ISO 4022 : 1977), of which it constitutes a minor revision.

Users should note that all International Standards undergo revision from time to time and that any reference made herein to any other International Standard implies its latest edition, unless otherwise stated.

Printed in Switzerland

Permeable sintered metal materials — Determination of fluid permeability

1 Scope and field of application

This International Standard specifies a method for the determination of the fluid permeability of permeable sintered metal materials in which the porosity is deliberately continuous or interconnecting, testing being carried out under such conditions that the fluid permeability can be expressed in terms of viscous and inertia permeability coefficients (see annex A).

This International Standard does not apply to very long hollow cylindrical test pieces of small diameter, in which the pressure drop of the fluid in passing along the bore of the cylinder may not be negligible compared with the pressure drop of the fluid passing through the wall thickness (see annex A, clause A.5).

2 Reference

ISO 2738, *Permeable sintered metal materials — Determination of density, oil content and open porosity.*

3 Principle

Passage of a test fluid of known viscosity and density through a test piece, and measurement of the pressure drop and the volumetric flow rate.

Determination of the viscous and inertia permeability coefficients, which are parameters of a formula describing the relationship between the pressure drop, the volumetric flow rate, the viscosity and density of the test fluid, and the dimensions of the porous metal test piece permeated by this fluid.

4 Symbols and definitions

For the purposes of this International Standard, the symbols and definitions given in the table apply:

Table — Symbols and definitions

Term	Symbol	Definition	Unit
Permeability	—	Ability of a porous metal to pass a fluid under the action of a pressure gradient	—
Test area	A	Area of a porous metal normal to the direction of the fluid flow	m^2
Thickness	e	Dimension of the test piece in the direction of fluid flow a) for flat test pieces: equal to the thickness b) for hollow cylinders: given by the equation in 6.1.2	m
Length	L	Length of cylinder (see figure 2)	m
Viscous permeability coefficient	ψ_v	Volume flow rate at which a fluid of unit viscosity is transmitted through unit area of porous metal permeated under the action of unit pressure gradient when the resistance to fluid flow is due only to viscous losses. It is independent of the quantity of porous metal considered.	m^2
Inertia permeability coefficient	ψ_i	Volume flow rate at which a fluid of unit density is transmitted through unit area of porous metal permeated under the action of unit pressure gradient when the resistance to fluid flow is due only to inertia losses. It is independent of the quantity of porous metal considered.	m
Volume flow rate	Q	Mass flow rate of the fluid divided by its density	m^3/s
Upstream pressure	p_1	Pressure upstream of the test piece	N/m^2
Downstream pressure	p_2	Pressure downstream of the test piece	
Mean pressure	p	Half the sum of the upstream and downstream pressures	
Pressure drop	Δp	Difference between the pressures on the upstream and downstream surfaces of the porous test piece	N/m^2
Pressure gradient	$\Delta p/e$	Pressure drop divided by the thickness of porous test piece	N/m^3
Velocity	Q/A	Ratio of the volumetric flow rate to the test area	m/s
Density	ϱ	Density of the test fluid at the mean temperature and pressure	kg/m^3
Dynamic viscosity	η	Absolute dynamic viscosity coefficient as defined by Newton's law	$N{\cdot}s/m^2$
Apparatus correction (to be subtracted from the observed pressure drop)	—	Pressure difference observed between the upstream and downstream pressure tappings when the test apparatus is used without a porous test piece in position. (It varies with the flow rate through the apparatus and arises from venturi effects at the pressure tappings and other causes)	N/m^2
Mean absolute temperature	T	Half the sum of the temperatures of the fluid at the upstream side and the downstream side of the test piece	K

5 Test piece

Before testing with gas, all liquid shall be removed from the pores of the test piece. Oil and grease shall be removed by using a suitable solvent with the extraction method given in ISO 2738. The test piece shall be dried before testing.

6 Apparatus

6.1 Equipment

The choice of apparatus is mainly dictated by the size, shape and physical characteristics of the test piece.

This International Standard refers to two different types of apparatus suitable for determining the fluid permeability of porous test pieces.

6.1.1 Guard ring test head for flat test pieces

This is a type of test apparatus which is recommended for carrying out non-destructive testing of partial areas of flat porous sheets.

The permeable metal sheet is clamped between two pairs of flexible seals. The inner pair, corresponding to the test area, has a mean diameter of D_1. The outer pair, of mean diameter D_2, forms a guard ring surrounding the test-area, which is

pressurized to prevent side leakage from the test area (see figure 1). The width of the annulus formed by the guard ring test head shall be not less than the thickness of the sheet, i.e.:

$$\frac{D_2 - D_1}{2} \geqslant e$$

The guard ring test head minimizes side leakage by ensuring that the pressure is the same in the inner and outer chambers. On the upperstream face of the test piece, this is achieved by arranging that the port area connecting the upper chambers (as shown in figure 1) is as large as possible. On the downstream face of the test piece, the inner chamber leads to a flowmeter, usually subject to a small back pressure, and the outer chamber

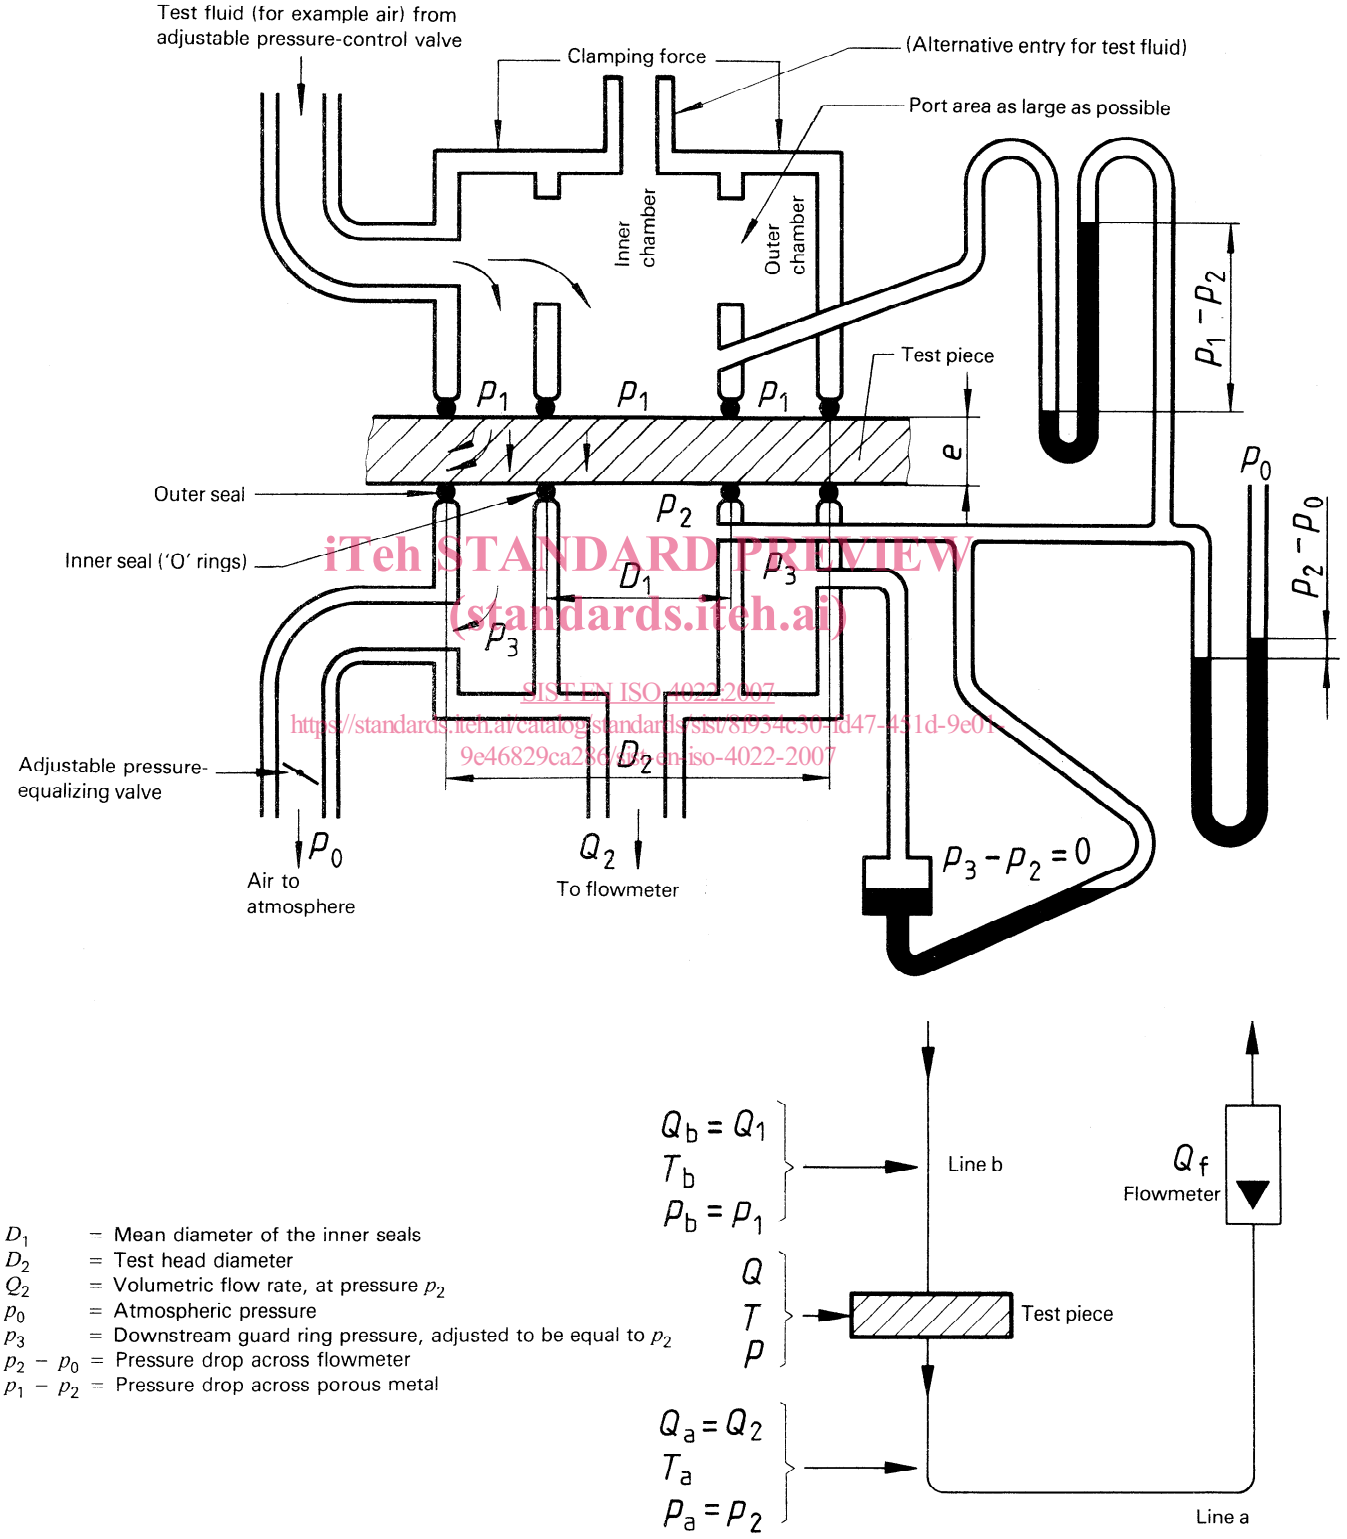

D_1 = Mean diameter of the inner seals
D_2 = Test head diameter
Q_2 = Volumetric flow rate, at pressure p_2
p_0 = Atmospheric pressure
p_3 = Downstream guard ring pressure, adjusted to be equal to p_2
$p_2 - p_0$ = Pressure drop across flowmeter
$p_1 - p_2$ = Pressure drop across porous metal

Figure 1 — Guard ring test head