



SLOVENSKI STANDARD

SIST EN 24499:2000

01-december-2000

Hardmetals - Metallographic determination of microstructure (ISO 4499:1978)

Hardmetals - Metallographic determination of microstructure (ISO 4499:1978)

Hartmetalle - Metallographische Bestimmung der Mikrostruktur (ISO 4499:1978)

Métaux-durs - Détermination métallographique de la microstructure (ISO 4499:1978)

Ta slovenski standard je istoveten z: **EN 24499:1993**

[SIST EN 24499:2000](https://standards.iteh.ai/catalog/standards/sist/60efbaf6-f64e-4377-a73c-b7daa3621553/sist-en-24499-2000)

<https://standards.iteh.ai/catalog/standards/sist/60efbaf6-f64e-4377-a73c-b7daa3621553/sist-en-24499-2000>

ICS:

77.040.30	Kemijska analiza kovin	Chemical analysis of metals
77.160	Metalurgija prahov	Powder metallurgy

SIST EN 24499:2000

en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 24499:2000

<https://standards.iteh.ai/catalog/standards/sist/60efbafa-f64e-4377-a73c-b7daa3621553/sist-en-24499-2000>

EUROPEAN STANDARD

EN 24499:1993

NORME EUROPÉENNE

EUROPÄISCHE NORM

April 1993

UDC 669.018.25:620.186

Descriptors: Powder metallurgy, hard metals, metallography, microscopic analysis, microstructure, grain structure

English version

**Hardmetals - Metallographic determination of
microstructure (ISO 4499:1978)**Métaux-durs - Détermination métallographique de
la microstructure (ISO 4499:1978)Hartmetalle - Metallographische Bestimmung der
Mikrostruktur (ISO 4499:1978)**STANDARD PREVIEW**
(standards.iteh.ai)[SIST EN 24499:2000](https://standards.iteh.ai/catalog/standards/sist/60efbafa-f64e-4377-a73c-b7daa3621553/sist-en-24499-2000)<https://standards.iteh.ai/catalog/standards/sist/60efbafa-f64e-4377-a73c-b7daa3621553/sist-en-24499-2000>

This European Standard was approved by CEN on 1993-04-02. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

The European Standards exist in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CENEuropean Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Page 2
EN 24499:1993

Foreword

In 1992 ISO 4499:1978 "Hardmetals - Metallographic determination of microstructure" was submitted to the CEN Primary Questionnaire procedure.

Following the positive result of the CEN/CS Proposal ISO 4499:1978 was submitted to the CEN Formal Vote. The result of the Formal Vote was positive.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 1993, and conflicting national standards shall be withdrawn at the latest by October 1993.

According to the Internal Regulations of CEN/CENELEC, the following countries are bound to implement this European Standard :

Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

iTeh STANDARD PREVIEW (standards.iteh.ai)

Endorsement notice

SIST EN 24499:2000

<https://standards.iteh.ai/catalog/standards/sist/60efbafa-f64e-4377-a73c-57115014499-1993>

The text of the International Standard ISO 4499:1978 was approved by CEN as a European Standard without any modification.

INTERNATIONAL STANDARD



4499

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

Hardmetals — Metallographic determination of microstructure

Métaux-durs — Détermination métallographique de la microstructure

First edition — 1978-08-01

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 24499:2000](https://standards.iteh.ai/catalog/standards/sist/60efbafa-f64e-4377-a73c-b7daa3621553/sist-en-24499-2000)

<https://standards.iteh.ai/catalog/standards/sist/60efbafa-f64e-4377-a73c-b7daa3621553/sist-en-24499-2000>

UDC 621.762 : 661.665.2 : 620.186

Ref. No. ISO 4499-1978 (E)

Descriptors : hardmetals, metallography, microstructure, designations, microscopic analysis, test specimens.

FOREWORD

ISO (the International Organization for Standardization) is a worldwide federation of national standards institutes (ISO member bodies). The work of developing International Standards is carried out through ISO technical committees. Every member body interested in a subject for which a technical committee has been set up has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council.

International Standard ISO 4499 was developed by Technical Committee ISO/TC 119, *Powder metallurgical materials and products*, and was circulated to the member bodies in April 1977.

It has been approved by the member bodies of the following countries :

Australia	Ireland	Spain
Austria	Italy	Sweden
Bulgaria	Japan	Turkey
Canada	Mexico	United Kingdom
Chile	Poland	U.S.A.
Czechoslovakia	Portugal	U.S.S.R.
France	Romania	Yugoslavia
Germany	South Africa, Rep. of	

No member body expressed disapproval of the document.

Hardmetals — Metallographic determination of microstructure

1 SCOPE AND FIELD OF APPLICATION

This International Standard specifies methods of metallographic determination of the microstructure of hardmetals.

2 SYMBOLS AND DESIGNATIONS

TABLE 1

Symbol	Designation
α -phase	Tungsten carbide
β -phase	Binder phase (for example based on Co, Ni, Fe)
γ -phase	Carbide having a cubic lattice (for example TiC, TaC) which may contain other carbides (for example WC) in solid solution
η -type phases	Multiple carbides of tungsten and at least one metal of the binder phase

3 APPARATUS

3.1 Metallographic microscope, permitting observations at magnifications up to 1 500 X.

3.2 Equipment for preparation of test-piece sections

4 PREPARATION OF TEST-PIECE SECTION

The test-piece section shall be prepared as for metallographic examination and the surface to be examined shall be free from grinding and polishing marks. Care shall be taken to avoid tearing out of particles, which may lead to a wrong evaluation of microstructure.

NOTE — There are several methods for preparation of hardmetal surfaces for metallographic examination. Firstly, careful coarse grinding is carried out to remove sufficient material to ensure that the true structure is revealed. After grinding with fine diamond grit wheels, polishing is effected by using diamond paste or diamond powders of progressively finer grain size down to 1 μ m on rigidly supported laps of, for example, thin plastic, thin felt or paper.

5 PROCEDURE

The microstructure is examined by the gradual development of phases by etching. There are several methods for etching hardmetal surfaces for metallographic examination. Examples of suitable etching techniques are given in table 2. Care shall be taken to ensure that the true microstructure is revealed.

5.1 The existence of η -type phases is determined after lightly etching the section, for example by technique 1 (see table 2). Phases of η -type are coloured orange to brown, while other phases are unetched. Etching by technique 1 does not prevent subsequent etching by techniques 2 and 3.

TABLE 2

Etching technique	Composition of etchants	Conditions of etching	Application of etching
1	A Freshly prepared mixture of equal quantities of 10 to 20 % (m/m) aqueous solutions of potassium hexacyanoferrate(III) (potassium ferricyanide) and potassium or sodium hydroxide	Etch in mixture A at approximately 20 °C for 1 to 20 s. Flush the test-piece section with water immediately, without removing the oxide layer. Dry the surface carefully with acetone or alcohol without wiping	Identification of η -phases
2	A See technique 1 B A mixture of equal volumes of concentrated hydrochloric acid and water	Etch at approximately 20 °C in mixture A for 3 to 4 min. Then wash in water and etch in mixture B for approximately 10 s. Next wash in water, then in alcohol, and dry the test-piece section. Finally, etch in mixture A for approximately 20 s	Identification of γ -phase
3	A See technique 1	Etch in mixture A at approximately 20 °C for 3 to 6 min	Identification of α -phase

NOTE — The separate solutions of potassium hexacyanoferrate(III) and potassium or sodium hydroxide may be stored for a long time, but must be freshly mixed each day when used.

ISO 4499-1978 (E)

The whole surface is examined at a low magnification and, if necessary, at magnifications up to 1 500 X. The existence and distribution of η -type phases is noted and recorded.

5.2 The existence of γ -type phases is determined after etching the surface, for example by technique 2 (see table 2). This phase is coloured light yellowish-brown and has a typically rounded shape (see figure 1). The etched section is examined and the existence of γ -phase is noted and recorded. Its size is estimated and recorded according to figure 1 as γ -fine, γ -medium or γ -coarse.

5.3 The existence of α -phase is determined after etching the surface, for example by technique 3 or, in the case of the presence of γ -phase, by technique 2 (see table 2). The α -phase appears grey and often has an angular shape. The etched section is examined and the existence of α -phase is noted and recorded. Its size is estimated and recorded according to figure 2 as α -fine, α -medium or α -coarse.

5.4 The β -phase is identified after etching the surface, for example by technique 2 or 3 (see table 2). This phase remains white.

6 TEST REPORT

The test report shall include the following information :


- a) reference to this International Standard;
- b) all details necessary for identification of the test sample;
- c) the result obtained;
- d) all operations not specified by this International Standard, or regarded as optional;
- e) details of any occurrence which may have affected the result.

iTeh STANDARD PREVIEW **(standards.iteh.ai)**

[SIST EN 24499:2000](https://standards.iteh.ai/catalog/standards/sist/60efbafa-f64e-4377-a73c-b7daa3621553/sist-en-24499-2000)

<https://standards.iteh.ai/catalog/standards/sist/60efbafa-f64e-4377-a73c-b7daa3621553/sist-en-24499-2000>

γ -fine

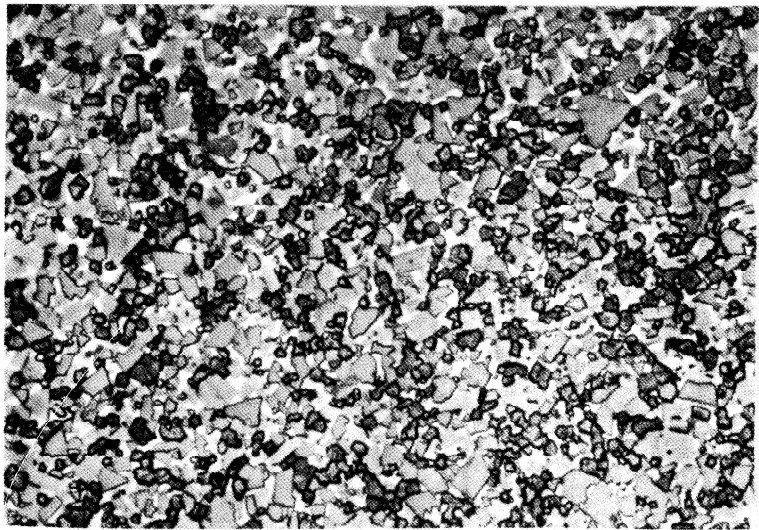

γ -medium

iTeh STANDARD PORTAL
(standards.iteh.ai)
SIST EN 24499:2000
<https://standards.iteh.ai/catalog/standards/sist/24499-2000/iso-4499-1978>
b7daa331-7c01-4271-9000-000000000000



γ -coarse

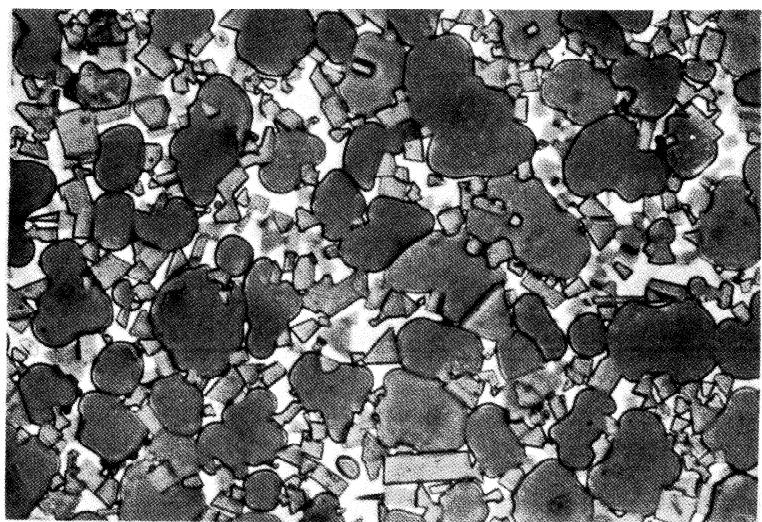


FIGURE 1 — γ -phase X 1 500