



Designation: G 72 – 82 (Reapproved 1996)^{ε1}

Standard Test Method for Autogenous Ignition Temperature of Liquids and Solids in a High-Pressure Oxygen-Enriched Environment¹

This standard is issued under the fixed designation G 72; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

^{ε1} NOTE—Keywords were added editorially in March 1996.

1. Scope

1.1 This method covers the determination of the temperature at which liquids and solids will spontaneously ignite. These materials must ignite without application of spark or flame in a high-pressure oxygen-enriched environment.

1.2 This method is intended for use at pressures of 2.1 to 20.7 MPa (300 to 3000 psi). The pressure used in the description of the method is 10.3 MPa (1500 psi). The method, as described, is for liquids or solids with ignition temperature in the range from 60 to 425°C (140 to 800°F).

1.3 This method is for high-pressure pure oxygen. The method may be used in atmospheres from 0.5 % to 100 % oxygen.

1.4 An apparatus suitable for these requirements is described. This method could be applied to higher pressures and materials of higher ignition temperature. If more severe requirements or other oxidizers than those described are desired, care must be taken in selecting an alternative safe apparatus capable of withstanding the conditions.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 Federal Specification:²

BB-O-925 Oxygen, Technical, Gas and Liquid

2.2 Military Standard:^{3,4}

MIL-C-81302 Cleaning Compound, Solvent, Trichlorotrifluoroethane

2.3 Other Documents:

Compressed Gas Association Booklets G-1 and G-4.1^{3,4}

¹ This method is under the jurisdiction of ASTM Committee G-4 on Compatibility and Sensitivity of Materials in Oxygen Enriched Atmospheres and is the direct responsibility of Subcommittee G04.01 on Test Methods.

Current edition approved Feb. 26, 1982. Published April 1982.

² Available from U.S. Government Printing Office, Washington, DC 20402.

³ Available from Standardization Documents Order Desk, Bldg. 4 Section D, 700 Robbins Ave., Philadelphia, PA 19111-5094, Attn: NPODS.

⁴ Available from Compressed Gas Assn., 500 Fifth Ave., New York, NY 10110.

3. Summary of Method

3.1 This autogenous ignition temperature test method is designed to expose solid or liquid sample material to increasing temperature in a high-pressure reaction vessel. The reaction vessel (bomb), including a sample holding assembly, is pressurized with the oxygen-enriched environment. The bomb is heated in an electric furnace at a predetermined rate. The temperature of the sample-holding assembly is monitored as a function of time by means of a thermocouple and recording potentiometer.

3.2 The minimum temperature required to cause the sample to ignite spontaneously is determined at any selected system pressure. The point at which spontaneous ignition occurs is denoted by a sudden rise in temperature and the destruction of the sample. The amount of rise in temperature is related to the sample size. A sample size is selected to prevent damage to the equipment caused by exceeding safe system pressure or temperature limits because of the temperature rise.

3.3 The system is pressurized to the desired test pressure at the start of the test. During the test as the temperature is increased, the pressure increases. No effort is made to control the pressure during the test. It is monitored only so that the pressure does not exceed a safe limit for the test equipment.

4. Significance and Use

4.1 Most organic liquids and solids will ignite in a pressurized oxidizing gas atmosphere if heated to a sufficiently high temperature and pressure. This procedure provides a numerical value for the temperature at the onset of ignition under carefully controlled conditions. Means for extrapolation from this idealized situation to the description, appraisal, or regulation of fire and explosion hazards in specific field situations, are not established. Ranking of the ignition temperatures of several materials in the standard apparatus is generally in conformity with field experience.

4.2 The temperature at which material will ignite spontaneously (AIT) will vary greatly with the geometry of the test system and the rate of heating. To achieve good interlaboratory agreement of ignition temperatures, it is necessary to use equipment of approximately the dimensions described in the method. It is also necessary to follow the described procedure

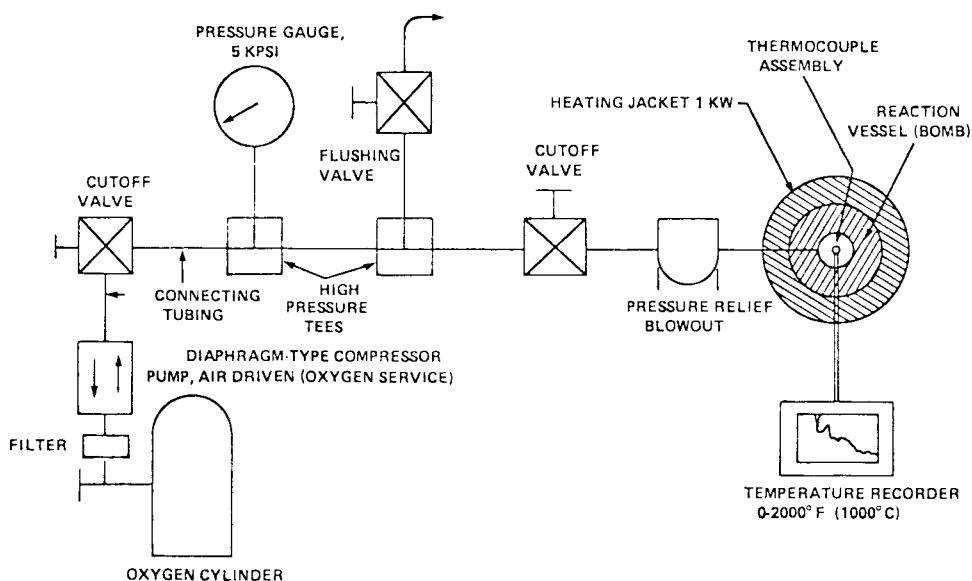


FIG. 1 AIT Equipment Assembly

as closely as possible.

4.3 The decomposition and oxidation of some fully fluorinated materials releases so little energy that there is no clear-cut indication of ignition. Nor will there be a clear indication of ignition if a sample volatilizes, distilling to another part of the reaction vessel, before reaching ignition temperature.

5. Apparatus

5.1 Suitable components shall be assembled so that the specified reaction vessel (bomb), including sample-holding assembly, can be charged with oxygen and heated. The assembly shall provide a means of recording time and temperature at which ignition occurs. A suitable assembly is illustrated in Fig. 1.

5.2 *Cylinder Oxygen*, conforming to Federal Specification BB-O-925, Type I or oxygen of 99.5 % minimum purity. Oxygen of higher purity may be used if desired.

5.3 *Line Filter*, sintered stainless steel, 5- μ m porosity, maximum pressure 206.8 MPa (30 000 psi), for 6.35-mm (1/4-in.) high-pressure tubing with a 3.18-mm (1/8-in.) port.⁵

5.4 *Compressor Pumps*, diaphragm-type, air-driven.⁶

5.5 *Valves*, 6.35 mm (1/4 in.), 206.8 MPa (30 000 psi) working pressure, nonrotating stem valves.⁷

5.6 *Pressure Gage*, 20.7 MPa (3000 psi), 216 mm (8 1/2 in.).⁸ Heise 2 or equivalent has been found satisfactory.

5.7 *Connecting Tubing*, Type 316 stainless steel, 6.35 mm

(1/4 in.), 448.1 MPa (65 000 psi) pressure rating at 37.8°C (100°F).⁹

5.8 *High-Pressure Tees*, Type 316 stainless steel with gland nuts and sleeves of Type 416 stainless steel, 6.35 mm (1/4 in.) high-pressure. Superpressure, Inc., Catalog No. 45-14311.¹⁰ All connection fittings shall be of cold-drawn Type 316 stainless steel, 413.7 MPa (60 000 psi) maximum pressure, tubing size 6.35 mm (1/4 in.) high-pressure and 14.3-mm (9/16-in.) insertion depth.¹¹

5.9 *Pressure-Relief Blowout with Rupture Discs*, pressure-relief blow-out assembly, Type 316 stainless steel, 6.35 mm (1/4 in.), angle type¹² with 48.3 MPa (7000 psi) at 22.2°C (72°F) rupture disks.¹³

5.10 *Reaction Vessel (Bomb)*—A suitable reaction vessel for the method is cylindrical, approximately 65 mm (2 9/16 in.) in outside diameter and 298 mm (11 3/4 in.) long and weighs 9.75 kg (21 1/2 lb). The vessel is bored from a solid forging of AISI 316SS (8 1/4 in.) depth, with a volume equal to approximately 110 mL. The maximum working pressure at 427°C (800°F) is 82.7 MPa (12 000 psi).¹⁴

5.11 *Thermocouple Assembly*—A Chromel-Alumel thermocouple with suitable high-pressure fittings for the reaction vessel with a 203-mm (8-in.) thermocouple to extend into the reaction chamber.¹⁵

⁹ Catalog No. 45-11021 available from Superpressure, Inc., Silver Spring, Md. 20910 or equivalent has been found satisfactory.

¹⁰ Catalog No. 45-14311 available from Superpressure, Inc., Silver Spring, Md. 20910 or equivalent has been found satisfactory.

¹¹ Catalog No. 45-11311 available from Superpressure, Inc., Silver Spring, Md. 20910 or equivalent has been found satisfactory.

¹² Catalog No. 45-19123 available from Superpressure, Inc., Silver Spring, Md. 20910 or equivalent has been found satisfactory.

¹³ Catalog No. 45-19210 available from Superpressure, Inc., Silver Spring, Md. 20910 or equivalent has been found satisfactory.

¹⁴ Type B Reaction Vessel Catalog No. 41-12555, available from Superpressure, Inc., Silver Spring, Md. 20910 or equivalent will meet these requirements.

¹⁵ Thermocouple Assembly Catalog No. 45-17620 available from Superpressure, Inc. or equivalent can be used.

⁵ Catalog No. 49-14405 available from Superpressure, Inc., Silver Spring, Md. 20910 or equivalent has been found satisfactory.

⁶ Catalog No. 46-14035 available from Superpressure, Inc., Silver Spring, Md. 20910 or equivalent has been found satisfactory.

⁷ Catalog No. 44-13121 available from Superpressure, Inc., Silver Spring, Md. 20910 or equivalent has been found satisfactory.

⁸ Model C available from Heise Bourdon Tube Co., Newton, Conn. 06740 or equivalent has been found satisfactory.