



SLOVENSKI STANDARD
SIST ISO 11257:2001
01-junij-2001

Železove rude – Ugotavljanje razpada in metalizacije vhodne surovine za direktno redukcijo s procesi transformacije plinov

Iron ores -- Determination of disintegration and metallization of feedstock for direct reduction by gas reforming processes

iTeh STANDARD PREVIEW

Minerais de fer -- Détermination de la dégradation et de la métallisation des charges utilisées dans les procédés de reforming par réduction directe

[SIST ISO 11257:2001](https://standards.iteh.ai/catalog/standards/sist/a67501f1-630a-4733-af61-6659210b71/sist-iso-11257-2001)

Ta slovenski standard je istoveten z: ISO 11257:1998

ICS:

73.060.10 Železove rude Iron ores

SIST ISO 11257:2001 **en**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST ISO 11257:2001

<https://standards.iteh.ai/catalog/standards/sist/a67501f1-630a-4733-afe1-b639f2f0b71/sist-iso-11257-2001>

INTERNATIONAL
STANDARD

ISO
11257

First edition
1998-07-01

**Iron ores — Determination of disintegration
and metallization of feedstock for direct
reduction by gas reforming processes**

*Minerais de fer — Détermination de la dégradation et de la métallisation des
charges utilisées dans les procédés de reforming par réduction directe*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST ISO 11257:2001](https://standards.iteh.ai/catalog/standards/sist/a67501f1-630a-4733-afe1-b639f2f0b71/sist-iso-11257-2001)

[https://standards.iteh.ai/catalog/standards/sist/a67501f1-630a-4733-afe1-
b639f2f0b71/sist-iso-11257-2001](https://standards.iteh.ai/catalog/standards/sist/a67501f1-630a-4733-afe1-b639f2f0b71/sist-iso-11257-2001)



Reference number
ISO 11257:1998(E)

ISO 11257:1998(E)

Contents	Page
1 Scope	1
2 Normative references	1
3 Definitions	1
4 Principle	2
5 Apparatus	2
6 Test conditions	3
6.1 General.....	3
6.2 Composition of reducing gas	3
6.3 Purity of reducing gas	3
6.4 Flow rate of reducing gas	3
6.5 Purity of heating and cooling gas	3
6.6 Temperature of test	3
7 Sampling and sample preparation	3
8 Procedure	4
8.1 Number of determinations	4
8.2 Test portion	4
8.3 Reduction	4
9 Expression of results	5
9.1 Reduction-disintegration index (RDI_{DR}).....	5
9.2 Degree of metallization (M)	5
9.3 Number of tests and permissible tolerance	5
10 Test report	6
11 Verification	6
Annex A (normative) Flowsheet of the procedure for the acceptance of test results	7
Annex B (informative) Bibliography	8

© ISO 1998

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
 Case postale 56 • CH-1211 Genève 20 • Switzerland
 Internet central@iso.ch
 X.400 c=ch; a=400net; p=iso; o=isocs; s=central

Printed in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 11257 was prepared by Technical Committee ISO/TC 102, *Iron ores*, Subcommittee SC 5, *Physical testing for direct reduction*.

Annex A forms an integral part of this International Standard. Annex B is for information only.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST ISO 11257:2001](https://standards.iteh.ai/catalog/standards/sist/a67501f1-630a-4733-afe1-b639f2f0b71/sist-iso-11257-2001)

<https://standards.iteh.ai/catalog/standards/sist/a67501f1-630a-4733-afe1-b639f2f0b71/sist-iso-11257-2001>

Introduction

Direct reduction processes are intended to reduce iron ores partially, or almost completely by thermal processes to form high grade feedstocks for iron- and steelmaking. Several kinds of direct reduction processes are in operation worldwide and others are still under development. The behaviour of the iron ores, as feedstock, may vary from process to process. ISO 11257 was prepared addressing specifically the direct reduction by gas reforming processes.

The obtained proportion of generated fines is a relative measure of the disintegration behaviour and the degree of metallization is a measure of the metallization behaviour of the iron ore.

The results of this test should be considered in conjunction with the results of other tests used to evaluate the quality of iron ores for direct reduction processes.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST ISO 11257:2001](https://standards.iteh.ai/catalog/standards/sist/a67501f1-630a-4733-afe1-b639f2f0b71/sist-iso-11257-2001)

<https://standards.iteh.ai/catalog/standards/sist/a67501f1-630a-4733-afe1-b639f2f0b71/sist-iso-11257-2001>

Iron ores — Determination of disintegration and metallization of feedstock for direct reduction by gas reforming processes

WARNING — This International Standard may involve hazardous materials, operations and equipment. This International Standard does not purport to address all of the safety problems associated with its use. It is the responsibility of the user of this International Standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to its use.

1 Scope

This International Standard specifies a test method for evaluating the disintegration and metallization behaviour of iron ore pellets and lumps under conditions that resemble the ones prevailing in direct reduction by gas reforming processes, such as the Midrex-type process.¹⁾

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 2597-1:1994, *Iron ores — Determination of total iron content — Part 1: Titrimetric methods after tin(II) chloride reduction*.

ISO 3310-1:—²⁾, *Test sieves — Requirements and tests — Part 1: Metal wire cloth sieves*.

ISO 4701:—³⁾, *Iron ores — Determination of size distribution by sieving*.

ISO 5416:1997, *Direct reduced iron — Determination of metallic iron content — Bromine-methanol titrimetric method*.

ISO 9507:1990, *Iron ores — Determination of total iron content — Titanium(III) chloride reduction methods*.

ISO 9508:1990, *Iron ores — Determination of total iron content — Silver reduction titrimetric method*.

ISO 10836:1994, *Iron ores — Method of sampling and sample preparation for physical testing*.

ISO 11323:1996, *Iron ores — Vocabulary*.

3 Definitions

For the purposes of this International Standard the definitions given in ISO 11323 and the following apply:

3.1 reduction-disintegration: Size degradation of lump ores or agglomerates resulting under reduction test conditions that resemble the ones prevailing in the direct reduction processes.

1) Midrex is a trade-name used by Midrex International B.V. This information is given for the convenience of users of this International Standard and does not constitute an endorsement by ISO of the method named. Equivalent methods may be used if they can be shown to lead to the same results.

2) To be published. (Revision of ISO 3310-1:1990)

3) To be published. (Revision of ISO 4701:1985)

4 Principle

Isothermal reduction of the test portion in a rotation tube by reducing gas consisting of H_2 , CO , CO_2 and CH_4 at temperature of $760\text{ }^\circ\text{C}$, over 300 min.

Heating and cooling in an inert atmosphere.

Sieving with test sieve having square opening of 3,15 mm.

Calculation of the reduction-disintegration index as the percentage mass of material less than 3,15 mm.

Calculation of the degree of metallization from the chemical analysis of the reduced material.

5 Apparatus

See figure 1.

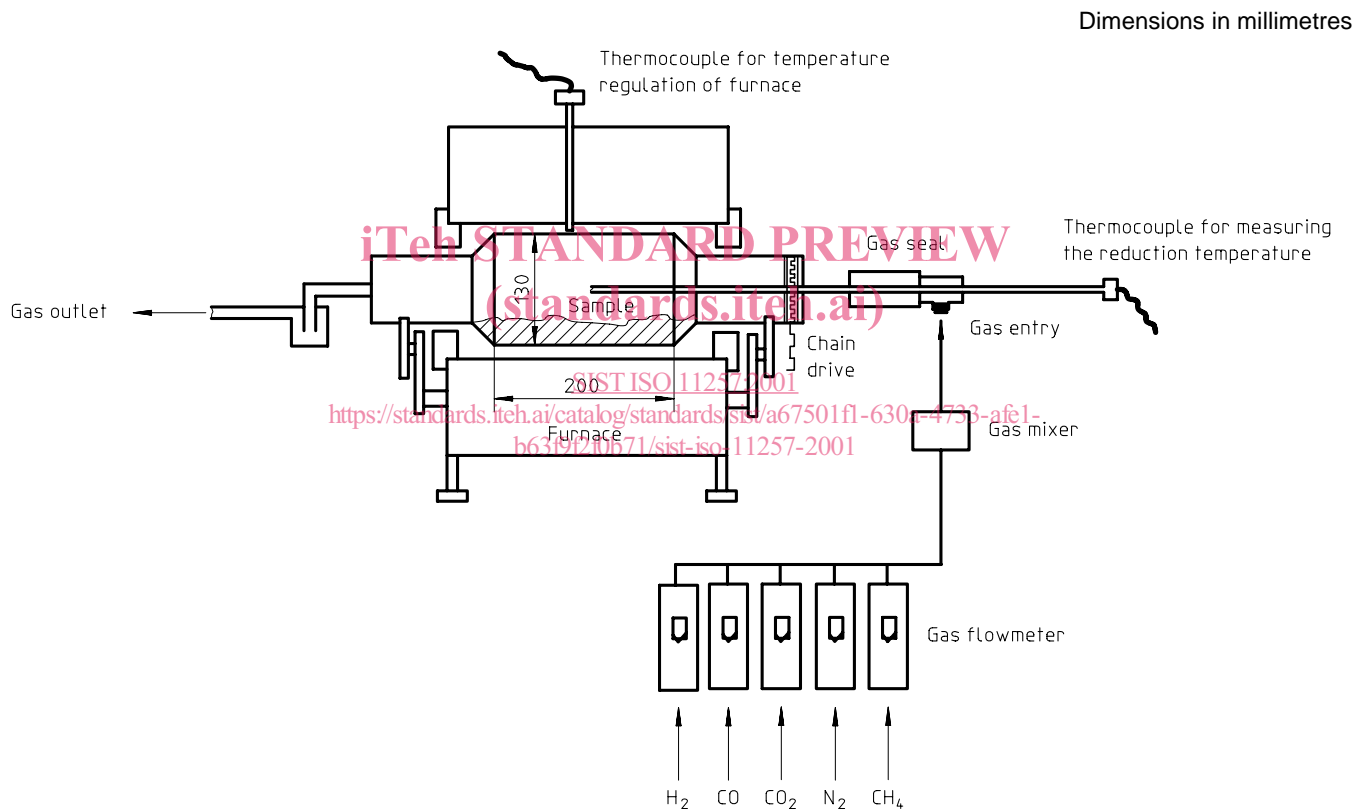


Figure 1 — Reduction-disintegration test apparatus

5.1 Gas supply system, capable of supplying the gases and regulating the gas flow rates.

5.2 Reduction tube, without lifters, made of non-scaling, heat-resisting metal to withstand a temperature greater than $760\text{ }^\circ\text{C}$. The internal diameter of the reduction tube shall be $130\text{ mm} \pm 1\text{ mm}$ and the internal length 200 mm.

5.3 Furnace, having a heating capacity and controls sufficient to reach the test temperature within 90 min and to maintain the entire test portion at $760\text{ }^\circ\text{C} \pm 5\text{ }^\circ\text{C}$.

5.4 Rotation equipment, to permit rotation of the reduction tube at a constant rate of $0,167\text{ s}^{-1} \pm 0,017\text{ s}^{-1}$ (10 rpm \pm 1 rpm).

5.5 Dust collector, to trap any fine solid particles carried in the gas stream out of the tube during the test.

5.6 Test sieves, conforming to ISO 3310-1 and having square openings of the following nominal aperture size: 20 mm; 16 mm; 12,5 mm; 10 mm and 3,15 mm.

5.7 Weighing device, capable of weighing the test portion and the reduced material to an accuracy of 0,1 g.

6 Test conditions

6.1 General

Volumes and flow rates of gases used in this International Standard are as measured at a temperature of 0 °C and at an atmospheric pressure of 101,325 kPa.

6.2 Composition of reducing gas

The reducing gas shall consist of:

H₂ 55 % ± 1 % (V/V)

CO 36 % ± 1 % (V/V)

CO₂ 5 % ± 1 % (V/V)

CH₄ 4 % ± 1 % (V/V)

6.3 Purity of reducing gas

Impurities in the reducing gas shall not exceed:

O₂ 0,1 % (V/V)

H₂O 0,2 % (V/V).

6.4 Flow rate of reducing gas

The reducing gas flow rate shall, during the reducing period, be maintained at 13 l/min ± 0,5 l/min.

6.5 Purity of heating and cooling gas

Impurities in the nitrogen shall not exceed 0,1% (V/V).

6.6 Temperature of test

The reducing gas shall be preheated while entering the reduction tube to maintain the temperature within the reduction tube and hence the entire test portion at 760 °C ± 5 °C, during the entire reduction period.

7 Sampling and sample preparation

The sampling and the preparation of test samples and test portions shall be in accordance with ISO 10836. 4)

The test sample shall be oven dried at 105 °C ± 5 °C and cooled to room temperature before the preparation of the test portions.

4) ISO 10836:1994 does not yet include test sample preparation for this test method. Subclause 7.2.3 can be applied with the sieves adjusted accordingly.