
Veziva za barve in lake - Klorirane polimerizacijske smole - Splošne metode preskušanja

Binders for paints and varnishes -- Chlorinated polymerization resins -- General methods of test

iTeh STANDARD PREVIEW**Liants pour peintures et vernis -- Résines polymérisées chlorées -- Méthodes générales d'essai****SIST ISO 11668:1998****Ta slovenski standard je istoveten z: ISO 11668:1997**<https://standards.itih.ai/catalog/standards/sist/5391945f-3f3e-49a2-b370-2c80c2509e6b/sist-iso-11668-1998>**ICS:**

87.060.20 Veziva

Binders

SIST ISO 11668:1998**en**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST ISO 11668:1998

<https://standards.iteh.ai/catalog/standards/sist/5391945f-3fe-49a2-b370-2e86c2509e6b/sist-iso-11668-1998>

INTERNATIONAL
STANDARD

ISO
11668

First edition
1997-11-15

**Binders for paints and varnishes —
Chlorinated polymerization resins —
General methods of test**

*Liants pour peintures et vernis — Résines polymérisées chlorées —
Méthodes générales d'essai*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST ISO 11668:1998](https://standards.iteh.ai/catalog/standards/sist/5391945f-3fe-49a2-b370-2e86c2509e6b/sist-iso-11668-1998)

[https://standards.iteh.ai/catalog/standards/sist/5391945f-3fe-49a2-b370-
2e86c2509e6b/sist-iso-11668-1998](https://standards.iteh.ai/catalog/standards/sist/5391945f-3fe-49a2-b370-2e86c2509e6b/sist-iso-11668-1998)



Reference number
ISO 11668:1997(E)

ISO 11668:1997(E)**Foreword**

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 11668 was prepared by Technical Committee ISO/TC 35, *Paints and varnishes*, subcommittee SC 10, *Test methods for binders for paints and varnishes*.

Annex A forms an integral part of this International Standard.

© ISO 1997

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case postale 56 • CH-1211 Genève 20 • Switzerland
Internet central@iso.ch
X.400 c=ch; a=400net; p=iso; o=isocs; s=central

Printed in Switzerland

Binders for paints and varnishes – Chlorinated polymerization resins – General methods of test

1 Scope

This International Standard describes general methods of test for

- a) chlorinated rubber and
- b) vinyl chloride copolymers

for use in paints, varnishes and similar products.

The test methods to be applied in each individual case shall be the subject of agreement between the interested parties.

2 Normative references

iTeh STANDARD PREVIEW

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 842:1984, *Raw materials for paints and varnishes – Sampling.*

ISO 1158:—¹⁾, *Plastics – Vinyl chloride homopolymers and copolymers – Determination of chlorine content.*

ISO 3219:1993, *Plastics – Polymers/resins in the liquid state or as emulsions or dispersions – Determination of viscosity using a rotational viscometer with defined shear rate.*

ISO 4630:1997, *Binders for paints and varnishes – Estimation of colour of clear liquids by the Gardner colour scale.*

ISO 6271:1997, *Clear liquids – Estimation of colour by the platinum-cobalt scale.*

ISO 8130-2:1992, *Coating powders – Part 2: Determination of density by gas comparison pycnometer (referee method).*

ISO 12058-1:1997, *Plastics – Determination of viscosity using a falling-ball viscometer – Part 1: Inclined-tube method.*

1) To be published. (Revision of ISO 1158:1984)

3 Definitions

For the purposes of this International Standard the following definitions apply.

3.1 chlorinated rubber: Resin resulting from the action of chlorine on polyisoprene, natural rubber or similar polymers and containing chlorine contents of 64 % to 68 % (*m/m*).

3.2 vinyl chloride copolymer: Resin resulting from the polymerization of vinyl chloride together with other monomers and containing predominantly polyvinyl chloride.

4 Sampling

Take a representative sample of the product to be tested, as described in ISO 842.

5 Test methods

5.1 Colour number

For the determination of the colour number dissolve the resin.

Determine the colour number of the resin solution as described in ISO 4630 (Gardner colour scale). For resin solutions with a Gardner colour number less than 1 determine the colour as described in ISO 6271 (Platinum-cobalt scale).

The test method, the solvent used and the concentration of the resin solution shall be given in the test report.

5.2 Viscosity

Determine the viscosity of the resin solution as described in ISO 3219.

Indicate the solution temperature and the time period from dissolving the resin until the determination because the viscosity of some polymer solutions depends on this time. For referee methods wait at least 24 h before determining the viscosity.

NOTE It should be borne in mind that not only the temperature but also the intensity of stirring (rate of shear), the duration of the dissolving process and the extent of distribution of the polymer in the solvent when beginning the dissolving process influences the viscosity of the solution.

The viscosity may be determined using a falling-ball viscometer as described in ISO 12058-1 if agreed between the interested parties.

5.3 Density

Determine the density of the resin with a gas comparison pycnometer as described in ISO 8130-2.

5.4 Chlorine content

5.4.1 Chlorine content > 50 % (*m/m*)

Determine the chlorine content as described in ISO 1158.

5.4.2 Chlorine content ≤ 50 % (*m/m*)

Determine the chlorine content as described in annex A.

6 Test report

The test report shall contain at least the following information:

- a) all details necessary to identify the product tested;
- b) a reference to this International Standard (ISO 11668);
- c) the colour (Gardner colour number or Platinum-cobalt colour number), the solvent used and the concentration of the solution;
- d) the viscosity, the method used, the solvent or thinner used, the concentration of the solution, the temperature of the solution and the time between dissolving the resin and the determination;
- e) the density;
- f) the chlorine content and the method used;
- g) any deviations from the procedures specified;
- h) the dates of the tests.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST ISO 11668:1998](https://standards.iteh.ai/catalog/standards/sist/5391945f-3fe-49a2-b370-2e86c2509e6b/sist-iso-11668-1998)

<https://standards.iteh.ai/catalog/standards/sist/5391945f-3fe-49a2-b370-2e86c2509e6b/sist-iso-11668-1998>

Annex A (normative)

Determination of chlorine content – Decomposition by the Wickbold method

A.1 Test apparatus

General laboratory apparatus, and

A.1.1 Wickbold combustion apparatus

(see figure A.1)

A.1.2 Bottled hydrogen, oxygen and nitrogen (commercial quality). Bottles must have pressure reducing valves.

A.1.3 Balance with 0,1 mg divisions

A.1.4 Gas burner

A.1.5 250 ml or 100 ml measuring flasks

A.2 Reagents

A.2.1 Absorption solution.

Sodium hydroxide solution, c approximately 0,1 mol/l.

Add 5 to 7 drops of 30 % (m/m) hydrogen peroxide solution to every litre of sodium hydroxide solution.


A.2.2 Nitric acid, diluted 1 + 1.

Mix 1 part by volume of nitric acid ($\rho = 1,40$ g/ml) with 1 part by volume of water.

A.3 Procedure

A.3.1 Safety

- The normal safety regulations concerning gas supply equipment must be observed, especially when handling hydrogen and oxygen.
- The ignition flame must always be adjusted in the presence of excess oxygen.
- A shield made from safety glass or fine wire-mesh must be placed in front of the burner and the combustion chamber.
- Special care must be taken not to allow hydrogen to enter the combustion chamber when the apparatus is being flushed with hydrogen.
- Spectacles with UV filters must be worn.

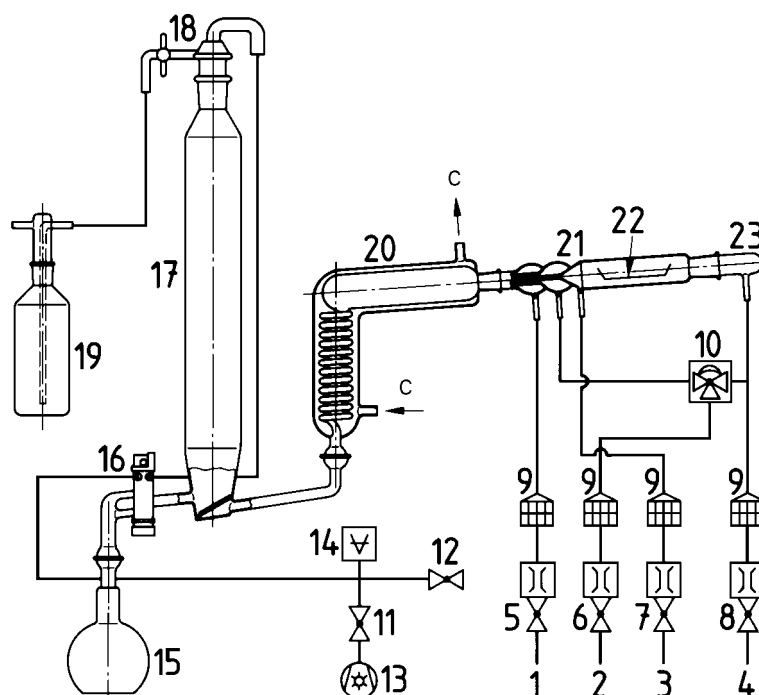

iTeh STANDARD PREVIEW

- (standards.iteh.ai)
- SIST ISO 11668:1998
<https://standards.iteh.ai/en/log/standards/sist/5791945f-3f3e-49a2-b370-2a8617500e6b/sist-iso-11668-1998>
- 1 Hydrogen supply
 - 2 Oxygen supply
 - 3 Hydrogen or oxygen supply
 - 4 Nitrogen supply
 - 5 Regulator valve and flow meter for hydrogen
 - 6 Regulator valve and flow meter for oxygen
 - 7 Regulator valve and flow meter for oxygen or hydrogen
 - 8 Regulator valve and flow meter for nitrogen
 - 9 Flashback arresters
 - 10 Mixer valve
 - 11 Vacuum valve
 - 12 Vacuum bypass valve
 - 13 Water ring pump
 - 14 Vacuum gauge
 - 15 Volumetric flask
 - 16 Multiport valve
 - 17 Absorption vessel with fritted-glass filters
 - 18 Rinsing device
 - 19 Flask containing absorption solution
 - 20 Combustion space with condenser
 - 21 Combustion tube
 - 22 Combustion boat
 - 23 Ground-glass joint
 - C Coolant

Figure A.1 – Diagram of Wickbold combustion apparatus