



SLOVENSKI STANDARD SIST EN ISO 7438:2000

01-oktober-2000

Kovinski materiali - Upogibni preskus (ISO 7438:1985)

Metallic materials - Bend test (ISO 7438:1985)

Metallische Werkstoffe - Biegeversuch (ISO 7438:1985)

Matériaux métalliques - Essai de pliage (ISO 7438:1985)

Ta slovenski standard je istoveten z: **EN ISO 7438:2000**

[SIST EN ISO 7438:2000](https://standards.iteh.ai/catalog/standards/sist/7cbcdfba-0f01-407c-8b8a-6e43e6a70551/sist-en-iso-7438-2000)

<https://standards.iteh.ai/catalog/standards/sist/7cbcdfba-0f01-407c-8b8a-6e43e6a70551/sist-en-iso-7438-2000>

ICS:

77.040.10 Mehansko preskušanje kovin Mechanical testing of metals

SIST EN ISO 7438:2000

en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 7438:2000

<https://standards.iteh.ai/catalog/standards/sist/7cbcdfba-0f01-407c-8b8a-6e43e6a70551/sist-en-iso-7438-2000>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN ISO 7438

January 2000

ICS 77.040.00

English version

Metallic materials - Bend test (ISO 7438:1985)

Matériaux métalliques - Essai de pliage (ISO 7438:1985)

Metallische Werkstoffe - Biegeversuch (ISO 7438:1985)

This European Standard was approved by CEN on 12 November 1999.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

ITeH STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 7438:2000

<https://standards.iteh.ai/catalog/standards/sist/7cbcdfba-0f01-407c-8b8a-6e43e6a70551/sist-en-iso-7438-2000>



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Foreword

The text of the International Standard from Technical Committee ISO/TC 164 "Mechanical testing of metals" of the International Organization for Standardization (ISO) has been taken over as an European Standard by Technical Committee ECISS/TC 1 "Steel - Mechanical testing", the secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by July 2000, and conflicting national standards shall be withdrawn at the latest by July 2000.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.


Endorsement notice

The text of the International Standard ISO 7438:1985 has been approved by CEN as a European Standard without any modification.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 7438:2000

<https://standards.iteh.ai/catalog/standards/sist/7cbcdfba-0f01-407c-8b8a-6e43e6a70551/sist-en-iso-7438-2000>

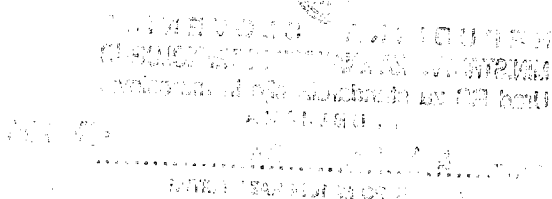

International Standard



7438

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

Metallic materials — Bend test

Matériaux métalliques — Essai de pliage

First edition — 1985-07-01

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN ISO 7438:2000](https://standards.iteh.ai/catalog/standards/sist/7cbcdfba-0f01-407c-8b8a-6e43e6a70551/sist-en-iso-7438-2000)

<https://standards.iteh.ai/catalog/standards/sist/7cbcdfba-0f01-407c-8b8a-6e43e6a70551/sist-en-iso-7438-2000>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council. They are approved in accordance with ISO procedures requiring at least 75 % approval by the member bodies voting.

International Standard ISO 7438 was prepared by Technical Committee ISO/TC 164, *Mechanical testing of metals*.

It cancels and replaces ISO Recommendations ISO/R 85-1959, ISO/R 87-1959, ISO/R 398-1964 and ISO/R 954-1969, of which it constitutes a technical revision.

Metallic materials — Bend test

iTeh STANDARD PREVIEW (standards.iteh.ai)

1 Scope and field of application

This International Standard specifies the method for determining the ability of metallic materials to undergo plastic deformation in bending.

This International Standard applies to the bend test of test pieces taken from metallic products as specified in the relevant product standard. It is not applicable to certain materials and/or products, for example tubes in full section or welded joints, for which other standards exist.

2 Principle

The bend test consists in submitting a test piece of round, square, rectangular, or polygonal cross-section to plastic deformation by bending, without changing the direction of loading, until a specified angle of bend is reached.

The axes of the two legs of the test piece remain in a plane perpendicular to the axis of bending. In the case of a 180° bend, the two lateral surfaces may, depending on the requirements of the material standard, lie flat against each other or may be parallel at a specified distance, an insert being used to control this distance.

3 Symbols and designations

Symbols and designations used in the bend test are shown in figures 1 and 2, and specified in table 1.

Table 1

Symbol	Designation	Unit
	Thickness or diameter of test piece (or diameter of the inscribed circle for pieces of polygonal cross-section)	mm
b	Width of test piece	mm
L	Length of test piece	mm
l	Distance between supports	mm
D	Diameter of mandrel	mm
α	Angle of bend	degree
r	Internal radius of bend portion of test piece after bending	mm

4 Test equipment

The bend test shall be carried out in testing machines or presses equipped with the following devices:

- bending device with two supports and a mandrel as shown in figure 1;
- bending device with a V-block and a mandrel as shown in figure 2;
- bending device with a clamp as shown in figure 3.

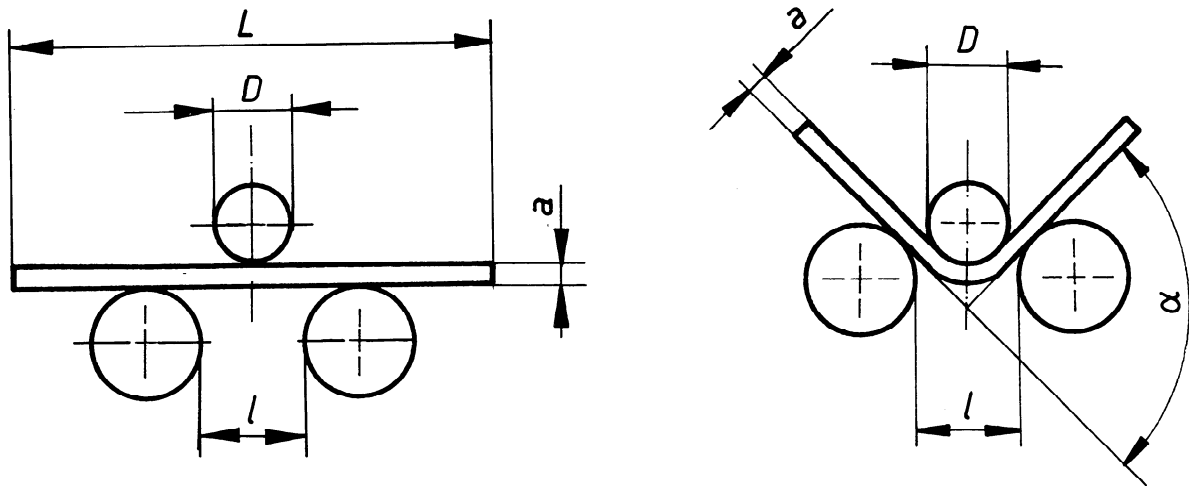


Figure 1

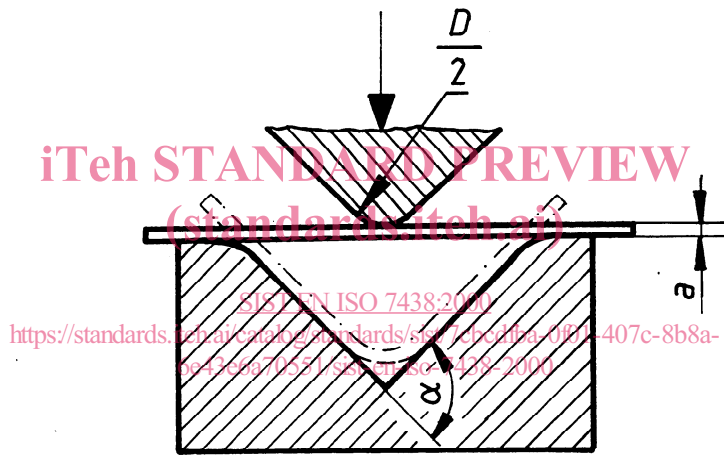


Figure 2

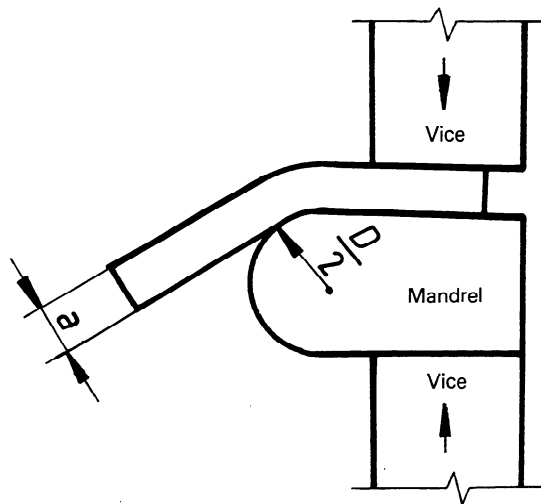


Figure 3

4.1 Bending device with supports and a mandrel

4.1.1 The length of the supports and the width of the mandrel shall be greater than the width or diameter of the test piece. The diameter of the mandrel is determined by the material standard. The test piece supports and the mandrel shall be of sufficient hardness (see figure 1).

4.1.2 Unless otherwise specified, the distance between the supports, l , shall be:

$$l = (D + 3a) \pm a/2$$

and shall not change during the bend test.

4.2 Bending device with a V-block

The tapered surfaces of the V-block shall form an angle of $180^\circ - \alpha$ (see figure 2). This angle is specified in the relevant standard.

The edges of the V-block shall have a radius between 1 and 10 times the thickness of the test piece and shall be of sufficient hardness.

4.3 Bending device with a clamp

The device consists of a clamp and a mandrel of sufficient hardness; it may be equipped with a lever for applying force to the test piece (see figure 3).

5 Test piece

5.1 Round, square, rectangular, or polygonal cross-section test pieces shall be used in the test. Any areas of the material affected by shearing or flame cutting and similar operations during the sampling of test pieces shall be removed. However, testing a test piece, the affected parts of which have not been removed, is acceptable, provided that the result is satisfactory.

5.2 The edges of rectangular test pieces shall be rounded to a radius not exceeding one-tenth of the thickness of the test pieces. The rounding shall be made so that no transverse burrs, scratches or marks are formed which might adversely affect the test results. However, testing a test piece, the edges of which have not been rounded, is acceptable, provided that the result is satisfactory.

5.3 Unless otherwise specified in the relevant standard, the width of the test piece shall be as follows:

- the same as the product width, if the latter is equal to or less than 20 mm;
- when the width of a product is more than 20 mm:
 - 20 ± 5 mm for products of thickness less than 3 mm,
 - between 20 and 50 mm for products of thickness equal to or greater than 3 mm.

5.4 Thickness of the test piece

5.4.1 The thickness of the test pieces from sheets, strips and sections shall be equal to the thickness of the product to be tested. If the thickness of the product is greater than 25 mm, it may be reduced by machining one surface to give a thickness not less than 25 mm. During bending, the unmachined side shall be on the tension-side surface of the test piece.

5.4.2 The round or polygonal cross-section test pieces shall be submitted to the bend test while having a cross-section equal to that of the product if the diameter (for a round cross-section) or the inscribed circle diameter (for a polygonal cross-section) does not exceed 50 mm. When the diameter, or the inscribed circle diameter, of the test piece exceeds 30 mm up to and including 50 mm, it may be reduced to not less than 25 mm. When the diameter, or the inscribed circle diameter, of the test piece exceeds 50 mm, it shall be reduced to not less than 25 mm (see figure 4). During bending, the unmachined side shall be on the tension-side surface of the test piece.

5.5 In the case of forgings, castings and semifinished products, the dimensions of the test piece and sampling shall be defined in the general delivery requirements or by agreement.

5.6 By agreement but not in cases of dispute, test pieces of a greater thickness and width than those specified in 5.3 and 5.4 may be subjected to the bend test.

5.7 The length of a test piece depends on the thickness of the test piece and the test equipment used.

6 Procedure

6.1 In general, the test shall be carried out at ambient temperature between 10 and 35 °C. Tests carried out under controlled conditions shall be made at a temperature of 23 ± 5 °C.



Figure 4