



SLOVENSKI STANDARD

SIST EN 10034:1997

01-december-1997

Profili I in H iz konstrukcijskih jekel - Mejni odstopki mer in tolerance oblik

Structural steel I and H sections - Tolerances on shape and dimensions

I- und H-Profil aus Baustahl - Grenzabmaße und Formtoleranzen

Poutrelles I et H en acier de construction - Tolérances de formes et de dimensions

Ta slovenski standard je istoveten z: **EN 10034:1993**

[SIST EN 10034:1997](https://standards.iteh.ai/catalog/standards/sist/b0222bbf-9622-424b-aa56-df597c87b331/sist-en-10034-1997)

<https://standards.iteh.ai/catalog/standards/sist/b0222bbf-9622-424b-aa56-df597c87b331/sist-en-10034-1997>

ICS:

77.140.70 Jekleni profili Steel profiles

SIST EN 10034:1997 en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 10034:1997](https://standards.iteh.ai/catalog/standards/sist/b0222bbf-9622-424b-aa56-df597c87b331/sist-en-10034-1997)

<https://standards.iteh.ai/catalog/standards/sist/b0222bbf-9622-424b-aa56-df597c87b331/sist-en-10034-1997>

EUROPEAN STANDARD

EN 10034:1993

NORME EUROPÉENNE

EUROPÄISCHE NORM

September 1993

UDC 669.14.018.29-423.1:621.753.1

Descriptors: Iron and steel products, I beams, structural steels, dimensional tolerances, form tolerances

English version

**Structural steel I and H sections - Tolerances on
shape and dimensions**Poutrelles I et H en acier de construction -
Tolerances de formes et de dimensionsI- und H-Profile aus Baustahl - Grenzabmaße und
Formtoleranzen**STANDARD PREVIEW**
(standards.iteh.ai)SIST EN 10034:1997<https://standards.iteh.ai/catalog/standards/sist/b0222bbf-9622-424b-aa56-df597c87b331/sist-en-10034-1997>

This European Standard was approved by CEN on 1993-08-30. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

The European Standards exist in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CENEuropean Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Page 2
EN 10034:1993

Contents list	page
Foreword	
1 Scope	3
2 Normative references	4
3 Definitions	4
4 Rolling tolerances for structural steel I and H sections	4
5 Tolerance on mass	5
6 Tolerance on length	5
Tables	
1 Dimensional tolerances for structural steel I and H sections	6
2 Tolerances on out-of-square and web off-centre of I and H steel sections	7
3 Tolerances on straightness of I and H steel sections	8
Annex A (informative) Straightness measurement	9

<https://standards.iteh.ai/catalog/standards/sist/b0222bbf-9622-424b-aa56-df597c87b331/sist-en-10034-1997>

Foreword

This European Standard has been prepared by ECISS/TC11 Sections: Tolerances and Dimensions; the Secretariat of which is held by BSI.

The discussions within ECISS/TC11 were based on

Euronorm 34-62 Broad flanged beams with parallel sides. Rolling tolerances
and

Euronorm 44-63 Hot rolled IPE joists. Rolling tolerances

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at least by march 1994, and conflicting national standards shall be withdrawn at the latest by march 1994.

According to the CEN/CENELEC Internal Regulations, the following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland, United Kingdom.

Itch STANDARD PREVIEW
(standards.itech.ai)

SIST EN 10034:1997

<https://standards.itech.ai/catalog/standards/sist/b0222bbf-9622-424b-aa56-df597c87b331/sist-en-10034-1997>

1 Scope

This European Standard specifies tolerances on shape dimensions and mass of structural steel I and H sections. These requirements do not apply to I and H sections rolled from stainless steel. These requirements do not apply to taper flange sections.

NOTE: Until a European Standard for dimensions of I and H beams is published Euronorm 19 and Euronorm 53 or corresponding national standards may be used.

2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated into it by amendment or revision. For undated references the latest edition of the publication referred to applies.

EN 10079 Definition of steel products

Euronorm 19: 1957 IPE beams, parallel flanged beams

Euronorm 53: 1962 Wide flange beams with parallel flanges

iTeh STANDARD PREVIEW
(standards.iteh.ai)
SIST EN 10034:1997
<https://standards.iteh.ai/catalog/standards/sist/b0222b0f-9b22-424b-aa56-df597c87b331/sist-en-10034-1997>

3 Definitions

For the purpose of this European Standard, the definitions in EN 10079 apply.

4 Rolling tolerances for structural steel I and H sections

4.1 Section height (h)

The deviation from nominal on section height measured at the centre line of web thickness shall be within the tolerance given in table 1.

4.2 Flange width (b)

The deviation from nominal on flange width shall be within the tolerance given in table 1.

4.3 Web thickness (s)

The deviation from nominal on web thickness measured at the mid-point of dimension h shall be within the tolerance given in table 1.

4.4 Flange thickness (t)

The deviation from nominal on flange thickness measured at the quarter flange width point shall be within the tolerance given table 1.

4.5 Out-of-squareness ($k + k'$)

The out-of-squareness of the section shall not exceed the maximum given in table 2.

4.6 Web off-centre (e)

The mid-thickness of the web shall not deviate from the mid-width position on the flange by more than the distance (e) given in table 2.

4.7 Straightness (q_{xx} or q_{yy})

The straightness shall comply with the requirements given in table 3.

5 Tolerance on mass

The deviation from the nominal mass of a batch or a piece shall not exceed $\pm 4.0\%$.

The mass deviation is the difference between the actual mass of the batch or piece and the calculated mass.

The calculated mass shall be determined using a density of $7,85 \text{ kg/dm}^3$.

6 Tolerance on length

The sections shall be cut to ordered lengths to tolerances of:

a) $\pm 50 \text{ mm}$

or b) $+ 100 \text{ mm}$ where minimum lengths are requested

L represents the longest useable length of the section assuming that the ends of the section have been cut square (see figure 1).


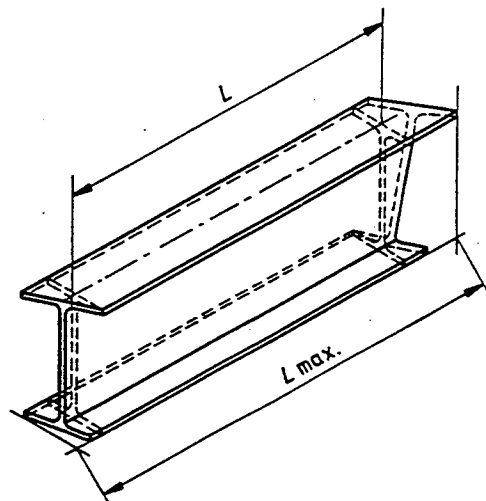


Figure 1: Measurement of length L on I and H steel sections

Table 1 Dimensional tolerances for structural steel I and H sections

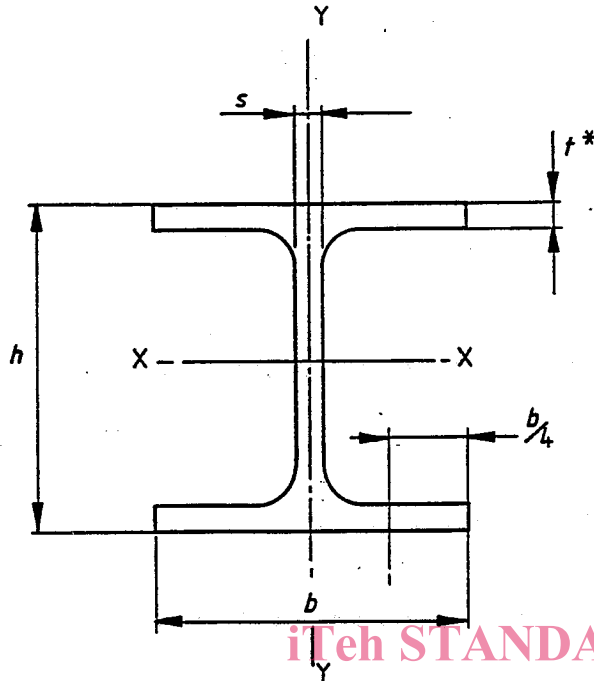


* t is measured at $b/4$
(see clause 4.4.)

iTeh STANDARD PREVIEW

(standards.iteh.ai)

Section height h		Flange width b		Web thickness s		Flange thickness t	
height mm	tol mm	width mm	tol mm	thickness mm	tol mm	thickness mm	tol mm
$h \leq 180$	+3.0 -2.0	$b \leq 110$	+4.0 -1.0	$s < 7$	± 0.7	$t < 6.5$	+1.5 -0.5
$180 < h \leq 400$	+4.0 -2.0	$110 < b \leq 210$	+4.0 -2.0	$7 \leq s < 10$	± 1.0	$6.5 \leq t < 10$	+2.0 -1.0
$400 < h \leq 700$	+5.0 -3.0	$210 < b \leq 325$	+4.0 -4.0	$10 \leq s < 20$	± 1.5	$10 \leq t < 20$	+2.5 -1.5
$h > 700$	+5.0 -5.0	$b > 325$	+6.0 -5.0	$20 \leq s < 40$	± 2.0	$20 \leq t < 30$	+2.5 -2.0
				$40 \leq s < 60$	± 2.5	$30 \leq t < 40$	+2.5 -2.5
				$s \geq 60$	± 3.0	$40 \leq t < 60$	+3.0 -3.0
						$t \geq 60$	+4.0 -4.0

Table 2 Tolerances on out-of-square and web off-centre of structural steel I and H sections

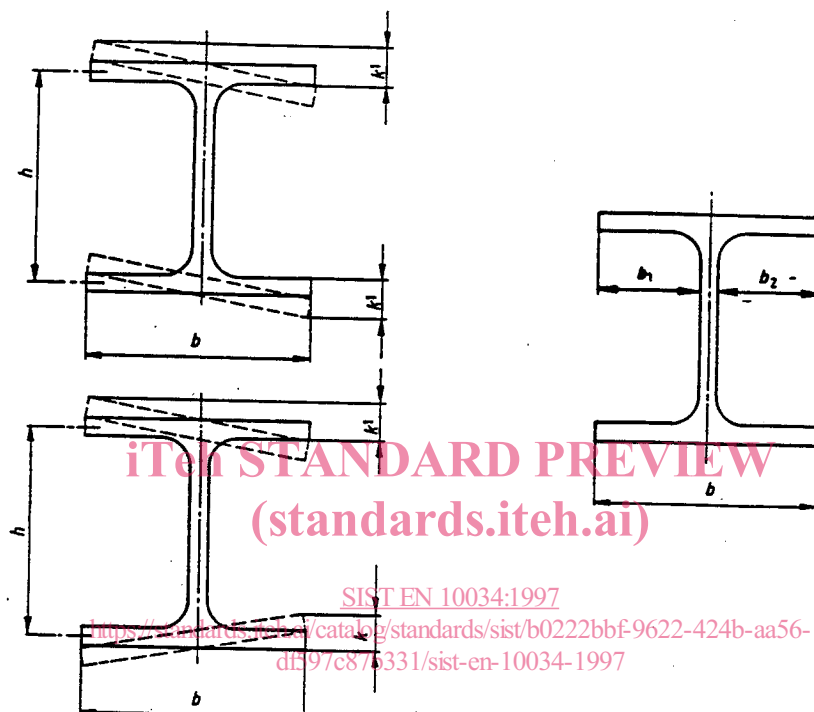

SIST EN 10034:1997

<http://standards.iteh.ai/catalog/standards/sist/b0222bbf-9622-424b-aa56-d197c876331/sist-en-10034-1997>

Out-of-square $k + k'$		Web off-centre e where $e = \frac{b_1 - b_2}{2}$	
flange width b mm	tol mm	flange width b mm	tol mm
$b \leq 110$	1.5	Where $t < 40$	4.0
$b > 110$	2 % of b (max 6.5 mm)	$b \leq 110$	2.5
		$110 < b \leq 325$	3.5
		$b > 325$	5.0
		Where $t \geq 40$	4.0
		$110 < b \leq 325$	5.0
		$b > 325$	8.0