

INTERNATIONAL STANDARD



Magnetic materials –
Part 6: Methods of measurement of the magnetic properties of magnetically soft metallic and powder materials at frequencies in the range 20 Hz to ~~200~~ 100 kHz by the use of ring specimens

iTeh Standards
Document Preview

[IEC 60404-6:2018](#)

<https://standards.iteh.ai/catalog/standards/iec/db58708d-a55f-485c-b8d3-2ec8937fe596/iec-60404-6-2018>





THIS PUBLICATION IS COPYRIGHT PROTECTED
Copyright © 2018 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

IEC Catalogue - webstore.iec.ch/catalogue

The stand-alone application for consulting the entire bibliographical information on IEC International Standards, Technical Specifications, Technical Reports and other documents. Available for PC, Mac OS, Android Tablets and iPad.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and also once a month by email.

Electropedia - www.electropedia.org

The world's leading online dictionary of electronic and electrical terms containing 21 000 terms and definitions in English and French, with equivalent terms in 16 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Glossary - std.iec.ch/glossary

67 000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

[IEC 60404-6:2018](https://standards.iteh.ai/catalog/standards/iec/db58708d-a55f-485c-b8d3-2ec8937fe596/iec-60404-6-2018)

<https://standards.iteh.ai/catalog/standards/iec/db58708d-a55f-485c-b8d3-2ec8937fe596/iec-60404-6-2018>



IEC 60404-6

Edition 3.0 2018-05
REDLINE VERSION

INTERNATIONAL STANDARD



Magnetic materials –

Part 6: Methods of measurement of the magnetic properties of magnetically soft metallic and powder materials at frequencies in the range 20 Hz to ~~200~~ 100 kHz by the use of ring specimens

iTeh Standards
Document Preview

[IEC 60404-6:2018](#)

<https://standards.iteh.ai/catalog/standards/iec/db58708d-a55f-485c-b8d3-2ec8937fe596/iec-60404-6-2018>

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 17.220.20; 29.030

ISBN 978-2-8322-5754-8

Warning! Make sure that you obtained this publication from an authorized distributor.

CONTENTS

FOREWORD.....	4
INTRODUCTION.....	4
1 Scope.....	7
2 Normative references	7
3 Terms and definitions	8
4 General principles of measurement	8
4.1 Principle of the ring method	8
4.2 Test specimen	8
4.3 Windings.....	9
5 Temperature measurements	10
6 Measurement of magnetic the relative amplitude permeability and the AC magnetization curve using the voltmeter-ammeter method	10
6.1 Introduction General	10
6.2 Apparatus and connections	10
6.3 Waveform of induced secondary voltage or magnetizing current	11
6.4 Determination of characteristics.....	12
6.4.1 Determination of the peak value of the magnetic field strength	12
6.4.2 Determination of the peak value of the magnetic flux density	13
6.4.3 Determination of the r.m.s. amplitude permeability and the relative amplitude permeability.....	13
6.4.4 Determination of the AC magnetization curve	14
7 Measurement of the specific total loss by the wattmeter method.....	14
7.1 Principle of measurement.....	14
7.2 Voltage measurement.....	16
7.2.1 Average type voltmeter, V_1	16
7.2.2 R.M.S. type voltmeter, V_2	16
7.3 Power measurement	16
7.4 Procedure for the measurement of the specific total loss	16
7.5 Determination of the specific total loss.....	16
Measurement of magnetic properties using a digital impedance bridge.....	16
 Principle of measurement.....	16
 Apparatus.....	16
 Procedure.....	16
 Determination of the relative a.c. inductance permeability.....	16
 Determination of the specific total loss.....	16
Measurement of magnetic properties using digital methods.....	16
 Introduction.....	16
 Apparatus and connections.....	16
 Magnetizing current waveform.....	16
 Magnetizing winding.....	16
 Determination of the magnetic field strength.....	16
 Determination of the magnetic flux density.....	16
 Determination of the relative a.c. permeability.....	16
 Determination of a.c. magnetization curve.....	16
 Determination of the specific total loss.....	16
8 Uncertainties	22

9	Test report.....	22
	Annex A (informative) Guidance on requirements for windings and instrumentation in order to minimise additional losses	24
	A.1 Introduction General	24
	A.2 Reduction of additional losses	24
	Annex B (informative) Digital sampling technique for the determination of magnetic properties and numerical air flux compensation	25
	B.1 General.....	25
	B.2 Technical details and requirements	25
	B.3 Calibration aspects	29
	B.4 Numerical air flux compensation	29
	Annex C (informative) Sinusoidal waveform control by digital means	30
	Bibliography.....	31
	Figure – Circuit of the digital impedance bridge method.....	
	Figure – Circuit of the digital method	
	Figure 1 – Circuit of the ring method measurement apparatus.....	11
	Figure 2 – Circuit of the conventional analogue wattmeter method (also representing the metrological principle of the digital wattmeter method)	15
	Figure 3 – The wattmeter method when connected with the digital sampling technique (example of circuit)	15

(https://standards.iteh.ai)
Document Preview

[IEC 60404-6:2018](https://standards.iteh.ai/catalog/standards/iec/db58708d-a55f-485c-b8d3-2ec8937fe596/iec-60404-6-2018)

<https://standards.iteh.ai/catalog/standards/iec/db58708d-a55f-485c-b8d3-2ec8937fe596/iec-60404-6-2018>

INTERNATIONAL ELECTROTECHNICAL COMMISSION

MAGNETIC MATERIALS –

Part 6: Methods of measurement of the magnetic properties of magnetically soft metallic and powder materials at frequencies in the range 20 Hz to ~~200~~ 100 kHz by the use of ring specimens

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as “IEC Publication(s)”). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

This redline version of the official IEC Standard allows the user to identify the changes made to the previous edition. A vertical bar appears in the margin wherever a change has been made. Additions are in green text, deletions are in strikethrough red text.

International Standard IEC 60404-6 has been prepared by IEC technical committee 68: Magnetic alloys and steels.

This third edition cancels and replaces the second published in 2003. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) adaption to modern measurement and evaluation methods, in particular the introduction of the widely spread digital sampling method for the acquisition and evaluation of the measured data;
- b) limitation of the frequency range up to 100 kHz;
- c) deletion of Clause 7 of the second edition that specified the measurement of magnetic properties using a digital impedance bridge;
- d) addition of a new Clause 7 on the measurement of the specific total loss by the wattmeter method, including an example of the application of the digital sampling method;
- e) addition of an informative annex on the technical details of the digital sampling technique for the determination of magnetic properties.

The text of this International Standard is based on the following documents:

FDIS	Report on voting
68/595/FDIS	68/600/RVD

Full information on the voting for the approval of this International Standard can be found in the report on voting indicated in the above table.

This document has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all parts in the IEC 60404 series, published under the general title *Magnetic materials*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under "<http://webstore.iec.ch>" in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

The contents of the corrigendum of November 2018 have been included in this copy.

IMPORTANT – The “colour inside” logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this publication using a colour printer.

INTRODUCTION

~~This edition of IEC 60404-6 has been prepared by WG2 in the TC68 maintenance programme of publications. The d.c. measurements in the first edition of this standard are now covered in IEC 60404-4 and Amendment 1 to that standard. This edition of IEC 60404-6 includes measurements on magnetically soft powder materials. Since measurements on these materials at high frequencies employ some of the techniques used to measure magnetic components, there has been active collaboration with IEC TC51. IEC TC51 recently started to publish the new IEC 62044 series which will be composed of four parts. IEC 62044-3 presents methods of measurement of magnetic properties at high excitation levels appropriate to various ferrite core applications, whereas this edition of IEC 60404-6 covers the requirements of material measurements excluding ferrites, so that the two standards do not overlap.~~

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[IEC 60404-6:2018](#)

<https://standards.iteh.ai/catalog/standards/iec/db58708d-a55f-485c-b8d3-2ec8937fe596/iec-60404-6-2018>

MAGNETIC MATERIALS –

Part 6: Methods of measurement of the magnetic properties of magnetically soft metallic and powder materials at frequencies in the range 20 Hz to ~~200~~ 100 kHz by the use of ring specimens

1 Scope

This part of IEC 60404 specifies methods for the measurement of AC magnetic properties of soft magnetic materials, other than electrical steels and soft ferrites, in the frequency range 20 Hz to ~~200~~ 100 kHz. The materials covered by this part of IEC 60404 include those speciality alloys listed in IEC 60404-8-6, amorphous and nano-crystalline soft magnetic materials, pressed and sintered and metal injection moulded parts such as are listed in IEC 60404-8-9, cast parts and magnetically soft composite materials.

The object of this part is to define the general principles and the technical details of the measurement of the magnetic properties of magnetically soft materials by means of ring methods. For materials supplied in powder form, a ring test specimen is formed by the appropriate pressing method for that material.

~~DC magnetic measurements on magnetically soft materials shall be~~ The measurement of the DC magnetic properties of soft magnetic materials is made in accordance with the ring method of IEC 60404-4. The determinations of the magnetic characteristics of magnetically soft components ~~shall be~~ are made in accordance with IEC 62044-3.

NOTE IEC 62044-3:2000 specifies methods for the measurement of AC magnetic characteristics of magnetically soft components in the frequency range up to 10 MHz.

Normally, the measurements ~~shall be~~ are made at an ambient temperature of $(23 \pm 5)^\circ\text{C}$ on ring test specimens which have first been magnetized, then demagnetized. Measurements can be made over other temperature ranges by agreement between ~~supplier and purchaser~~ parties concerned.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60050-121, *International Electrotechnical Vocabulary – Part 121: Electromagnetism*

IEC 60050-221, *International Electrotechnical Vocabulary – Chapter 221: Magnetic materials and components*

IEC 60404-2:~~1996~~, *Magnetic materials – Part 2: Methods of measurement of the magnetic properties of electrical steel sheet and strip by means of an Epstein frame*

IEC 60404-4:~~1995~~, *Magnetic materials – Part 4: Methods of measurement of d.c. magnetic properties of iron and steel*

~~Amendment 1:2000~~

IEC 60404-8-6:~~1999~~, *Magnetic materials – Part 8-6: Specifications for individual materials – Soft magnetic metallic materials*

IEC 60404-8-9:~~1994~~, *Magnetic materials – Part 8: Specifications for individual materials – Section 9: Standard specification for sintered soft magnetic materials*

IEC 62044-3:~~2000~~, *Cores made of soft magnetic materials – Measuring methods – Part 3: Magnetic properties at high excitation levels*

ISO/IEC Guide 98-3, *Uncertainty of measurement – Part 3: Guide to the expression of uncertainty in measurement*, ~~1993~~ (GUM:1995)

3 Terms and definitions

For the purposes of this document, the terms and definitions given in IEC 60050-121 and IEC 60050-221 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 General principles of measurement

4.1 Principle of the ring method

The measurements are made on a closed magnetic circuit in the form of a ring test specimen wound with ~~one or~~ two windings.

4.2 Test specimen

The test specimen shall be in the form of a ring of rectangular cross-section which may be formed by

- winding thin strip or wire to produce a clock-spring wound toroidal core; or
- ~~punching, laser cutting or photochemically etching~~ a stack of punched, laser cut, wire cut or photochemically etched ring laminations; or
- pressing and sintering of powders, metal injection moulding, 3D printing or casting.

In the case of powder materials, the production of a ring test specimen by metal injection moulding or by pressing (with heating if applicable) shall be carried out in accordance with the material manufacturer's recommendations to achieve the optimum magnetic performance of the powder material.

For all types of test specimen, burrs and sharp edges should be removed prior to heat treatment. ~~In the case of high permeability material,~~ It is preferable to enclose the ~~ring~~ test specimen in a two-part non-magnetic annular case. The case dimensions shall be such that it closely fits without introducing stress into the material of the test specimen.

The ring shall have dimensions such that the ratio of the outer to inner diameter shall be no greater than 1,4 and preferably less than 1,25 to achieve a sufficiently homogenous magnetization of the test specimen.

For solid and pressed powder materials, the dimensions of the test specimen, that is the outer and inner diameters and the height of the ring, shall be measured with suitable calibrated measuring instruments. The respective dimensions shall be measured at several locations on a test specimen and averaged. The cross-sectional area of the test specimen shall be calculated from Formula (1).

$$A = \frac{(D - d)}{2} h \quad (1)$$

where

A is the cross-sectional area of the test specimen, in square metres;

D is the outer diameter of the test specimen, in metres;

d is the inner diameter of the test specimen, in metres;

h is the height of the test specimen, in metres.

For a stack of laminations or a toroidal wound core, the cross-sectional area of the test specimen shall be calculated from the mass, density and the values of the inner and outer diameter of the ring specimen. The mass and diameters shall be measured with suitable calibrated instruments. The density shall be the conventional density for the material supplied by the manufacturer. The cross-sectional area shall be calculated from Formula (2).

$$A = \frac{2 m}{\rho \pi (D + d)} \quad (2)$$

where

m is the mass of the test specimen, in kilograms;

ρ is the density of the material, in kilograms per cubic metre.

For the calculation of the magnetic field strength ~~use~~ the mean magnetic path length of the test specimen determined from Formula (3) ~~shall be used~~.

$$l_m = \pi \frac{(D + d)}{2} \quad (3)$$

where

l_m is the mean magnetic path length of the test specimen, in metres.

NOTE For measurements of magnetically soft components, an effective core cross-sectional area and an effective magnetic path length are used (described in IEC 62044-3:2000). The difference in results between material measurements and component measurements is larger when the ratio of the outer to inner diameter is larger.

If the specific total loss is to be determined, ~~then~~ the mass of the test specimen shall be measured with a suitable calibrated balance.

4.3 Windings

The test specimen shall be wound with a magnetizing winding and a secondary winding (see Annex A).

The numbers of ~~windings and~~ turns depend upon the measuring equipment and method being used. ~~For specific total loss measurements, a magnetizing and a secondary winding are normally required. In this case,~~ The secondary winding shall be wound as closely as possible to the test specimen to minimize the effect of air flux ~~included in~~ enclosed between the test specimen and the secondary winding. All windings shall be wound uniformly over the whole length of the test specimen.

For measurements at frequencies above power frequencies, care shall be taken to avoid complications related to capacitance and other effects. These are introduced and discussed in Annex A.

Care shall be taken to ensure that the wire insulation is not damaged during the winding process causing a short circuit to the test specimen. An electrical check shall be made with a

suitable AC insulation resistance measuring device to ensure that there is no direct connection between the windings and the test specimen.

5 Temperature measurements

When the temperature of the surface of the test specimen is required, it shall be measured by affixing a calibrated non-magnetic thermocouple (for example a type T thermocouple) to the test specimen. Where the test specimen is ~~encapsulated~~ enclosed in an annular case, a small hole shall be made in the ~~encapsulation case~~, taking care not to damage the material of the test specimen, and the thermocouple fixed in contact with the ~~core material~~ test specimen. If this is not possible, the thermocouple shall be affixed to the ~~encapsulation case~~ and this procedure shall be reported in the test report. The thermocouple shall be connected to a suitable calibrated ~~digital~~ voltmeter in order to measure its output voltage which can be related to the corresponding temperature through the calibration tables for the thermocouple.

Where the temperature of the test specimen is found to vary with time after magnetization, the measurements of the magnetic properties shall be carried out either when an agreed temperature is reached or after a time agreed between the ~~purchaser and supplier~~ parties concerned. If measurements are to be made at elevated temperatures, these may be carried out with the test specimen placed in a suitable oven to produce the required temperature.

NOTE A second smaller time-dependent magnetic relaxation effect ~~may~~ can also affect the magnetic properties. For the types of materials covered by this document, the effect is usually masked by temperature changes. However, if such magnetic relaxation effects become apparent, then the test specimen should ~~be allowed to~~ dwell at the prescribed magnetic flux density or magnetic field strength for an agreed period of time before making the final measurements.

6 Measurement of ~~magnetic~~ the relative amplitude permeability and the AC magnetization curve ~~using the voltmeter-ammeter method~~

6.1 Introduction General

IEC 60404-6:2018

The measurements are made using the ring method at frequencies normally from 20 Hz to ~~200~~ 100 kHz, the upper frequency being limited by the performance of the instrumentation.

NOTE Where suitable calibrated instruments exist and careful winding to reduce interwinding capacitance has been performed, this upper limit may be extended to 1 MHz (See Annex A).

NOTE ~~DC measurements should be made in accordance with the ring method described in IEC 60404-4.~~

NOTE ~~A selection of methods for the measurement of loss and effective permeability of cores, taken from current production, at high excitation levels and at frequencies ranging from practically d.c. to 10 MHz and even higher, is given in 6.2 and 6.3 of IEC 62044-3.~~


6.2 Apparatus and connections

~~The ring test specimen shall be wound with a magnetizing winding, N_1 , and a secondary winding, N_2 (see 3.2 and Annex A).~~

The apparatus shall be connected as shown in Figure 1.

NOTE 1 Figure 3 can be used for the measurement of the relative amplitude permeability and the magnetization curve using the digital sampling technique.

NOTE 2 For the application of digital sampling technique, see Annex B.

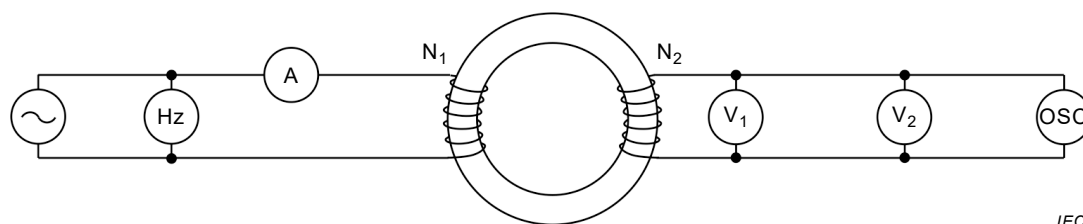

IEC

Key

- ~ power supply (usually an oscillator and a power amplifier)
- A true r.m.s. or peak reading ammeter, or a true r.m.s. or peak reading voltmeter and a non-inductive precision resistor to measure the magnetizing current
- Hz frequency meter
- N_1 magnetizing winding
- N_2 secondary winding
- OSC oscilloscope
- V_1 average type voltmeter
- V_2 r.m.s. voltmeter

Figure 1 – Circuit of the ring-method measurement apparatus

NOTE When conducting sinusoidal current measurements, a non-inductive precision resistor should be connected in series with the magnetizing winding N_1 to guarantee that the magnetizing circuit resistance is at least ten times greater than the impedance of the magnetizing winding N_1 on the test specimen.

The source of alternating current shall have a variation of voltage and frequency at its output individually not exceeding $\pm 0,2\%$ of the adjusted value during the measurement. It shall be connected to a true r.m.s. or peak reading ammeter, or a true r.m.s. or peak reading voltmeter and a parallel non-inductive precision resistor, in series with the magnetizing winding N_1 on the ring test specimen, to measure the magnetizing current.

The secondary circuit comprises a secondary winding N_2 connected to two voltmeters in parallel. One voltmeter V_2 measures the true r.m.s. value, the other voltmeter V_1 measures the average rectified value but is sometimes scaled in values 1,111 times the rectified value.

NOTE The waveform of the induced secondary voltage that is induced in the secondary winding N_2 should be checked with an oscilloscope to ensure that only the fundamental component is present.

6.3 Waveform of induced secondary voltage or magnetizing current

In order to obtain comparable measurements, it shall be agreed prior to the measurements that either the waveform of the induced secondary voltage or the waveform of the magnetizing current shall be maintained sinusoidal with a form factor of 1,111 with a relative tolerance of $\pm 1\%$. In the latter case, a non-inductive precision resistor connected in series with the magnetizing circuit winding is required.

NOTE 1 The waveform of the induced secondary voltage and the magnetizing current can be measured by the digital sampling technique. See Figure 3 and Annex B.

NOTE The time constant of the non-inductive precision resistor should be checked to be low to ensure that the waveform is within the specified limits.

NOTE The non-inductive precision resistor can may be the same resistor as used for the measurement of the magnetizing current.

NOTE 2 Sinusoidal waveform control may can be achieved by digital means (see Annex C).

At frequencies in the range 20 Hz to 50 kHz, the form factor of the induced secondary voltage can be determined by connecting two voltmeters having a high impedance (typically > 1 MΩ in parallel with 90 pF to 150 pF) across the secondary winding. One voltmeter shall be responsive to the r.m.s. value of voltage and ~~one~~ the other shall be responsive to the average rectified value of the ~~secondary~~ voltage. The form factor is then determined from the ratio of the r.m.s. value to the average rectified value.

NOTE For optimum power transfer, it may be necessary to optimize the number of turns of the magnetizing winding to match the output impedance of the power ~~source~~ supply. This can be determined from Formula (4).

$$Z = j\omega L \tag{4}$$

where

Z is the output impedance of the power ~~source~~ supply, in ohms;

j is the complex number sign;

ω is the angular frequency of the output of the power ~~source~~ supply, in radians per second;

L is the effective inductance of the magnetizing winding of the ~~ring~~ test specimen, in henrys, calculated from Formula (5).

$$L = \frac{N_1^2 A \mu_0 \mu_r}{l_m} \tag{5}$$

where

N_1 is the number of turns of the magnetizing winding;

A is the cross-sectional area of the test specimen, in square metres;

μ_0 is the magnetic constant ($4 \pi \times 10^{-7}$ henrys per metre);

μ_r is the relative **amplitude** permeability of the test specimen;

l_m is the mean magnetic path length of the test specimen, in metres.

Where the relative ~~magnetic amplitude~~ permeability is not known, a preliminary measurement may need to be made of the **peak values** of magnetic field strength and magnetic flux density as described in 6.4.1 and 6.4.2 and the relative ~~magnetic amplitude~~ permeability calculated as described in 6.4.3.

6.4 Determination of characteristics

6.4.1 Determination of the peak value of the magnetic field strength

The **peak value** of magnetic field strength at which the measurement is to be made is calculated from Formula (6).

$$H = \frac{N_1 I}{l_m} \quad \hat{H} = \frac{N_1 \hat{I}}{l_m} \tag{6}$$

where

\hat{H} is the **peak value** of the magnetic field strength, in amperes per metre;

N_1 is the number of turns of the magnetizing winding on the test specimen;

\hat{I} is the **peak value** of the magnetizing current, in amperes;

l_m is the mean magnetic path length of the test specimen, in metres.