



SLOVENSKI STANDARD

SIST EN 10235:1998

01-avgust-1998

Kovinski materiali - Cev - Preskus robljenja

Metallic materials - Tube - Flanging test

Metallische Werkstoffe - Rohr - Bördelversuch

Matériaux métalliques - Tubes - Essai de rabattement de collerette

Ta slovenski standard je istoveten z: **EN 10235:1993**

[SIST EN 10235:1998](https://standards.iteh.ai/catalog/standards/sist/6d7b0e7e-cccc-410e-be4d-84321a4035aa/sist-en-10235-1998)

<https://standards.iteh.ai/catalog/standards/sist/6d7b0e7e-cccc-410e-be4d-84321a4035aa/sist-en-10235-1998>

ICS:

77.040.10 Mehansko preskušanje kovin Mechanical testing of metals

SIST EN 10235:1998

en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 10235:1998

<https://standards.iteh.ai/catalog/standards/sist/6d7b0e7e-cccd-410e-be4d-84321a4035aa/sist-en-10235-1998>

EUROPEAN STANDARD

EN 10235

NORME EUROPÉENNE

EUROPÄISCHE NORM

October 1993

UDC 669-462:620.163.24

Descriptors: Metal tubes, mechanical tests, flanging tests

English version

Metallic materials - Tube - Flanging testMatériaux métalliques - Tubes - Essai de rabattement de collerette
Metallische Werkstoffe - Rohr - Bördelversuch**STANDARD PREVIEW**
(standards.iteh.ai)

SIST EN 10235:1998

<https://standards.iteh.ai/catalog/standards/sist/6d7b0e7e-cccd-410e-be4d-84321a4035aa/sist-en-10235-1998>

This European Standard was approved by CEN on 1993-10-25. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

The European Standards exist in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Contents	Page
Foreword	2
Introduction	2
1 Scope	3
2 Normative references	3
3 Principle	3
4 Symbols, descriptions and units	4
5 Testing equipment	4
6 Test piece	5
7 Procedure	5
8 Test report	6

Foreword

iTeh STANDARD PREVIEW

This European Standard has been prepared by sub-committee ECISS/TC 29, the secretariat of which has been allocated to the United Kingdom (BSI).

No meeting of the sub-committee has been held but the following countries voted positively by the PQ-procedure on the acceptability of the reference document as a European Standard: Belgium, Denmark, Finland, France, Germany, Greece, Italy, Netherlands, Norway, Spain, Sweden, Switzerland and the United Kingdom. No country voted negatively.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by April 1994, and conflicting national standards shall be withdrawn at the latest by April 1994.

In accordance with the CEN/CENELEC Internal Regulations, following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

Introduction

This standard is based on ISO 8494:1986 "Metallic materials - Tube - Flanging test" which has been editorially changed in the light of the comments received. Several minor changes have been made in clauses 5 to 8. The usage of symbols has been aligned with the requirements of ISO 3545-1:1989.



1 Scope

This European Standard specifies a method for determining the ability of metallic tubes of circular cross section to undergo plastic deformation during flange formation.

It is intended that the standard should be applicable to tubes having an outside diameter not greater than 150 mm and a wall thickness not greater than 10 mm. The range of diameters or wall thicknesses for which this European Standard is applicable could be more exactly specified in the relevant product standard.

2 Normative reference

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revision of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

ISO 3545-1:1989 Steel tubes and fittings - Symbols for use in specifications - Part 1: Tubes and tubular accessories with circular cross-section

3 Principle

Forming on the end of a test piece cut from a tube, a flange in a plane perpendicular to the axis of the tube, until the external diameter of the flange reaches the value specified in the relevant product standard.

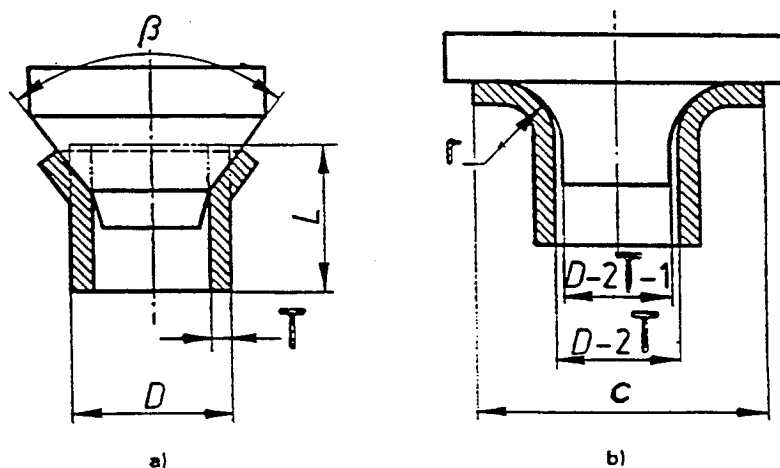


Figure 1: Symbols for flanging test

4 Symbols, descriptions and units

Symbols, descriptions and units for the flanging test of tubes are in accordance with ISO 3545-1:1989 and are given in figure 1 and table 1.

Table 1: Symbols, descriptions and units

Symbol	Description	Unit
D	Original outside diameter of the tube	mm
T	Wall thickness of the tube	mm
L	Length of the test piece before the test	mm
r	Corner radius of the flanging tool	mm
C	Maximum outside diameter of the flange	mm
β	Angle of the conical mandrel	degree

SIST EN 10235:1998

<https://standards.iteh.ai/catalog/standards/sist/6d7b0e7e-cccc-410e-be4d-84321a4035aa/sist-en-10235-1998>

5 Testing equipment

5.1 The test shall be carried out in a variable-speed press or a universal testing machine.

5.2 The forming equipment shall consist of

- a) a conical mandrel having a suitable angle (generally 90 °);
- b) where r is specified in the relevant product standard a flanging tool having
 - a cylindrical end of a diameter about 1 mm less than the inside diameter of the tube,
 - a flat concentric portion, perpendicular to the axis of the forming tool, and having a diameter not less than the required diameter of the flange.

NOTE: When necessary a supporting die may be used to support the tube during the formation of the flange

5.3 The forming tools shall be made of polished material of sufficient hardness.

6 Test piece

6.1 The length L of the test piece shall be approximately $1,5 D$. The test piece may be shorter provided that the cylindrical part remaining after flanging is at least $0,5 D$.

6.2 Both ends of the test piece shall be in a plane perpendicular to the axis of the tube. The edges of the end to be tested may be rounded by filing or chamfered by other methods.

NOTE: Non-rounded or non-chamfered edges are permissible if the test result meets the test requirements

6.3 When welded tubes are subjected to the test, the internal welded flash may be removed.

(standards.iteh.ai)

SIST EN 10235:1998

7 Procedure <https://standards.iteh.ai/catalog/standards/sist/6d7b0e7e-cccc-410e-be4d-84321a4035aa/sist-en-10235-1998>

7.1 In general, the test shall be carried out at ambient temperature within the limits of 10°C to 35°C . The test carried out under controlled conditions shall be made at a temperature of $(23 \pm 5)^{\circ}\text{C}$.

7.2 Preform the test piece by forcing the conical mandrel into one end of the test piece until the diameter of the drifted test pieces is such that a flange having the specified diameter can be formed (see figure 1a)). The axis of the mandrel shall be aligned with the axis of the tube.

7.3 Remove the conical mandrel and, if necessary, replace with the flanging tool (see figure 1b)).

7.4 Form the flange by applying axial force to the test piece until the drifted portion has formed a flange of the required diameter perpendicular to the axis of the test piece.

7.5 The forming tools may be lubricated. The tools shall not rotate relative to the test piece during the test.

Page 6
EN 10235:1993

7.6 In case of dispute, the rate of movement of the forming tools shall not exceed 50 mm/min.

7.7 The diameter of the flange and the radius r shall be as specified in the relevant product standard.

7.8 Interpretation of the flanging test shall be carried out according to the requirements of the relevant product standard. When these requirements are not specified, absence of cracks visible without the use of magnifying aids shall be considered as evidence that the test piece passed the test. Slight premature failure at the edges shall not be considered cause for rejection.

8 Test report

8.1 A test report shall be provided when so specified in the relevant product standard.

iTeh STANDARD PREVIEW

(standards.iteh.ai)

8.2 The test report shall include at least the following information:

- a) reference to this European Standard;
<https://standards.iteh.ai/catalog/standards/sist/6d7b0e7e-cccd-410e-be4d-633e07e7c107/sist-en-10235-1998>
- b) identification of the test piece;
- c) dimensions of the test piece;
- d) maximum outside diameter of the expanded part of the test piece C or relative expansion as a percentage of the original diameter D ;
- e) corner radius r of the flanging tool, when relevant;
- f) result of the test.