



# SLOVENSKI STANDARD SIST EN 10246-8:2000

01-november-2000

BYdcfi ý]lj Ybc`dfYg\_i ýUb`Y`Y`Yb]`Wj]!', "XY.I [ cHj`Ub`Y`j nXc`yb]`bUdU\_ j UfUY`Y`f] bc`j Uf`Yb]`Y`Yb]`Wj]n`Uj lca Urg\_c`i`fUhj c bc`dfY]g\_Uj c

Non-destructive testing of steel tubes - Part 8: Automatic ultrasonic testing of the weld seam of electric welded steel tubes for the detection of longitudinal imperfections

Zerstörungsfreie Prüfung von Stahlrohren - Teil 8: Automatische Ultraschallprüfung der Schweißnaht elektrisch geschweißter Stahlrohre zum Nachweis von Längsfehlern

Essais non destructifs des tubes en acier - Partie 8: Contrôle automatique par ultrasons du cordon de soudure pour la détection des imperfections longitudinales des tubes en acier soudés électriquement

<https://standards.iteh.ai/catalog/standards/sist/4328355c-9ad2-4d09-ae83-9221e826c685/sist-en-10246-8-2000>

Ta slovenski standard je istoveten z: EN 10246-8:1999

## ICS:

23.040.10	Železne in jeklene cevi	Iron and steel pipes
25.160.40	Varjeni spoji in vari	Welded joints
77.040.20	Neporušitveno preskušanje kovin	Non-destructive testing of metals

SIST EN 10246-8:2000

en

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST EN 10246-8:2000

<https://standards.iteh.ai/catalog/standards/sist/4328355c-9ad2-4d09-ae83-9221e826c685/sist-en-10246-8-2000>

EUROPEAN STANDARD  
NORME EUROPÉENNE  
EUROPÄISCHE NORM

**EN 10246-8**

November 1999

ICS 23.040.10; 25.160.40; 77.040.20

English version

**Non-destructive testing of steel tubes - Part 8: Automatic ultrasonic testing of the weld seam of electric welded steel tubes for the detection of longitudinal imperfections**

Essais non destructifs des tubes en acier - Partie 8:  
Contrôle automatique par ultrasons du cordon de soudure  
pour la détection des imperfections longitudinales des  
tubes en acier soudés électriquement

Zerstörungsfreie Prüfung von Stahlrohren - Teil 8:  
Automatische Ultraschallprüfung der Schweißnaht  
elektrisch geschweißter Stahlrohre zum Nachweis von  
Längsfehlern

This European Standard was approved by CEN on 6 October 1999.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

<https://standards.iteh.ai/catalog/standards/sist/4328355c-9ad2-4d09-ac83-9221e826c685/sist-en-10246-8-2000>



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

## Contents

	Page
Foreword	3
1 Scope	4
2 General requirements	4
3 Method of test	4
4 Reference standards	5
5 Equipment calibration and checking	7
6 Acceptance	8
7 Test reporting	8
Annex A (informative) Table of parts of EN 10246 - Non-destructive testing of steel tubes	10
Annex B (normative) Manual/semi-automatic ultrasonic testing of untested ends/suspect areas	11

## iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN 10246-8:2000

<https://standards.iteh.ai/catalog/standards/sist/4328355c-9ad2-4d09-ac83-9221e826c685/sist-en-10246-8-2000>

This document is a preview of the standard. It is not intended for use as a reference.

For more information on this standard, please visit the iTeh website.

## Foreword

This European Standard has been prepared by Technical Committee ECISS/TC 29 "Steel tubes and fittings for steel tubes", the secretariat of which is held by UNI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by May 2000, and conflicting national standards shall be withdrawn at the latest by May 2000.

This European Standard has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association. This European Standard is considered to be a supporting standard to those application and product standards which in themselves support an essential safety requirement of a New Approach Directive and which make reference to this European Standard.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN 10246-8:2000

<https://standards.iteh.ai/catalog/standards/sist/4328355c-9ad2-4d09-ac83-9221e826c685/sist-en-10246-8-2000>

## 1 Scope

This Part of EN 10246 specifies the requirements for automatic ultrasonic shear wave and Lamb wave testing of the weld seam of electric welded steel tubes for the detection of longitudinal imperfections. The standard specifies acceptance levels and calibration procedures.

This Part of EN 10246 is applicable to the inspection of tubes with an outside diameter equal to or greater than 10 mm.

European Standard EN 10246 "Non-destructive testing of steel tubes" comprises the Parts shown in Annex A.

## 2 General requirements

2.1 The ultrasonic inspection covered by this Part of EN 120246 is usually carried out on tubes after completion of all the primary production process operations.

2.2 The tubes to be tested shall be sufficiently straight and free from foreign matter as to ensure the validity of the test.

## 3 Method of test

3.1 The weld seam of tube shall be tested using an ultrasonic shear wave or Lamb wave technique for the detection of predominantly longitudinal imperfections.

3.2 During testing, the tube and the transducer assembly shall be moved relative to each other and the transducer assembly shall be maintained in proper alignment over the whole of the weld seam along the entire tube length.

It is recognised that there may be a short length at both tube ends which cannot be tested. Any untested ends shall be dealt with in accordance with the requirements of the appropriate product standards (see also Annex B).

The relative speed during testing shall not vary by more than +10%.

3.3 During testing, the weld seam shall be scanned, unless otherwise agreed between purchase and manufacturer, in two opposite directions of beam travel at right angles to the weld.

3.4 The ultrasonic test frequency applied shall be in the range of 1 MHz to 15 MHz for shear waves and in the range of 0,3 MHz to 1 MHz for Lamb waves, depending on the thickness and surface finish of the tubes to be tested.

3.5 The maximum width of each individual transducer, measured parallel to the major axis of the weld, shall be 25 mm for shear waves and 35 mm for Lamb waves.

3.6 The equipment shall be capable of classifying tubes as either acceptable or suspect tubes by means of an automatic trigger/alarm level combined with a marking and/or sorting system.

**3.7** Where manual ultrasonic testing of untested tube ends and/or local suspect areas is required, this shall be carried out in accordance with Annex B.

## **4 Reference standards**

### **4.1 General**

**4.1.1** The reference standards defined in this Part of EN 10246 are convenient standards for calibration of non-destructive testing equipment. The dimensions of these standards should not be construed as the minimum size of imperfections detectable by such equipment.

**4.1.2** The ultrasonic equipment shall be calibrated using a reference notch on the outside and inside surfaces, or the outside surface only of a tubular test piece.

The internal notch shall not be used when the tube internal diameter is less than 20mm, unless otherwise agreed between purchaser and manufacturer.

Alternatively, a circular reference hole drilled radially through the full thickness of the test piece may be used for equipment calibration by agreement between the purchaser and the manufacturer. In this case the diameter of the drill required to produce the reference hole for a specific acceptance level shall be agreed upon and the manufacturer shall demonstrate to the satisfaction of the purchaser that the test sensitivity achieved using the reference hole is essentially equivalent to that obtained when using the specified reference notch or notches.

**4.1.3** The test piece shall be of the same specified diameter, thickness, surface finish and heat treatment conditions as the tube to be tested and shall have similar acoustic properties (for example velocity, attenuation coefficient).


**4.1.4** The external notch (and internal notch or reference hole when used) shall be sufficiently separated from the ends of the test piece and from each other (when both notches are used), so that clearly distinguishable signal indications are obtained.

### **4.2 Types of reference notches**

**4.2.1** The reference notch(es) shall lie parallel to the major axis of the weld seam. The reference notch(s) shall be of the "N" type except that the "V" type notch may be used at the discretion of the manufacturer when the specified notch depth is less than or equal to 0,5 mm (see figure 1). In the case of the "N" type notch, the sides shall be nominally parallel and the bottom shall be nominally square to the sides.

**4.2.2** The reference notch shall be formed by machining, spark erosion or other methods

NOTE: It is recognized that the bottom or the bottom comers of the notch may be rounded.

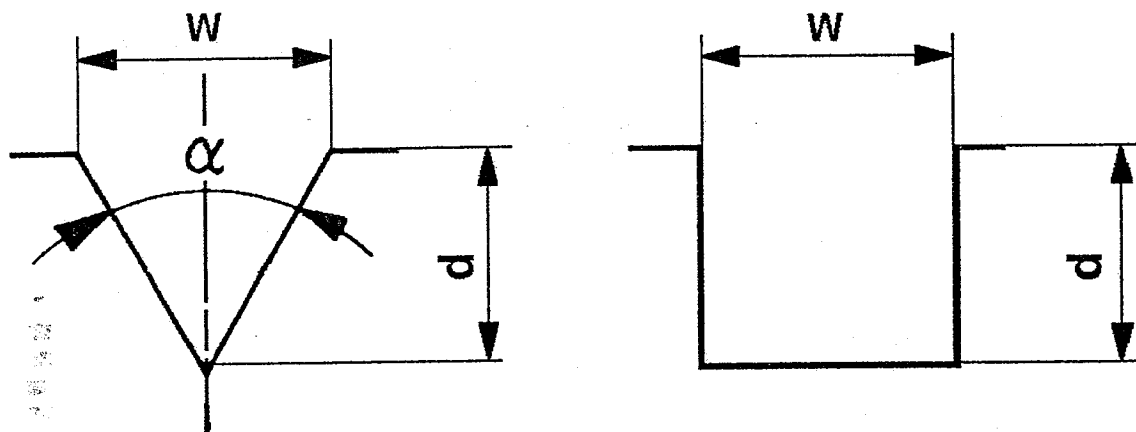

“V” type notch

(only to be used when  $d \leq 0,5$  mm)

$\alpha = 60^\circ$ ,

$w =$  width,

“N” type notch

$d =$  depth

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

Figure 1: Reference notch forms

SIST EN 10246-8:2000

#### 4.3 Dimensions of reference notch

<https://standards.iteh.ai/catalog/standards/sist/4328355c-9ad2-4d09-ac83-9221e826c685/sist-en-10246-8-2000>

4.3.1 The width,  $w$  (see figure 1), of the reference notch shall not be greater than 1,0 mm.

4.3.2 The reference notch depth shall be as given in table 1 with the following limitations:

- minimum notch depth: 0,3 mm for U2/U3 categories tubes and 0,5 mm for U4/U5/U6 categories tubes;
- maximum notch depth: 1,5mm for all acceptance levels.

4.3.3 The tolerance on notch depth shall be  $\pm 15\%$  of the reference notch depth or  $\pm 0,05$  mm whichever is the larger.

4.3.4 The length of the reference notch shall be twice the width of each individual transducer, with a maximum of 50 mm.

#### 4.4 Verification of reference notch

The reference notch dimensions and shape shall be verified by a suitable technique.



**Table 1: Acceptance level designation and corresponding reference notch depth**

Acceptance Level	Notch depth in % of the specified thickness (see note 1)
U2	5
U3	10
U4	12,5
U5	15
U6	20

Note. The values of notch depth specified in this table are the same for the corresponding categories, in all European Standards concerning non-destructive testing of steel tubes where reference is made to different acceptance levels. It should, however, be kept in mind that although the reference standards are identical, the various test methods involved can give different test results. Accordingly the acceptance level designation prefix U (ultrasonic) has been adopted to avoid any inferred direct equivalence with other test methods.

## 5 Equipment calibration and checking

5.1 The equipment shall be calibrated to produce consistently, (e.g. from three consecutive passes of the test piece through the equipment), clearly identifiable signals from the reference standard (s) (see 4.2). The full amplitude of these signals shall be used to set the trigger/alarm level(s) of the equipment.

Where a single trigger/alarm level is used, the transducer(s) shall be adjusted so that the signals from the internal and external reference notches are as near equal as possible and the full signal amplitude of the lesser of the two signals shall be used to set the trigger/alarm level of the equipment. Where separate trigger/alarm levels are used for internal and external reference notches, the full signal amplitude from each notch shall be used to set the relevant trigger/alarm level of the equipment.

When using the reference hole, the manufacturer shall demonstrate to the satisfaction of the purchaser that the sensitivity achieved at the inner and outer surfaces is essentially equivalent to that achieved when using the specified external and internal reference notches.

5.2 During calibration check, the relative speed of movement between the test piece and the transducer assembly shall be the same as that to be used during the production test. Semi-dynamic calibration checking may be used.

5.3 The calibration of the equipment shall be checked at regular intervals during the production testing of tubes of the same specified diameter, thickness and grade by passing the test piece through the test equipment.

The frequency of checking the calibration shall be at least every four hours but also whenever there is an equipment operator team changeover and at the start and end of production.