
**Dense and insulating shaped refractory
products — Determination of modulus
of rupture at ambient temperature**

*Produits réfractaires façonnés denses et isolants — Détermination
du module de rupture par flexion à température ambiante*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 5014:1997](#)

[https://standards.iteh.ai/catalog/standards/sist/a78ac296-0285-407b-b756-
b07181b8daa4/iso-5014-1997](https://standards.iteh.ai/catalog/standards/sist/a78ac296-0285-407b-b756-b07181b8daa4/iso-5014-1997)



Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 5014 was prepared by Technical Committee ISO/TC 33, *Refractories*.

This second edition cancels and replaces the first edition (ISO 5014:1986), which has been technically revised.

iTeh STANDARD PREVIEW
(standards.iteh.ai)
<https://standards.iteh.ai/catalog/standards/sist/a78ac296-0285-407b-b756-b07181b8daa4/iso-5014-1997>

© ISO 1997

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case postale 56 • CH-1211 Genève 20 • Switzerland
Internet central@iso.ch
X.400 c=ch; a=400net; p=iso; o=isocs; s=central

Printed in Switzerland

Dense and insulating shaped refractory products — Determination of modulus of rupture at ambient temperature

1 Scope

This International Standard specifies a method for the determination of the modulus of rupture of dense and insulating shaped refractory products at ambient temperature, under conditions of a constant rate of increase of stress.

The method relates primarily to shaped and fired refractories. If it is to be applied to chemically bonded or tar-bonded bricks, they will usually require some form of preliminary heat treatment. This preliminary treatment, the details of which are outside the scope of this standard, is a matter of agreement between the interested parties and is described in the test report.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

2 Definition

For the purposes of this International Standard, the following definition applies:

2.1 modulus of rupture: The maximum stress that a prismatic test piece of specified dimensions can withstand when it is bent in a three-point bending device.

3 Principle

Loading of test pieces of the product to be tested at a constant rate of increase of stress until failure occurs.

4 Apparatus

4.1 Loading device

4.1.1 The loading device shall have three bearing edges, two to support the test piece and one for the application of the load (see figure 1). The three edges shall have a radius of curvature in accordance with the requirements given in table 1 and shall be of length not less than 5 mm greater than the breadth (*b*) of the test piece (see figure 2). The contact lines of the three edges shall be parallel to each other in a direction perpendicular to the length and the plane of the breadth of the test piece. Two supporting edges shall rest on an intermediate bearing piece, cylindrical on its lower surface, so that each edge may rotate independently in a vertical plane to accommodate any slight twist in the test piece (see figure 2). Alternatively, one supporting edge may be fixed, with the other supporting edge and the load-bearing edge being capable of rotation in a vertical plane. The distance between the two supporting edges shall be in accordance with table 1 and the load-bearing edge shall be positioned equidistantly, at $L_s/2 \pm 2$ mm from each supporting edge.

Table 1 — Dimensions and tolerances associated with the tests on test pieces of various sizes

Dimensions in millimetres


Test piece size <i>l x b x h</i>	Tolerance for the breadth <i>b</i> and height <i>h</i>	Tolerance for the parallelism of the cross-section sides	Tolerance for the parallelism of the top and bottom faces	Distance between supports <i>L_s</i>	Radius of curvature for the loading edge and bearing edges
230 x 114 x 76 230 x 114 x 64	—	—	—	180 ± 1	15 ± 0,5
200 x 40 x 40	± 1	± 0,15	± 0,25	180 ± 1	15 ± 0,5
150 x 25 x 25	± 1	± 0,1	± 0,2	125 ± 1	5 ± 0,5

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 5014:1997

<https://standards.iteh.ai/catalog/standards/sist/a78ac296-0285-407b-b756-b07181b8daa4/iso-5014-1997>

Dimensions in millimetres

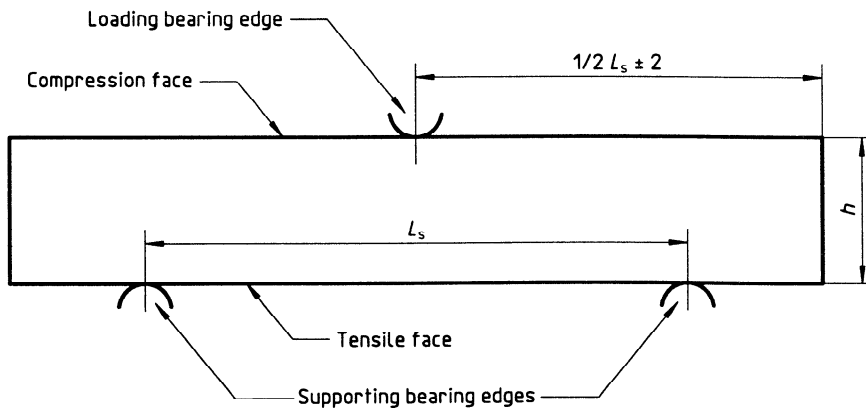

NOTE — For tolerances see table 1.

Figure 1 — Arrangements and dimensions of test piece and bearing edges of loading device

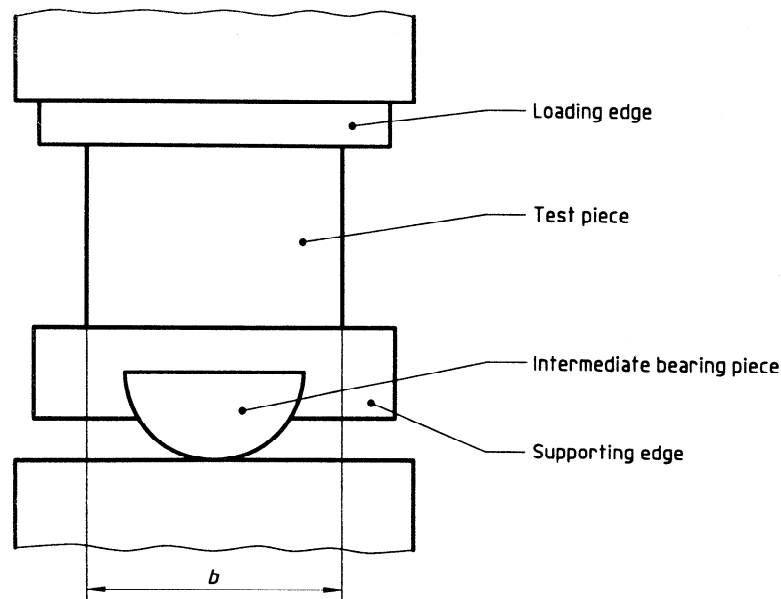


Figure 2 — Diagrammatic representation of loading device — Intermediate bearing piece

iTeh STANDARD PREVIEW

4.1.2 The loading device shall be capable of applying a load uniformly across the centre of the test piece and of increasing it at a uniform rate. A means shall be provided of recording or indicating the load at failure with an accuracy of $\pm 2\%$.

4.2 Drying oven, capable of being controlled at $(110 \pm 5)^\circ\text{C}$.

5 Preparation of test pieces

5.1 Number

5.1.1 The number of items (for example, bricks, shapes, nozzles) to be tested shall be determined by agreement between the interested parties.

5.1.2 If test pieces are cut out of bricks or blocks, the same number shall be cut from each one, in order to facilitate statistical analysis.

NOTE — The number of test pieces to be cut from each item (which detail is outside the scope of this International Standard) is a matter for agreement between the interested parties. It should be stated in the test report.

5.2 Shape and size

Each test piece shall be a whole standard rectangular brick (230 mm x 114 mm x 76 mm or 230 mm x 114 mm x 64 mm) or one of the other sizes shown in table 1.

5.3 Preparation

5.3.1 Standard size bricks (see 5.2) shall be tested as received.

5.3.2 If test pieces are cut out of bricks, it shall be done in such a way that, if the direction in which the brick was pressed is known, the upper longitudinal face in the testing position (the face in compression) is parallel to, or coincides with, one of the original faces of the brick perpendicular to the direction of pressing.

NOTE — Cutting with a continuous rim diamond wheel is recommended. If a serrated rim wheel is used, the edges of the cut where the wheel emerges are often frayed; it is therefore recommended that such a wheel should enter the face of the brick that is to form the tensile face of the test piece during the test.

5.3.3 The direction of pressing, if known, shall be marked on the test piece.

6 Procedure

6.1 Dry the test piece to constant mass in the oven (4.2), controlled at $(110 \pm 5) ^\circ\text{C}$, cooling it each time away from moisture.

6.2 Measure the breadth and height of each test piece at its mid-point with an accuracy of $\pm 0,1$ mm and the distance between the supporting edges with an accuracy of $\pm 0,5$ mm.

6.3 Place the test piece on the lower bearing edges of the loading device (4.1) so that it rests symmetrically across them. When the test piece is a normal standard brick, the face bearing any brand mark, i.e. the upper face, shall be in compression. If the test pieces have been cut out of the brick, the face of the test piece which corresponds to the original face of the brick (if it has been preserved) shall be in compression.

ISO 5014:1997

<https://standards.iteh.ai/catalog/standards/sist/a78ac296-0285-407b-b756->

6.4 Apply the load vertically to the test piece until failure occurs. The rate of increase of stress shall be:

- a) for a dense shaped refractory product or material:

$$0,15 \text{ MPa/s} \pm 0,015 \text{ MPa/s.}$$

- b) for a shaped insulating refractory product or material:

$$0,05 \text{ MPa/s} \pm 0,005 \text{ MPa/s.}$$

6.5 Record the load at which failure of the test piece occurs (F_{max}) and the temperature at which the test was conducted.

7 Expression of results

7.1 The modulus of rupture σ_F is the ratio of the bending moment at the point of failure M_{max} to the moment of resistance W (the section modulus), and is calculated from the following equation:

$$\sigma_F = \frac{M_{\text{max}}}{W} = \frac{3}{2} \times \frac{F_{\text{max}} L_s}{bh^2}$$

where

- F_{\max} is the maximum force exerted on the test piece, in newtons;
- L_s is the distance between the points of support of the test piece, in millimetres;
- b is the breadth of the test piece, in millimetres;
- h is the height of the test piece, in millimetres.

7.2 The result shall be expressed in megapascals.

7.3 For bricks of standard size, the value obtained for a brick constitutes the result of that item.

7.4 For cut test pieces, record the individual values and the mean value for each item; these constitute the result for that item.

8 Test report

The test report shall include the following information:

- iTeh STANDARD PREVIEW**
(standards.iteh.ai)
- a) the name of the testing establishment;
- b) the date of the test;
- c) reference to this International Standard, i.e. "Determined in accordance with ISO 5014";
- d) the designation of the bricks tested (manufacturer, type, shape, batch number);
- e) the number of items tested;
- f) the pre-treatment, if any, given to the test pieces (see clause 1);
- g) the number of test pieces per item;
- h) the dimensions of the test pieces;
- i) the position of the test pieces in the item;
- j) the distance between the supports;
- k) the nominal rate of tensile stress increase for each test piece;

either

- l) the individual values and the mean values of the modulus of rupture for each item (when more than one test piece is cut from each item);

or

- m) the value of the modulus of rupture for each item (when whole bricks are used).

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 5014:1997

<https://standards.iteh.ai/catalog/standards/sist/a78ac296-0285-407b-b756-b07181b8daa4/iso-5014-1997>

ICS 81.080

Descriptors: refractory materials, shaped refractories, tests, mechanical tests, bend rupture tests, determination, break modulus, test report sheets.

Price based on 5 pages
