

# INTERNATIONAL STANDARD

**ISO**  
**12636**

First edition  
1998-07-15

---

---

## **Graphic technology — Blankets for offset printing**

*Technologie graphique — Blanchets pour impression offset*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 12636:1998](https://standards.iteh.ai/catalog/standards/sist/b23429ca-6a9c-4171-92e8-571f0c6d31a4/iso-12636-1998)

<https://standards.iteh.ai/catalog/standards/sist/b23429ca-6a9c-4171-92e8-571f0c6d31a4/iso-12636-1998>



ISO 12636:1998(E)

| Contents   | Page |
|--|------|
| 1 Scope.....   | 1    |
| 2 Terms and definitions.....                                       | 1    |
| 3 Requirements .....   | 2    |
| 4 Test methods.....  | 4    |
| Annex A (informative): Equivalence of SI values to FPS values .... | 8    |

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 12636:1998

<https://standards.iteh.ai/catalog/standards/sist/b23429ca-6a9c-4171-92e8-571f0c6d31a4/iso-12636-1998>

© ISO 1998

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization  
Case postale 56 • CH-1211 Genève 20 • Switzerland  
Internet iso@iso.ch

Printed in Switzerland

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

iTeh STANDARD PREVIEW

International Standard ISO 12636 was prepared by Technical Committee ISO/TC 130, *Graphic technology*.

Annex A of this International Standard is for information only.

<https://standards.iteh.ai/catalog/standards/sist/b23429ca-6a9c-4171-92e8-571f0c6d31a4/iso-12636-1998>

## Introduction

The blanket is an essential part of every offset printing press. Its properties exert a profound influence on the mechanical conditions within the press and the visual characteristics of the prints produced. It is therefore useful to provide test methods, unified data, and tolerances for some essential properties of the blankets. This permits the suppliers to state properties of blanket types in a unified and well-known manner. It also helps the printer to select the appropriate blanket type for a particular press type or press condition. A further benefit is that the design of printing presses can be based on blanket data resulting from unified test methods.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 12636:1998](https://standards.iteh.ai/catalog/standards/sist/b23429ca-6a9c-4171-92e8-571f0c6d31a4/iso-12636-1998)

<https://standards.iteh.ai/catalog/standards/sist/b23429ca-6a9c-4171-92e8-571f0c6d31a4/iso-12636-1998>

# Graphic technology — Blankets for offset printing

## 1 Scope

This International Standard defines vocabulary, specifies test methods, characteristics, ordering and labeling information for blankets for offset printing. This International Standard does not apply to untensioned or unclamped blankets for offset printing, nor offset printing sleeves used with gapless presses.

## 2 Terms and definitions

For the purposes of this International Standard, the following terms and definitions apply.

### 2.1

#### **across direction**

direction of the side of the blanket as intended to be applied perpendicular to the direction of rotation

### 2.2

#### **around-the-cylinder direction**

direction of the side of the blanket as intended to be applied in the direction of the rotation

### 2.3

#### **average thickness**

mean of four measurements on a cut blanket where the measurements have been made on the points indicated in figure 1, namely on 2 diagonally opposed corners and one each at the middle of the two sides that are perpendicular to each other within a right triangle

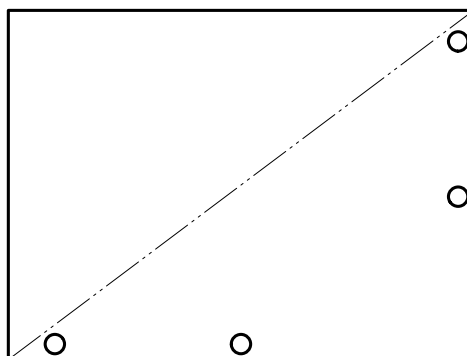


Figure 1 — Thickness measurement points

### 2.4

#### **blanket**

composite body, consisting of coated carrier material, e.g. fabric, used for transfer of the printing ink from the forme onto material to be printed on, e.g. for offset printing

**2.5****compressibility-deflection**

average thickness reduction of a blanket measured under a specific pressure, expressed in millimetres

**2.6****compressibility-indentation**

average depth of impression,  $l$ , in a blanket measured under a specific pressure, expressed in millimetres or as percentage indentation  $l_p$

**2.7****elongation**

increase of the dimension in the around-the-cylinder direction of a blanket under longitudinal stress, expressed in percent of the length at a specified force per width

**2.8****packing**

underlay material placed under the blanket to adjust the effective thickness of the blanket on press

**2.9****printing surface**

side of the blanket that is used for the transfer of printing ink

**2.10****shrinkage**

decrease in thickness due to exposure of the blanket printing surface to a liquid, expressed as a percentage of the original blanket thickness, or as an absolute thickness decrease in millimetres

**2.11****sizes**

dimensions (thickness, width and length) of a cut ready-to-use blanket

**2.12****swelling**

increase in thickness due to exposure of the blanket printing surface to a liquid, expressed as a percentage of the original blanket thickness, or as an absolute thickness increase in millimetres

**2.13****tensile strength**

force per unit width required for breaking a blanket under longitudinal stress in the around-the-cylinder direction

**2.14****thickness variation**

difference between the greatest and the smallest thickness value in millimetres

**3 Requirements****3.1 Dimensions****3.1.1 Thickness**

The test method according to 4.1 shall be used. For applications with packing the nominal thickness shall be 1,68 mm or 1,95 mm. For applications without packing the nominal thickness should be agreed upon between the supplier and the user of the product.

NOTE The nominal thickness should be stated in technical descriptions and when ordering.

The thickness variations of blankets with an area not in excess of 1,5 m<sup>2</sup> shall be less than  $\pm 0,02$  mm, those of greater sizes shall be less than  $\pm 0,03$  mm. No individual thickness measurement shall yield a value which deviates more than 0,05 mm from the ordered thickness.

### 3.1.2 Accuracy of width and length

If one of the sides is 1 m or less, the tolerance shall be  $\pm 3$  mm, otherwise it shall be  $\pm 4$  mm.

### 3.1.3 Plan view

The sides of the blanket shall form right angles. The difference between the length of the diagonals and the length of any two parallel sides shall not exceed 0,5 %.

## 3.2 Materials and surface finish

No specifications are given. The material formulation and surface finish are the choice of the manufacturer and may be stated in technical descriptions by the supplier. The surface finish may vary, e.g. cast (molded) or ground (buffed).

## 3.3 Elongation

The elongation  $E$  shall be less than 1,5 %. The test method according to 4.2 shall be used or any other method where results can be correlated to those of the test method.

## 3.4 Tensile strength

For all blankets of thickness 1,68 mm or more, the tensile strength shall be greater than 40 N/mm. The test method according to 4.3 shall be used or any other method where results can be correlated to those of the test method. For blankets of lower thickness no specification is given.

## 3.5 Compressibility

No specification is given. Either test method according to 4.4 or 4.5 shall be used.

NOTE The use of compressibility-deflection or compressibility-indentation method is the choice of the manufacturer and may be stated by the supplier.

<https://standards.iteh.ai/catalog/standards/sist/b23429ca-6a9c-4171-92e8-571f0c6d31a4/iso-12636-1998>

## 3.6 Thickness change

### 3.6.1 Swelling or shrinkage due to printing ink ingredients

The thickness change  $\Delta T$  due to exposure to printing ink ingredients shall not exceed 4 % maximum swelling or 2 % maximum shrinkage. The test method according to 4.6 for each property shall be used.

### 3.6.2 Swelling and/or shrinkage due to blanket washes

When testing blanket washes for their compatibility to an offset printing blanket, it is the option of the blanket manufacturer to report test results using the test method according to 4.6 for each property.

When choosing a blanket cleaning material for composition, it should be tested for compatibility with the blanket.

NOTE The choice of a proper wash is a difficult decision due to the need to balance effectiveness versus safety and environmental needs.

## 3.7 Hardness

The overall hardness and the microhardness are not specified in this International Standard. They are the choice of the manufacturer.

## 3.8 Cut blanket markings

On the non-printing side of the cut-to-size blanket the following should be reported:

- a) Blanket dimensions (average actual thickness, width and length), indicating which dimension is the around-the-cylinder direction. If the recorded thickness is nominal this shall be stated.

- b) The batch control number.
- c) The name of the manufacturer or the supplier and the blanket brand or trade name.

## 4 Test methods

### 4.1 Thickness

Place the blanket between two parallel flat circular disks of 100 mm<sup>2</sup> to 200 mm<sup>2</sup> area. Load the disks with a force that produces a pressure of (60 ± 5) kPa. Measure the gap between the disks in millimetres. Other methods, e.g. continuous ones, may be used instead if the results can be correlated to those of the method specified.

### 4.2 Elongation

Cut a 50 mm by 350 mm (minimum) sample from the blanket with the long direction parallel to the around-the-cylinder direction. Apply to the sample two bench marks 250 mm apart. Clamp the shorter sides of the sample in a tensile testing apparatus with a jaw separation of 300 mm (minimum), and apply a static line force of 10 N/mm. After 10 min dwell time, determine the distance *L* between the benchmarks under load. Calculate the percentage elongation from


$$E = \frac{L - L_0}{L_0} \times 100 \%$$

where *L*<sub>0</sub> = 250 mm benchmarks and *L* is the length after 10 min under load.

### 4.3 Tensile strength

Cut a 50 mm by 300 mm (minimum) sample from the blanket with the long direction parallel to the around-the-cylinder direction. Clamp the shorter sides of the sample into a tensile strength testing apparatus with a minimum jaw separation of 200 mm. Apply the load with a jaw separation speed of 50 mm/min. Increase the load till the break occurs, read the force at break. The tensile strength is expressed in N/mm.

### 4.4 Compressibility - Deflection

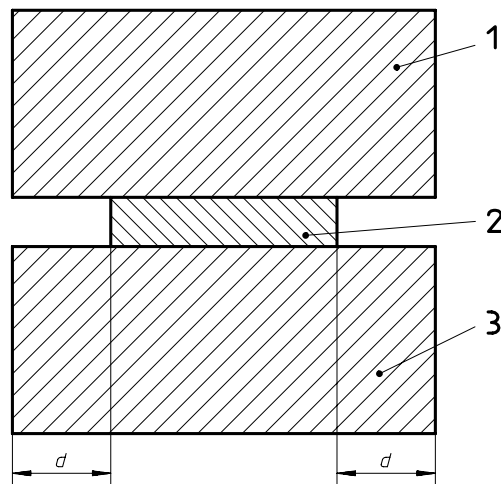

**Key**

- 1 Upper face of compression apparatus
- 2 Circular sample 700 mm<sup>2</sup>
- 3 Lower face
- d* Distance 10 mm (minimum)


**Figure 2 — Compressibility - Deflection (not to scale)**



- a) Indication of blanket compressibility is expressed as an absolute deflection at a pre-determined pressure of 2000 kPa.
- b) Apparatus: Continuous loading apparatus (tensometer).
- c) Use a compression load cell with parallel flat surfaces or a compression cage (maximum diameter 100 mm).
- d) Sample size  $(700 \pm 10) \text{ mm}^2$ .
- e) Head speed: 1 mm/min.
- f) Zero point:  $(60 \pm 5) \text{ kPa}$ .
- g) Compress the sample until a load of 2060 kPa is reached, recording the deflection at the 1st and 5th cycles at 1060 kPa and 2060 kPa.
- h) Report the 5th cycle deflection values at 1060 kPa and 2060 kPa from an average of 4 samples.

NOTE Due to machine deflection inherent in all test equipment, care should be taken to compensate for this deflection when reporting results. This deflection may be in the fixtures (e.g. compression cage) as well as the load cell. A test with a flat non-compressible circular disk  $(700 \pm 10) \text{ mm}^2$  is run to determine deflection of the testing system at different loads. This disk should be of minimum thickness such that all force is borne by the disk during the test. Suggested material for this disk is brass or steel. The stress-strain curve is used to correct for this instrument deflection in order to indicate correct blanket compressibility.

#### 4.5 Compressibility - Indentation

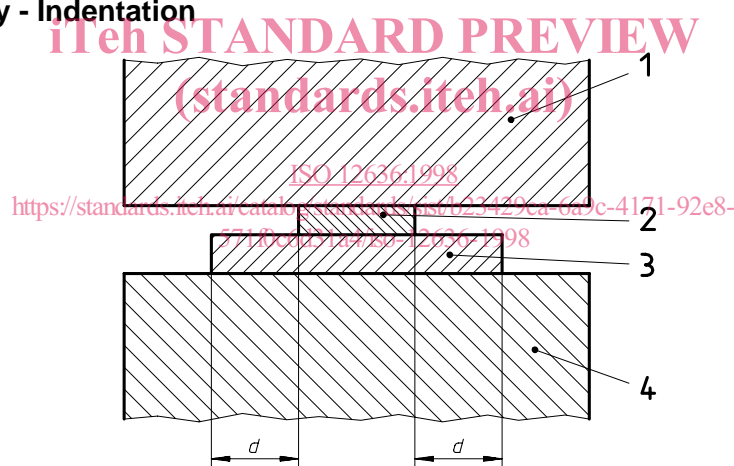

#### Key

- 1 Upper face of compression apparatus
- 2 Circular load disk of  $100 \text{ mm}^2$

$d$  Distance 9 mm (minimum)

**Figure 3 — Compressibility - Indentation** (not to scale)

- a) Indication of blanket compressibility is expressed as an absolute indentation at a pre-determined pressure of 1000 kPa.
- b) Apparatus: Continuous loading apparatus (tensometer) utilizing parallel flat surfaces and a circular load disk of  $100 \text{ mm}^2$ .
- c) Sample size  $(700 \pm 10) \text{ mm}^2$ .
- d) Zero point:  $(60 \pm 5) \text{ kPa}$ .