


INTERNATIONAL STANDARD

NORME INTERNATIONALE



Optical fibres – **iTeh STANDARD PREVIEW**
Part 2-20: Product specifications – Sectional specification for category A2
multimode fibres
(standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/sist/d26e482b-bbcd-4281-961e-60793-2-20>
IEC 60793-2-20:2015
Fibres optiques –
Partie 2-20: Spécifications de produits – Spécification intermédiaire pour
les fibres multimodales de catégorie A2

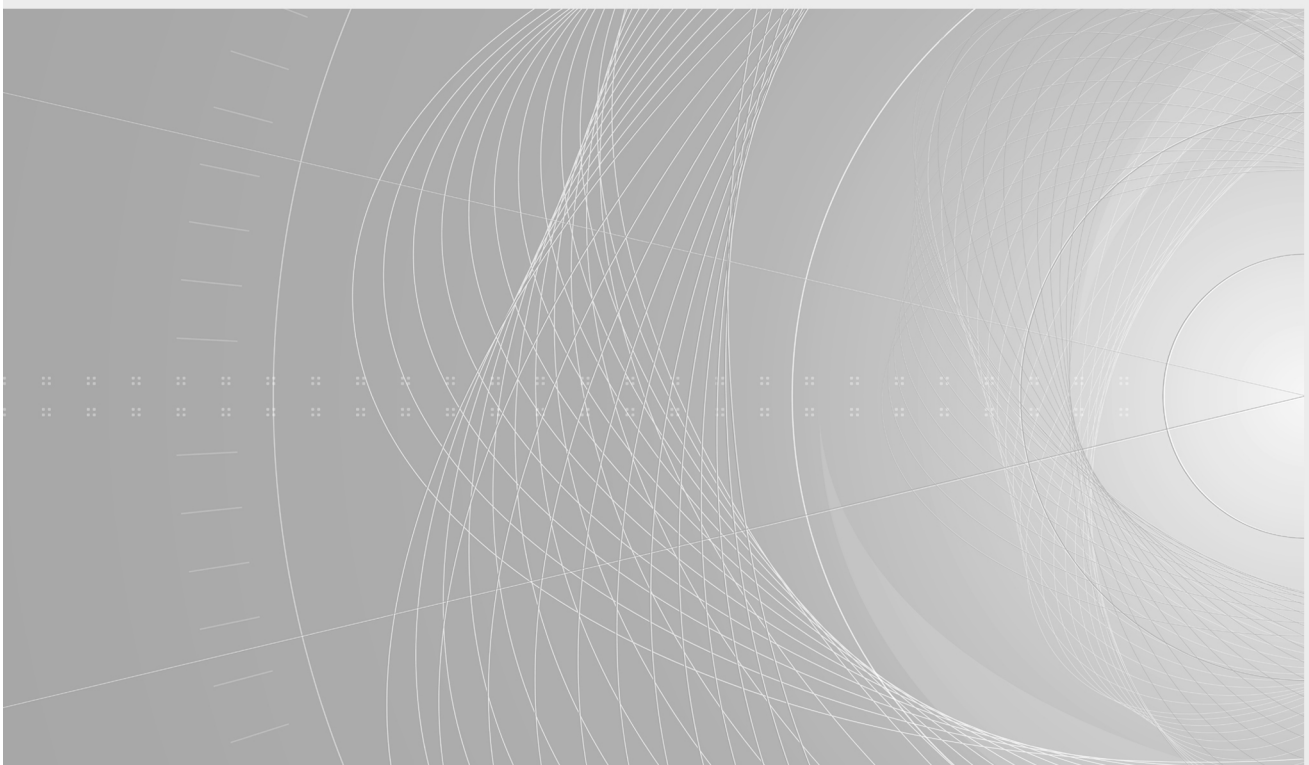



THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2015 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de l'IEC ou du Comité national de l'IEC du pays du demandeur. Si vous avez des questions sur le copyright de l'IEC ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de l'IEC de votre pays de résidence.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
Fax: +41 22 919 03 00
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

IEC Catalogue - webstore.iec.ch/catalogue

The stand-alone application for consulting the entire bibliographical information on IEC International Standards, Technical Specifications, Technical Reports and other documents. Available for PC, Mac OS, Android Tablets and iPad.

IEC publications search - www.iec.ch/searchpub

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and also once a month by email.

Electropedia - www.electropedia.org

The world's leading online dictionary of electronic and electrical terms containing 20 000 terms and definitions in English and French, with equivalent terms in 15 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Glossary - std.iec.ch/glossary

65 000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: csc@iec.ch.

A propos de l'IEC

La Commission Electrotechnique Internationale (IEC) est la première organisation mondiale qui élabore et publie des Normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications IEC

Le contenu technique des publications IEC est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

Catalogue IEC - webstore.iec.ch/catalogue

Application autonome pour consulter tous les renseignements bibliographiques sur les Normes internationales, Spécifications techniques, Rapports techniques et autres documents de l'IEC. Disponible pour PC, Mac OS, tablettes Android et iPad.

Recherche de publications IEC - www.iec.ch/searchpub

La recherche avancée permet de trouver des publications IEC en utilisant différents critères (numéro de référence, texte, comité d'études,...). Elle donne aussi des informations sur les projets et les publications remplacées ou retirées.

IEC Just Published - webstore.iec.ch/justpublished

Restez informé sur les nouvelles publications IEC. Just Published détaille les nouvelles publications parues. Disponible en ligne et aussi une fois par mois par email.

Electropedia - www.electropedia.org

Le premier dictionnaire en ligne de termes électroniques et électriques. Il contient 20 000 termes et définitions en anglais et en français, ainsi que les termes équivalents dans 15 langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International (IEV) en ligne.

Glossaire IEC - std.iec.ch/glossary

65 000 entrées terminologiques électrotechniques, en anglais et en français, extraites des articles Termes et Définitions des publications IEC parues depuis 2002. Plus certaines entrées antérieures extraites des publications des CE 37, 77, 86 et CISPR de l'IEC.

Service Clients - webstore.iec.ch/csc

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions contactez-nous: csc@iec.ch.

INTERNATIONAL STANDARD

NORME INTERNATIONALE



Optical fibres – iTeh STANDARD PREVIEW
Part 2-20: Product specifications – Sectional specification for category A2
multimode fibres
(standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/sist/d26e482b-bbcd-4281-961e-d379-8851e-60793-2-20>

Fibres optiques –
Partie 2-20: Spécifications de produits – Spécification intermédiaire pour
les fibres multimodales de catégorie A2

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

COMMISSION
ELECTROTECHNIQUE
INTERNATIONALE

ICS 33.180.10

ISBN 978-2-8322-3669-7

Warning! Make sure that you obtained this publication from an authorized distributor.
Attention! Veuillez vous assurer que vous avez obtenu cette publication via un distributeur agréé.

CONTENTS

FOREWORD.....	4
1 Scope.....	6
2 Normative references.....	6
3 Specifications.....	7
3.1 General.....	7
3.2 Dimensional requirements.....	7
3.3 Mechanical requirements.....	7
3.4 Transmission requirements.....	8
3.5 Environmental requirements.....	8
Annex A (normative) Specifications for sub-category A2a multimode fibres.....	9
A.1 General.....	9
A.2 Dimensional requirements.....	9
A.3 Mechanical requirements.....	9
A.4 Transmission requirements.....	9
A.5 Environmental requirements.....	10
Annex B (normative) Specifications for sub-category A2b multimode fibres.....	11
B.1 General.....	11
B.2 Dimensional requirements.....	11
B.3 Mechanical requirements.....	11
B.4 Transmission requirements.....	11
B.5 Environmental requirements.....	11
Annex C (normative) Specifications for sub-category A2c multimode fibres.....	13
C.1 General.....	13
C.2 Dimensional requirements.....	13
C.3 Mechanical requirements.....	13
C.4 Transmission requirements.....	13
C.5 Environmental requirements.....	13
Bibliography.....	15
Table 1 – Relevant dimensional attributes and measurement methods.....	7
Table 2 – Dimensional requirements common to all category A2 fibres.....	7
Table 3 – Additional dimensional attributes required for each sub-category.....	7
Table 4 – Relevant mechanical attributes and test methods.....	8
Table 5 – Mechanical requirements common to all category A2 fibres.....	8
Table 6 – Relevant transmission attributes and measurement methods.....	8
Table 7 – Requirements common to all category A2 fibres.....	8
Table 8 – Relevant environmental attributes and test methods.....	8
Table A.1 – Dimensional requirements specific to A2a fibres.....	9
Table A.2 – Mechanical requirements specific to A2a fibres.....	9
Table A.3 – Transmission requirements specific to A2a fibres.....	9
Table A.4 – Environmental exposure tests.....	10
Table A.5 – Attributes measured.....	10
Table B.1 – Dimensional requirements specific to A2b fibres.....	11

Table B.2 – Mechanical requirements specific to A2b fibres	11
Table B.3 – Transmission requirements specific to A2b fibres	11
Table B.4 – Environmental exposure tests	12
Table B.5 – Attributes measured	12
Table C.1 – Dimensional requirements specific to A2c fibres	13
Table C.2 – Mechanical requirements specific to A2c fibres	13
Table C.3 – Transmission requirements specific to A2c fibres	13
Table C.4 – Environmental exposure tests	14
Table C.5 – Attributes measured	14

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[IEC 60793-2-20:2015](https://standards.iteh.ai/catalog/standards/sist/d26e482b-bbcd-4281-961e-02329cf1f356/iec-60793-2-20-2015)

<https://standards.iteh.ai/catalog/standards/sist/d26e482b-bbcd-4281-961e-02329cf1f356/iec-60793-2-20-2015>

The text of this standard is based on the following documents:

CDV	Report on voting
86A/1602/CDV	86A/1628A/RVC

Full information on the voting for the approval of this standard can be found in the report on voting indicated in the above table.

The French version of this standard has not been voted upon.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all parts in the IEC 60793 series, published under the general title *Optical fibres*, can be found on the IEC website.

The committee has decided that the contents of this publication will remain unchanged until the stability date indicated on the IEC website under "<http://webstore.iec.ch>" in the data related to the specific publication. At this date, the publication will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

<https://standards.iteh.ai/catalog/standards/sis/02604826-b0cd-4281-961e-02329c1f356/iec-60793-2-20-2015>

OPTICAL FIBRES –

Part 2-20: Product specifications – Sectional specification for category A2 multimode fibres

1 Scope

This part of IEC 60793 is applicable to sub-categories A2a, A2b, and A2c. These fibres are used or can be incorporated in information transmission equipment and optical fibre cables (typically up to 2 km).

Three types of requirements apply to these fibres:

- general requirements as defined in IEC 60793-2;
- specific requirements common to the category A2 multimodal fibres covered in this standard and which are given in Clause 3;
- particular requirements applicable to individual sub-categories or specific applications, which are defined in the normative family specification annexes.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60793-1-20:2001, *Optical fibres – Part 1-20: Measurement methods and test procedures – Fibre geometry*

IEC 60793-1-21, *Optical fibres – Part 1-21: Measurement methods and test procedures – Coating geometry*

IEC 60793-1-22, *Optical fibres – Part 1-22: Measurement methods and test procedures – Length measurement*

IEC 60793-1-30, *Optical fibres – Part 1-30: Measurement methods and test procedures – Fibre proof test*

IEC 60793-1-31, *Optical fibres – Part 1-31: Measurement methods and test procedures – Tensile strength*

IEC 60793-1-40, *Optical fibres – Part 1-40: Measurement methods and test procedures – Attenuation*

IEC 60793-1-41, *Optical fibres – Part 1-41: Measurement methods and test procedures – Bandwidth*

IEC 60793-1-43, *Optical fibres – Part 1-43: Measurement methods and test procedures – Numerical aperture measurement*

IEC 60793-1-46, *Optical fibres – Part 1-46: Measurement methods and test procedures – Monitoring of changes in optical transmittance*

IEC 60793-1-50, *Optical fibres – Part 1-50: Measurement methods and test procedures – Damp heat (steady state) tests*

IEC 60793-1-51, *Optical fibres – Part 1-51: Measurement methods and test procedures – Dry heat (steady state) tests*

IEC 60793-1-52, *Optical fibres – Part 1-52: Measurement methods and test procedures – Change of temperature tests*

IEC 60793-2, *Optical fibres – Part 2: Product specifications – General*

3 Specifications

3.1 General

The fibre shall consist of a glass core and a glass cladding in accordance with the definition given in IEC 60793-2.

3.2 Dimensional requirements

Relevant dimensional attributes and measurement methods are indicated in Table 1.

Dimensional requirements common to all sub-categories appear in Table 2.

Table 3 lists additional dimensional attributes that shall be specified by each sub-category.

Table 1 – Relevant dimensional attributes and measurement methods

Attribute	Measurement method
Cladding diameter	IEC 60793-1-20
Core diameter ^a	IEC 60793-1-20
Core non-circularity	IEC 60793-1-20
Core-cladding concentricity error	IEC 60793-1-20
Coating diameter	IEC 60793-1-21
Fibre length	IEC 60793-1-22
^a Core diameter is specified at 850 nm \pm 10 nm with a test specimen length of 2,0 m \pm 0,2 m and a threshold value k_{CORE} of 0,5 (IEC 60793-1-20 Method B).	

Table 2 – Dimensional requirements common to all category A2 fibres

Attribute	Unit	Limit
Core non-circularity	%	≤ 4
Coating diameter	μm	^a
Fibre length	km	^b
^a The diameter of the coating is dependent on the cable structure and applications.		
^b Length requirements vary and should be agreed between supplier and customer.		

Table 3 – Additional dimensional attributes required for each sub-category

Attribute
Cladding diameter
Core diameter

3.3 Mechanical requirements

Relevant mechanical attributes and test methods are indicated in Table 4.

Mechanical requirements common to all sub-categories are given in Table 5.

Table 4 – Relevant mechanical attributes and test methods

Attribute	Test method
Tensile strength	IEC 60793-1-31 (0,5 m specimen length) Strain rate 3 %/min to 5 %/min
Proof test	IEC 60793-1-30

Table 5 – Mechanical requirements common to all category A2 fibres

Attribute	Unit	Limit
Proof stress level	GPa	≥ 0,345 ^a
^a For the relation between different units, see 7.4 of IEC TR 62048:2014.		

3.4 Transmission requirements

Relevant transmission attributes and measurement methods are given in Table 6.

Requirements common to all sub-categories are given in Table 7.

Table 6 – Relevant transmission attributes and measurement methods

Attribute	Test
Attenuation coefficient ^a	IEC 60793-1-40
Modal bandwidth ^a	IEC 60793-1-41
Numerical aperture NA _{ff} ^{a,b}	IEC 60793-1-43
Change of optical transmission	IEC 60793-1-46
^a When measuring attenuation, modal bandwidth and numerical aperture, the appropriate launching conditions should be applied as specified in the corresponding measurement methods (IEC 60793-1-40, IEC 60793-1-41 and IEC 60793-1-43). ^b Numerical aperture (NA _{ff}) is specified at a test specimen length of 2,0 m ± 0,2 m with a threshold value, k_{NA} of 0,5 measured at 850 nm.	

Table 7 – Requirements common to all category A2 fibres

Attribute	Unit	Limit
Attenuation coefficient at λ_{γ} nm ^a	dB/km	≤ 10
Modal bandwidth at λ_{γ} nm ^a	MHz · km	≥ 10
Numerical aperture (NA _{ff})	Unitless	0,23 ± 0,03 or 0,26 ± 0,03
^a The wavelength, λ_{γ} , shall be agreed between supplier and customer.		

3.5 Environmental requirements

Relevant environmental attributes and test methods are given in Table 8.

Table 8 – Relevant environmental attributes and test methods

Attribute	Test method
Damp heat tests	IEC 60793-1-50
Dry heat tests	IEC 60793-1-51
Change of temperature tests	IEC 60793-1-52

Annex A (normative)

Specifications for sub-category A2a multimode fibres

A.1 General

The clauses and tables in Annex A contain the particular requirements applicable to A2a fibres. Common requirements, repeated here for ease of reference from the sectional specification, are noted by an entry in the “Reference” column. Relevant notes from the sectional specification are not repeated but indicated with a superscript “SS”.

A.2 Dimensional requirements

Table A.1 contains dimensional requirements specific to A2a fibres.

Table A.1 – Dimensional requirements specific to A2a fibres

Attribute	Unit	Limit	Reference
Cladding diameter	μm	140 ±10	3.2
Core diameter	μm	100 ±4	3.2 Table 1
Core non-circularity	%	≤ 4	3.2
Coating diameter	μm	See 3.2	3.2
Fibre length	km	See 3.2	3.2

A.3 Mechanical requirements

Table A.2 contains mechanical requirements specific to A2a fibres.

Table A.2 – Mechanical requirements specific to A2a fibres

Attribute	Unit	Limit	Reference
Proof stress level	GPa	≥ 0,345 ^{SS}	3.3

A.4 Transmission requirements

Table A.3 contains transmission requirements specific to A2a fibres.

Table A.3 – Transmission requirements specific to A2a fibres

Attribute	Unit	Limit	Reference
Attenuation coefficient at λ_Y nm ^{SS}	dB/km	≤ 10	3.4
Modal bandwidth at λ_Y nm ^{SS}	MHz · km	≥ 10	3.4
Numerical aperture (NA _{ff})	Unitless	0,23 ±0,03 or 0,26 ±0,03	3.4 Table 6

A.5 Environmental requirements

Tables A.4 and A.5 contain environmental exposure tests and measurement methods specific to A2a fibres. Test and measurements shall be documented in two forms:

- relevant environmental attributes, test methods and test conditions are given in Table A.4;
- measurements of a particular mechanical and transmission attribute that may change during exposure to the environmental test are listed in Table A.5.

Table A.4 – Environmental exposure tests

Environment	Test method	Test condition
Damp heat	IEC 60793-1-50	+70 °C, 85 % RH, 30 days
Dry heat	IEC 60793-1-51	+70 °C, 30 days
Change of temperature	IEC 60793-1-52	T_a : -20 °C, T_b : +70 °C

Table A.5 – Attributes measured

Attribute	Unit	Limit	Reference
Change in optical transmission at attenuation coefficient at λ_y nm ^{SS}	dB/km	≤ 2	
Tensile strength	GPa at 15 % and 50 % Weibull probability levels	2,20 at 15 % 2,41 at 50 %	

These tests are normally conducted periodically as type-tests for a fibre design. Unless otherwise indicated, the recovery period allowed between the completion of the environmental exposure and measuring the attributes shall be as stated in the particular environmental test method.