

INTERNATIONAL STANDARD

ISO 8502-6

First edition
1995-12-15

Preparation of steel substrates before application of paints and related products — Tests for the assessment of surface cleanliness

(Part 6: [standards.iteh.ai](https://standards.iteh.ai/catalog/standards/iso/8502-6-1995))

Extraction of soluble contaminants for
analysis — The Bresle method

*Préparation des subjectiles d'acier avant application de peintures et de produits
assimilés — Essais pour apprécier la propreté d'une surface*

*Partie 6: Extraction des contaminants solubles en vue de l'analyse — Méthode
de Bresle*



Reference number
ISO 8502-6:1995(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 8502-6 was prepared by Technical Committee ISO/TC 35, *Paints and varnishes*, Subcommittee SC 12, *Preparation of steel substrates before application of paints and related products*.

ISO 8502 consists of the following parts, under the general title *Preparation of steel substrates before application of paints and related products — Tests for the assessment of surface cleanliness*:

- *Part 1: Field test for soluble iron corrosion products*
[Technical Report]
- *Part 2: Laboratory determination of chloride on cleaned surfaces*
- *Part 3: Assessment of dust on steel surfaces prepared for painting (pressure-sensitive tape method)*
- *Part 4: Guidance on the estimation of the probability of condensation prior to paint application*
- *Part 5: Measurement of chloride on steel surfaces prepared for painting — Ion detection tube method*
- *Part 6: Extraction of soluble contaminants for analysis — The Bresle method*

© ISO 1995

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

- *Part 7: Field method for determination of oil and grease*
- *Part 8: Field method for refractometric determination of moisture*
- *Part 9: Field method for conductometric determination of water-soluble salts*
- *Part 10: Field method for titrimetric determination of chloride*

At the time of publication of this part of ISO 8502, part 5 and parts 7 to 10 were in course of preparation.

Annex A forms an integral part of this part of ISO 8502.

iTeh STANDARD PREVIEW **(standards.iteh.ai)**

[ISO 8502-6:1995](https://standards.iteh.ai/catalog/standards/sist/260f8a2c-9cb0-4dcd-ac2d-9c1f32dde4bd/iso-8502-6-1995)

<https://standards.iteh.ai/catalog/standards/sist/260f8a2c-9cb0-4dcd-ac2d-9c1f32dde4bd/iso-8502-6-1995>

Introduction

The performance of protective coatings of paint and related products applied to steel is significantly affected by the state of the steel surface immediately prior to painting. The principal factors that are known to influence this performance are:

- a) the presence of rust and mill scale;
- b) the presence of surface contaminants, including salts, dust, oils and greases;
- c) the surface profile.

International Standards ISO 8501, ISO 8502 and ISO 8503 have been prepared to provide methods of assessing these factors, while ISO 8504 provides guidance on the preparation methods that are available for cleaning steel substrates, indicating the capabilities of each in attaining specified levels of cleanliness.

These International Standards do not contain recommendations for the protective coating systems to be applied to the steel surface. Neither do they contain recommendations for the surface quality requirements for specific situations even though surface quality can have a direct influence on the choice of protective coating to be applied and on its performance. Such recommendations are found in other documents such as national standards and codes of practice. It will be necessary for the users of these International Standards to ensure that the qualities specified are:

- compatible and appropriate both for the environmental conditions to which the steel will be exposed and for the protective coating system to be used;
- within the capability of the cleaning procedure specified.

The four International Standards referred to above deal with the following aspects of preparation of steel substrates:

ISO 8501 — *Visual assessment of surface cleanliness;*

ISO 8502 — *Tests for the assessment of surface cleanliness;*

ISO 8503 — *Surface roughness characteristics of blast-cleaned steel substrates;*

ISO 8504 — *Surface preparation methods.*

Each of these International Standards is in turn divided into separate parts.

This is one of a number of parts of ISO 8502 that specify tests for the assessment of surface cleanliness. In connection with such tests, there are several methods for the extraction, for analysis, of soluble contaminants on surfaces to be painted. Some of these methods are based on the swabbing of comparatively large test surfaces. This technique provides average values of the contamination present, but it may conceal localized concentrations of

contaminants. Also, swabbing may not ensure sufficient penetration to dissolve all of the deep-seated contamination such as ferrous salts.

There are other methods, however, which use small cells for the liquid used to remove and collect the surface contaminants. The cells (rigid or flexible) are attached to test surfaces where soluble contaminants could be expected, e.g. where pitting has occurred. This technique usually provides more accurate, point values of the contamination present.

This part of ISO 8502 describes a simple, inexpensive field test using flexible cells in the form of adhesive patches designed to be filled with solvent. The method was originally developed by a Swedish scientist, Dr. A. Bresle.

iTeh STANDARD PREVIEW **(standards.iteh.ai)**

[ISO 8502-6:1995](https://standards.iteh.ai/catalog/standards/sist/260f8a2c-9cb0-4dcd-ac2d-9c1f32ddc4bd/iso-8502-6-1995)

<https://standards.iteh.ai/catalog/standards/sist/260f8a2c-9cb0-4dcd-ac2d-9c1f32ddc4bd/iso-8502-6-1995>

iTeh STANDARD PREVIEW
This page intentionally left blank
(standards.iteh.ai)

ISO 8502-6:1995

<https://standards.iteh.ai/catalog/standards/sist/260f8a2c-9cb0-4dcd-ac2d-9c1f32ddc4bd/iso-8502-6-1995>

Preparation of steel substrates before application of paints and related products — Tests for the assessment of surface cleanliness

Part 6:

Extraction of soluble contaminants for analysis — The Bresle method

1 Scope

This part of ISO 8502 describes a method of extracting, for analysis, soluble contaminants from a surface by use of flexible cells in the form of adhesive patches which can be attached to any surface, regardless of its shape (flat or curved) and its orientation (facing in any direction, including downwards).

The method described is suitable for use in the field to determine the presence of soluble contaminants before painting or a similar treatment.

This part of ISO 8502 does not cover the subsequent analysis of the contaminants that have been dissolved off. Methods of analysis suitable for field use are described in other parts of ISO 8502.

2 Normative references

The following standards contain provisions, which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards listed below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 554:1976, *Standard atmospheres for conditioning and/or testing — Specifications*.

ISO 8501-1:1988, *Preparation of steel substrates before application of paints and related products — Visual assessment of surface cleanliness — Part 1: Rust grades and preparation grades of uncoated steel substrates and of steel substrates after removal of previous coatings*.

ISO 8503-2:1988, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 2: Method for the grading of surface profile of abrasive blast-cleaned steel — Comparator procedure*.

ISO/IEC Guide 2:1991, *General terms and their definitions concerning standardization and related activities*.

3 Principle

An adhesive patch with a central compartment designed to hold a solvent is attached to the surface from which soluble contaminants are to be removed. The solvent is injected into the compartment by means of a syringe, and then sucked back into the syringe. This operation is repeated a number of times. The solvent (now containing contaminants dissolved off the test surface) is then transferred to a suitable vessel for analysis.

4 Apparatus and materials

4.1 Adhesive patch, the body of which is made of ageing-resistant, flexible material with closed pores, e.g. polyethylene foam, and with a hole punched in the centre. The punched-out material is kept in the hole as a reinforcement until the patch is used. One side of the patch is coated with a thin elastomer film. The other side is coated with adhesive and covered by a removable protective sheet made of paper.

NOTE 1 The hole and the outer edge of the patch may be any shape, e.g. circular, rectangular, elliptical, etc.

The thickness of the patch shall be $1,5 \text{ mm} \pm 0,3 \text{ mm}$. The width of the adhesive rim between the hole and the outer edge of the patch shall be at least 5 mm. Patches with one of the standard compartment sizes specified in table 1 are called standard patches.

It is essential that the adhesive patch is leaktight. An easily performed leak test has therefore been developed for type testing (see annex A). Twelve patches of the same size shall be tested, and at least eight of them shall pass the test. The leak test shall be carried out by an accredited laboratory and the result stated in a test report. For terms and definitions in this context, see ISO/IEC Guide 2.

Table 1 — Standard patches

Patch size	Compartment area (mm ²)
A-0155	155 ± 2
A-0310	310 ± 3
A-0625	625 ± 6
A-1250	1 250 ± 13
A-2500	2 500 ± 25

4.2 Reusable syringe:

max. cylinder volume: 8 ml
 max. needle diameter: 1 mm
 max. needle length: 50 mm

4.3 Solvent, chosen as a function of the surface contaminants to be determined. For the determination of water-soluble salts or other water-soluble contaminants, use distilled or deionized water.

4.4 Contact thermometer, accurate to 0,5 °C and graduated at 0,5 °C intervals.

5 Procedure

The procedure for extracting soluble contaminants is carried out as follows:

5.1 Take an adhesive patch (4.1) of a suitable size (see table 1). Remove the protective paper and the punched-out material (see figure 1).

5.2 Press the adhesive side of the patch against the test surface (see figure 2) in such a way that the minimum amount of air is trapped in the compartment in the patch.

5.3 Fill the syringe (4.2) with solvent (4.3) (see figure 3).

NOTE 2 The volume of solvent needed to fill the patch compartment is proportional to the compartment area, and normally amounts to $2,6 \times 10^{-3}$ ml/mm² ± $0,6 \times 10^{-3}$ ml/mm².

5.4 Insert the syringe needle at an angle of about 30° to the test surface near the outer edge of the

patch, so that it passes through the adhesive foam body of the patch into the compartment formed between the elastomer film and the test surface (see figure 4).

If the patch is in a position which makes access to the patch compartment difficult, bend the syringe needle as required.

5.5 Inject the solvent, ensuring that it wets the whole of the test surface (see figure 4).

If necessary to avoid air remaining trapped in the patch compartment, carry out the injection in two steps as follows:

Inject half of the solvent. Evacuate the air through the needle by reverse operation of the syringe. Remove the needle from the patch. Holding the syringe with the needle pointing upwards, expel the air. Re-insert the needle into the compartment and inject the remainder of the solvent.

5.6 After a suitable period of time, to be agreed between the interested parties, suck the solvent back into the syringe (see figure 5).

NOTE 3 On unpitted blast-cleaned areas, a period of 10 min has been found satisfactory, as by then more than 90 % of the soluble salts have usually been dissolved.

5.7 Without removing the syringe needle from the patch, re-inject the solvent into the compartment and then suck the solvent back into the syringe cylinder. Repeat until at least four injection/sucking cycles have been completed.

5.8 At the end of the last cycle, retrieve as much as possible of the solvent from the compartment and transfer to a suitable vessel for analysis (see figure 6).

NOTE 4 In most cases, approximately 95 % of the soluble surface contaminants can be dissolved off by carrying out steps 5.3 to 5.8 only once. By repeating these steps with fresh solvent, almost all of the remaining 5 % can also be dissolved off.

5.9 During steps 5.3 to 5.8, it is essential that no solvent be lost from the patch or syringe, due for instance to inferior-quality materials or improper handling of the materials. If any solvent is lost, the solution obtained shall be rejected.

5.10 On completion of step 5.8, clean and rinse the syringe so that it can be re-used. A bent needle is best left as it is until it becomes necessary to straighten it or bend it further.

5.11 Record the temperature of the steel surface to the nearest 0,5 °C using the contact thermometer (4.4).

6 Test report

The test report shall contain at least the following information:

- a) a reference to this part of ISO 8502 (i.e. ISO 8502-6);
- b) the solvent used;
- c) the volume of solvent injected;
- d) the total time of contact between the solvent and substrate, i.e. the time agreed in 5.6 multiplied by the total number of cycles carried out;
- e) the temperature during steps 5.3 to 5.8 of the procedure;
- f) the date of the test.

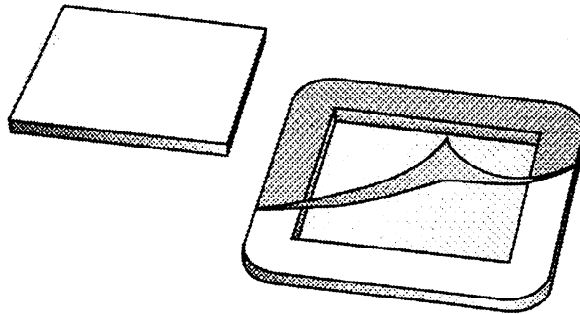


Figure 1 — Protective paper and punched-out material are removed

iTeh STANDARD PREVIEW
(standards.iteh.ai)

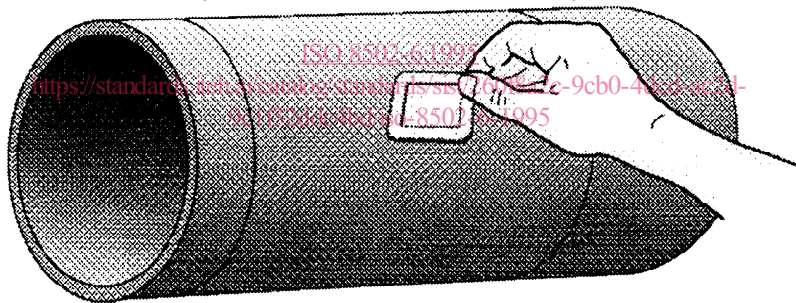


Figure 2 — The adhesive patch is attached to the test surface

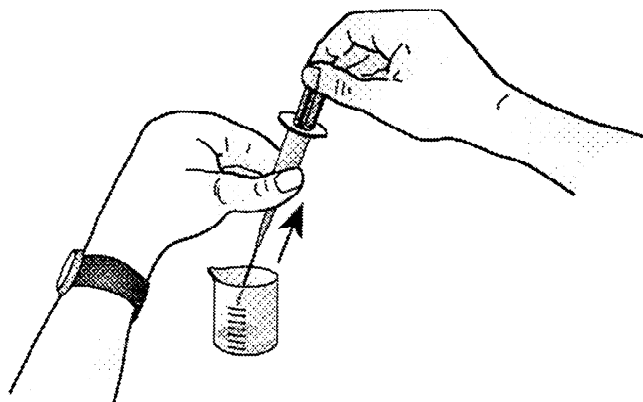


Figure 3 — The syringe is filled with solvent