IEC 62576

Edition 2.0 2018-02

INTERNATIONAL STANDARD

NORME INTERNATIONALE

colour inside

Electric double-layer capacitors for use in hybrid electric vehicles – Test methods for electrical characteristics

Condensateurs électriques à double couche pour véhicules électriques hybrides – Méthodes d'essai des caractéristiques électriques

IEC 62576:2018-02(en-fr)

IEC Central Office
3, rue de Varembé
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC
The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications
The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

IEC Catalogue - webstore.iec.ch/catalogue
The stand-alone application for consulting the entire bibliographical information on IEC International Standards, Technical Specifications, Technical Reports and other documents. Available for PC, Mac OS, Android Tablets and iPad.

IEC publications search - webstore.iec.ch/advsearchform
The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,…). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished
Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and also once a month by email.

Electropedia - www.electropedia.org
The world's leading online dictionary of electronic and electrical terms, containing 21 000 terms and definitions in English and French, with equivalent terms in 16 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Glossary - std.iec.ch/glossary
67 000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

IEC Customer Service Centre - webstore.iec.ch/csc
If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

A propos de l'IEC
La Commission Electrotechnique Internationale (IEC) est la première organisation mondiale qui élabore et publie des Normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications IEC
Le contenu technique des publications IEC est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

Catalogue IEC - webstore.iec.ch/catalogue
Application autonome pour consulter tous les renseignements bibliographiques sur les Normes internationales, Spécifications techniques, Rapports techniques et autres documents de l'IEC. Disponible pour PC, Mac OS, tablettes Android et iPad.

Recherche de publications IEC - webstore.iec.ch/advsearchform
La recherche avancée permet de trouver des publications IEC en utilisant différents critères (numéro de référence, texte, comité d'études,…). Elle donne aussi des informations sur les projets et les publications remplacées ou retirées.

IEC Just Published - webstore.iec.ch/justpublished
Restez informé sur les nouvelles publications IEC. Just Published détaille les nouvelles publications parues. Disponible en ligne et aussi une fois par mois par email.

Electropedia - www.electropedia.org
Le premier dictionnaire en ligne de termes électroniques et électriques. Il contient 21 000 termes et définitions en anglais et en français, ainsi que les termes équivalents dans 16 langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International (IEV) en ligne.

Glossaire IEC - std.iec.ch/glossary
67 000 entrées terminologiques électrotechniques, en anglais et en français, extraites des articles Termes et Définitions des publications IEC parues depuis 2002. Plus certaines entrées antérieures extraites des publications des CE 37, 77, 86 et CISPR de l'IEC.

Service Clients - webstore.iec.ch/csc
Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions contactez-nous: sales@iec.ch.

IEC 62576

Edition 2.0 2018-02

INTERNATIONAL STANDARD

NORME INTERNATIONALE

colour inside

Electric double-layer capacitors for use in hybrid electric vehicles – Test methods for electrical characteristics

Condensateurs électriques à double couche pour véhicules électriques hybrides – Méthodes d'essai des caractéristiques électriques

INTERNATIONAL ELECTROTECHNICAL COMMISSION

COMMISSION ELECTROTECHNIQUE INTERNATIONALE

ICS 31.060.99; 43.120

ISBN 978-2-8322-5341-0

Warning! Make sure that you obtained this publication from an authorized distributor.
Attention! Veuillez vous assurer que vous avez obtenu cette publication via un distributeur agréé.

CONTENTS

INTERNATIONAL ELECTROTECHNICAL COMMISSION

____

ELECTRIC DOUBLE-LAYER CAPACITORS FOR USE IN HYBRID ELECTRIC VEHICLES – TEST METHODS FOR ELECTRICAL CHARACTERISTICS

FOREWORD

1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
6) All users should ensure that they have the latest edition of this publication.
7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 62576 has been prepared by IEC technical committee 69: Electric road vehicles and electric industrial trucks.

This second edition cancels and replaces the first edition published in 2009. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

a) information on applicability of this document has been added in Clause 1;
b) the definitions of some terms in Clause 3 have been improved;
c) the description of test procedures in Clause 4 has been clarified;
d) information on endurance cycling test has been added (Annex E).

The text of this International Standard is based on the following documents:

CDV	Report on voting
69/486/CDV	69/539/RVC

Full information on the voting for the approval of this International Standard can be found in the report on voting indicated in the above table.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

The committee has decided that the contents of this publication will remain unchanged until the stability date indicated on the IEC website under "http://webstore.iec.ch" in the data related to the specific publication. At this date, the publication will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

INTRODUCTION

The electric double-layer capacitor (capacitor) is used as an energy storage system for vehicles. Capacitor-installed electric vehicles are commercialized with an eye to improving fuel economy by recovering regenerative energy, and by peak power assistance during acceleration, etc. Although standards for capacitors already exists (IEC 62391 series), those for electric vehicles involve patterns of use, usage environment, and values of current that are quite different from those assumed in the existing standards. Standard evaluation and test methods will be useful for both auto manufacturers and capacitor suppliers to speed up the development and lower the costs of such capacitors. With these points in mind, this document aims to provide basic and minimum specifications in terms of the methods for testing electrical characteristics, and to create an environment that supports the expanding market of electric vehicles and large capacity capacitors. Additional practical test items to be standardized should be reconsidered after technology and market stabilization of capacitors for electric vehicles. Regarding endurance, which is important in practical use, just a basic concept is set forth in the informative annexes.

ELECTRIC DOUBLE-LAYER CAPACITORS FOR USE IN HYBRID ELECTRIC VEHICLES – TEST METHODS FOR ELECTRICAL CHARACTERISTICS

1 Scope

This document describes the methods for testing electrical characteristics of electric double-layer capacitor cells (hereinafter referred to as "capacitor") used for peak power assistance in hybrid electric vehicles.

All the tests in this document are type tests.

This document can also be applicable to the capacitor used in idling reduction systems (start and-stop systems) for the vehicles.

This document can also be applicable to the capacitor modules consisting of more than one cell.

NOTE Annex E provides information on endurance cycling test.

2 Normative references

There are no normative references in this document.

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at http://www.electropedia.org/
- ISO Online browsing platform: available at http://www.iso.org/obp

3.1
ambient temperature
temperature of the air, in the immediate vicinity of a capacitor

3.2
applied voltage
voltage (V) applied between the terminals of a capacitor

3.3
calculation end voltage
voltage (V) at a selected end point for calculating the characteristics including capacitance under a state of voltage decrease during discharge

3.4
calculation start voltage
voltage (V) at a selected start point for calculating the characteristics including capacitance under a state of voltage decrease during discharge

3.5
capacitance
ability of a capacitor to store electrical charge (F)

3.6
charge accumulated electrical energy
amount of charged energy (J) accumulated from the beginning to the end of charging

3.7
charge current
I_c
current (A) required to charge a capacitor

3.8
charging efficiency
efficiency under specified charging conditions, and ratio (%) of stored energy to charge accumulated electrical energy

Note 1 to entry: This value is calculated from the internal resistance of a capacitor.

Note 2 to entry: Refer to Formula C.8.

3.9
constant voltage charging
charging during which the voltage is maintained at a constant value regardless of charge current or temperature

3.10
discharge accumulated electrical energy
amount of discharged energy (J) accumulated from the beginning to the end of discharging

3.11
discharge current
I_d
current (A) required to discharge a capacitor

3.12
discharging efficiency
efficiency under specified discharging conditions, and ratio (%) of discharge accumulated electrical energy to stored energy

Note 1 to entry: This value is calculated from the internal resistance of a capacitor.

Note 2 to entry: Refer to Formula C.10.

3.13
electric double-layer capacitor
capacitor
device that stores electrical energy using a double layer in an electrochemical cell, and whose positive and negative electrodes are of the same material

Note 1 to entry: The electrolytic capacitor is not included in capacitor of this document.

3.14
energy efficiency
E_f
ratio (%) of discharge accumulated electrical energy to charge accumulated electrical energy under specified charging and discharging conditions

3.15
internal resistance
combined resistance (Ω) of constituent material specific resistance and inside connection resistance of a capacitor

3.16
maximum power density
P_{dm}
greatest electrical power output of a capacitor per mass (W/kg) or volume (W/l)

3.17
nominal internal resistance
R_N
nominal value of the internal resistance (R_N) to be used in design and measurement condition setting (Ω), generally at the ambient temperature

3.18
post-treatment
discharging and storage of a capacitor under specified ambient conditions (temperature, humidity, and pressure) after tests

Note 1 to entry: Generally, post-treatment implies that a capacitor is discharged and stored until its inner temperature attains thermal equilibrium with the surrounding temperature before its electrical characteristics are measured.

3.19
pre-conditioning
charging and discharging and storage of a capacitor under specified ambient conditions (temperature, humidity, and pressure) before testing.

Note 1 to entry: Generally, pre-conditioning implies that a capacitor is discharged and stored until its inner temperature attains thermal equilibrium with the surrounding temperature, before its electrical characteristics are measured.

3.20
rated voltage
U_R
maximum DC voltage (V) that may be applied continuously for a certain time under the upper category temperature to a capacitor so that a capacitor can exhibit specified demand characteristics

Note 1 to entry: This voltage is the setting voltage in capacitor design.

Note 2 to entry: The endurance test using the rated voltage is described in Annex A.

3.21
ambient temperature
temperature of air in the vicinity of the device under test, in this document (25 ± 2) °C

3.22
stored energy
energy (J) stored in a capacitor

3.23
upper category temperature
highest ambient temperature at which a capacitor is designed to operate continuously

3.24
voltage maintenance characteristics
ability of a capacitor to maintain the voltage, with its terminals open, after a specified time period subsequent to the charging

3.25
voltage maintenance rate
ratio of voltage maintenance
ratio of the voltage at the open-ended terminals to the charge voltage after a specified time period subsequent to the charging of a capacitor

4 Tests methods

4.1 Capacitance, internal resistance, and maximum power density

4.1.1 Circuit for measurement

The capacitance and the internal resistance shall be measured by using the constant current and constant voltage charging and the constant current discharging. Figure 1 shows the basic circuit to be used for the measurement.

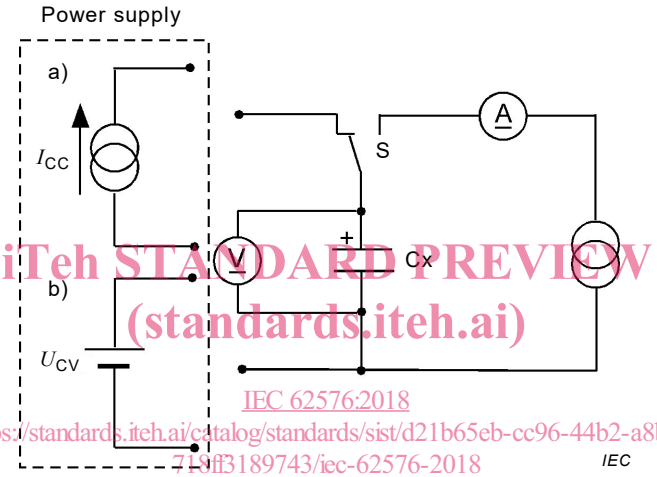

Key

I_{CC}	constant-current
U_{CV}	constant-voltage
Ⓐ	DC ammeter
Ⓥ	DC voltage recorder
S	changeover switch
Cx	capacitor under test
⊖	constant current discharger
a)	constant current charging
b)	constant voltage charging

Figure 1 – Basic circuit for measuring capacitance, internal resistance and maximum power density

4.1.2 Test equipment

The test equipment shall be capable of constant current charging, constant voltage charging, constant current discharging, and continuous measurement of the current and the voltage between the capacitor terminals in time-series as shown in Figure 2. The test equipment shall be able to set the current and the voltage with the accuracy equal to ±1 % or less, and to measure the current and voltage with accuracy equal to ±0,1 %.

The power supply shall provide the constant charge current for the capacitor charge with 95 % efficiency, set the duration of constant voltage charge, and provide a discharge current

corresponding to the specified discharge efficiency. The DC voltage recorder shall be capable of conducting measurements and recording with a sampling interval of 10 ms or less.

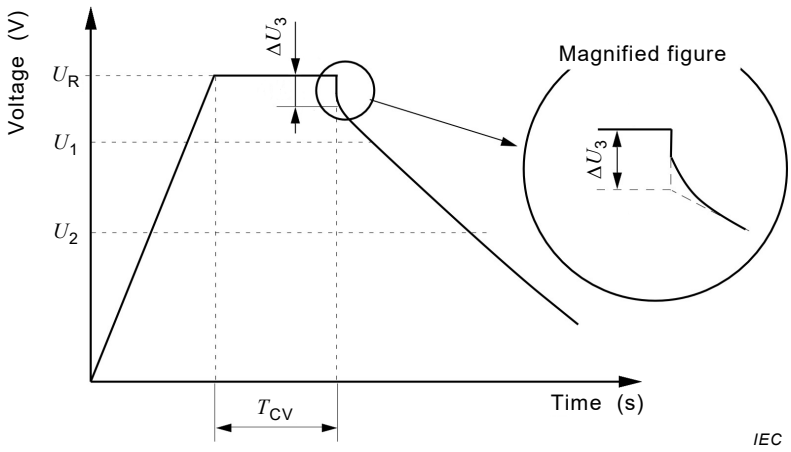

Key

U_R rated voltage (V)
U_1 calculation start voltage (V)
U_2 calculation end voltage (V)
ΔU_3 voltage drop (V)
T_{CV} constant voltage charging duration (s)

Figure 2 – Voltage–time characteristics between capacitor terminals in capacitance and internal resistance measurement

4.1.3 Measurement procedure

Measurements shall be carried out in accordance with the following procedures using the test equipment specified in 4.1.2.

a) Pre-conditioning

Before measurement, the capacitors shall be fully charged and fully discharged, and then incubated for 2 h to 6 h under the ambient temperature or that specified by the related standards.

NOTE 1 The heat equilibrium time, which provides a reference for the soaking time, is described in Annex B.

NOTE 2 Charging and discharging can be repeated if necessary until the capacity and internal resistance are stabilized.

EXAMPLE

Charge and discharge the sample using the current specified by the manufacturer in the following order:

1) fully discharge;
2) charge up to U_R;
3) discharge down to 0,5 U_R;
4) repeat 2) and 3) ten times.

b) Sample setting

Fit the sample capacitors with the test equipment.

c) Test equipment setup

Unless otherwise specified by related standards, the test equipment shall be set up in the following manner.

1) Set the constant current I_c for charging. At this current, the capacitors shall be able to charge with 95 % charging efficiency based on their nominal internal resistance R_N. The current value is calculated by $I_c = U_R/38R_N$. The constant current value or the

charging efficiency may be changed according to the agreement between the customer and the supplier.

NOTE The general concept for 95 % charging or discharging efficiency is described in Annex C. When the rated value of internal resistance of a capacitor is uncertain, the current for the measurement can be set according to the advisable procedures described in Annex D.

2) Set the maximum voltage for constant current charging as the rated voltage U_R.

3) Set the duration of constant voltage charging T_{cv} to 300 s.

4) Set the constant current discharge value. This value shall allow for a 95 % discharging efficiency based on the capacitor's nominal internal resistance R_N, and is calculated by $I_d = U_R/40R_N$.

   The constant current value or the discharging efficiency may be changed according to the agreement between the customer and the supplier.

5) Set the sampling interval to 10 ms or less, and set the test-equipment so as to measure the voltage drop characteristics up to 0,5 U_R.

d) Test

According to the set-up in 4.1.3 c), charge and discharge the sample in the following order, and measure the voltage between the capacitor terminals as shown in Figure 2:

– constant current charging up to U_R;
– constant voltage charging at U_R for 300 s;
– constant current discharging down to 0,4 U_R.

4.1.4 Calculation method for capacitance

The capacitance C shall be calculated using Formula (1) based on the voltage-time characteristics between capacitor terminals obtained in 4.1.4.

NOTE This calculation method is called "energy conversion capacitance method".

$$C = \frac{2W}{(0{,}9U_R)^2 - (0{,}7U_R)^2} \quad (1)$$

where

C is the capacitance (F) of capacitor;

W is the measured discharged energy (J) from calculation start voltage (0,9 U_R) to calculation end voltage (0,7 U_R);

U_R is the rated voltage (V).

4.1.5 Calculation method for internal resistance

The internal resistance R shall be calculated using Formula (2) based on the voltage-time characteristics between capacitor terminals obtained in 4.1.4.

$$R = \frac{\Delta U_3}{I_d} \quad (2)$$

where

R is the internal resistance (Ω) of capacitor;

I_d is the discharge current (A);

ΔU_3 is the voltage drop (V).

To obtain ΔU_3, apply the straight-line approximation to the voltage drop characteristics from the calculation start voltage (0,9 U_R) to the calculation end voltage (0,7 U_R) by using the least squares method. Obtain the intercept (voltage value) of the straight line at the discharge start time. ΔU_3 is the difference of voltages (V) between the intercept voltage value and the set value of constant voltage charging.

NOTE This calculation method is called "least squares internal resistance method".

4.1.6 Calculation method for maximum power density

The maximum power density P_{dm} is calculated by using the internal resistance value calculated in 4.1.5 and Formula (3).

NOTE This calculation method is called "matched impedance power density method".

$$P_{dm} = \frac{0{,}25 U_R^2}{RM} \quad (3)$$

where

P_{dm} is the maximum power density of capacitor (W/kg or W/l);

U_R is the rated voltage (V);

R is the calculated internal resistance (Ω);

M is the mass or volume of capacitor (kg or l).

4.2 Voltage maintenance characteristics

4.2.1 Circuit for measurement

Figure 3 shows the basic circuit for measuring the voltage maintenance characteristics.