

TECHNICAL REPORT

RAPPORT TECHNIQUE

**Environmental testing –
Part 3-12: Supporting documentation and guidance – Method to evaluate a
possible lead-free solder reflow temperature profile**

**Essais d'environnement –
Partie 3-12: Documentation d'accompagnement et guide – Méthode d'évaluation
d'un profil de température possible de brasage sans plomb par refusion**

<https://standards.iteh.ai/catalog/standards/iec/7bf36906-acb0-4594-80d5-bb1bf6478b7d/iec-tr-60068-3-12-2014>

WILSON



THIS PUBLICATION IS COPYRIGHT PROTECTED
Copyright © 2014 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de l'IEC ou du Comité national de l'IEC du pays du demandeur. Si vous avez des questions sur le copyright de l'IEC ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de l'IEC de votre pays de résidence.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
Fax: +41 22 919 03 00
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

IEC Catalogue - webstore.iec.ch/catalogue

The stand-alone application for consulting the entire bibliographical information on IEC International Standards, Technical Specifications, Technical Reports and other documents. Available for PC, Mac OS, Android Tablets and iPad.

IEC publications search - www.iec.ch/searchpub

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and also once a month by email.

Electropedia - www.electropedia.org

The world's leading online dictionary of electronic and electrical terms containing more than 30 000 terms and definitions in English and French, with equivalent terms in 14 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Glossary - std.iec.ch/glossary

More than 55 000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: csc@iec.ch.

A propos de l'IEC

La Commission Electrotechnique Internationale (IEC) est la première organisation mondiale qui élabore et publie des Normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications IEC

Le contenu technique des publications IEC est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

Catalogue IEC - webstore.iec.ch/catalogue

Application autonome pour consulter tous les renseignements bibliographiques sur les Normes internationales, Spécifications techniques, Rapports techniques et autres documents de l'IEC. Disponible pour PC, Mac OS, tablettes Android et iPad.

Recherche de publications IEC - www.iec.ch/searchpub

La recherche avancée permet de trouver des publications IEC en utilisant différents critères (numéro de référence, texte, comité d'études,...). Elle donne aussi des informations sur les projets et les publications remplacées ou retirées.

IEC Just Published - webstore.iec.ch/justpublished

Restez informé sur les nouvelles publications IEC. Just Published détaille les nouvelles publications parues. Disponible en ligne et aussi une fois par mois par email.

Electropedia - www.electropedia.org

Le premier dictionnaire en ligne de termes électroniques et électriques. Il contient plus de 30 000 termes et définitions en anglais et en français, ainsi que les termes équivalents dans 14 langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International (IEV) en ligne.

Glossaire IEC - std.iec.ch/glossary

Plus de 55 000 entrées terminologiques électrotechniques, en anglais et en français, extraites des articles Termes et Définitions des publications IEC parues depuis 2002. Plus certaines entrées antérieures extraites des publications des CE 37, 77, 86 et CISPR de l'IEC.

Service Clients - webstore.iec.ch/csc

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions contactez-nous: csc@iec.ch.

TECHNICAL REPORT

RAPPORT TECHNIQUE

**Environmental testing –
Part 3-12: Supporting documentation and guidance – Method to evaluate a
possible lead-free solder reflow temperature profile**

**Essais d'environnement –
Partie 3-12: Documentation d'accompagnement et guide – Méthode d'évaluation
d'un profil de température possible de brasage sans plomb par refusion**

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

COMMISSION
ELECTROTECHNIQUE
INTERNATIONALE

PRICE CODE
CODE PRIX



ICS 19.040

ISBN 978-2-8322-1888-4

**Warning! Make sure that you obtained this publication from an authorized distributor.
Attention! Veuillez vous assurer que vous avez obtenu cette publication via un distributeur agréé.**

CONTENTS

FOREWORD.....	3
1 Scope.....	5
2 Basics	5
3 Boards under investigation	6
3.1 Test board approach.....	6
3.2 Production board approach.....	6
4 Temperature tolerances.....	7
4.1 Temperature tolerances in Study A.....	7
4.2 Temperature tolerance and board size influence in Study B.....	8
5 Peak form and width.....	9
5.1 Peak form and width in Study A.....	9
5.2 Reflow oven investigation in Study B.....	9
6 Classification.....	10
6.1 Device classification in Study A.....	10
6.2 Board classification in Study B.....	12
7 Consideration for a lead-free reflow temperature profile.....	13
7.1 Determined lead-free reflow temperature profile in Study A.....	13
7.2 Lead-free reflow temperature profile approach in Study B.....	14
8 Conclusion.....	15
Bibliography.....	16
Figure 1 – Curve shape for a peak temperature of at least 20 s at 230 °C and 1 s at 233 °C.....	6
Figure 2 – Position of the assembled devices and temperature dependence on the device position.....	7
Figure 3 – Lower and upper temperature tolerances of the reflow solder profile.....	8
Figure 4 – Temperature tolerance and board size influence.....	8
Figure 5 – Hat type peak profile with 40 s at $T_{max} - 5 K = 255 °C$ for the small devices and the PCB.....	9
Figure 6 – ΔT by different reflow oven capabilities.....	10
Figure 7 – Representative test board measurements.....	11
Figure 8 – Example of the small board (camcorder).....	13
Figure 9 – Example of the mid-size board (personal computer (PC)).....	13
Figure 10 – Lead-free reflow temperature profile for device qualification.....	14
Table 1 – Measured temperatures of devices and values including lower and upper tolerances.....	11
Table 2 – Possible temperature classification of surface mount devices.....	12
Table 3 – Proposed requirements for a lead-free reflow profile.....	14

INTERNATIONAL ELECTROTECHNICAL COMMISSION

ENVIRONMENTAL TESTING –

**Part 3-12: Supporting documentation and guidance –
Method to evaluate a possible lead-free solder
reflow temperature profile**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

The main task of IEC technical committees is to prepare International Standards. However, a technical committee may propose the publication of a technical report when it has collected data of a different kind from that which is normally published as an International Standard, for example "state of the art".

IEC TR 60068-3-12, which is a technical report, has been prepared by IEC technical committee 91: Electronics assembly technology.

This second edition cancels and replaces the first edition published in 2007 and constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- the content has been adapted to the state-of-the-art of reflow-oven technology and termination finishes;
- minor language adjustments were performed.

The text of this technical report is based on the following documents:

Enquiry draft	Report on voting
91/1158/DTR	91/1177/RVC

Full information on the voting for the approval of this technical report can be found in the report on voting indicated in the above table.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all the parts in the IEC 60068 series, under the general title *Environmental testing*, can be found on the IEC website.

The committee has decided that the contents of this publication will remain unchanged until the stability date indicated on the IEC website under "<http://webstore.iec.ch>" in the data related to the specific publication. At this date, the publication will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

IEC TR 60068-3-12:2014

<https://standards.iteh.ai/catalog/standards/iec/7b36706-acb0-4594-80d5-bb1bf6478b7d/iec-tr-60068-3-12-2014>

ENVIRONMENTAL TESTING –

Part 3-12: Supporting documentation and guidance – Method to evaluate a possible lead-free solder reflow temperature profile

1 Scope

This part of IEC 60068, which is a technical report, presents two approaches for establishing a possible temperature profile for a lead-free reflow soldering process using SnAgCu solder paste.

This process covers a great variety of electronic products, including a large range of package sizes (e.g. molded active electronic components, passive components and electromechanical components).

Study A addresses requirements needed in the production of high-reliability electronic control units (ECU), as for example in automotive electronics. These requirements include measurement and production tolerances.

Study B represents consumer electronics products and includes reflow oven capability, board design and package sizes.

2 Basics

The process temperature for SnPb solder paste has a wide margin due to the liquid temperature of the solder alloy. During reflow soldering, temperature differences between components exist but are not critical. The process temperature of SnAgCu solder paste is about 20 K to 30 K higher than SnPb solder paste. Furthermore, the temperature difference between components (ΔT) becomes wider and sometimes the heat resistance temperature of components can become critical.

To avoid soldering failures which could be very harmful in safety-related applications and also generate higher failure costs, the capability of the soldering process is very important. A compromise between the temperature requirements of highly reliable solder joints and the limited solder-heat resistance of the electronic components has to be sought. In addition, the different aspects of mass production have to be considered. To achieve a reliable solder joint, the conventional reflow soldering process with eutectic SnPb solder paste is usually performed at a minimum peak temperature of about 203 °C at the coldest solder joint (i.e. at least 20 K above the liquid temperature of SnPb $T_{\text{liquid}} = 183$ °C).

The selected lead-free solder is SnAgCu with a melting point at around $T_{\text{liquid}} = 217$ °C [1]¹. It is a generally preferred material for lead-free reflow and wave soldering in mass production [2]. Using SnAgCu solder paste, it is not possible to solder the coldest solder joints at least 20 K above the liquid temperature ($T_{\text{liquid}} = 217$ °C), which would result in minimum temperatures of 237 °C. When the coldest solder joint is 237 °C, the temperature spread between small and large components, small semiconductor, and passive components, as well as the printed circuit board (PCB), will be too large for the components to survive the heat impact. Despite the aim to achieve a relatively low temperature at the coldest solder joint, the reliability of the solder joint has to be assured.

¹ Numbers in square brackets refer to the Bibliography.

To reach this target in Study A, the temperature at the coldest solder joint is taken to be $T_{\min} = 230\text{ °C}$, for a minimum time of 20 s, which is just 13 K above the melting temperature. Considering the peak shape (see Figure 1) this condition corresponds to 1 s at 233 °C. From a physical point of view, the risk of insufficient solder wetting during mass production is significantly higher if the solder joint temperature is lower than the above mentioned temperature of 230 °C. In addition, lead-free termination finishes (like tin layers with a post-bake process or very thin NiPdAu finishes) are known to exhibit a poorer wetting behavior than conventional SnPb pin finishes.

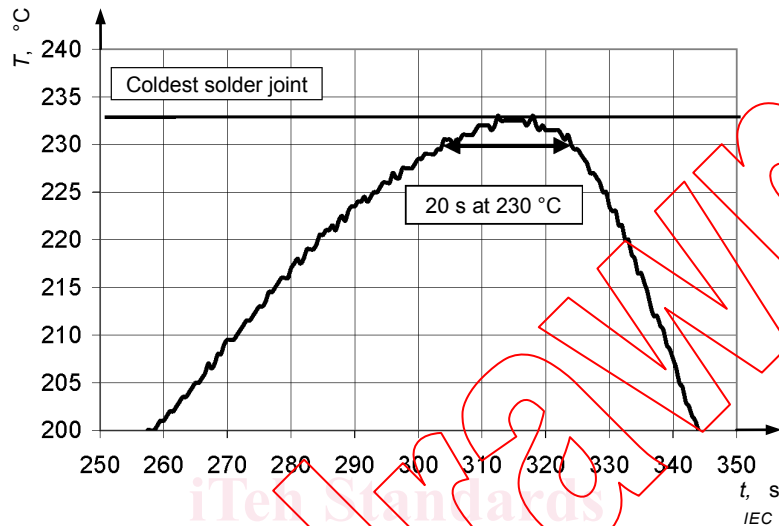


Figure 1 – Curve shape for a peak temperature of at least 20 s at 230 °C and 1 s at 233 °C

The experiments had been performed under mass production conditions (850 mm/min) using state-of-the-art reflow equipment, i.e. ovens featuring multiple heating zones, full convection and N_2 atmosphere.

3 Boards under investigation

3.1 Test board approach

For the experiment in Study A, a special test PCB was designed. Polyimide resin with a glass transition temperature of $T_g = 260\text{ °C}$ was used as base material for the PCB. Such a test board can represent the entire automotive ECU spectrum. The largest temperature difference (ΔT) between the coldest solder joint and the hottest point existing on this printed circuit assembly (PCA) spectrum is reflected on this test board (ΔT can be even larger for even more complex PCAs). The coldest solder joint was represented by a defined thermal mass, to represent large integrated circuits (ICs), coils or aluminium electrolytic capacitors. Its temperature behavior was correlated with the temperatures of the coldest solder joints on serial boards.

3.2 Production board approach

For Study B, PCB and reflow oven were taken from actual series production.

4 Temperature tolerances

4.1 Temperature tolerances in Study A

For tolerances during temperature profiling, different systematic failures shall be considered. First of all, there is an error associated with the temperature measurement itself. The measurement was performed in the centre on top of the packages with a well defined and repeatable preparation technique. Nevertheless, the failure due to preparation had to be fixed within $\pm 1,0$ K. In addition, the thermocouple (NiCrNi), together with the evaluation unit has an accuracy of $\pm 1,5$ K for pre-selected thermocouples. According to IEC 60584-2 [6] the NiCrNi thermocouples, class K, tolerance class 1 are specified with a tolerance of $\pm 1,5$ K for just the thermocouple itself without the measurement unit. Based on suppliers indication and own measurements, the furnace tolerance based on furnace load is $\pm 0,5$ K and the furnace tolerance for long term stability is $\pm 2,5$ K.

- Thermocouple with measurement unit: $\pm 1,5$ K
- Preparation of thermocouple: $\pm 1,0$ K
- Furnace load variation: $\pm 0,5$ K
- Long term stability of furnace: $\pm 2,5$ K

Because these variations are independent, the Gaussian error propagation can be applied, which results in a total tolerance of $\pm 3,0$ K, due to measurement errors and variations in mass production. The tolerance of $-3,0$ K results in the requirement to profile the coldest solder joint at 236 °C, instead of 233 °C (i.e. 233 °C + $3,0$ K). This tolerance is known as the "lower tolerance". In addition to the measurement errors and variations due to mass production, the influences of the test board have to be considered. The measured temperatures of the electronic components depend also on the position on the test board because of the longitudinal and transversal temperature spread in the furnace and along the test board (see Figure 2). These temperature differences are the result of the heat flow conditions in the furnace and around the test board. The actual temperature of a device can be up to $3,5$ K higher than the measured values at the position where the device is mounted on the test board. The temperature dependence on the device position was measured independently before measuring the device temperatures on the assembled test board.


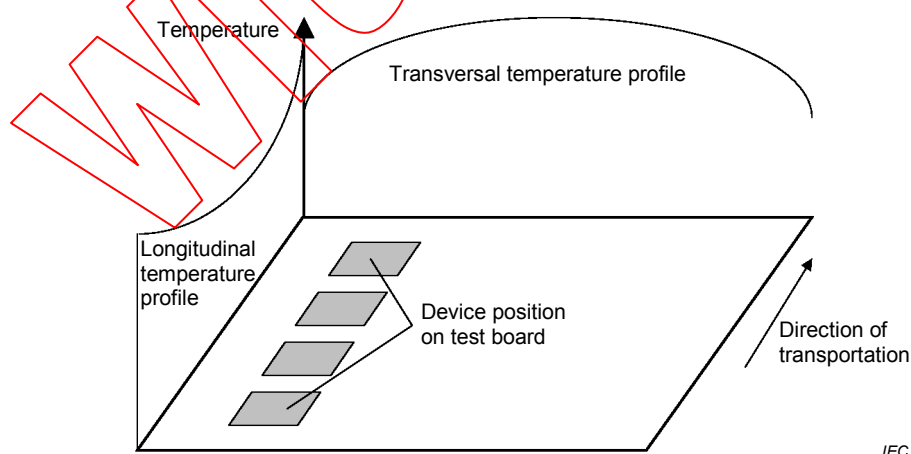


Figure 2 – Position of the assembled devices and temperature dependence on the device position

The thermal mass on the test board, which represents the coldest solder joint on the serial boards, was designed to include the relevant position-dependent tolerances. The upper temperature tolerances consist of the position-dependent temperature tolerances of 2 K to $3,5$ K and the above mentioned $+3$ K. This leads to a total upper tolerance of 5 K to $6,5$ K.

Regarding the whole temperature window of the lead-free soldering process, a total position-dependent temperature tolerance of 8 K to 9,5 K has to be added to the measured ΔT spread of the devices (see Figure 3).

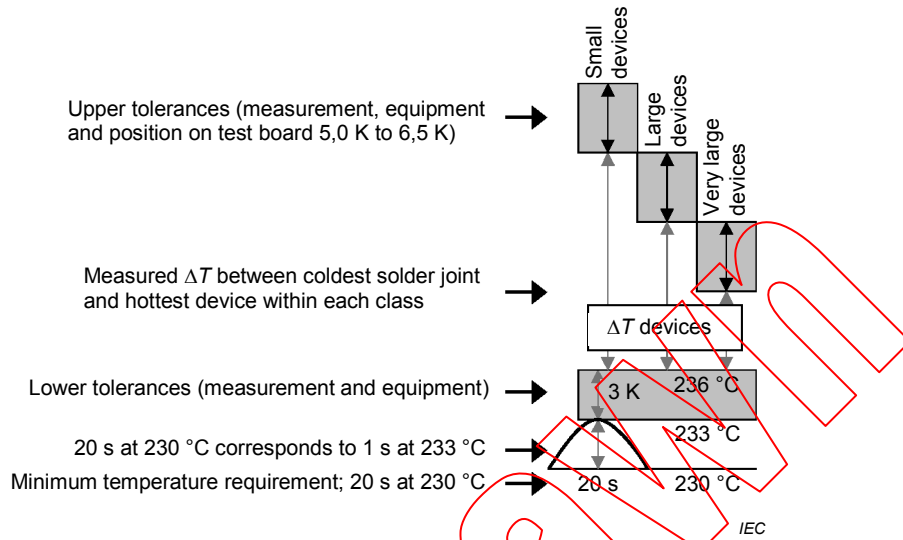

NOTE Electronic devices are divided into three temperature classes.

Figure 3 – Lower and upper temperature tolerances of the reflow solder profile

4.2 Temperature tolerance and board size influence in Study B

In the consumer board study, the measured temperature includes lower temperature tolerance and upper temperature tolerance. Therefore at the coldest solder joint temperature of 230 °C, the "worst-case" temperature becomes 227 °C (i.e. 230 °C – 3 K) which is still 10 K higher than the melting point of the SnAgCu solder alloy (see Figure 4).


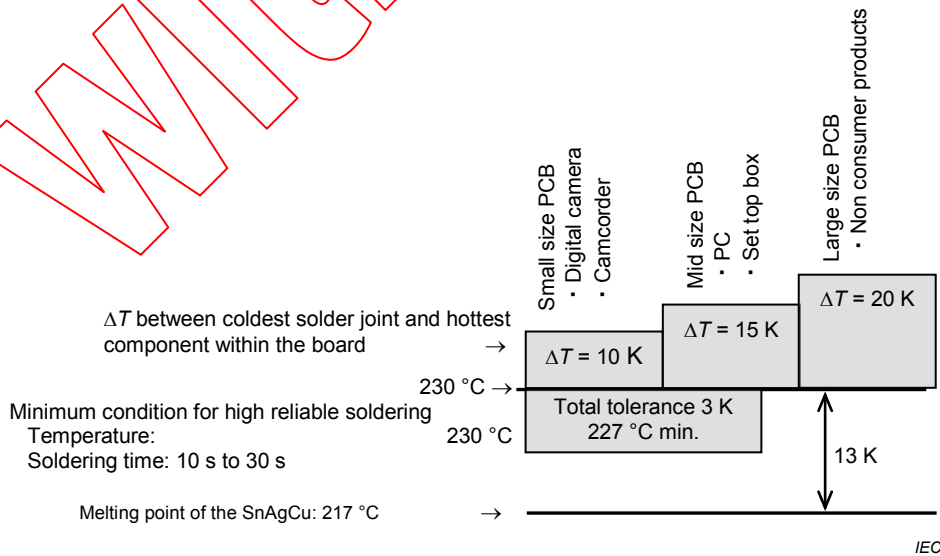


Figure 4 – Temperature tolerance and board size influence

5 Peak form and width

5.1 Peak form and width in Study A

The requirements were to maintain a temperature of at least 230 °C for 20 s at the coldest solder joint, and to limit the peak package temperature of the smallest devices (e.g. SOT23, small LQFP, TopLEDs and passive components) to $T_{\text{peak}} \leq 260$ °C. In order to meet these requirements, a soak-type preheating, as well as a hat type soldering peak were necessary in the investigation. The soak-type preheating allowed the temperatures of the individual packages to be close to each other upon entering the peak zone (see Figure 7). The hat type form of the soldering peak was used to minimize the temperature differences between the individual packages during reflow soldering. After conducting the experiment, it was discovered that the hat type form of the soldering peak required a soak time of 40 s at $T_{\text{max}} - 5 \text{ K} = 255$ °C for the hottest devices on the PCB (see Figure 5).

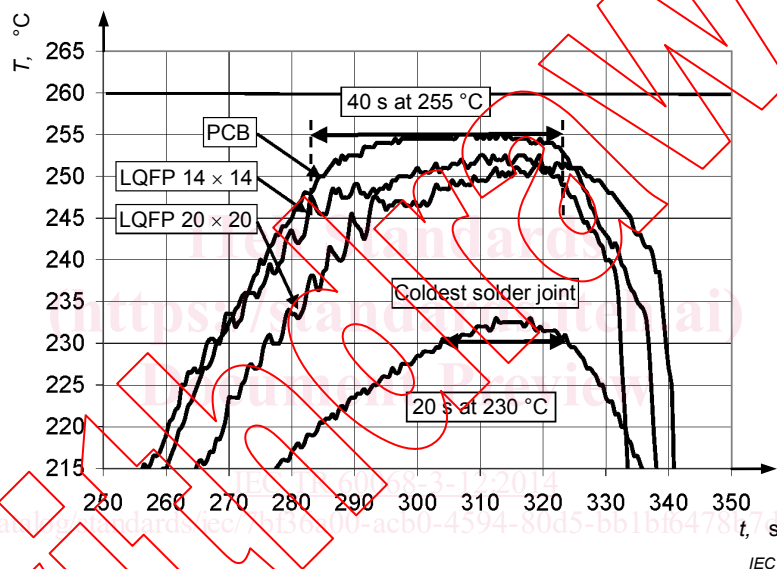


NOTE Temperature tolerances are included.

Figure 5 – Hat type peak profile with 40 s at $T_{\text{max}} - 5 \text{ K} = 255$ °C for the small devices and the PCB

5.2 Reflow oven investigation in Study B

Figure 6 shows temperature profiles on quad flat package (QFP) leads and a 1608 size surface mounting device (SMD) resistor using the same board but different reflow ovens. The reflow oven of Maker B, having more heating zones than the oven of Maker A, shows a wider temperature spread ΔT in the temperature profile than the oven of Maker A. Thus, the temperature spread ΔT does not depend primarily on the number of heating zones of the reflow oven but on the design of the reflow oven.

The peak reflow temperature for smallest components may vary according to the reflow oven being used. Also board size and board design are other factors affecting the peak reflow temperature.

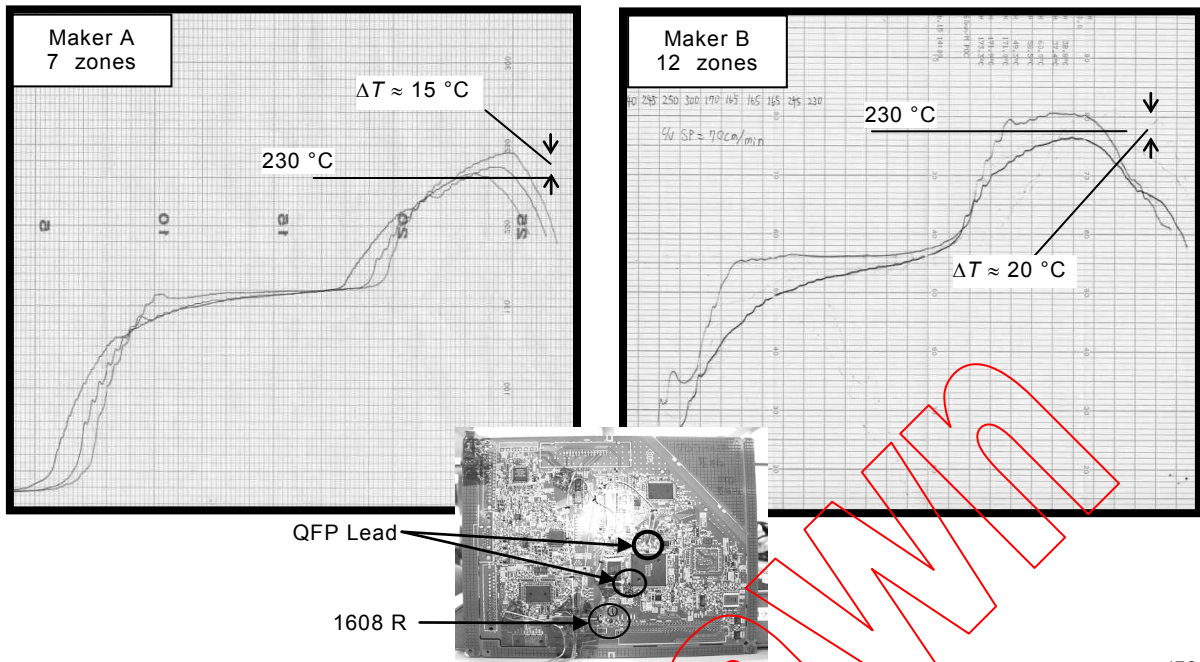

IEC

Figure 6 – ΔT by different reflow oven capabilities

6 Classification

6.1 Device classification in Study A

To classify the non-hermetic solid-state surface-mount devices into temperature groups with respect to the reflow peak, the heat capacity and heat conductivity should be taken into consideration. To simplify the study, the component similarity with respect to the composition (molded silicon) is taken into account and only the package volume and thickness are considered. In Figure 7, some typical temperature measurements of molded components using the described test board with a soak preheating and a hat-type reflow soldering peak are shown. The transportation speed was 850 mm/min and the temperature measurements were performed centrally on the top of the packages. In total, the temperature profiles for 19 characteristic molded package types and several passive and electromechanical devices were measured on a multiple heating zone reflow oven with full convection. Between the coldest solder joint and the PCB itself, a temperature difference of 13 K was measured. Small plastic components like small connectors, switches or TopLEDs showed even higher peak package temperatures with a temperature difference of 17 K from the coldest solder joint [3], [4].