

Standard Specification for Installation of Lathing and Furring to Receive Interior and Exterior Portland Cement-Based Plaster¹

This standard is issued under the fixed designation C 1063; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

1. Scope

- 1.1 This specification covers the minimum requirements for lathing and furring for the application of exterior and interior portland cement-based plaster as in Specification C 926.
- 1.2 Where a fire resistance rating is required for plastered assemblies and constructions, details of construction shall be in accordance with reports of fire tests of assemblies that have met the requirements of the fire rating imposed.
- 1.3 Where a specific degree of sound control is required for plastered assemblies and constructions, details of construction shall be in accordance with official reports of tests conducted in recognized testing laboratories in accordance with the applicable requirements of Test Method E 90.
- 1.4 The values stated in inch-pound units are to be regarded as the standard. The SI (metric) values given in parentheses are approximate and are provided for information purposes only.

2. Referenced Documents

2.1 ASTM Standards:

- A 526/A 526M Specification for Steel Sheet, Zinc-Coated (Galvanized) by the Hot-Dip Process, Commercial Quality²
- A 641/A 641M Specification for Zinc-Coated (Galvanized) Carbon Steel Wire³
- B 69 Specification for Rolled Zinc⁴
- B 221 Specification for Aluminum-Alloy Extruded Bars, Rods, Wire, Profiles, and Tubes⁵
- C 11 Terminology Relating to Gypsum and Related Building Materials and Systems⁶
- C 841 Specification for Installation of Interior Lathing and Furring⁶
- C 847 Specification for Metal Lath⁶
- ¹ This specification is under the jurisdiction of ASTM Committee C-11 on Gypsum and Related Building Materials and Systems and is the direct responsibility of Subcommittee C11.03 on Specifications for Application of Gypsum and Other Products in Assemblies.
- Current edition approved June 10, 1999. Published August 1999. Originally published as C 1063–86. Last previous edition C 1063–98.
 - ² Discontinued; see 1994 Annual Book of ASTM Standards, Vol 01.06.
 - ³ Annual Book of ASTM Standards, Vol 01.06.
 - ⁴ Annual Book of ASTM Standards, Vol 02.04.
 - ⁵ Annual Book of ASTM Standards, Vol 02.02.
 - ⁶ Annual Book of ASTM Standards, Vol 04.01.

- C 926 Specification for Application of Portland Cement-Based Plaster⁶
- C 933 Specification for Welded Wire Lath⁶
- C 954 Specification for Steel Drill Screws for the Application of Gypsum Panel Products or Metal Plastic Bases to Steel Studs from 0.033 in. (0.84 mm) to 0.112 in. (2.84 mm) in Thickness⁶
- C 1002 Specification for Steel Drill Screws for the Application of Gypsum Panel Products or Metal Plaster Bases⁵
- C 1032 Specification for Woven Wire Plaster Base⁶
- D 1784 Specification for Rigid Poly(Vinyl Chloride) (PVC) Compounds and Chlorinated Poly(Vinyl Chloride) (CPVC) Compounds⁷
- D 4216 Specification for Rigid Poly(Vinyl Chloride) (PVC) and Related Plastic Building Products Compounds⁸
- E 90 Test Method for Laboratory Measurement of Airborne-Sound Transmission Loss of Building Partitions⁹

3. Terminology

- 3.1 *Definitions*—For definitions relating to Ceilings and Walls, see Terminology C 11.
 - 3.2 Definitions of Terms Specific to This Standard:
- 3.2.1 *hangers*—wires or steel rods or straps used to support main runners for suspended ceilings beneath floor or roof constructions.
- 3.2.2 *inserts*—devices embedded in concrete structural members to provide a loop or opening for attachment of hangers.
 - 3.2.3 saddle tie—see Figs. 1 and 2.
- 3.2.4 *self-furring*—a metal plaster base manufactured with evenly-spaced indentations that hold the body of the lath approximately $\frac{1}{4}$ in. (6.4 mm) away from solid surfaces to which it is applied.
- 3.2.5 framing member, n—studs, joist, runners (track), bridging, bracing, and related accessories manufactured or supplied in wood or light gage steel.

4. Delivery of Materials

4.1 All materials shall be delivered in the original packages,

⁷ Annual Book of ASTM Standards, Vol 08.01.

⁸ Annual Book of ASTM Standards, Vol 08.02.

⁹ Annual Book of ASTM Standards, Vol 04.06.




FIG. 1 Saddle Tie

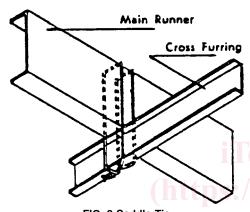


FIG. 2 Saddle Tie

containers, or bundles bearing the brand-name and manufacturer's (or supplier's) identification.

5. Storage of Materials

- 5.1 All materials shall be kept dry. Materials shall be stacked off the ground, supported on a level platform, and protected from the weather and surface contamination.
- 5.2 Materials shall be neatly stacked with care taken to avoid damage to edges, ends, or surfaces.
- 5.3 Paper backed metal plaster bases shall be handled carefully in delivery, storage, and erection to prevent puncturing or removal of paper.

6. Materials

- 6.1 Metal Plaster Bases:
- 6.1.1 Expanded Metal Lath—Specification C 847, galvanized.
 - 6.1.2 Wire Laths:
 - 6.1.2.1 Welded Wire Lath—Specification C 933.
 - 6.1.2.2 Woven Wire Lath—Specification C 1032.
 - 6.1.2.3 Paper Backed Plaster Bases—Specification C 847.
 - 6.2 Accessories:
- 6.2.1 General—All accessories shall have perforated or expanded flanges or clips shaped to permit complete embedment in the plaster, to provide means for accurate alignment, and to secure attachment of the accessory to the underlying surface. Accessories shall be designed to receive application of the specified plaster thickness.

6.2.2 Accessories shall be fabricated from Zinc Alloy (99 % pure zinc), galvanized (zinc coated) steel, rigid PVC or CPVC plastic, or anodized aluminum alloy. See Specification B 221. (See Table 1 for minimum allowable thicknesses).

Note 1—The selection of an appropriate type of material for accessories shall be determined by applicable surrounding climatic and environmental conditions specific to the project location, such as salt air, industrial pollution, high moisture, or humidity.

- 6.2.3 *Steel*—Specification A 526 and shall have a G60 coating.
 - 6.2.4 PVC Plastic—Specification D 1784 or D 4216.
 - 6.2.5 Zinc Alloy—Specification B 69, 99 % pure zinc.
- 6.2.6 Thickness of base material shall be as shown in Table 1.
- 6.2.7 Cornerite—1.75 lb/yd²(0.059 kg/m²), galvanized expanded metal lath, galvanized, 1.7 lb/yd²(0.057 kg/m²) galvanized woven or welded wire fabric of 0.0410 in. (1.04 mm) wire. When shaped for angle reinforcing, it shall have outstanding flanges (legs) of not less than 2 in. (51 mm).
- 6.3 Channels—Shall be cold-formed from steel with minimum 33 000 psi (228 MPa) yield strength and 0.0538 in. (1.37 mm) minimum bare steel thickness. Channel shall have a protective coating conforming to Specification A 653–G60, or have a protective coating with an equivalent corrosion resistance for exterior applications, or shall be coated with a rust inhibitive paint, for interior applications, and shall have the following minimum weights in pounds per 1000 linear feet (kg/m).

| Sizes, in. (mm) | Weight, lb/1000 ft (kg/m) | Flange Width, in. (mm) |
|-----------------|---------------------------|------------------------|
| 3/4 (19) | 277 (0.412) | 1/2 (13) |
| 1½ (38) | 414 (0.616) | 1/2 (13) |
| 2 (51) | 506 (0.753) | 1/2 (13) |
| 21/2 (64) | 597 (0.888) | 1/2 (13) |

Note 2—Channels used in areas subject to corrosive action of salt air shall be hot-dipped galvanized, G60 coating.

- 6.3.1 External Corner Reinforcement—Expanded lath, welded wire, or woven wire mesh bent to approximately 90° used to reinforce portland cement stucco at external corners. This accessory shall be fully embedded in the stucco.
- 6.3.2 Foundation Weep Screed—Accessory used to terminate portland cement based stucco at the bottom of exterior walls. This accessory shall have a sloped, solid, or perforated, ground or screed flange to facilitate the removal of moisture from the wall cavity and a vertical attachment flange not less than $3\frac{1}{2}$ in. (89 mm) long.
- 6.4 *Wire*—As specified in Specification A 641 with a Class I zinc coated (galvanized), soft temper steel. Wire diameters (uncoated) specified herein correspond with United States Steel Wire Gage numbers as follows:

TABLE 1 Minimum Thickness of Accessories

| A 2222227/ | Base Material, in. (mm) | | | |
|----------------|-------------------------|---------------|--------------|--|
| Accessory | Steel | Zinc Alloy | P.V.C. | |
| Corner Beads | 0.0172 (0.44) | 0.0207 (0.53) | 0.035 (0.89) | |
| Casing Beads | 0.0172 (0.44) | 0.0207 (0.53) | 0.035 (0.89) | |
| Weep Screeds | 0.0172 (0.44) | 0.0207 (0.53) | 0.050 (1.27) | |
| Control Joints | 0.0172 (0.44) | 0.018 (0.46) | 0.050 (1.27) | |



| Wire Gage | Diameter (in.) | |
|----------------------|----------------|------|
| (US Steel Wire Gage) | | mm |
| No. 20 | 0.0348 | .88 |
| No. 19 | 0.0410 | 1.04 |
| No. 18 | 0.0475 | 1.21 |
| No. 17 | 0.0540 | 1.37 |
| No. 16 | 0.0625 | 1.59 |
| No. 14 | 0.0800 | 2.03 |
| No. 13 | 0.0915 | 2.32 |
| No. 12 | 0.1055 | 2.68 |
| No. 11 | 0.1205 | 3.06 |
| No. 10 | 0.1350 | 3.43 |
| No. 9 | 0.1483 | 3.77 |
| No. 8 | 0.1620 | 4.12 |
| | | |

- 6.5 *Rod and Strap Hangers*—Mild steel, zinc or cadmium plated, or protected with a rust-inhibiting paint.
- 6.6 Clips—Form from steel wire, Specification A 641 zinc-coated (galvanized), Specification A 641 or steel sheet, Specification A 526, depending on use and manufacturer's requirements.

6.7 Fasteners:

- 6.7.1 *Nails*—For attaching metal plaster bases to wood supports, 0.1205-in. 11 gage (3.06-mm) diameter, 7/16-in. (11.1-mm) head, barbed, galvanized roofing nails or galvanized common nails.
- 6.7.1.1 Nails for attaching metal plaster bases to solid substrates shall be not less than ³/₄ in. (19 mm) long.
- 6.7.2 Screws for attaching metal plaster base shall be fabricated in accordance with either Specification C 954 or C 1002 and shall have a 7/16 in. (11.1 mm) diameter pan wafer

head and a 0.120 in. (3.0 mm) diameter shank. Screws used for attachment to metal framing members shall be self-drilling and self-tapping. Screws used for attachment to wood framing members shall be sharp-point.

7. Installation

- 7.1 Workmanship—Metal furring and lathing shall be erected so that the finished plaster surfaces are true to line (allowable tolerance of ½ in. [6.4 mm] in 10 ft [3.05 m]), level, plumb, square, or curved as required to receive the specified plaster thickness.
 - 7.2 Hangers and Inserts:
- 7.2.1 Hangers shall be of ample length and shall conform to the requirements of Table 2 both as to size and maximum area to be supported, except as modified in this section.
- 7.2.2 When 1 by $\frac{3}{16}$ -in. (25 by 4.8-mm) flat inserts and hangers are used, $\frac{7}{16}$ -in. (11.1-mm) diameter holes shall be provided on the center line at the lower end of the insert and upper end of the hanger to permit the attachment of the hanger to the insert. The edge of the holes in both the inserts and the hangers shall be not less than $\frac{3}{8}$ in. (9.5 mm) from the ends.
- 7.2.3 In concrete, hangers shall be attached to inserts embedded in the concrete or to other attachment devices designed for this purpose and able to develop full strength of the hanger.
- 7.2.4 Flat, steel hangers shall be bolted to 1 by ³/₁₆-in. (25 by 4.8-mm) inserts with ³/₈-in. (9.5-mm) diameter round-head

TABLE 2 Allowable Support or Hanger Wire Spacing ft-in. (mm) and Cold-Rolled Channel Main Runner Spans, ft-in. (mm)¹⁻¹⁰

Note—1 in. = 25.4 mm; 1 ft² = 0.093 m²

| | Member Weight, lb/1000 ft (kg/m) | | Uniform Load = 12 psf (0.479 kPa) Member Spacing, in. (mm) | | | | |
|--------|-------------------------------------|--------------------------------|---|-----------------|-----------------------|--------------------|-------------|
| | | Span Condition ^{9,10} | | | | | |
| | is/1000 it (kg/iii) | | 24 (610) | 36 (914) | 48 (1220) | 60 (1520) | 72 (1830) |
| | | .ai/catalog/stand | ards/sist/f927 | Allowable Hange | er Wire or Support Sp | acing, ft-in. (mm) | m-c1063-9 |
| 11/2 | 414 | Single | 3-6 (1070) | 3-1 (940) | 2-9 (840) | 2-9 (790) | 2-5 (740) |
| (38.1) | (0.615) | 2 or More | 4-11 (1500) | 4-2 (1270) | 3-7 (1090) | 3-2 (970) | 2-11 (890) |
| 2 | 506 | Single | 3-9 (1140) | 3-3 (990) | 3-0 (910) | 2-9 (840) | 2-8 (810) |
| (50.8) | (0.753) | 2 or More | 5-2 (1570) | 4-6 (1370) | 4-1 (1240) | 3-10 (1170) | 3-7 (1090) |
| 21/2 | 597 | Single | 3-11 (1190) | 3-5 (1040) | 3-2 (970) | 2-11 (890) | 2-9 (840) |
| (63.5) | (0.888) | 2 or More | 5-5 (1650) | 4-9 (1450) | 4-4 (1320) | 4.0 (1220) | 3-10 (1170) |
| | | | Uniform Load = 15 psf (0.287 kPa) | | | | |
| | Member Weight, lb/1000 ft (kg/m) | Span Condition ^{9,10} | | Me | ember Spacing, in. (n | nm) | |
| | is/ recent (ng/m/ | _ | 24 (610) | 36 (914) | 48 (1220) | 60 (1520) | 72 (1830) |
| 11/2 | 414 | Single | 3-3 (990) | 2-10 (860) | 2-7 (790) | 2-4 (710) | 2-2 (660) |
| (38.1) | (0.616) | 2 or More | 4-6 (1370) | 3-8 (1120) | 3-2 (970) | 2-10 (860) | 2-7 (790) |
| 2 | 506 | Single | 3-6 (1070) | 3-1 (940) | 2-10 (880) | 2-7 (790) | 2-5 (740) |
| (50.8) | (0.753) | 2 or More | 4-10 (1470) | 4-3 (1300) | 3-10 (1170) | 3-6 (1070) | 3-3 (990) |
| 21/2 | 597 | Single | 3-8 (1120) | 3-3 (990) | 2-11 (890) | 2-9 (840) | 2-7 (790) |
| (63.5) | (0.888) | 2 or More | 5-0 (1520) | 4-5 (1350) | 4-0 (1220) | 3.9 (1140) | 3-6 (1070) |

Allowable Spans Notes:

¹ Bare metal thickness of cold-rolled main runners shall be not less than 0.0538 in. (1.367 mm).

 $^{^2}$ Inside corner radii shall not be greater than $^{1\!/\!_{8}}\,$ in. (3.19 mm).

³ Spans based on upper flange of main runners laterally unbraced.

⁴ Maximum deflection limited to 1/360 of the span length.

⁵ Steel yield stress, Fy, shall be not less than 33 000 psi (228 MPa).

⁶ Uniform load 12 psf (dry density) shall be used for portland cement plaster ceilings with plaster thicknesses up to % in. (22 mm) and 15 psf shall be used for ceilings with plaster thicknesses over % in. (22 mm) and not more than 1-1/4 in. (32 mm).

⁷ "2 or More" spans refers to two or more continuous, equal spans.

⁸ For the "2 or More" span condition, listed spans represent the center-to-center distance between adjacent supports.

⁹ These tables are designed for dead loads. Specific conditions such as exterior installations in high wind areas require additional engineering.

¹⁰ Where uplift resistance is required for suspended ceilings to resist negative forces, the architect or engineer of record shall select the method to be used.

stove bolts. (See Fig. 3.)

7.2.5 The nuts of the bolts shall be drawn up tight.

Note 3—Hangers required to withstand upward wind pressures shall be of a type to resist compression. Struts of formed channels shall be permitted.

- 7.3 Installation of Hangers for Suspended Ceilings Under Wood Constructions—Hangers shall be attached to supports by any of the following methods:
- 7.3.1 A hole shall be drilled through the wood member not less than 3 in. (76 mm) above the bottom with the upper end of the wire hanger passed through the hole and twisted three times around itself. See Fig. 4.
- 7.3.2 Three 12d nails shall be driven, on a downward slant, into the sides of the wood member with not less than $1\frac{1}{4}$ in. (31.8 mm) penetration and not less than 5 in. (127 mm) from the bottom edges, and not more than 36 in. (914 mm) on the center with the upper end of the wire hanger wrapped around the nails and twisted three times around itself. See Fig. 5.
- 7.3.3 A loop shall be formed in the upper end of the wire hanger and secured to the wood member by four 1½-in. (38.1-mm), not less than 9 gage, 0.1483-in. (3.77-mm) diameter wire staples driven horizontally or on a downward slant into the sides of the wood members, three near the upper end of the loop and the fourth to fasten the loose end. See Fig. 6.
- (38.1 mm) and are spaced more than 4 ft (1.2 m) on center, $1\frac{1}{2}$ in. (38.1-mm) No. 1/0 (0.3065 in.) (7.78 mm) eye screws, or equivalent, spaced not more than 3 ft (0.9 m) on centers shall

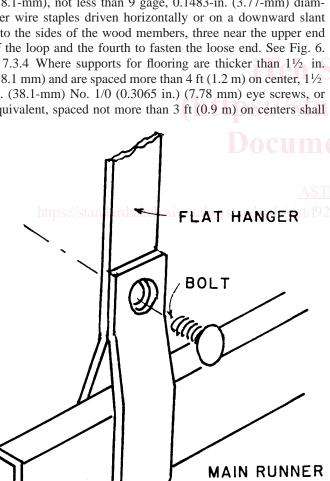


FIG. 3 Flat Hanger Attached to Main Runner Using Round-Head Stove Bolt

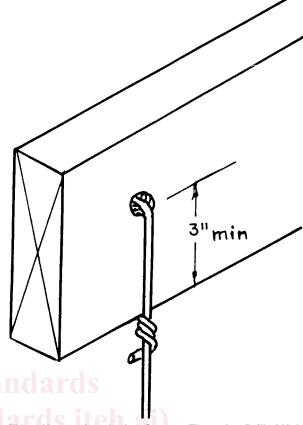


FIG. 4 Hanger Attached to Support Through a Drilled Hole

be screwed into the flooring supports with the upper end of the wire hanger inserted through the eye screws and twisted three times around itself.

- 7.3.5 Two holes shall be drilled in the upper end of the flat hangers and nailed to the sides of the wood members with 12d nails driven through the holes and clinched. Nails shall be not less than 3 in. (76 mm) above the bottom edge of the framing member. See Fig. 7.
 - 7.4 Attachment of Hangers to Main Runners:
- 7.4.1 Wire hangers shall be saddle-tied to the runners. See Fig. 1.
- 7.4.2 Smooth or threaded rod hangers shall be fastened to the runners with special attachments appropriate to the design.
- 7.4.3 The lower ends of flat hangers shall be bolted to the main runners, or bent tightly around the runners and carried up and above the runners and bolt to the main part of the hanger. Bolts shall be 3/8-in. (9.5-mm) diameter, round-head stove bolts. See Fig. 3.
 - 7.5 Installation of Main Runners:
- 7.5.1 Minimum sizes and maximum spans and spacings of main runners for the various spans between hangers or other supports shall be in accordance with the requirements of Table
- 7.5.2 A clearance of not less than 1 in. (25 mm) shall be maintained between the ends of the main runners and the abutting masonry or the concrete walls, partitions, and columns. Where special conditions require that main runners let into abutting masonry or concrete construction, within such constructions maintain a clearance of not less than 1 in. (25