



SLOVENSKI STANDARD
SIST ISO 4696-2:2000
01-junij-2000

Železne rude -- Statični preskus za nizkotemperaturno redukcijo-disintegracijo -- Del 2: Reakcija s CO

Iron ores -- Static test for low-temperature reduction-disintegration -- Part 2: Reaction with CO

iTeh STANDARD PREVIEW

Minerais de fer -- Essai statique de désagrégation par réduction à basse température -- Partie 2: Réaction avec CO

[SIST ISO 4696-2:2000](https://standards.iteh.ai/catalog/standards/sist/63af53aa-1901-4f90-b08a-90b01a2a55e9/sist-iso-4696-2-2000)

Ta slovenski standard je istoveten z: **ISO 4696-2:1998**

ICS:

73.060.10 Železove rude Iron ores

SIST ISO 4696-2:2000 en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST ISO 4696-2:2000

<https://standards.iteh.ai/catalog/standards/sist/63af53aa-1901-4f90-b08a-90b01a2a55e9/sist-iso-4696-2-2000>

INTERNATIONAL STANDARD

ISO
4696-2

First edition
1998-08-01

Iron ores — Static test for low-temperature reduction-disintegration —

Part 2: Reaction with CO

*Minerais de fer — Essai statique de désagrégation par réduction à basse
température —*
Partie 2: Réaction avec CO

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST ISO 4696-2:2000](https://standards.iteh.ai/catalog/standards/sist/63af53aa-1901-4f90-b08a-90b01a2a55e9/sist-iso-4696-2-2000)

<https://standards.iteh.ai/catalog/standards/sist/63af53aa-1901-4f90-b08a-90b01a2a55e9/sist-iso-4696-2-2000>



Reference number
ISO 4696-2:1998(E)

ISO 4696-2:1998(E)

Contents

| | |
|---|---|
| 1 Scope | 1 |
| 2 Normative references | 1 |
| 3 Principle | 1 |
| 4 Apparatus | 2 |
| 5 Test conditions | 4 |
| 5.1 Composition of reducing gas | 4 |
| 5.2 Flow rate of reducing gas | 4 |
| 5.3 Temperature of test | 5 |
| 6 Sampling and sample preparation | 5 |
| 7 Procedure | 5 |
| 7.1 Number of determinations | 5 |
| 7.2 Test portion | 5 |
| 7.3 Reduction | 5 |
| 7.4 Tumbling and sieving | 6 |
| 8 Expression of results | 6 |
| 9 Test report | 6 |
| 10 Verification | 7 |
| Annex A (normative) Repeatability and number of tests | 8 |

STANDARD PREVIEW
(standards.iteh.ai)

[SIST ISO 4696-2:2000](https://standards.iteh.ai/catalog/standards/sist/63af53aa-1901-4f90-b08a-90001a2a55e9/sist-iso-4696-2-2000)

<https://standards.iteh.ai/catalog/standards/sist/63af53aa-1901-4f90-b08a-90001a2a55e9/sist-iso-4696-2-2000>

© ISO 1998

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case postale 56 • CH-1211 Genève 20 • Switzerland
Internet iso@iso.ch

Printed in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 4696-2 was prepared by Technical Committee ISO/TC 102, *Iron ores*, Subcommittee SC 3, *Physical testing*.

Together with part 1, this part of ISO 4696 cancels and replaces ISO 4696:1984, which has been technically revised.

ISO 4696 consists of the following parts, under the general title *Iron ores — Static test for low-temperature reduction-disintegration*:

— Part 1: Reaction with CO, CO₂ and H₂

— Part 2: Reaction with CO

ITEH STANDARD PREVIEW
(standards.iteh.ai)

Annex A forms an integral part of this part of ISO 4696.

[SIST ISO 4696-2:2000](https://standards.iteh.ai/catalog/standards/sist/63af53aa-1901-4f90-b08a-90b01a2a55e9/sist-iso-4696-2-2000)

<https://standards.iteh.ai/catalog/standards/sist/63af53aa-1901-4f90-b08a-90b01a2a55e9/sist-iso-4696-2-2000>

Introduction

This part of ISO 4696 describes a test method for evaluating the disintegration behaviour of iron ores reduced in a fixed bed under specific conditions. The specific features of this test are:

- a) isothermal reduction in a fixed bed at 550 °C;
- b) tumbling the reduced sample at room temperature;
- c) measurement of the disintegration of a test portion by sieving after tumbling.

The results of this test should be considered in conjunction with the results of other tests, particularly those showing the physical behaviour of materials during reduction.

ISO 4696-1 describes an alternative method adopting different test conditions.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST ISO 4696-2:2000](https://standards.iteh.ai/catalog/standards/sist/63af53aa-1901-4f90-b08a-90b01a2a55e9/sist-iso-4696-2-2000)

<https://standards.iteh.ai/catalog/standards/sist/63af53aa-1901-4f90-b08a-90b01a2a55e9/sist-iso-4696-2-2000>

Iron ores — Static test for low-temperature reduction-disintegration —

Part 2: Reaction with CO

WARNING — This part of ISO 4696 may involve hazardous materials, operations or equipment. It does not purport to address all the safety problems, if any, associated with its use. It is the responsibility of the user of this part of ISO 4696 to establish appropriate safety and health practices and to determine the applicability of any regulatory limitations prior to use.

1 Scope

This part of ISO 4696 specifies a method for testing the disintegration of iron ores by tumbling, at room temperature, a test portion that has been reduced in a fixed bed at a temperature of 550 °C.

The method is applicable to natural iron ores and to iron ore agglomerates such as pellets or sinter.

2 Normative references

SIST ISO 4696-2:2000

[https://standards.iteh.ai/catalog/standards/sist/63af53aa-1901-4f90-b08a-](https://standards.iteh.ai/catalog/standards/sist/63af53aa-1901-4f90-b08a-901b01a2b559/iso-4696-2:2000)

The following standards contain provisions which, through reference in this text, constitute provisions of this part of ISO 4696. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this part of ISO 4696 are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 3082:1998, *Iron ores — Sampling and sample preparation procedures*.

ISO 3310-1:—¹⁾, *Test sieves — Requirements and tests — Part 1: Metal wire cloth sieves*.

ISO 3310-2:—²⁾, *Test sieves — Requirements and tests — Part 2: Perforated metal plate sieves*.

3 Principle

A test portion with a specified size range is subjected to static reduction at a temperature of 550 °C using reducing gas consisting of carbon monoxide (CO) and nitrogen (N₂).

After 30 min reduction time, the test portion is cooled to a temperature below 100 °C and tumbled by using a small tumbler drum for 900 revolutions in total. It is then sieved with a test sieve having square mesh apertures of 2,8 mm.

1) To be published. (Revision of ISO 3310-1:1990)

2) To be published. (Revision of ISO 3310-2:1990)

The reduction-disintegration index (RDI- $2_{-2,8}$) is calculated as a quantitative measure of the degree of disintegration of an iron ore that has been reduced and then tumbled: the percentage by mass of material less than 2,8 mm is related to the total mass of the test portion after reduction and before tumbling.

4 Apparatus

The apparatus shall consist of the following:

- a system to supply and regulate the gases;
- a reduction tube;
- an electrically heated furnace to heat the sample to the specified temperature;
- a tumbler drum;
- test sieves;
- a weighing device.

4.1 Reduction tube, made of non-scaling, heat-resisting metal to withstand a temperature of greater than 600 °C. The diameter of the sample bed shall be 75 mm \pm 1 mm.

Figure 1 shows an example of such a reduction tube.

The test portion may be placed on a perforated plate or, if desired, on balls of alumina on the perforated plate, in order to ensure a uniform flow of gas through the test portion.

4.2 Furnace, having a heating capacity sufficient to maintain the entire test portion and the gas entering the bed at 550 °C, and being equipped with a heating element suitable for the specified temperature.

4.3 Tumbler drum, consisting of a vessel having an internal diameter of 130 mm and an inside length of 200 mm.

Two equally spaced steel lifters 200 mm long, 20 mm wide and 2 mm thick shall be mounted longitudinally inside the drum. These may be mounted on a frame that can be inserted inside the vessel from one end.

One end of the vessel shall be closed and the other open. A close-fitting lid shall be held in place on the opening to ensure a dust-tight seal.


Figure 2 shows an example of such a tumbler drum.

4.4 Test sieves, having square mesh apertures of the following nominal sizes in accordance with ISO 3310-1 or ISO 3310-2:

22,4 mm; 20,0 mm; 16,0 mm; 12,5 mm; 10,0 mm; 2,8 mm.

4.5 Weighing device, of adequate load capacity and accurate to 0,1 g.

Dimensions in millimetres

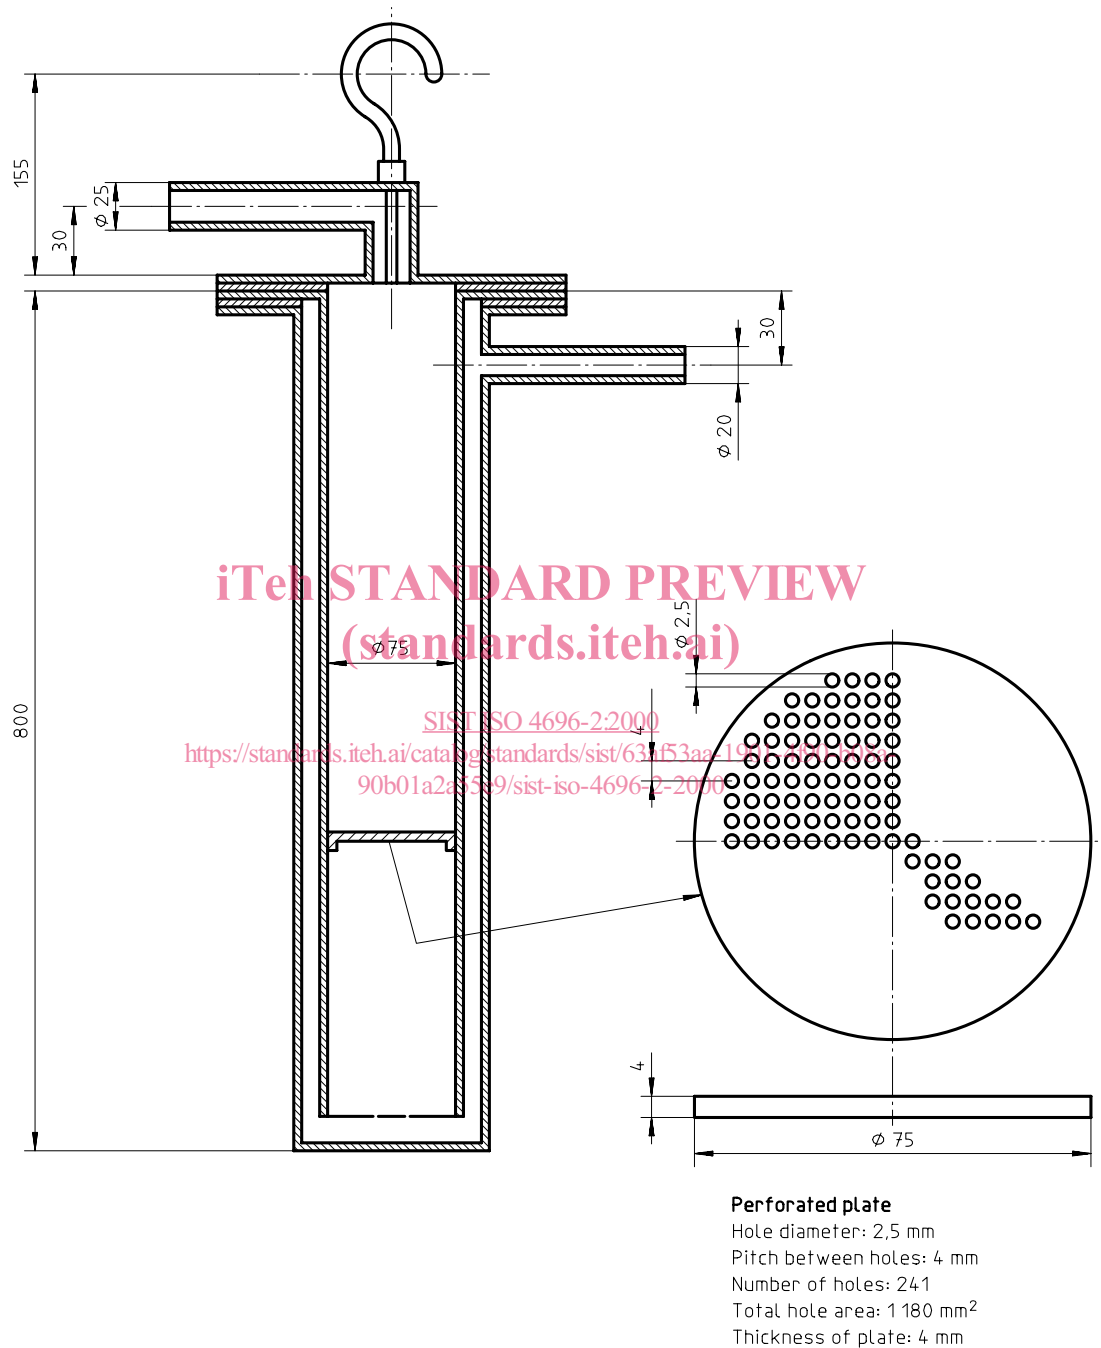

NOTE — The dimensions not specified in clause 4 are shown for information only.

Figure 1 — Example of reduction tube