

INTERNATIONAL STANDARD

NORME INTERNATIONALE



**Measurement procedures for materials used in photovoltaic modules –
Part 5-1: Edge seals – Suggested test methods for use with edge seal materials**

**Procédures de mesure des matériaux utilisés dans les modules
photovoltaïques –**

**Partie 5-1: Joints d'étanchéité périphériques – Méthodes d'essai suggérées pour
l'utilisation des matériaux de joints d'étanchéité périphériques**



THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2020 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de l'IEC ou du Comité national de l'IEC du pays du demandeur. Si vous avez des questions sur le copyright de l'IEC ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de l'IEC de votre pays de résidence.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

Electropedia - www.electropedia.org

The world's leading online dictionary on electrotechnology, containing more than 22,000 terminological entries in English and French, with equivalent terms in 16 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Glossary - std.iec.ch/glossary

67,000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

A propos de l'IEC

La Commission Electrotechnique Internationale (IEC) est la première organisation mondiale qui élabore et publie des Normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications IEC

Le contenu technique des publications IEC est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

Recherche de publications IEC -

webstore.iec.ch/advsearchform

La recherche avancée permet de trouver des publications IEC en utilisant différents critères (numéro de référence, texte, comité d'études,...). Elle donne aussi des informations sur les projets et les publications remplacées ou retirées.

IEC Just Published - webstore.iec.ch/justpublished

Restez informé sur les nouvelles publications IEC. Just Published détaille les nouvelles publications parues. Disponible en ligne et une fois par mois par email.

Service Clients - webstore.iec.ch/csc

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions contactez-nous: sales@iec.ch.

Electropedia - www.electropedia.org

Le premier dictionnaire d'électrotechnologie en ligne au monde, avec plus de 22 000 articles terminologiques en anglais et en français, ainsi que les termes équivalents dans 16 langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International (IEV) en ligne.

Glossaire IEC - std.iec.ch/glossary

67 000 entrées terminologiques électrotechniques, en anglais et en français, extraites des articles Termes et Définitions des publications IEC parues depuis 2002. Plus certaines entrées antérieures extraites des publications des CE 37, 77, 86 et CISPR de l'IEC.

INTERNATIONAL STANDARD

NORME INTERNATIONALE



**Measurement procedures for materials used in photovoltaic modules –
Part 5-1: Edge seals – Suggested test methods for use with edge seal materials**
(standards.iteh.ai)

**Procédures de mesure des matériaux utilisés dans les modules
photovoltaïques –
Partie 5-1: Joints d'étanchéité périphériques – Méthodes d'essai suggérées
pour l'utilisation des matériaux de joints d'étanchéité périphériques**

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

COMMISSION
ELECTROTECHNIQUE
INTERNATIONALE

ICS 27.160

ISBN 978-2-8322-7919-9

**Warning! Make sure that you obtained this publication from an authorized distributor.
Attention! Veuillez vous assurer que vous avez obtenu cette publication via un distributeur agréé.**

CONTENTS

FOREWORD.....	3
1 Scope.....	5
2 Normative references	5
3 Terms, definitions and symbols.....	6
3.1 Terms and definitions.....	7
3.2 Symbols.....	7
4 Recommended tests	7
4.1 General.....	7
4.2 Moisture permeation properties.....	7
4.2.1 Moisture breakthrough time	7
4.2.2 Fickian materials	7
4.2.3 Non-Fickian materials	8
4.3 Electrical properties	8
4.3.1 Dielectric strength of the film	8
4.3.2 Volume resistivity	9
4.3.3 Comparative tracking index	9
4.4 Adhesion testing	9
4.4.1 General.....	9
4.4.2 Lap shear strength.....	9
4.4.3 “T” peel test.....	10
4.4.4 90° peel test	11
4.4.5 Butt joint test	11
4.5 Durability of the materials.....	12
4.5.1 Relative thermal endurance.....	12
4.5.2 Dielectric strength degradation	12
4.5.3 Accelerated stress testing.....	13
4.6 Flame resistance	15
4.7 Coefficient of thermal expansion	15
4.8 Rheological properties	15
4.8.1 Complex shear modulus	15
4.8.2 Melt flow rate.....	15
4.9 Other data	15
5 Test report.....	15
Bibliography.....	17
Figure 1 – Lap shear test sample for proving cemented joint.....	10
Figure 2 –Photograph (a)) and schematic (b)) of a z-tensile adhesion test specimen	12
Figure 3 – Schematic of test structure for RTI or RTE dielectric durability testing.....	13
Figure 4 – Test flow for cemented joint evaluation	14

INTERNATIONAL ELECTROTECHNICAL COMMISSION

—————

**MEASUREMENT PROCEDURES FOR MATERIALS
USED IN PHOTOVOLTAIC MODULES –**

**Part 5-1: Edge seals –
Suggested test methods for use with edge seal materials**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 62788-5-1 has been prepared by IEC technical committee 82: Solar photovoltaic energy systems.

The text of this International Standard is based on the following documents:

FDIS	Report on voting
82/1658/FDIS	82/1689/RVD

Full information on the voting for the approval of this International Standard can be found in the report on voting indicated in the above table.

This document has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all parts in the IEC 62788 series, published under the general title *Measurement procedures for materials used in photovoltaic modules*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under "<http://webstore.iec.ch>" in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[IEC 62788-5-1:2020](#)

<https://standards.iteh.ai/catalog/standards/sist/5d2076ef-c88d-4512-8a04-6055152c8669/iec-62788-5-1-2020>

MEASUREMENT PROCEDURES FOR MATERIALS USED IN PHOTOVOLTAIC MODULES –

Part 5-1: Edge seals – Suggested test methods for use with edge seal materials

1 Scope

This part of IEC 62788 provides procedures for standardized test methods for evaluating the properties of materials designed to be used as edge seals. When modules are constructed with impermeable (or extremely low permeability) front- and backsheets designed to protect moisture-sensitive photovoltaic (PV) materials, there is still the possibility for moisture to get in from the sides. This moisture ingress pathway can be restricted by using a low-diffusivity material around the perimeter of a module between the impermeable front- and backsheets. Alternatively, it can be desirable to use a low-diffusivity encapsulant, which may significantly reduce moisture ingress over the lifetime of the module, and to evaluate it in a similar way to an edge seal material.

In addition to restricting moisture ingress, edge seal materials also provide electrical insulation. To perform these functions, edge seal materials are relied upon to adhere well.

The test methods described in this document are intended to be used to standardize the way edge seals are evaluated. Only some of these tests are applied for IEC 61215 and IEC 61730, and that status depends on the specific design. It is not required that all of these tests be performed, but that if these measurements are made that they be performed as outlined here.

<https://standards.iteh.ai/catalog/standards/sist/5d2076ef-c88d-4512-8a04-6055152c8669/iec-62788-5-1-2020>

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60112, *Method for the determination of the proof and the comparative tracking indices of solid insulating materials*

IEC 60243-1:2013, *Electrical strength of insulating materials – Test methods – Part 1: Tests at power frequencies*

IEC 60243-2:2013, *Electrical strength of insulating materials – Test methods – Part 2: Additional requirements for tests using direct voltage*

IEC 60216-5, *Electrical insulating materials – Thermal endurance properties – Part 5: Determination of relative thermal endurance index (RTE) of an insulating material*

IEC 60664-1, *Insulation coordination for equipment within low-voltage systems – Part 1: Principles, requirements and tests*

IEC 60695-11-10, *Fire hazard testing – Part 11-10: Test flames – 50 W horizontal and vertical flame test methods*

IEC 61730-2:2016, *Photovoltaic (PV) module safety qualification – Part 2: Requirements for testing*

IEC TS 61836, *Solar photovoltaic energy systems – Terms, definitions and symbols*

IEC 62788-1-2, *Measurement procedures for materials used in photovoltaic modules – Part 1-2: Encapsulants – Measurement of volume resistivity of photovoltaic encapsulants and other polymeric materials*

IEC TS 62788-2:2017, *Measurement procedures for materials used in photovoltaic modules – Part 2: Polymeric materials – Frontsheets and backsheets*

IEC 62788-6-2, *Measurement procedures for materials used in photovoltaic modules – Part 6-2: General Tests – Moisture permeation testing with polymeric materials*

ISO 62, *Plastics – Determination of water absorption*

ISO 1133-1, *Determination of the melt mass-flow rate (MFR) and melt volume-flow rate (MVR) of thermoplastics – Part 1: Standard method*

ISO 4587, *Adhesives – Determination of tensile lap-shear strength of rigid-to-rigid bonded assemblies*

ISO 6721-6, *Plastics – Determination of dynamic mechanical properties – Part 6: Shear vibration – Non-resonance method*

ISO 11359-2, *Plastics – Thermomechanical analysis (TMA) – Part 2: Determination of coefficient of linear thermal expansion and glass transition temperature*

ISO 11443, *Plastics – Determination of the fluidity of plastics using capillary and slit-die rheometers*

ISO 15512, *Plastics – Determination of water content*

UL 746B, *Polymeric materials – Long term property evaluations*

UL 746C, *Polymeric materials – Use in electrical equipment evaluations*

ASTM D3835–08, *Standard test methods determination of properties of polymeric materials by means of a capillary rheometer*

ASTM D6869–03, *Standard test method for coulometric and volumetric determination of moisture in plastics using the Karl Fischer reaction (the reaction of iodine with water)*

ASTM D7191–10, *Standard test method for determination of moisture in plastics by relative humidity sensor*

3 Terms, definitions and symbols

For the purposes of this document, the terms and definitions given in IEC TS 61836 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1 Terms and definitions

3.1.1

edge seal

polymeric material designed to be placed between two impermeable (or with extremely low permeability) frontsheet and backsheet materials to restrict moisture ingress from the sides

3.1.2

Fickian

material for which the diffusivity is constant, independent of the concentration of the permeant within the experimental uncertainty

3.2 Symbols

$t_{10\%}$	time required for an edge seal to reach 10 % of its equilibrium water vapour transmission rate [h]
$K_{10\%}$	10 % moisture ingress breakthrough proportionality constant [$\text{cm}\cdot\text{h}^{-0,5}$]
$K_{o10\%}$	Arrhenius prefactor for $K_{10\%}$ [$\text{cm}\cdot\text{h}^{-0,5}$]
$Ea_{K_{10\%}}$	Arrhenius activation energy for $K_{10\%}$ [$\text{cm}\cdot\text{h}^{-0,5}$]
X	edge seal film thickness [mm]
D	Fickian diffusivity at a given temperature [cm^2/s]
D_o	Arrhenius prefactor for diffusivity [cm^2/s]
Ea_D	Arrhenius activation energy for diffusivity [kJ/mol]
S	maximum absorption of moisture in a material in equilibrium with liquid water [g/cm^3]
S_{IR}	irreversible absorption capacity of moisture in a material [g/cm^3]
S_o	Arrhenius prefactor for solubility [g/cm^3]
Ea_S	Arrhenius activation energy for solubility [kJ/mol]
P	permeability [$\text{g}\cdot\text{mm}\cdot\text{m}^{-2}\cdot\text{day}^{-1}$]
P_o	Arrhenius prefactor for permeability [$\text{g}\cdot\text{mm}\cdot\text{m}^{-2}\cdot\text{day}^{-1}$]
Ea_p	Arrhenius activation energy for permeability [kJ/mol]

4 Recommended tests

4.1 General

This document is intended to be used as a guideline for presenting edge seal data. When the properties outlined in this document are reported, they shall be reported as measured using the outlined methods. A datasheet may include more data, or less data, than the list of tests outlined. The tests outlined are recommendations only.

4.2 Moisture permeation properties

4.2.1 Moisture breakthrough time

10 % moisture ingress breakthrough proportionality constant [$K_{10\%}$, ($X = K_{10\%} \cdot t_{10\%}^{1/2}$)] at $(85 \pm 2)^\circ\text{C}$ as determined in IEC 62788-6-2. Include activation energy if available. For a Fickian material, $K_{10\%} = 3,89 \cdot D^{1/2}$.

4.2.2 Fickian materials

Permeability (P) at $(85 \pm 2)^\circ\text{C}$ steady state. Include activation energy (Ea_p) if available.

If the material is Fickian, report the diffusivity (D) at $(85 \pm 2)^\circ\text{C}$ and activation energy for diffusivity (E_{aD}) as determined from IEC 62788-6-2. Also indicate the temperature range over which the diffusivity was measured.

If the material is Fickian, report the solubility (S) at $(85 \pm 2)^\circ\text{C}$ and activation energy for solubility as determined from IEC 62788-6-2. Also indicate the temperature range over which the solubility was measured.

4.2.3 Non-Fickian materials

For non-Fickian materials, report the solubility (S) at $(85 \pm 2)^\circ\text{C}$ using ISO 62, ASTM D7191-10, ASTM D6869-03, or ISO 15512. Samples should be equilibrated at temperature while placed in a sealed container with water, but not in contact with the water. The use of sufficient sample equilibration time shall be verified by testing multiple samples at progressively longer times. Samples should be tested immediately after removal from the container because of the potential for the evaporation of moisture.

If applicable, also report the irreversible solubility (S_{IR}) by measuring the reversible absorption of a sample saturated at $(85 \pm 2)^\circ\text{C}$ using ISO 15512, ASTM D7191-10 or ASTM D6869-03 and subtracting that from S .

NOTE If the sample contains desiccant, ASTM D7191-10 and ASTM D6869-03 may not work because the water may be irreversibly adsorbed. Furthermore, for molecular sieve-type desiccants, the time required to remove trace amounts of water fully from the desiccant can severely limit the accuracy of these methods and the temperature required to dry the samples can cause other volatile molecules to evaporate.

4.3 Electrical properties

(standards.iteh.ai)

4.3.1 Dielectric strength of the film

Perform a measurement of dielectric strength in accordance with IEC 60243-2 for a DC test. This shall conform to IEC TS 62788-2:2017, 4.5.1 and IEC TS 62788-2:2017, Annex C. Use a material thickness that is useable at a practical voltage, which is rarely greater than 100 kV DC, for the testing equipment. The surfaces of the samples shall be free of volumetric defects (e.g. bubbles, voids or foreign particles) and be made smooth, which may require curing according to the manufacturer's specifications.

Measure and report values before and after saturation with water to duplicate conditions after the desiccant is spent. For the saturated samples, precondition at $(85 \pm 2)^\circ\text{C}$ and $(85 \pm 5)\%$ relative humidity (RH) prior to testing. Allow materials to equilibrate at room temperature prior to testing. Ensure that saturated samples do not dry out before testing, but one may remove any water droplets from the surface. The amount of time needed for equilibration will be determined by the manufacturer such that the mass of the sample does not increase over the course of 24 h.

Materials shall be tested in a surrounding medium selected to prevent flashover as indicated in IEC 60243-1 and IEC 60243-2. The short-time (rapid-rise) method (see IEC 60243-1:2013, 10.1) shall be used with a voltage rise of $2\,000\text{ V}\cdot\text{s}^{-1}$ unless breakdown occurs in less than 10 s. Equal diameter electrodes measuring $(25 \pm 1)\text{ mm}$ shall be used as indicated in IEC 60243-1:2013, 5.2.1.2.

NOTE In IEC 61730-1:2016, 5.6.4.3, requirements for dielectric testing are described for that document. This test method only applies if the edge seal material is part of "relied upon insulation". Because of the potential of polyisobutylene (PIB) based desiccants to absorb or to dissolve in mineral oil, this test is performed as quickly as is reasonable.

4.3.2 Volume resistivity

Volume resistivity in accordance with IEC 62788-1-2. Test before and after saturation with water to evaluate the properties of the material with the spent desiccant. Condition at room temperature in a sealed package to prevent moisture exposure for the "before exposure" condition. Precondition at $(85 \pm 2) ^\circ\text{C}$ and $(85 \pm 5) \% \text{RH}$ prior to testing. The manufacturer shall determine the amount of time needed to fully saturate the desiccant (if applicable) and fill the material with moisture such that the weight no longer increases over time.

NOTE In IEC 61730-1:2016, 5.6.4.2, if the edge seal functions as a cemented joint, then in the context of IEC 61730-1 it has a volume resistivity greater than $50 \times 10^6 \Omega\cdot\text{cm}$ when dry and greater than $10 \times 10^6 \Omega\cdot\text{cm}$ when wet. For most polymeric materials, these values would be expected to be exceeded by many orders of magnitude.

4.3.3 Comparative tracking index

Comparative tracking index (CTI) in accordance with IEC 60112 or UL 746C.

NOTE If the material is used as the relied upon insulation, then in the context of IEC 61730-1 the CTI determines the material group that is then used to define the creepage distance. If the edge seal is considered a cemented joint in the PV module, then IEC 61730-1 does not use creepage and clearance distances, but distances through cemented joints.

4.4 Adhesion testing


4.4.1 General

Adhesion testing is designed to conform to the data necessary to consider the edge seal being listed as a cemented joint in accordance with IEC 61730-2. As such, the strength is reported as the average and standard deviation of 10 replicate measurements.

4.4.2 Lap shear strength

Lap shear strength at $(23 \pm 2) ^\circ\text{C}$ in accordance with ISO 4587 using a sample thickness of $(0,5 \pm 0,1) \text{ mm}$, an overlap area of $(25 \pm 0,25) \text{ mm} \times (12,5 \pm 0,25) \text{ mm}$, and a strain rate of $(0,8 \pm 0,01) \text{ mm}\cdot\text{min}^{-1}$ (see Figure 1, taken from Figure 11 in IEC 61730-2:2016.) Typically, at least one substrate in a PV module will be glass; therefore, testing is accomplished with photovoltaic soda lime glass. If one of the substrate surfaces in the module application is not glass and is a rigid substrate, then that substrate shall be tested.

Dimensions in millimetres

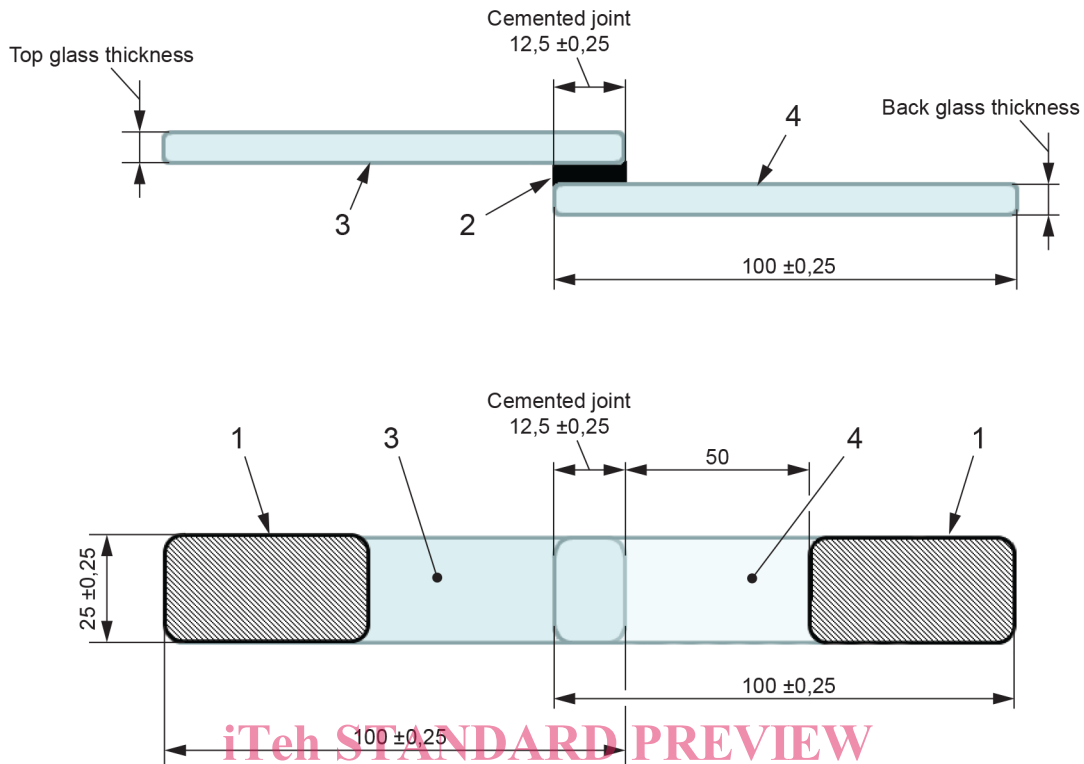

STANDARD PREVIEW
 (standards.itech.ai)

IEC

Key:

- 1 area held in grips
- 2 cemented joint
- 3 PV module front glass
- 4 PV module back glass

<https://standards.itech.ai/catalog/standards/sist/5d2076ef-c88d-4512-8a04-6055152c8669/iec-62788-5-1-2020>

NOTE Schematic taken from IEC 61730-2:2016, Figure 11.

Figure 1 – Lap shear test sample for proving cemented joint

NOTE ISO 4587 specifies that the test should take (65 ± 20) s or use a shear load rate of $8,3 \text{ MPa} \cdot \text{min}^{-1}$ to $9,8 \text{ MPa} \cdot \text{min}^{-1}$. Edge seals typically fail at between 200 % and 600 % strain at around 0,5 MPa. For a sample 0,5 mm thick, the pull rate is between $1 \text{ mm} \cdot \text{min}^{-1}$ and $3 \text{ mm} \cdot \text{min}^{-1}$, but IEC 61730 specifies $0,8 \text{ mm} \cdot \text{min}^{-1}$. If the shear load rate is used, edge seals would be expected to fail in around 3 s to 3,6 s.

4.4.3 “T” peel test

For applications with flexible substrates or superstrates test the adhesion strength as a peel test. Samples shall be tested in a “T” peel configuration in accordance with IEC 61730-2:2016, 10.24 (MST 35). Always use the complete superstrate and substrate laminates in the test sample because the mechanics of the adherend will affect the loading properties and the final values. Use two sets of samples, one comprising only superstrates, and another comprising only substrates. This serves to test adhesion to both surfaces and may make it easier to maintain angles of $(90 \pm 10)^\circ$ as specified in MST 35. The pull rate shall be $(50 \pm 5) \text{ mm} \cdot \text{min}^{-1}$. The sample width shall be $(10 \pm 1) \text{ mm}$. Condition the samples for at least 16 h at $(23 \pm 2)^\circ \text{C}$, or according to the edge seal manufacturer’s recommendation, prior to testing.