

TECHNICAL SPECIFICATION



Measurement procedures for materials used in photovoltaic modules –
Part 5-2: Edge seals – Durability evaluation guideline

(standards.iteh.ai)

IEC TS 62788-5-2:2020

<https://standards.iteh.ai/catalog/standards/sist/578a5856-e9fd-4966-947c-992f4935e02c/iec-ts-62788-5-2-2020>



THIS PUBLICATION IS COPYRIGHT PROTECTED
Copyright © 2020 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

Electropedia - www.electropedia.org

The world's leading online dictionary on electrotechnology, containing more than 22 000 terminological entries in English and French, with equivalent terms in 16 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Glossary - std.iec.ch/glossary

67 000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

[IEC TS 62788-5-2:2020](https://standards.iec.ch/catalog/standards/sis/578a5856-c9fd-4966-947c-992f4935e02c/iec-ts-62788-5-2-2020)

<https://standards.iec.ch/catalog/standards/sis/578a5856-c9fd-4966-947c-992f4935e02c/iec-ts-62788-5-2-2020>

TECHNICAL SPECIFICATION



**Measurement procedures for materials used in photovoltaic modules –
Part 5-2: Edge seals – Durability evaluation guideline**

STANDARD PREVIEW
(standards.iteh.ai)

IEC TS 62788-5-2:2020
<https://standards.iteh.ai/catalog/standards/sist/578a5856-e9fd-4966-947c-992f4935e02c/iec-ts-62788-5-2-2020>

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 27.160

ISBN 978-2-8322-8387-5

Warning! Make sure that you obtained this publication from an authorized distributor.

CONTENTS

FOREWORD.....	3
1 Scope.....	5
2 Normative references	5
3 Terms and definitions	6
4 Testing.....	7
4.1 General.....	7
4.2 Material level tests.....	7
4.2.1 Moisture ingress	7
4.2.2 Adhesion	7
4.2.3 Dielectric strength.....	7
4.2.4 Material specimen UV exposure conditions.....	7
4.2.5 Volume resistivity	8
4.3 Mini-module testing.....	9
4.4 Full-size module testing	11
5 Test report.....	12
Annex A (informative) Example of breakthrough time extrapolation	14
Figure 1 – Material specimen test flow diagram	8
Figure 2 – Mini-module test flow diagram.....	10
Figure 3 – Module test flow diagram	12
Figure A.1 – Example plot of transient WVTR through a 1 mm thick film of a desiccant filled polyisobutylene based edge seal at 100 % RH at 85 °C and at 60 °C	15

IEC STANDARD PREVIEW
 (standards.iteh.ai)
 IEC TS 62788-5-2:2020
<https://standards.iteh.ai/catalog/standards/sist/578a5856-e9fd-4966-947c-992f4935e02c/iec-ts-62788-5-2-2020>

INTERNATIONAL ELECTROTECHNICAL COMMISSION

**MEASUREMENT PROCEDURES FOR MATERIALS
USED IN PHOTOVOLTAIC MODULES –****Part 5-2: Edge seals –
Durability evaluation guideline**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

The main task of IEC technical committees is to prepare International Standards. In exceptional circumstances, a technical committee may propose the publication of a Technical Specification when

- the required support cannot be obtained for the publication of an International Standard, despite repeated efforts, or
- the subject is still under technical development or where, for any other reason, there is the future but no immediate possibility of an agreement on an International Standard.

Technical Specifications are subject to review within three years of publication to decide whether they can be transformed into International Standards.

IEC TS 62788-5-2, which is a Technical Specification, has been prepared by IEC technical committee 82: Solar photovoltaic energy systems.

The text of this Technical Specification is based on the following documents:

DTS	Report on voting
82/1665/DTS	82/1712A/RVDTS

Full information on the voting for the approval of this Technical Specification can be found in the report on voting indicated in the above table.

This document has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all parts in the IEC 62788 series, published under the general title *Measurement procedures for materials used in photovoltaic modules*, can be found on the IEC website.

The committee has decided that the contents of this publication will remain unchanged until the stability date indicated on the IEC website under "<http://webstore.iec.ch>" in the data related to the specific publication. At this date, the publication will be

- transformed into an International standard,
- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

<https://standards.iteh.ai/catalog/standards/sist/578a5836-e91d-4900-947c-992f4935e02c/iec-ts-62788-5-2-2020>

MEASUREMENT PROCEDURES FOR MATERIALS USED IN PHOTOVOLTAIC MODULES –

Part 5-2: Edge seals – Durability evaluation guideline

1 Scope

This part of IEC TS 62788 provides guidelines to assess the ability of an edge seal to prevent moisture ingress from the edges of PV modules. This document does not cover frame adhesives (sometimes colloquially referred to as edge seals) which by design do not serve to prevent moisture ingress to a meaningful degree. Edge seals should keep moisture out, remain adhered, and maintain electrically insulation from the environment. Much of the testing can be done on the material level, but given the fact that there are multiple surfaces, materials interactions, and mechanical stresses, testing on mini modules or modules is necessary. To accomplish this, this document contains three types of test sample types, materials, mini-modules, and full-size modules. It is intended that a quick evaluation and comparison can be made using materials only. This would be followed up by more rigorous tests using mini-modules where all the interfaces are correctly represented. And finally, full-size module tests are used to evaluate the actual construction process to allow unanticipated concerns to be addressed.

This document is structured to evaluate the ability of an edge seal and the overall packaging design to prevent moisture ingress and to provide sufficient electrical insulation according to accepted qualification standards. It seeks to uncover inadequacies in the permeation properties of the edge seal, electrical safety issues, or delamination resulting in moisture ingress. Here it is implied that mini-modules and full-size modules are constructed in accordance with IEC 61730 series. This document does not attempt to evaluate the predicted service life of a module with respect to overall performance. It is designed to determine at the material level if the edge seal can keep moisture out, and then to uncover potential failure modes and/or evaluate the probable effect of manufacturing changes on the performance of edge seals. Test conditions focus on stresses likely to produce safety, moisture ingress, and debonding related failure modes.

For the purposes of this document, an edge seal is defined as a polymeric material designed to be placed between two impermeable (or extremely low permeability) frontsheet and backsheet materials to restrict moisture ingress from the sides. In some cases, an encapsulant with a diffusivity much lower than is found in polyethylene-co-vinyl acetate (EVA) may also serve the purpose of an edge seal and may be evaluated according to this document for comparison.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60904 (all parts), *Photovoltaic devices*

IEC 61215-1:2016, *Terrestrial photovoltaic (PV) modules – Design qualification and type approval – Part 1: Test requirements*

IEC 61215-2:2016, *Terrestrial photovoltaic (PV) modules – Design qualification and type approval – Part 2: Test procedures*

IEC TS 61836, *Solar photovoltaic energy systems – Terms, definitions and symbols*

IEC TS 62782, *Photovoltaic (PV) modules – Cyclic (dynamic) mechanical load testing*

IEC 62788-1-2, *Measurement procedures for materials used in photovoltaic modules – Part 1-2: Encapsulants – Measurement of volume resistivity of photovoltaic encapsulant and other polymeric materials*

IEC 62788-5-1, *Measurement procedures for materials used in photovoltaic modules – Part 5-1: Edge seals – Suggested test methods for use with edge seal materials*

IEC 62788-6-2, *Measurement procedures for materials used in photovoltaic modules – Part 6-2: General tests – Moisture permeation testing of polymeric materials*

IEC TS 62788-7-2, *Measurement procedures for materials used in photovoltaic modules – Part 7-2: Environmental exposures – Accelerated weathering test of polymeric materials*

ISO 10365, *Adhesives – Designation of main failure patterns*

ASTM D7869-13, *Standard practice for xenon arc exposure test with enhanced light and water exposure for transportation coatings*

ASTM G154 – 12a, *Standard practice for operating fluorescent ultraviolet (UV) lamp apparatus for exposure of nonmetallic materials*

(standards.iteh.ai)

3 Terms and definitions

IEC TS 62788-5-2:2020

For the purposes of this document, the terms and definitions given in IEC TS 61836 apply, as well as the following.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1

edge seal

polymeric material designed to be placed between two impermeable (or extremely low permeability) frontsheet and backsheet materials to restrict moisture ingress from the sides

3.2

backsheet

(combination of) outer layer(s) of the PV module, located on the back of PV module and providing protection of the inner components of the PV module from external stresses and weather elements, as well as electrical insulation

3.3

frontsheet

(combination of) outer layer(s) of the PV module, located on the front of PV module and providing protection of the inner components of the PV module from external stresses and weather elements, as well as electrical insulation

4 Testing

4.1 General

This document is separated into three different types of testing, materials, mini-modules, and full-size modules as outlined in Figure 1, Figure 2 and Figure 3 respectively. Material testing determines if the edge seal material is suitable for the application and provides some basic information for a gross comparison of materials. Here some longer-term durability is evaluated because of the ease with which this can be done on small material specimens.

Next, mini-module tests are designed to evaluate if the different materials can work together. These samples consist of most or all of the materials used in the module, but just in a smaller size consisting of a few cells or of one cell for crystalline Si modules, or a small number of small cells for monolithically integrated thin film cells. This includes some UV, thermal and humidity stress factors, but not mechanical stress. Because of its small size, significant UV exposure is still possible.

Finally, full-size modules are evaluated because this enables a more accurate evaluation of the response to mechanical stress factors, but because of the large size, there is a reduction in the amount of UV stress. The intent here is to determine if the design is adequate and if the design can be manufactured well.

4.2 Material level tests

4.2.1 Moisture ingress

Measure the permeation breakthrough time (τ_{F10} %) from the transient permeation through a film of material according to IEC 62788-6-2. Measure the transient water vapour transmission curve at $(85 \pm 2)^\circ\text{C}$ and 100 % RH. An additional measurement at $(60 \pm 2)^\circ\text{C}$ and 100 % RH may also be performed allowing the thermal acceleration to be determined, (see Annex A).

4.2.2 Adhesion

The adhesion of the edge seal material is critical in evaluating the ability of a PV package to prevent moisture ingress. If an edge seal delaminates, it will do nothing in that area to keep moisture out. This test attempts to allow qualitative comparison of different materials, but the viscoelastic properties of an adhesive material also affect its resistance to delamination limiting the accuracy in comparing the results of one material to another without a greater amount of data from other experiments. Furthermore, the mechanical stresses for a given module construction will affect the edge seal's resistance to delamination.

Measure adhesion strength according to IEC 62788-5-1 using the Butt Joint test with samples cut from the edge of a module or a module mock-up. Samples may be cut with a tile saw or water jet cutter. Measure a total of 30 samples, 10 unexposed replicates, 10 replicates after 1 000 h of 85°C and 85 % RH, and 10 replicates after UV exposure (4.2.4) (Figure 1). For exposed samples, cut the test specimens out after exposure. Describe the failure mode using ISO 10365 for guidance. Report the average and standard deviation of all three sets of measurements. For the UV exposed samples report which side showed adhesive failure if any.

4.2.3 Dielectric strength

Measure the dielectric strength according to IEC 62788-5-1 using a total of 30 samples. Measure 10 unexposed replicates, 10 replicates after 1 000 h of 85°C and 85 % RH, and 10 replicates after UV exposure (4.2.4) (Figure 1).

4.2.4 Material specimen UV exposure conditions

Expose specimens in a weathering chamber according to IEC TS 62788-7-2, condition A2 (Figure 1):

- a) Ambient air temperature of $(55 \pm 2) \text{ }^\circ\text{C}$.
- b) Humidity at ambient air temperature of $(20 \pm 5) \text{ %}$ relative.
- c) Irradiance controlled at 340 nm to $(0,80 \pm 0,05) \text{ W}\cdot\text{m}^{-2}\cdot\text{nm}^{-1}$ or $(81 \pm 5) \text{ W}\cdot\text{m}^{-2}$ (300 nm to 400 nm).
- d) Black panel temperature of $(80 \pm 5) \text{ }^\circ\text{C}$.
- e) Total UV exposure time of 4 000 h (or $324 \text{ kWh}\cdot\text{m}^{-2}$, 300 nm to 400 nm).
- f) The UV light source shall be from a Xenon Arc lamp according to ASTM D7869-13, designed to duplicate outdoor spectral conditions.
- g) Glass shall be chosen that will either duplicate the glass used in the module, or more generically a low-Fe soda-lime glass with at least 30 % transmittance at 300 nm.

NOTE Condition A2 was chosen because the materials are typically black and will run at a hotter temperature for better comparison to white or to transparent materials tested in the A3 condition.

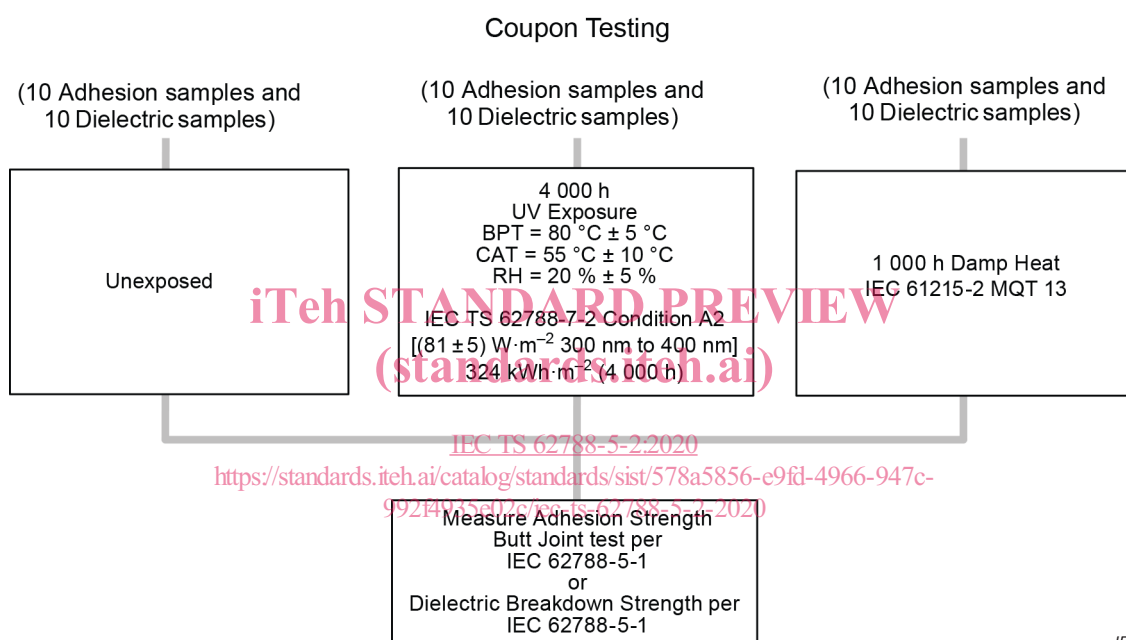


Figure 1 – Material specimen test flow diagram

4.2.5 Volume resistivity

Measure the volume resistivity according to IEC 62788-1-2. Test before and after saturation with water. Condition at room temperature in sealed package to prevent moisture exposure for “before exposure” condition. Precondition at $(85 \pm 2) \text{ }^\circ\text{C}$ and $(85 \pm 5) \text{ %}$ RH prior to exposure. The amount of time shall be determined by the manufacturer to fully saturate the desiccant (if applicable) and fill the material with moisture such that the weight is no longer increasing in time. Test according to IEC 62788-1-2, Method A.

4.3 Mini-module testing

To capture the nuances of an actual application, but with a minimal and reasonable amount of effort, a mini-module test may be done. Mini-modules shall be prepared with the same bill of material as the full-sized modules in as much as is reasonably possible. For thin film monolithically integrated cells on glass, a mini-module sample shall be made similarly to a full-size module except that the number and size of cells is reduced. Cell dimensions shall only be shortened in the longer of the two dimensions. For modules made of discrete cells (e.g. CIGS cells on stainless steel foil), use a mini-module consisting of at least one cell. Any mini-module type shall have largest dimension of at least 150 mm. Dimensions of the edge delete (region where absorber is removed in a thin film on glass module) and/or perimeter construction of the module shall be maintained. If the full-size module design uses a frame, a frame shall be used on the mini-modules. Results obtained for framed mini-modules cannot be used to derive conclusions for unframed mini-modules.

The variation in module thickness from the sides shall be consistent with that of a full-size module. Thickness variation as measured at ~0 cm, 2 cm, 4 cm and 6 cm, when measured diagonally from the four corners and perpendicularly from the sides, shall be comparable to that achieved for a full-size module. For glass/glass modules this is especially important because the presence of edge flare or edge pinch will dramatically affect adhesion.

A junction box, or other method of termination the same as is used in a full-size module, shall be attached. If one does not want to consider humidity ingress through the junction box, it may be omitted and some other means for electrical connection may be devised.

- a) Prior to exposure, perform according to IEC 61215-2:2016 a wet leakage current test (MQT 15), and initial stabilization (MQT 19.1), and determine the maximum power of the device (MQT 02) using I-V characteristics measurement according to the IEC 60904-1 series.

As long term dark storage under elevated temperature, and (UV-)illumination may change metastable processes in TF and xSI cells, care shall be taken to choose proper stabilization measures.

- b) Expose 10 samples to the environmental conditions of heat, humidity and UV irradiance using one of the following three conditions, (see Figure 2):
- 1) Xenon Arc lamp according to ASTM D7869-13, designed to duplicate outdoor spectral conditions.
 - i) Irradiance shall be controlled at 340 nm to $0,8 \text{ W}\cdot\text{m}^{-2}\cdot\text{nm}^{-1}$ or $81 \text{ W}\cdot\text{m}^{-2}$ (300 nm to 400 nm).
 - ii) Expose samples for 4 000 h.
 - iii) Ambient air temperature of $(55 \pm 10) \text{ }^\circ\text{C}$.
 - iv) Ambient air humidity of $(20 \pm 5) \text{ } \%$ RH.
 - v) Black panel temperature of $(80 \pm 5) \text{ }^\circ\text{C}$.
 - 2) Metal halide or other type of lamp consistent with IEC 61215-2:2016 MQT 10.
 - i) Shall have a total irradiance of $81 \text{ W}\cdot\text{m}^{-2}$ between 300 nm and 400 nm.
 - ii) Total exposure time shall be 4 000 h.
 - iii) At least 3 % but not more than 10 % of the light energy between 280 nm and 400 nm shall be between 280 nm and 320 nm.
 - iv) The sample temperature shall be controlled to $(80 \pm 5) \text{ }^\circ\text{C}$.
 - v) If humidity is controllable, control it to $(10 \pm 5) \text{ } \%$ RH at $80 \text{ }^\circ\text{C}$.
 - 3) UV-A lamp (according to ASTM G154 – 12a, Daylight UV)
 - i) If it can be shown that minimal attenuation of the UV light is obtained before the light reaches the first edge seal interface, then a UV-A lamp may be used. The transmittance to this interface shall be greater than 40 % at 300 nm.