



**SLOVENSKI STANDARD**  
**SIST ISO 14104:1998**

**01-junij-1998**

---

**Zobniki - Preskušanje zobnih bokov po brušenju na prežig**

Gears -- Surface temper etch inspection after grinding

Engrenages -- Contrôle par attaque chimique des zones revenues lors de la rectification

**Ta slovenski standard je istoveten z: ISO 14104:1995**

[SIST ISO 14104:1998](https://standards.iteh.ai/catalog/standards/sist/d42f01ce-95d5-4595-a8a1-e62da82e0df9/sist-iso-14104-1998)

<https://standards.iteh.ai/catalog/standards/sist/d42f01ce-95d5-4595-a8a1-e62da82e0df9/sist-iso-14104-1998>

**ICS:**

21.200

Gonila

Gears

**SIST ISO 14104:1998**

**en**

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST ISO 14104:1998

<https://standards.iteh.ai/catalog/standards/sist/d42f01ce-95d5-4595-a8a1-e62da82e0d9/sist-iso-14104-1998>

INTERNATIONAL  
STANDARD

**ISO**  
**14104**

First edition  
1995-12-15

---

---

**Gears — Surface temper etch inspection  
after grinding**

**iTeh STANDARD PREVIEW**

*Engrenages — Contrôle par attaque chimique des zones revenues lors  
de la rectification*

[SIST ISO 14104:1998](https://standards.iteh.ai/catalog/standards/sist/d42f01ce-95d5-4595-a8a1-e62da82e0d9/sist-iso-14104-1998)

[https://standards.iteh.ai/catalog/standards/sist/d42f01ce-95d5-4595-a8a1-  
e62da82e0d9/sist-iso-14104-1998](https://standards.iteh.ai/catalog/standards/sist/d42f01ce-95d5-4595-a8a1-e62da82e0d9/sist-iso-14104-1998)



Reference number  
ISO 14104:1995(E)

**Contents**

Page

<b>1</b>	Scope .....	<b>1</b>
<b>2</b>	Equipment .....	<b>1</b>
<b>3</b>	Reagents .....	<b>1</b>
<b>4</b>	Procedure .....	<b>2</b>
<b>5</b>	Inspection criteria .....	<b>4</b>
<b>6</b>	Rework of surface-tempered parts .....	<b>5</b>
<b>7</b>	Temper etch removal .....	<b>5</b>
<b>8</b>	Maintenance and control .....	<b>5</b>
<b>9</b>	Safety and environmental precautions .....	<b>6</b>

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[SIST ISO 14104:1998](https://standards.iteh.ai/catalog/standards/sist/d42f01ce-95d5-4595-a8a1-e62da82e0d9/sist-iso-14104-1998)

<https://standards.iteh.ai/catalog/standards/sist/d42f01ce-95d5-4595-a8a1-e62da82e0d9/sist-iso-14104-1998>

© ISO 1995

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization  
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 14104 was prepared by The American Gear Manufacturers Association (AGMA) (as ANSI/AGMA 2007-B92) and was adopted, under a special "fast-track procedure", by Technical Committee ISO/TC 60, *Gears*, in parallel with its approval by the ISO member bodies.

The AGMA metallurgic committee undertook a revision of the former temper etch procedure (AGMA 230.01-1967) in 1989. It was renamed "Surface temper etch inspection after grinding" for better definition, the contents reorganized, and obsolete procedures deleted. The revision AGMA 230.01 was redesignated AGMA 2007-B92, and was approved by the AGMA membership in February 1992.

An industry-wide survey was conducted to establish common solutions in time that were acceptable to the greatest number of users. The safety and environmental precautions were included therein for those not familiar with storage, handling, use and disposal of concentrated acids, alkalis and solvents. These precautions, however, do not supersede the latest applicable requirements.

## Introduction

This International Standard explains the materials and procedures necessary to determine, evaluate and describe localized overheating on ground surfaces. A system to describe and classify the indications produced during this inspection is included. However, specific acceptance or rejection criteria are not contained.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST ISO 14104:1998](https://standards.iteh.ai/catalog/standards/sist/d42f01ce-95d5-4595-a8a1-e62da82e0d9/sist-iso-14104-1998)

<https://standards.iteh.ai/catalog/standards/sist/d42f01ce-95d5-4595-a8a1-e62da82e0d9/sist-iso-14104-1998>

# Gears — Surface temper etch inspection after grinding

## 1 Scope

This International Standard specifies standard procedures and requirements for the detection and classification of localized overheating on ground surfaces by chemical etch methods.

Some methods which have been used in the past are no longer recommended. Specifications should be changed to use the methods in this International Standard. These etching methods are more sensitive to changes in surface hardness than most hardness testing methods.

This International Standard applies to steel parts such as gears, shafts, splines and bearings, but is not applicable to nitrided parts and stainless steels.

NOTE 1 This process, although at times called "nital etch", should not be confused with other processes also known as "nital etch".

The surface temper etch procedure is to be performed after grinding and before additional finishing operations.

## 2 Equipment

### 2.1 Container materials

Container materials shall not react with the solutions contained, nor damage the parts to be processed. All containers shall be labelled with the solution contained and covered when not in use.

### 2.2 Inspection area

The area to be inspected shall be sufficiently illuminated to be free of shadows and reflections. Light capable of ensuring 3 200 lux (300 foot candles) at the inspection level is recommended.

### 2.3 Timing device

A suitable timing device shall be used for the uniform processing of all parts in a group.

### 2.4 Cleaner

An alkaline cleaner, vapour degreaser, solvent wash, or equivalent cleaning process should be used.

## 3 Reagents

All chemicals shall be technical grade or better.

### 3.1 Cleaning materials

Cleaning materials shall be used which are capable of ensuring removal of all dirt, grit, grease and oil, to obtain a "water break" free surface. A "water break" free surface is one which maintains a continuous water film for a minimum period of 15 s after having been rinsed in clean water at a temperature below 40 °C.

**3.2 Nitric acid**,  $\rho = 1,42$  g/ml.

**3.3 Hydrochloric acid**,  $\rho = 1,19$  g/ml.

### 3.4 Alcohol


Methanol or denaturated ethanol, clean and free of contaminants such as oil, should be used.

**3.5 Water**, clean and free of contaminants.

### 3.6 Alkaline solution

A solution such as 4 % to 6 % sodium hydroxide in water with a minimum pH value of 10, or 13 % to 17 % ammonium hydroxide in alcohol, should be used.

**3.7 Rust-preventive oil**, which does not mask the results of etching.

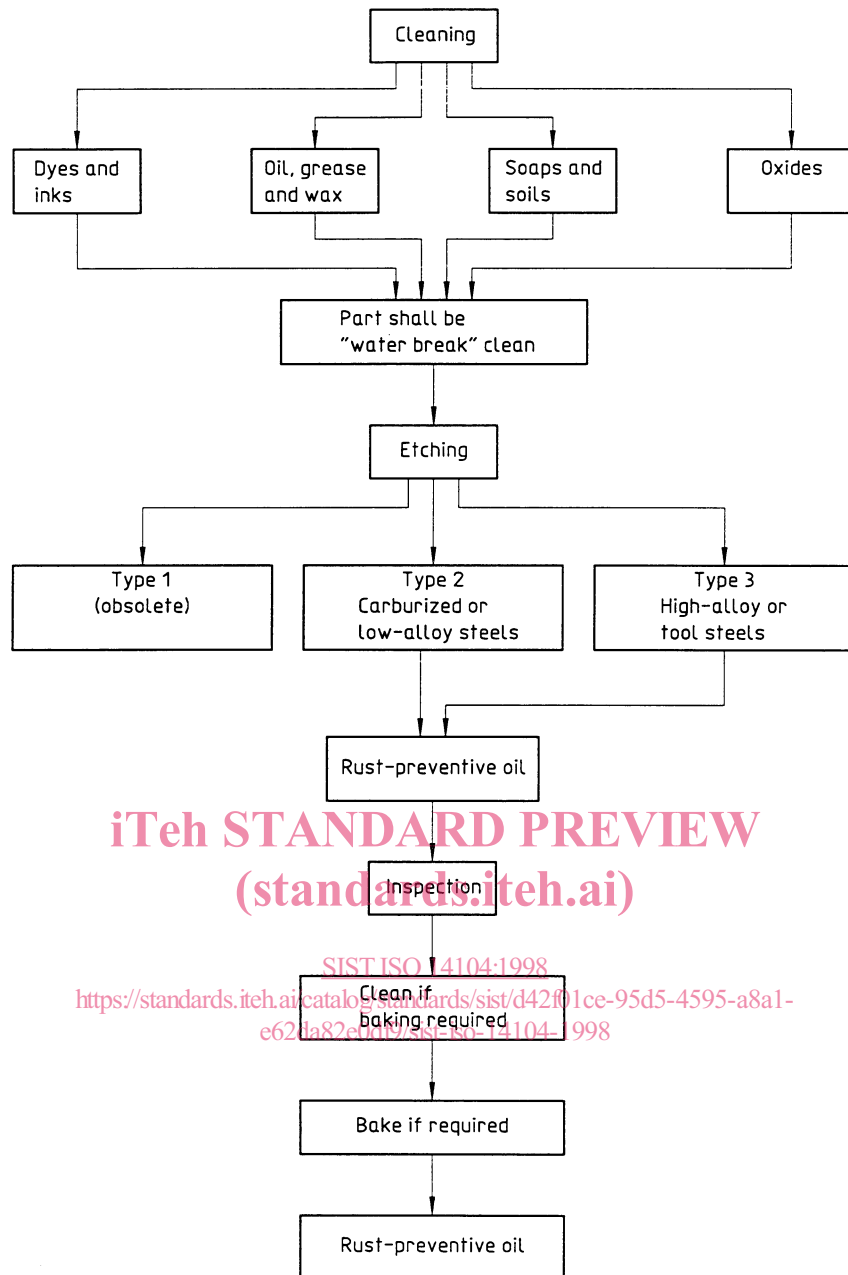

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

SIST ISO 14104:1998  
<https://standards.iteh.ai/catalog/standards/sist/d42f01ce-95d5-4595-a8a1-e62da82e0109/sist-iso-14104-1998>

Figure 1 — Procedure flowchart

## 4 Procedure

As shown in figure 1, first clean the part (see 4.1 and table 1) then etch it using one of the procedures shown in either table 2 or 3, as appropriate for the type of steel being inspected. Unless otherwise specified, selection of the specific procedure shall be at the supplier's option.

### 4.1 Cleaning

Proper cleaning is mandatory for parts to be etched and inspected. Satisfactory cleaning will be evidenced

by the absence of "water breaks" on the cleaned parts when rinsed in water. The cleaning procedure shall be chosen by the supplier. The exact method depends on the type of contaminant present. Table 1 lists contaminants and corresponding methods of cleaning in common use.

It should be noted that additional processes may be required to remove residues from the parts prior to etching. Thorough cleaning of parts prior to etching is imperative in order to obtain good results. Improper cleaning will result in non-uniform discoloration and staining, which may lead to difficult interpretation of etching results. Typical (recommended) cleaning procedure consists of:



- a) vapour degreasing or solvent cleaning;
- b) abrasive cleaning: select particle size and blasting procedure to maintain surface finish and dimensions; handle parts with clean white gloves;
- c) alkaline or ultrasonic clean; examine for water breaks and repeat if water break occurs.

**Table 1 — Examples of cleaning methods**

Type of contaminant	Method of cleaning
Dyes and inks	Alcohol, methyl ethyl ketone, or equivalent
Oil and grease	Vapour degreasing
Soaps	Alkaline cleaner (60 °C to 80 °C) or ultrasonic cleaner

## 4.2 Etching

The following etching techniques are effective preparation for surface temper inspection. The type of

etching should be chosen based on the material to be inspected and the ease of handling.

Type 2 etching (see table 2) is generally accepted as a good production inspection method. Type 2 is normally used for inspecting carburized steels and can also be used for surface-hardened areas of through-hardened steels. Type 3 (see table 3) is normally used for inspecting tool and high-alloy steels, and can be used in place of Type 2. When the Type 3 etching procedure is used, abrasive cleaning is not required.

Parts which cannot be immersed in tanks can be etched using cotton swabs, using the same materials and techniques described either in table 2 or 3. The swabbing technique is difficult to control and interpret, therefore, tank immersion is preferred where practical. Use of a swabbing technique should be agreed upon by the customer and supplier.

Inspect parts immediately following the complete etch procedure.

An elevated-temperature bake to relieve hydrogen embrittlement is optional. The maximum bake temperature shall be at least 14 °C below the final heat-treat tempering temperature. A baking time of 2 h to 4 h is recommended.

(standards.iteh.ai)

**Table 2 — Type 2 etching**

Step <sup>1)</sup>	Process	Solution <sup>2)</sup>	Recommended time <sup>3)</sup>	Remarks
1	Nitric acid etch <sup>4)</sup>	Nitric acid, 3 % to 5 % (by volume), in alcohol: ..... in water: .....	30 s to 60 s 10 s to 30 s	Exact time to develop black oxide film will vary; time should be established and reproduced
2	Rinse	Water	As required	To remove acid
3	Alcohol dip <sup>5)</sup>	Alcohol	Dip and dry	To remove water
4	Bleach <sup>3)</sup>	Hydrochloric acid, 4 % to 6 % (by volume), in alcohol: ..... in water: .....	30 s to 60 s	Part should be immersed for a sufficient time to cause a <i>uniform brownish-grey colour</i> on part; exact bleaching time should be established by test and reproduced
5	Rinse	Water	As required	To remove acid
6	Neutralize	Alkali solution with pH of 10 minimum	10 s to 60 s	Agitate parts while immersed
7	Rinse	Water	As required	To remove caustic solvents
8	Alcohol dip <sup>5)</sup>	Alcohol	Dip and dry	To remove water
9	Oil	Rust preventive	Dip only	To prevent corrosion and aid in colour contrast

1) Uniform agitation of the parts while immersed in the respective baths and rinses is required to avoid a spotty etching condition as well as to accomplish complete neutralization.

2) All solutions are used at ambient temperature.

3) It is permissible to deviate from these recommended times.

4) Areas with close tolerances which do not require surface temper etch inspection should be suitably masked to avoid stock removal. Approximately 0,003 mm of stock per surface is removed by etching each time this process is performed.

5) Optional procedure: hot water rinse at 65 °C minimum, followed by a dry air blast, may be used in lieu of alcohol dip.