

**SLOVENSKI STANDARD  
SIST EN 546-2:2007****01-marec-2007****BUXca Yý U.  
SIST EN 546-2:1998****Aluminij in aluminijeve zlitine - Folija - 2. del: Mehanske lastnosti**

Aluminium and aluminium alloys - Foil - Part 2: Mechanical properties

Aluminium und Aluminiumlegierungen - Folien - Teil 2: Mechanische Eigenschaften

**iTeh STANDARD PREVIEW**  
Aluminium et alliages d'aluminium - Feuille mince - Partie 2 : Caractéristiques  
mécaniques**Ta slovenski standard je istoveten z:** [SIST EN 546-2:2007](#) [EN 546-2:2006](#)  
[84018f69108d/sist-en-546-2-2007](#)**ICS:**

77.150.10      Alumijski izdelki      Aluminium products

**SIST EN 546-2:2007**      **en**

## iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN 546-2:2007

<https://standards.iteh.ai/catalog/standards/sist/b64275bb-c4d1-4393-8a5b-84018fe9108d/sist-en-546-2-2007>

EUROPEAN STANDARD  
NORME EUROPÉENNE  
EUROPÄISCHE NORM

**EN 546-2**

December 2006

ICS 77.150.10

Supersedes EN 546-2:1996

English Version

**Aluminium and aluminium alloys - Foil - Part 2: Mechanical properties**

Aluminium et alliages d'aluminium - Feuille mince - Partie 2  
: Caractéristiques mécaniques

Aluminium und Aluminiumlegierungen - Folien - Teil 2:  
Mechanische Eigenschaften

This European Standard was approved by CEN on 25 November 2006.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

**iTeh STANDARD PREVIEW**

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

SIST EN 546-2:2007

<https://standards.iteh.ai/catalog/standards/sist/b64275bb-c4d1-4393-8a5b-84018fe9108d/sist-en-546-2-2007>



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

## Contents

	Page
<b>Foreword</b> .....	<b>3</b>
<b>1 Scope</b> .....	<b>4</b>
<b>2 Normative references</b> .....	<b>4</b>
<b>3 Tensile testing</b> .....	<b>4</b>
<b>4 Mechanical properties</b> .....	<b>5</b>
<b>5 Rounding of test results</b> .....	<b>5</b>
<b>Annex A (normative) Rules for rounding</b> .....	<b>8</b>
<b>Bibliography</b> .....	<b>9</b>

## Figures

<b>Figure 1 — Parallel sided test piece</b> .....	<b>4</b>
<b>Figure 2 — Example of double-bladed cutter</b> .....	<b>5</b>

## Tables

<b>Table 1 — Longitudinal mechanical properties for converter/household foil<sup>a</sup></b> .....	<b>6</b>
<b>Table 2 — Longitudinal mechanical properties for container foil<sup>a</sup></b> .....	<b>7</b>

## Foreword

This document (EN 546-2:2006) has been prepared by Technical Committee CEN/TC 132 "Aluminium and aluminium alloys", the secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2007, and conflicting national standards shall be withdrawn at the latest by June 2007.

This document supersedes EN 546-2:1996.

Within its programme of work, Technical Committee CEN/TC 132 entrusted CEN/TC 132/WG 6 "Foil and finstock" to revise EN 546-2:1996.

The following modifications have been made:

- Clause 4: Table 1 and Table 2 amended. Alloy EN AW-8021B added in Table 1.

EN 546 comprises the following parts under the general title "*Aluminium and aluminium alloys - Foil*":

- *Part 1: Technical conditions for inspection and delivery*
- *Part 2: Mechanical properties* (**standards.iteh.ai**)
- *Part 3: Tolerances on dimensions*    [SIST EN 546-2:2007](#)  
<https://standards.iteh.ai/catalog/standards/sist/b64275bb-c4d1-4393-8a5b-84018fe9108d/sist-en-546-2-2007>
- *Part 4: Special property requirements*

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

CEN/TC 132 affirms it is its policy that in the case when a patentee refuses to grant licenses on standardised standard products under reasonable and not discriminatory conditions, then this product shall be removed from the corresponding standard.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

## 1 Scope

This document specifies the mechanical properties of wrought aluminium and aluminium alloy foil.

The chemical composition limits of these materials are specified in EN 573-3.

The designations of aluminium and aluminium alloys and the temper designations used in this standard are specified in EN 573-3 and the temper designation are defined EN 515.

## 2 Normative references


The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 546-1, *Aluminium and aluminium alloys — Foil — Part 1: Technical conditions for inspection and delivery*

## 3 Tensile testing

The selection and number of specimens and test pieces shall be as specified in EN 546-1. Preparation of test pieces shall be carried out as follows:

- parallel sided test pieces (see Figure 1) with a width of  $15 \text{ mm} \pm 0,1 \text{ mm}$  and a gauge length of  $50 \text{ mm} \pm 1 \text{ mm}$  or  $100 \text{ mm} \pm 1 \text{ mm}$  shall be used. They shall be prepared using a double-bladed cutter (see Figure 2) or a precision ground sample shear of "punch and die" construction;
- the tensile test shall be carried out on suitably calibrated equipment. The test speed shall be in the range 5 % to 25 % of the gauge length per minute.  
<https://standards.iteh.ai/catalog/standards/sist-en-546-2-2007-84018fe9108d/sist-en-546-2-2007>

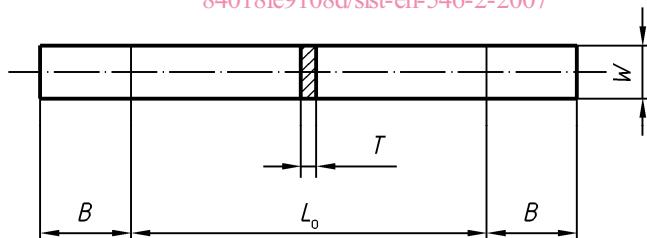

### Key


$L_0$  = Gauge length =  $(50 \pm 1) \text{ mm}$  or  $(100 \pm 1) \text{ mm}$

$W$  = Width =  $(15 \pm 0,1) \text{ mm}$

$T$  = Thickness of strip

$B$  = Length of grip section = minimum value 25 mm

Figure 1 — Parallel sided test piece

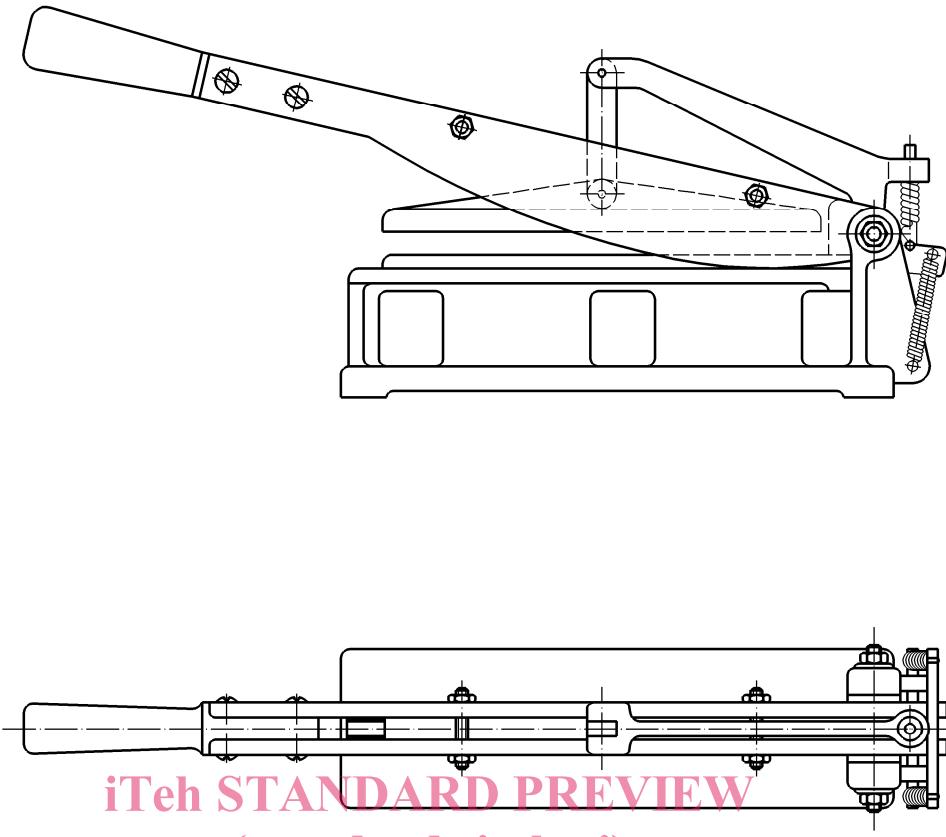

**Figure 2 — Example of double-bladed cutter**

Considering the difficulty in marking thin gauge material, the gauge length may be measured by the distance between the grips of the testing machine. The elongation is then determined from the difference in the distance between the grips before testing and at fracture, or by direct reading from the load vs-crosshead displacement diagram when available. This provision only applies to parallel-sided test pieces.

#### 4 Mechanical properties

Mechanical properties of foil for converter/household as specified in Table 1 and for container foil as specified in Table 2. For the elongation measurement, two different gauge lengths may be used. The choice of the gauge length, either 50 mm or 100 mm, shall be at the discretion of the manufacturer unless otherwise agreed; nevertheless, the supplier shall inform the purchaser of the length used.

#### 5 Rounding of test results

Test results shall be rounded in accordance with the rounding rules given in Annex A.

**Table 1 — Longitudinal mechanical properties for converter/household foil**

Material	Gauge range <sup>a</sup> μm		Temper			
			O		H18 <sup>a</sup>	
			Tensile strength $R_m$ MPa		Elongation $A_{50\text{ mm or }} A_{100\text{ mm}}$ %	Tensile strength $R_m$ MPa
	Over	Up to and including	min.	max.	min.	min.
EN AW-1050A [Al 99,5]	≥ 6	10	35	80	1	135
	10	25	40	85	1	135
	25	40	45	90	2	135
	40	90	50	95	4	135
	90	140	50	95	6	135
	140	200	50	95	10	135
EN AW-1200 [Al 99,0]	≥ 6	10	40	95	1	140
	10	25	45	100	1	140
	25	40	50	105	3	140
	40	90	55	105	6	140
	90	140	60	105	10	140
	140	200	60	105	14	140
EN AW-8006 [Al Fe1,5Mn]	≥ 6	10	80	135	1	190
	10	25	85	140	2	190
	25	40	85	140	6	190
	40	90	90	140	10	190
	90	140	90	140	15	190
	140	200	90	140	15	190
EN AW-8011A [Al FeSi(A)]	≥ 6	10	50	110	1	160
	10	25	55	115	1	160
	25	40	55	120	3	160
	40	90	65	130	7	160
	90	140	65	130	12	160
	140	200	65	130	16	160
EN AW-8014 [Al Fe1,5Mn0,4]	≥ 6	10	70	130	1	170
	10	25	75	135	2	170
	25	40	75	135	6	170
	40	90	80	135	10	170
	90	140	80	135	14	170
	140	200	80	135	15	170
EN AW-8021B [Al Fe1,5]	≥ 6	10	60	100	2	160
	10	25	65	105	3	160
	25	40	70	110	7	160
	40	90	75	110	12	160
	90	140	75	110	14	160
	140	200	75	110	16	160
EN AW-8079 [Al Fe1Si]	≥ 6	10	45	100	1	150
	10	25	50	105	1	150
	25	40	55	110	4	150
	40	90	60	110	8	150
	90	140	60	110	13	150
	140	200	60	110	16	150
EN AW-8111 [Al FeSi(B)]	≥ 6	10	55	105	2	160
	10	25	60	110	3	160
	25	40	70	120	11	160
	40	90	70	130	12	160
	90	140	70	130	14	160
	140	200	70	130	16	160
NOTE If no values are available, this should be agreed between supplier and purchaser.						
a In H18 temper, maximum values for tensile strength and minimum values for elongation shall be subject to agreement between supplier and purchaser, if required. H18 can be replaced by the supplier in agreement with the purchaser into H19 temper.						

Table 2 — Longitudinal mechanical properties for container foil <sup>a</sup>

Material	Gauge range μm	Temper															
		O		H22		H24		H26		H18							
		Tensile strength $R_m$ MPa		Elongation $A_{50mm}$ or $A_{100mm}$ %		Tensile strength $R_m$ MPa		Elongation $A_{50mm}$ or $A_{100mm}$ %		Tensile strength $R_m$ MPa		Elongation $A_{50mm}$ or $A_{100mm}$ %		Tensile strength $R_m$ MPa			
		Over	Up to and including	min.	max.	min.	max.	min.	max.	min.	max.	min.	max.	min.	max.		
EN AW-1200 [Al 99,0]	≥ 35 40 90 140 140	40 90 140 200	50 55 60 60	105 105 105 105	3 6 10 14	90 90 90 90	135 135 135 135	2 4 6 7	110 110 110 110	155 155 155 155	2 3 4 5	125 125 125 125	180 180 180 180	1 1 2 2	140 140 140 140	200 200 200 200	1 1 1 1
EN AW-3003 [Al Mn1Cu]	≥ 35 40 90 140 140	40 90 140 200	85 85 85 85	135 135 135 135	5 6 10 13	120 120 120 120	160 160 160 160	5 6 8 9	145 145 145 145	185 185 185 185	6 7 8 9	150 150 150 150	190 190 190 190	2 3 4 4	190 190 190 190	230 230 230 230	1 1 1 1
EN AW-3005 [Al Mn1Mg0,5]	≥ 35 40 90 140 140	40 90 140 200	125 125 125 125	165 165 165 165	8 9 10 10	- - -	-	180 180 180 180	225 225 225 225	3 3 3 4	- - -	- - -	- - -	- - -	- - -	- - -	
EN AW-3103 [Al Mn1]	≥ 35 40 90 140 140	40 90 140 200	80 80 80 80	130 130 130 130	7 8 12 15	115 115 115 115	155 155 155 155	5 6 8 9	140 140 140 140	180 180 180 180	6 7 8 9	150 150 150 150	190 190 190 190	2 3 4 4	185 185 185 185	230 230 230 230	1 1 1 1
EN AW-8006 [Al Fe1,5Mn]	≥ 35 40 90 140 140	40 90 90 200	85 90 90 90	140 140 140 140	6 10 14 15	- -	-	110 110 110 110	170 170 170 170	3 4 5 7	- - -	- - -	- - -	- - -	- - -	- - -	
EN AW-8008 [Al Fe1Mn0,8]	≥ 35 40 90 140 140	40 90 80 200	80 80 80 80	140 140 140 140	8 10 14 15	120 120 120 120	155 155 155 155	5 8 12 13	140 140 140 140	175 175 175 175	3 5 8 10	150 150 150 150	190 190 190 190	2 4 6 8	180 180 180 180	250 250 250 250	1 1 1 1
EN AW-8011A [Al FeSi(A)]	≥ 35 40 90 140 140	40 90 140 200	55 65 65 65	120 130 130 130	4 7 12 16	90 90 90 90	150 150 150 150	2 4 5 6	110 110 110 110	165 165 165 165	2 3 4 5	140 140 140 140	185 185 185 185	1 2 2 3	160 160 160 160	220 220 220 220	1 1 1 1

<sup>a</sup> Single rolled (35 μm to 200 μm).

iTeh STANDARD PREVIEW (standards.iteh.ai)