
**Resistance welding — Destructive tests
of welds — Failure types and geometric
measurements for resistance spot, seam
and projection welds**

*Soudage par résistance — Essais destructifs des soudures — Types
de rupture et dimensions géométriques pour les assemblages soudés
par résistance par points, à la molette et par bossages*

**iTeh STANDARD PREVIEW
(standards.iteh.ai)**

[ISO 14329:2003](https://standards.iteh.ai/catalog/standards/sist/b458e975-f04e-4083-9940-40e27b4fe0a3/iso-14329-2003)

<https://standards.iteh.ai/catalog/standards/sist/b458e975-f04e-4083-9940-40e27b4fe0a3/iso-14329-2003>



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 14329:2003

<https://standards.iteh.ai/catalog/standards/sist/b458e975-f04e-4083-9940-40e27b4fe0a3/iso-14329-2003>

© ISO 2003

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 14329 was prepared in collaboration with the International Institute of Welding which has been approved by the ISO Council as an international standardizing body in the field of welding.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 14329:2003](https://standards.iteh.ai/catalog/standards/sist/b458e975-f04e-4083-9940-40e27b4fe0a3/iso-14329-2003)

<https://standards.iteh.ai/catalog/standards/sist/b458e975-f04e-4083-9940-40e27b4fe0a3/iso-14329-2003>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 14329:2003

<https://standards.iteh.ai/catalog/standards/sist/b458e975-f04e-4083-9940-40e27b4fe0a3/iso-14329-2003>

Resistance welding — Destructive tests of welds — Failure types and geometric measurements for resistance spot, seam and projection welds

1 Scope

This International Standard specifies the definitions of the geometric measurements and fracture types to be used in relation to the testing of resistance spot, projection and seam welds in which different loading configurations cause different stress distributions in the weld (see Figure 1). The aim of these definitions is to give a base for all other related standards.

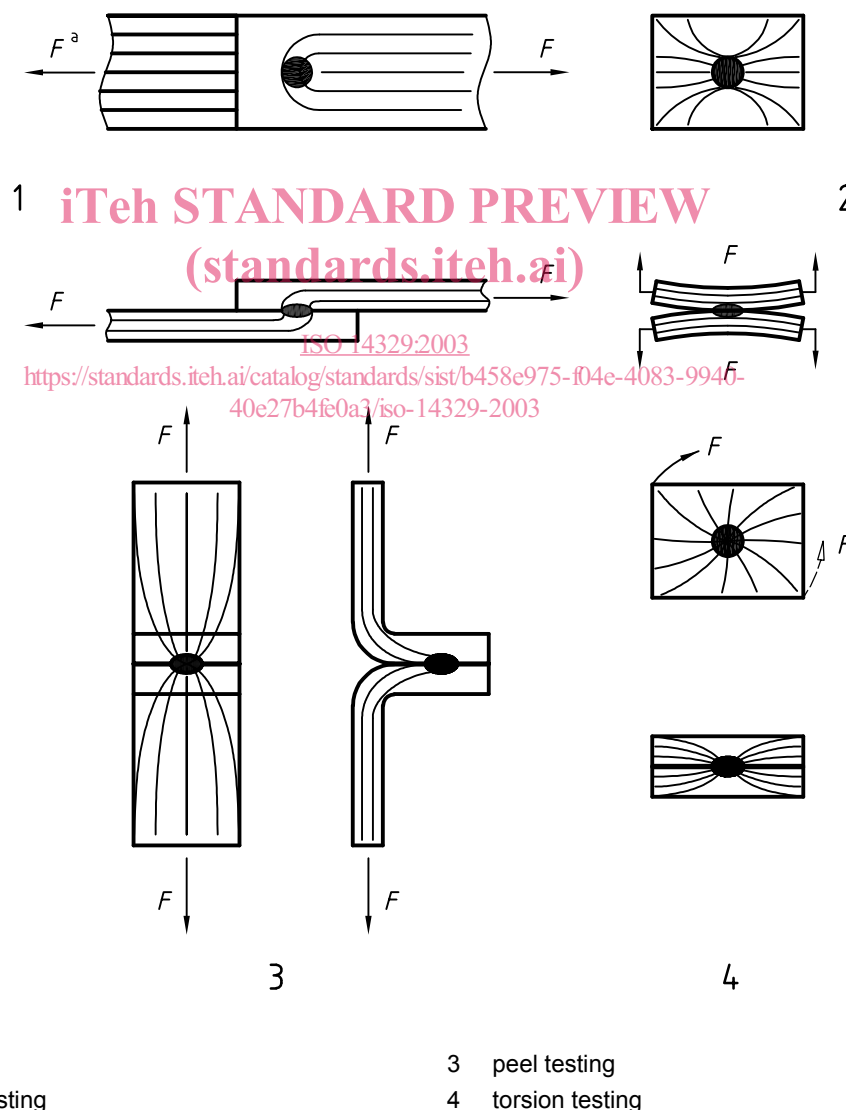


Figure 1 — Schematic illustrations showing stress distribution depending on direction of the testing load

2 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

2.1 Failure modes of specimens and components

2.1.1

interface failure

fracture through the weld nugget between the sheets at the place of the interface

See Figure 2.

2.1.2

partial plug failure

fracture in which a combination of plug and interface failures are present

See Figure 3.

2.1.3

plug

metal pulled from one sheet remaining attached to the surface of the other after testing

See Figure 3.

2.1.4

plug failure

fracture in the base metal, the heat affected zone (HAZ) or in the nugget leaving a lug

See Figure 3.

2.1.5

solid phase weld

pressure weld without a fused zone

See Figure 5 d).

iTeh STANDARD PREVIEW
(standards.iteh.ai)
<https://standards.iteh.ai/catalog/standards/sist/b458e975-f04e-4083-9940-40e27b4fe0a3/iso-14329-2003>
ISO 14329:2003

2.2 Measurements made on broken test specimens (Figures 2, 3 and 4)

2.2.1

asymmetrical welds

elongated or oval welds

NOTE Diameters " d_1 " and " d_2 " should be measured along the two main axes and reported separately (see Figure 3).

2.2.2

weld diameter

d

(interface failure) mean of the minimum and the maximum diameters of the fused zone measured at the interface omitting the corona bond area

See Figure 2.

2.2.3

weld diameter

d

(partial plug failure) mean of the diameter of the fused zone measured at the interface, omitting the corona bond area, and the maximum diameter of the plug segment

See Figure 3.

2.2.4 weld diameter

d

(plug failure) mean of the minimum and maximum diameters of the plug measured at the base of the plug

See Figure 3.

2.2.5 minimum width of resistance seam weld

w

(plug failure) width of the weld plugs measured at the base of the plug

See Figure 4.

2.2.6 minimum width of resistance seam weld

w

(interface failure) width of the nugget in the plane of the interface at right angles to the longitudinal axis of the seam

2.3 Measurements made on sections taken from the weld

2.3.1 brazed zone

(welding of metallic coated sheets) area over which the bond is formed between the coatings only

See Figure 5c).

2.3.2 brazed zone diameter

d_{sb}

diameter of the brazed zone measured in the plane of the interface between the joined pieces

NOTE The mean value should be used [see Figure 5c)].

2.3.3 corona bond diameter

d_c

diameter of the area surrounding the nugget of a spot or projection weld at the faying surfaces in which solid phase bonding only has occurred

See Figure 2.

NOTE The mean value should be used, if possible [see Figures 5a) and 5b)].

2.3.4 distance between nugget centres of seam welds

a

distance between the centres of two adjacent nuggets

See Figure 6.

NOTE The position of the nugget centre normally corresponds with the position of maximum nugget penetration.

2.3.5
distance of the minimum nugget penetration of seam welds

b
distance between two minimum nugget penetrations

See Figure 6.

NOTE The distance cannot be observed in every seam weld.

2.3.6
electrode indentation depth

e_u, e_l
maximum depth of the indentation of the electrode measured in the direction of the electrode force

See Figure 5a).

2.3.7
electrode indentation diameter

d_{eu}, d_{el}
diameters of the depression on the exterior surfaces of the work pieces

See Figure 5a).

NOTE The mean value should be used.

2.3.8
elongated welds
same as asymmetrical welds

iTeh STANDARD PREVIEW
(standards.iteh.ai)

See 2.2.1 and Figure 3.

ISO 14329:2003

NOTE Two sections in the major axis should be used to determine nugget width and length, nugget penetration, electrode indentation, and sheet separation as individual figures referred to the axis.

2.3.9
heat affected zone diameter

d_{HAZ}
diameter of the heat affected structure measured on a macro- or microsection

See Figures 5a) and b).

2.3.10
heat affected zone penetration

$p_{HAZ u}, p_{HAZ l}$
penetration of the heat affected zone in the thickness direction in each sheet

See Figure 5a).

2.3.11
maximum nugget penetration of seam welds

p_{max}
maximum penetration in the thickness direction expressed as a percentage of the combined thickness

See Figure 6.

2.3.12 minimum nugget penetration of seam welds

p_{\min}

minimum penetration of the nugget in the thickness direction expressed as a percentage of the combined thickness

See Figure 6.

NOTE The penetration can be measured in discontinuous seam and roll spot welds but the ability to do so in continuous seam and roll spot welds depends on the weld condition and material.

2.3.13 nugget diameter

d_n

mean of the maximum and the minimum diameters of the nugget measured in the plane of the interface between the pieces joined

See Figures 5a) to c).

2.3.14 nugget penetration

p_U, p_l

penetration of the nugget in the thickness direction in one sheet

See Figure 5a).

iTeh STANDARD PREVIEW
(standards.iteh.ai)

2.3.15 overlap of nuggets

o

length of common area between two adjacent and overlapping seam weld nuggets

<https://standards.iteh.ai/catalog/standards/sist/b458e975-f04e-4083-9940-40e27b4fe0a3/iso-14329-2003>

See Figure 6.

NOTE The area contains the portion of the preceding weld nugget remelted by the succeeding weld.

2.3.16 sheet separation

x

mean gap surrounding the weld between the faying surfaces measured at a distance of $0,5d_n$ from the edge of the weld nugget

See Figure 5a).

2.3.17 solid phase weld diameter

d_s

diameter of the solid phase weld measured in the lane of the interface between the pieces joined

NOTE The mean value should be used [see Figure 5d)].