# INTERNATIONAL STANDARD



First edition 2002-10-01

# Graphic technology — Colour and transparency of printing ink sets for four-colour-printing —

Part 3: Publication gravure printing

iTeh STANDARD PREVIEW Technologie graphique — Couleur et transparence des gammes d'encre d'impression en quadrichromie —

Partie 3: Impression hélio ISO 2846-3:2002 https://standards.iteh.ai/catalog/standards/sist/01ea2fa4-c4fb-4ce5-b168-77ce76c03330/iso-2846-3-2002



Reference number ISO 2846-3:2002(E)

#### PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

# iTeh STANDARD PREVIEW (standards.iteh.ai)

<u>ISO 2846-3:2002</u> https://standards.iteh.ai/catalog/standards/sist/01ea2fa4-c4fb-4ce5-b168-77ce76c03330/iso-2846-3-2002

© ISO 2002

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office Case postale 56 • CH-1211 Geneva 20 Tel. + 41 22 749 01 11 Fax + 41 22 749 09 47 E-mail copyright@iso.ch Web www.iso.ch

Printed in Switzerland

### Contents

Forewo	ord	v
	iction	
1	Scope	1
2	Normative references	1
3	Terms and definitions	2
4 4.1 4.2 4.3	Test method Principle Test print preparation Colour measurement procedure	2 2
5 5.1 5.2 5.3	Colour and transparency General Colorimetric values Transparency characteristics	3 3
	A (normative) Reference substrate	
	B (informative) Spectral data STANDARD PREVIEW	
Annex	C (informative) Colorimetric values for non-normative conditions	9
Annex	D (informative) Detailed explanation of the test method, including examples	0
Bibliog	raphy1 https://standards.iteh.ai/catalog/standards/sist/01ea2fa4-c4fb-4ce5-b168- 77ce76c03330/iso-2846-3-2002	3

#### Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this part of ISO 2846 may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 2846-3 was prepared by Technical Committee ISO/TC 130, Graphic technology.

ISO 2846 consists of the following parts, under the general title Graphic technology — Colour and transparency of printing ink sets for four-colour-printing:

- Part 1: Sheet-fed and heat-set web offset lithographic printing
- Part 2: Coldset offset lithographic printing https://standards.iten.ai/catalog/standards/sist/01ea2fa4-c4fb-4ce5-b168-77ce76c03330/iso-2846-3-2002
- Part 3: Publication gravure printing

— Part 4: Screen printing

— Part 5: Flexographic printing

Annex A forms a normative part of this part of ISO 2846. Annexes B to D are for information only.

#### Introduction

The demand for the publication gravure printing process to become more consistent and predictable has required a means of standardizing the product to ensure the easy flow of business between the various parties involved in its production. An essential component in this process is the colorimetric characteristics of the ink set.

To produce a set of standard four-colour process inks suitable for gravure printing it is necessary to specify a number of parameters. It is the purpose of this part of ISO 2846 to describe those parameters which affect the colorimetric characteristics in such a manner that a standard set of inks can be supplied by any ink manufacturer to any printer who can then supply prints to a print buyer with confidence in the colour of the work produced.

This part of ISO 2846 will allow publication gravure printers to obtain different sets of inks that will produce a similar colour when printed on the same substrate. In addition, it will allow colour separations for gravure printing to be based on known colour standards. The colorimetric characteristics specified may only be obtained when the inks are printed on the reference substrate. However, two inks of the same type that are similar in colorimetric characteristics and transparency according to this part of ISO 2846 will normally ensure similarity on another substrate.

# iTeh STANDARD PREVIEW (standards.iteh.ai)

<u>ISO 2846-3:2002</u> https://standards.iteh.ai/catalog/standards/sist/01ea2fa4-c4fb-4ce5-b168-77ce76c03330/iso-2846-3-2002

# iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 2846-3:2002 https://standards.iteh.ai/catalog/standards/sist/01ea2fa4-c4fb-4ce5-b168-77ce76c03330/iso-2846-3-2002

# Graphic technology — Colour and transparency of printing ink sets for four-colour-printing —

# Part 3: **Publication gravure printing**

#### 1 Scope

This part of ISO 2846 specifies the colour and transparency to be produced by a process colour ink set including extender intended for four-colour publication gravure printing when printed under specified gravure printing conditions. It also specifies the test method to ensure conformance.

This part of ISO 2846 does not specify pigments (or spectral reflectance) in order not to preclude developments which may enable different pigment combinations to be used advantageously while still achieving the colorimetric requirements specified in this part of ISO 2846.

NOTE This part of ISO 2846 may also apply to certain non-publication gravure applications.

#### (standards.iteh.ai)

#### 2 Normative references

<u>ISO 2846-3:2002</u>

https://standards.iteh.ai/catalog/standards/sist/01ea2fa4-c4fb-4ce5-b168-

The following normative documents contain provisions which through reference in this text, constitute provisions of this part of ISO 2846. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this part of ISO 2846 are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 535:1991, Paper and board — Determination of water absorptiveness — Cobb method

ISO 536:1995, Paper and board — Determination of grammage

ISO 2144:1997, Paper, board and pulps — Determination of residue (ash) on ignition at 900 °C

ISO 2846-1:1997, Graphic technology — Colour and transparency of ink sets for four-colour-printing — Part 1: Sheet-fed and heat-set web offset lithographic printing

ISO 6588:1981, Paper, board and pulps — Determination of pH of aqueous extracts

ISO 8254-1:1999, Paper and board — Measurement of specular gloss — Part 1: 75° gloss with a converging beam, TAPPI method

ISO 8791-4:1992, Paper and board — Determination of roughness/smoothness (air leak methods) — Part 4: Print-surf method

ISO 13655:1996, Graphic technology — Spectral measurement and colorimetric computation for graphic arts images

#### 3 Terms and definitions

For the purposes of this part of ISO 2846, the following terms and definitions apply.

#### 3.1

#### extension

addition of a transparent material (colorant-free ink) to the ink to reduce the pigment concentration without significantly influencing the rheological properties of the ink

#### 3.2

#### press-ready ink

ink that has all necessary components and is at press viscosity

#### 3.3

#### transparency

ability of an ink film to transmit and absorb light without scattering

NOTE It is generally expressed as some measure of the unwanted scattering.

[ISO 2846-1:1997, 3.5]

#### 4 Test method

## 4.1 Principle iTeh STANDARD PREVIEW

Each ink shall be printed on the reference substrate described in annex A at a range of colorations obtained by varying the extension of the press-ready ink. The colours which result shall be measured colorimetrically and the colour difference between the sample and the pertinent value in Table 1 shall be plotted versus the percentage of press-ready ink. If one or more samples conform to the values and tolerances specified, and the ink also meets the transparency criteria, that ink complies to this part of ISO 2846 stolerances (1990)

Transparency, *T*, shall be evaluated by printing or applying each of the chromatic process inks on a black substrate at a range of ink extensions. The CIELAB colour difference,  $\Delta E_{ab}^*$ , shall be determined for each sample, between the overprinted and unprinted black. The linear regression coefficient (slope of the regression line) between the percentage by mass of press-ready ink in each of the extended ink samples being tested and colour difference shall be calculated from a plot of  $\Delta E_{ab}^*$  vs. percentage press-ready ink over a range of extensions. An ink conforms to this requirement if the transparency, *T*, which is the reciprocal of the regression coefficient, is negative or greater than the value specified. For further details, see annex D.

#### 4.2 Test print preparation

#### 4.2.1 Prints for colorimetric evaluation

For each ink to be evaluated, prepare an extension series with 50 %, 60 %, 70 %, 80 %, 90 % and 100 % of press-ready ink using extender diluted to press viscosity. Apply the series of extended inks to the reference substrate specified in annex A with a method that produces an even ink film thickness. Examples are printing with a printability tester for gravure inks or coating applicator. The wet ink film thickness used for the extension series shall be approximately equal.

The method chosen shall produce a curve that shows a pronounced minimum or a data point which is in conformance with Table 1 when  $\Delta E_{ab}^*$  is plotted versus percentage of press-ready ink. If the extension series does not produce such a curve, produce another series of specimens with a different ink film thickness. Produce a higher ink film thickness if the colour difference decreases with an increasing percentage of press-ready ink. Produce a lower ink film thickness if the colour difference decreases with a decreasing percentage of press-ready ink.

See annex D for further information.

#### 4.2.2 Prints for transparency evaluation

Test prints for transparency evaluation shall be produced by printing the inks to be tested over black. The black shall have a lightness ( $L^*$ ) less than 6 when determined according to ISO 13655.

One appropriate substrate is the contrast card<sup>1</sup>).

Since the CIELAB values of the black need to be established, both when unprinted and overprinted by the chromatic ink, the measurements of the black alone shall be made prior to overprinting.

The ink to be tested shall then be printed on the substrate such that a range of samples is achieved, each with a different percentage of press-ready ink.

#### 4.2.3 Drying of test prints

Prior to colour measurement, all samples shall be thoroughly dried.

#### 4.3 Colour measurement procedure

Test prints shall be measured in accordance with ISO 13655, except that a substrate backing consisting of at least 3 sheets of the unprinted reference substrate shall be used.

NOTE The samples are measured spectrally, with a  $0^{\circ}/45^{\circ}$  or  $45^{\circ}/0^{\circ}$  geometry instrument. For calculation of CIELAB values and colour differences, CIE 1931 (2°) standard colorimetric observer data are used together with CIE illuminant D<sub>50</sub>.

# iTeh STANDARD PREVIEW

### 5 Colour and transparency (standards.iteh.ai)

#### 5.1 General

#### <u>ISO 2846-3:2002</u>

https://standards.iteh.ai/catalog/standards/sist/01ea2fa4-c4fb-4ce5-b168-

For an ink to conform to this part of ISO 2846 it shall meet the specification for colour defined in 5.2 and the specification for transparency defined in 5.3.

#### 5.2 Colorimetric values

To meet the specification for colour, an ink shall produce a colour that falls within the colour difference tolerances from the specified colorimetric values given in Table 1, when printed as defined in 4.2.1 at some percentage of press-ready ink.

NOTE 1 Unlike some other parts of ISO 2846, this part of ISO 2846 does not specify limits for concentration or ink film thickness within which to meet the specified colour difference, as such requirements are not applicable to the gravure process.

NOTE 2 Typical spectral data for inks conforming to this part of ISO 2846 are provided in annex B. Reference spectral data for 8°/diffuse (specular included) are also included in annex B.

NOTE 3 CIELAB data calculated from the CIE 1931 (2°) standard colorimetric observer, together with CIE standard illuminant  $D_{65}$ , are included in annex C for both geometries. CIELAB data for 8°/diffuse or diffuse/8° (specular included) geometry and illuminant  $D_{50}$  are also included in that annex.


<sup>1)</sup> Leneta paper or card (No. 105C) which can be purchased from Leneta Corp. Mahwah, N.J., USA. Leneta paper or card is a tradename of a product supplied by Leneta Corp. This information is given for the convenience of the users of this part of ISO 2846 and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

Ink	CIELAB values			Tolerances			
IIIK	$L^*$	<i>a</i> *	$b^*$	$\Delta E_{ab}^{*}$	$L^*$	$\Delta a^*$	$\Delta b^*$
Yellow	90,0	- 1,0	100,0	5,0	—	—	—
Magenta	51,0	78,0	8,0	6,0	_	_	—
Cyan	50,0	-31,0	- 50,0	6,0	_	_	—
Black	14,0	- 1,0	2,0	—	≼ 14,0 <sup>a</sup>	± 1,5	± 3,0
<sup>a</sup> This means that for black there is no symmetrical tolerance for $L^*$ but an upper limit.							

#### 5.3 Transparency characteristics

To meet the specification for transparency, an ink shall produce a value greater than that specified in Table 2 when determined according to the principles and test methods outlined in clause 4.

Table 2 — Transparency requirements

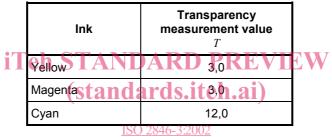

https://standards.iteh.ai/catalog/standards/sist/01ea2fa4-c4fb-4ce5-b168-

For highly transparent inks, the slope of the regression  $\sin^{8}$  may  $2be^{2}$  zero or negative. In such a situation the transparency *T* meets the specification.

NOTE For further information concerning transparency evaluation using instruments with different geometry, see D.3.2.

# Annex A

(normative)

#### **Reference substrate**

For the purpose of this part of ISO 2846, a light-fast gloss coated wood-free paper free of optical brightener shall be used, the characteristics of which shall be as follows:

#### **Colorimetric values**

CIELAB values:	$L^{*} = 95,5 \pm 2,0$
	$a^{*} = -0,4 \pm 1,0$
	$b^{*} =$ 4,7 $\pm$ 1,5
Method:	ISO 13655. See 4.3.

#### Water absorptiveness

Specification:	2 g/m <sup>2</sup> to 5 g/m <sup>2</sup> after 10 s
Method:	ISO 535
Gloss	iTeh STANDARD PREVIEW
Specification:	70 % to 80 % (standards.iteh.ai)
Method:	ISO 8254-1 ISO 2846-3:2002
Mass per area	https://standards.iteh.ai/catalog/standards/sist/01ea2fa4-c4fb-4ce5-b168- 77ce76c03330/iso-2846-3-2002
Specification:	$(150\pm3) \text{ g/m}^2$
Method:	ISO 536
Ash content	
Specification:	20 % to 30 %
Method:	ISO 2144
рН	
Specification:	8 to 10
Method:	ISO 6588
Roughness	
Specification:	(1,0 $\pm$ 0,1) $\mu m$ at a pressure of 1 N/mm^2
Method:	ISO 8791-4

NOTE In practice there has been only one supplier of this material, and it has become the de-facto standard. This material is the gloss-coated wood-free paper Phoenix Imperial APCO II/II from Scheufelen, D-73250 Lenningen, Germany. This information is given for the convenience of the users of this part of ISO 2846 and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.