

---

---

**Rotary shaft lip type seals —  
Part 4:  
Performance test procedures**

*Bagues d'étanchéité à lèvres pour arbres tournants —*

*Partie 4: Méthodes d'essai de performance*

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

ISO 6194-4:1999

<https://standards.iteh.ai/catalog/standards/sist/9b8b892b-7353-4fb3-86bb-2876d8c5728b/iso-6194-4-1999>



## Contents

1 Scope .....	1
2 Normative references .....	1
3 Terms and definitions .....	2
4 Pre-test procedure .....	2
5 Dynamic test.....	2
6 Dynamic low temperature test.....	5
7 Material testing of elastomeric components.....	7
Annex A (informative) Example of a seal test report for the dynamic test.....	9
Annex B (informative) Example of a seal test report for the dynamic low temperature test.....	11
Annex C (informative) Example of a material test report .....	13
Bibliography .....	15

iteh STANDARD PREVIEW  
(standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/sist/9b8b892b-7353-4fb3-86bb-2876d8c5728b/iso-6194-4-1999>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 6194-4 was prepared by Technical Committee ISO/TC 131, *Fluid power systems*, Subcommittee SC 7, *Sealing devices*.

This second edition cancels and replaces the first edition (ISO 6194-4:1988), which has been technically revised.

ISO 6194 consists of the following parts, under the general title *Rotary shaft lip type seals*:

- *Part 1: Nominal dimensions and tolerances*
- *Part 2: Vocabulary*
- *Part 3: Storage, handling and installation*
- *Part 4: Performance test procedures*
- *Part 5: Identification of visual imperfections*

Annexes A, B and C of this part of ISO 6194 are for information only.

ITIH STANDARD PREVIEW  
(standards.iteh.ai)

ISO 6194-4:1999

<http://standards.iteh.ai/catalog/standards/sist/9b8b892b-7353-4fb3-86bb-2876d8c5728b/iso-6194-4-1999>

## Introduction

Lip type seals are used for retaining fluid or grease in equipment employing rotating shafts. In some instances, the shaft is stationary and the housing rotates. Sealing of a lip type seal with a low differential pressure is normally a result of a designed interference fit between the shaft and the flexible sealing element, which is usually fitted with a garter spring. An interference fit between the outside surface of the seal and the housing bore surface retains the seal in the housing and prevents leakage at the outer diameter.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 6194-4:1999](https://standards.iteh.ai/catalog/standards/sist/9b8b892b-7353-4fb3-86bb-2876d8c5728b/iso-6194-4-1999)

<https://standards.iteh.ai/catalog/standards/sist/9b8b892b-7353-4fb3-86bb-2876d8c5728b/iso-6194-4-1999>

# Rotary shaft lip type seals —

## Part 4: Performance test procedures

### 1 Scope

This part of ISO 6194 specifies test requirements for rotary shaft lip type seals. The tests may be used for qualification purposes. Materials quality control, dynamic testing and supplementary low temperature testing requirements are also covered.

### 2 Normative references

The following normative documents contains provisions which, through reference in this text, constitute provisions of this part of ISO 6194. For dated references, subsequent amendments to, or revisions of, these publication do not apply. However, parties to agreements based on this part of ISO 6194 are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 6194-4:1999

ISO 48:1994, *Rubber, vulcanized or thermoplastic — Determination of hardness (hardness between 10 IRHD and 100 IRHD)*.

ISO 188:1998, *Rubber, vulcanized — Accelerated ageing and heat resistance tests*.

ISO 815:1991, *Rubber, vulcanized or thermoplastic — Determination of compression set at ambient, elevated or low temperatures*.

ISO 1432:1988, *Rubber, vulcanized or thermoplastic — Determination of low temperature stiffening (Gehman test)*.

ISO 1817:1998, *Rubber, vulcanized — Determination of the effect of liquids*.

ISO 2781:1988, *Rubber, vulcanized — Determination of density*.

ISO 2921:1997, *Rubber, vulcanized — Determination of low-temperature characteristics — Temperature-retraction procedure (TR test)*.

ISO 5598:1985, *Fluid power systems and components — Vocabulary*.

ISO 6194-1:1982, *Rotary shaft lip type seals — Part 1: Nominal dimensions and tolerances*.

ISO 6194-2:1991, *Rotary shaft lip type seals — Part 2: Vocabulary*.

### 3 Terms and definitions

For the purposes of this part of ISO 6194, the terms and definitions given in ISO 6194-2 and ISO 5598 and the following definition apply.

#### 3.1

##### **batch**

identifiable and traceable consignment of rubber compound of definite composition and manufactured in a single production operation

### 4 Pre-test procedure

**4.1** Inspect all seals submitted for testing for conformity to a relevant drawing or detailed specification declared by the seal manufacturer.

**4.2** For seals with an elastomeric component, ensure that the seal manufacturer has stated the material designation batch number from which the seals have been made, together with the nominal density, nominal hardness, maximum compression set value and maximum mass change after immersion in the test fluid.

Where the seal is required for the low temperature stiffness test, ensure that the seal manufacturer has also stated the maximum modulus after test at the selected test temperature.

Ensure that the batch of elastomer has been tested in accordance with clause 7.

**4.3** To facilitate accurate analysis of the test results, determine the following data concerning the physical characteristics of the seal and test apparatus before testing:


- a) lip diameter (with spring);
- b) lip diameter (without spring, measured not less than 24 h after removal of spring);
- c) outer case mean diameter and out-of-roundness;
- d) shaft diameter, material hardness and surface roughness;
- e) housing diameter, material and surface roughness;
- f) minor lip diameter, where applicable (with and without primary lip spring fitted).

**4.4** Ensure that the specified shaft eccentricity and housing off-set of the test apparatus have been incorporated.

### 5 Dynamic test

#### 5.1 Test apparatus

The test apparatus shall be similar to the typical example shown in Figure 1 and shall consist of a suitable housing for retaining the test fluid and for positioning the test seals, as well as a rotating member having a spindle mounted horizontally on suitable bearings. The design of the housing for the seal shall be in accordance with the dimensions specified in ISO 6194-1. The housing and the rotating member shall be capable of reproducing the eccentricity and off-set specified in 4.4.

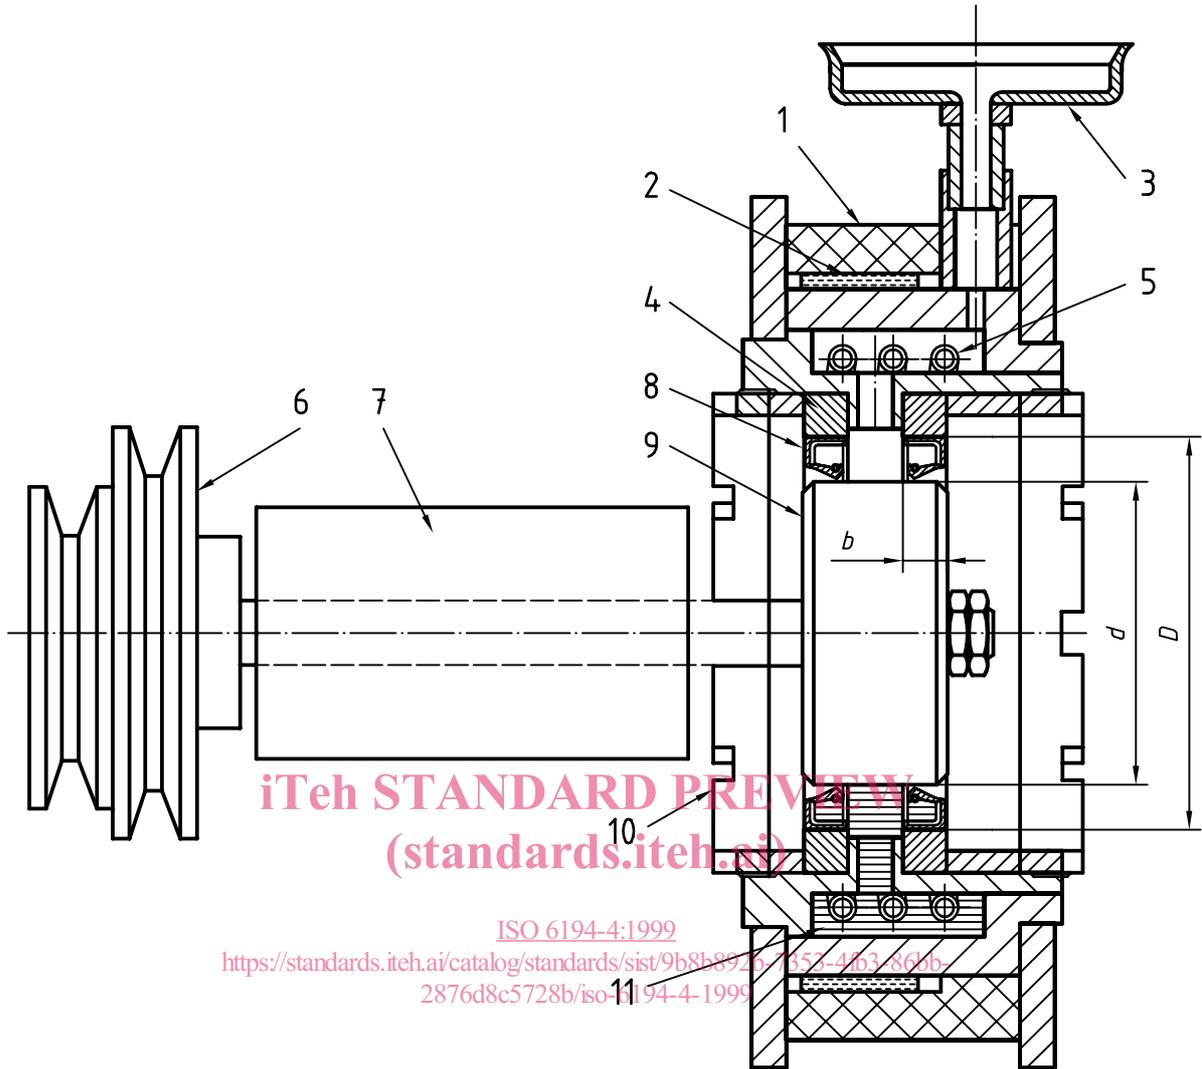

ISO 6194-4:1999  
<https://standards.iteh.ai/catalog/standards/sist/9b8b8926-7657-42b3-86bb-2876d8c5728b/iso-6194-4-1999>

**Key**

- |   |                        |    |                   |
|---|------------------------|----|-------------------|
| 1 | Insulation             | 7  | Test head support |
| 2 | Heater band            | 8  | Test seal         |
| 3 | Filler tray            | 9  | Test shaft        |
| 4 | Seal housing           | 10 | Locking ring      |
| 5 | Cooling coils          | 11 | Test fluid        |
| 6 | Drive from prime mover |    |                   |

**Figure 1 — Typical example of dynamic test apparatus**

Where it is not practicable to provide a test apparatus with the particular shaft and housing size relevant to the application, the test apparatus shall be selected from the standard sizes listed in Table 1. The size selected shall be that nearest to the application size.

Table 1 — Standard shaft and housing dimensions

Dimensions in millimetres

Shaft diameter <i>d</i>	Housing diameter <i>D</i>	Seal width <i>b</i>
20	35	7
40	55	8
60	80	8
90	120	12
200	230	15

The test apparatus shall also conform to the following additional requirements:

- a) the shaft shall be capable of cycling and/or maintaining the shaft speeds to within  $\pm 3\%$ ;
- b) the shaft shall be capable of maintaining the specified test eccentricity under dynamic conditions to within  $\pm 0,03$  mm throughout each test;
- c) the test head shall be designed and constructed so as to maintain the housing bore alignment relative to the test shaft axis within 0,03 mm throughout the operating temperature range;
- d) the design of the test head support shall ensure minimum deformation and vibration;
- e) the test head and heat transfer system shall be capable of maintaining the temperature of the test fluid within  $\pm 3$  °C, and shall be vented to atmosphere;
- f) heat shall be applied in a manner that does not subject the test fluid to high localized temperatures that could cause fluid decomposition;
- g) the test shaft shall have a surface that is free of helical machine marks and shall comply with the requirements for shafts specified in ISO 6194-1;
- h) the test housing bore shall comply with the requirements specified in ISO 6194-1;
- i) the materials, surface finish and dimensions of the test shaft and test housing bore shall conform as closely as possible to the shaft and housing bore to be used in service;
- j) a minimum quantity of 0,75 l of test fluid shall be used;
- k) the level of the test fluid in the test head shall be  $0,3d$  to  $0,5d$  above the lowest point of the shaft diameter  $d$ ;
- l) for seal housings with inboard bearings, the test housing shall be suitably relieved at the bearing supports to prevent excessive fluid pressure between the bearing and seals;
- m) means shall be provided for collecting and measuring the mass of any fluid leakage from the seals during the test;
- n) the test head shall have a device capable of pressurising the seal housing to the working pressure;
- o) a liquid level measuring device shall be provided on the test head.

## 5.2 Installation

**5.2.1** Thoroughly clean the test head of contaminants and extraneous matter.

**5.2.2** Install the seal into the test head so that the cumulative eccentricities of the seal and the test head are known.

**5.2.3** Ensure that the plane of the seal lip is perpendicular to the shaft axis, unless otherwise specified.

**5.2.4** Locate the test shaft in such a position that a clean unused area of its surface is in contact with the sealing element of the test seal.

## 5.3 Test conditions

Apply test conditions that simulate the seal application operating conditions specified by the customer, i.e. normal operating temperature, normal operating shaft speed, maximum envisaged operating temperature and maximum envisaged shaft speed (see annex A).

## 5.4 Test procedure

Submit six seals to 10 cycles, each of 24 h duration, consisting of 14 h at normal operating temperature and speed, according to service conditions, and 6 h at the maximum envisaged operating temperature and speed, followed by a 4 h shut-down when the test machine is allowed to cool to room temperature. If applicable, each alternate cycle shall be in the reverse direction of rotation.

## 5.5 Post-test measurements

After completion of the test, determine the seal lip diameters, the minor lip diameters where applicable, and the contact band width. Inspect the seal lip, noting any cracks, tears, splits or any imperfections that may have appeared as a result of the test.

## 5.6 Recording

ISO 6194-4:1999  
<https://standards.iteh.ai/catalog/standards/sist/9b8b892b-7353-4fb3-86bb-2876d8c5728b/iso-6194-4-1999>

Record all test data on a seal test report. An example of a seal test report for a dynamic test is shown in annex A.

## 5.7 Acceptance criteria

Unless otherwise agreed between manufacturer and purchaser, the total leakage from all six seals shall not be greater than 12 ml, and the leakage from any single seal shall not be greater than 3 ml.

## 6 Dynamic low temperature test


### 6.1 General

This test is applicable to all rotary shaft lip type seals for which the minimum specified operating temperature is stated to be – 10 °C or lower.

### 6.2 Test fixture

The test fixture shall be similar to the typical example shown in Figure 2.

The test shaft and seal housing shall simulate the envisaged maximum eccentricities specified by the customer. The test shaft diameter, the test shaft surface roughness and seal housing dimensions shall also be those specified by the customer or as specified in ISO 6194-1.

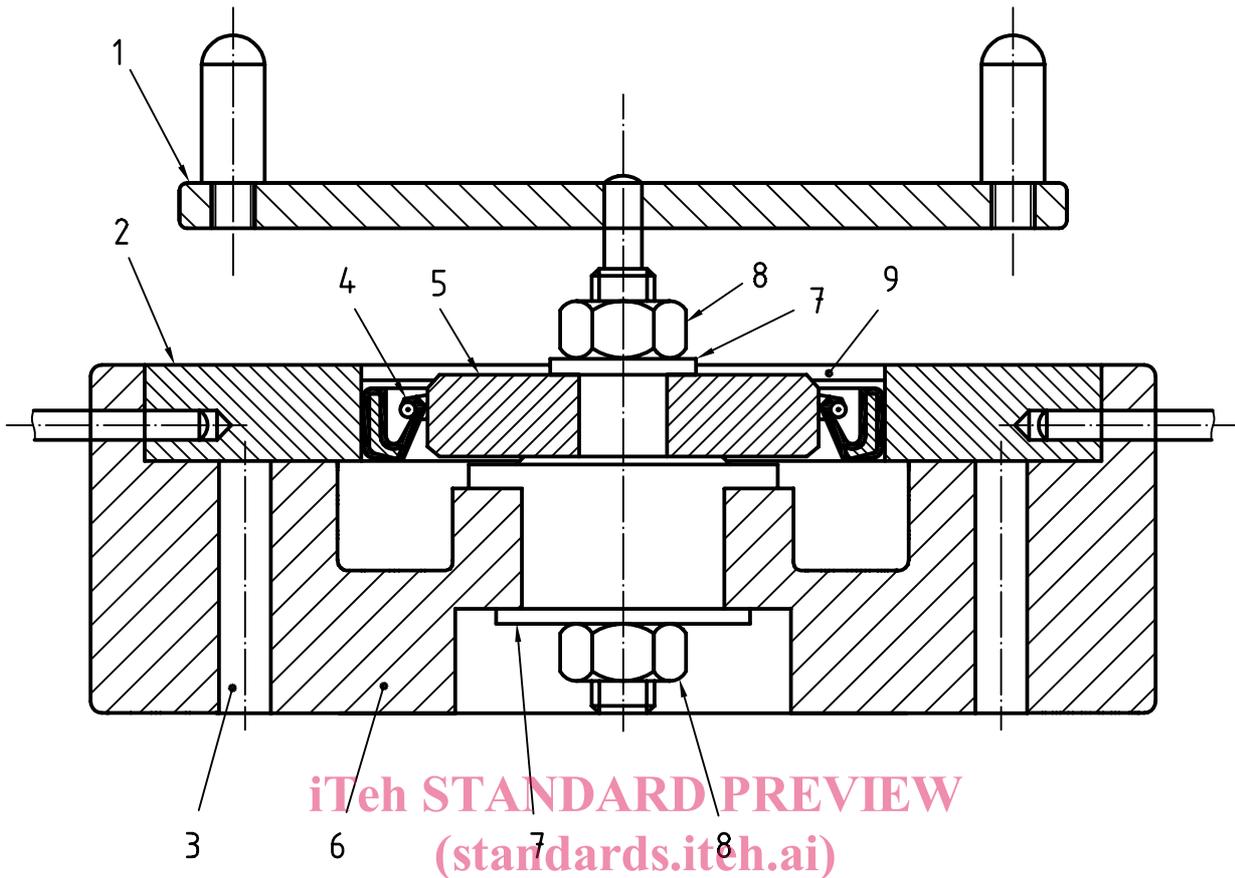

**Key**

- |   |   |   |   |
|---|---|---|---|
| 1 | Handle  | 5 | ISO 6194-4:1999<br>Test shaft   |
| 2 | Seal housing  | 6 | <a href="https://standards.iteh.ai/catalog/standards/sist/9b8b892b-7353-4fb3-86bb-2876d8c57281/iso-6194-4-1999">https://standards.iteh.ai/catalog/standards/sist/9b8b892b-7353-4fb3-86bb-2876d8c57281/iso-6194-4-1999</a><br>Base |
| 3 | Holes to locate with pins in base plate of refrigeration unit | 7 | Washer  |
| 4 | Test seal   | 8 | Plain hexagonal nut   |
|   |   | 9 | Test fluid  |

**Figure 2 — Typical example of low temperature test fixture**

**6.3 Installation**

The requirements of 5.2.1, 5.2.2 and 5.2.3 shall be followed.

**6.4 Test procedure**

Submit two seals to the following procedure.

- 6.4.1 Soak the seal in test fluid for 70 h at normal operating temperature (see annex B).
- 6.4.2 Remove the seal from the test fluid and shake off the excess. Do not blot dry.
- 6.4.3 Lubricate the test shaft with a small quantity of the test fluid.
- 6.4.4 Correctly locate the seal in the test fixture.
- 6.4.5 Fill the test fixture with the test fluid to submerge the wetted side of the seal lip.
- 6.4.6 Place the test fixture in a cold box and soak for 16 h at the minimum temperature specified by the customer (see annex B).
- 6.4.7 With the test fixture still in the cold box, rotate the shaft 10 revolutions by hand in the clockwise direction at an approximate speed of 1 Hz, pausing once every 180°.

**6.4.8** Remove the test fixture from the cold box and allow to stand at room temperature for a minimum period of 6 h.

**6.4.9** Remove the seal from the test fixture.

## 6.5 Post-test measurements

Inspect for leakage that may have occurred during the test and visually inspect seal lip, noting any cracks, tears, splits or any imperfections that may have appeared as a result of the test.

## 6.6 Recording

Record all test data on a seal test report. An example of a seal test report for the dynamic low temperature test is shown in annex B.

## 6.7 Acceptance criteria

There shall be no visible damage to lip and there shall be no leakage greater than that specified by the customer.

# 7 Material testing of elastomeric components

## 7.1 Elastomeric material requirements

Each batch of material from which the test seals are manufactured shall be tested for the purpose of quality control. In order to ensure that the material used for production seals does not vary significantly from that of the dynamic test seals, subsequent production batches shall also be tested on a random sample basis. The materials used for tests shall be in an unused condition.

Tests shall be in accordance with 7.2 to 7.7. [ISO 6194-4:1999](#)

## 7.2 Density

<https://standards.iteh.ai/catalog/standards/sist/9b8b892b-7353-4fb3-86bb-2876d8c5728b/iso-6194-4-1999>

Each batch of material shall be tested in accordance with ISO 2781.

The result shall be the specified nominal density (see 4.2) within a tolerance of  $\pm 0,03 \text{ g/cm}^3$  for all materials.

## 7.3 Hardness

Each batch of material shall be tested in accordance with ISO 48.

If the dimension of the test piece is greater than 4 mm then the normal test procedure shall be used. If less than 4 mm, then the microtest procedure shall be used.

The result shall be the specified nominal hardness (see 4.2) within a tolerance of  $\pm 7 \text{ IRHD}$ .

## 7.4 Compression set

Each batch of material shall be tested in accordance with ISO 815.

The duration of the test shall be 22 h, and the temperature of the test for different elastomers shall be as given in Table 2.

The result shall be not greater than the specified maximum value (see 4.2).